

**APPENDICES FOR CHAPTER 2
IN THE ENVIRONMENTAL IMPACT STATEMENT
OF THE MINAGO PROJECT**

LIST OF APPENDICES SUPPLEMENTAL TO CHAPTER 2

APPENDIX 2.2 Supplemental Material for Certificate of Title and Mineral Depositions

Quarry Lease QL-2067

APPENDIX 2.8 Supplemental Material for Geochemical Rock Characterization

Appendix 2.8-A: Waste Rock

App. 2.8-A1: Phase I and Phase II Drill Log Summaries

App. 2.8-A2: Phase I Static and Metal Test Results
& Phase II Grainsize, Static and Metal Test Results

App. 2.8-A3: Shake Flask Extraction Test Results

App. 2.8-A4: Kinetic Test Results

Appendix 2.8-B: Tailings

App. 2.8-B1: Static, Grainsize and Metal Results

App. 2.8-B2: 2006 SGS SGS Lakefield Research Ltd. ABA Report

App. 2.8-B3: Kinetic Test Results

APPENDIX 2.9 Supplemental Material for Mining Processes

APPENDIX 2.10 Supplemental Material for Milling Processes

Appendix 2.10-A: Material Safety Data Sheets for the Mill Reagents
and Flocculants

Appendix 2.10-B: Process Flow Diagrams for the Frac Sand Plant

APPENDIX 2.14 Supplemental Material for Site Water Management

Appendix 2.14-A: Detailed Key Parameters and Considerations used for the Water
Balance Model

Appendix 2.14-B: Water Balance Model Results for Year 1 through Year 4 Operations

Appendix 2.14-C: Water Balance Model Results for Year 5 through Year 8 Operations

Appendix 2.14-D: Water Balance Model Results for Year 9 and Year 10 Operations

Appendix 2.14-E: Water Balance Model Results for the Closure and
Post Closure Periods

Appendix 2.14-F: Water Balance Model Results for Temporary Suspension
after Year 5 & the State of Inactivity after one year of
Temporary Suspension

APPENDIX 2.2

Supplemental Material to Certificate of Title and Mineral Depositions

Quarry Lease QL-2067



Innovation, Energy and Mines
Mines Branch
360-1395 Ellice Ave, Winnipeg, Manitoba R3G 3P2
T 204 945-6505 F 204 948-2578
www.manitoba.ca

December 14, 2009

Mr. Paul Jones
Victory Nickel Inc.
80 Richmond Street West, Suite 1802
Toronto Ontario M5H 2A4

Dear Paul:

RE: QUARRY LEASE NO. QL-2067

Attached in duplicate is Quarry Lease No. QL-2067 prepared in the name of Victory Nickel Inc. in accordance with Subsection 139(2) of The Mines and Minerals Act. Prior to the commencement of mining the following conditions shall be met:

1. A work permit must be obtained from the local Natural Resources Office; and
2. All lease boundaries shall be marked and the Mining Recording Office advised upon completion.
3. Please refer to the "additional clauses" in your lease document and contact MTS and any other utility prior to any excavating.

Your application for Quarry Lease No. QL-2067 was submitted with annual rent in the amount of \$1,678.00. The actual rent required to cover 69.92 hectares is \$1,680.00. Therefore, we require \$2.00 to cover the additional rent for Quarry Lease No. QL-2067. We will recover the \$2.00 from your application fee for casual quarry permit.

Please find attached a copy of the Minago River Final Consultation Report dated November 5, 2009.

If you require assistance in preparing the Mine Closure Plan please contact Mrs. Doina Priscu, P.Eng., Chief Mining Engineer telephone no. (204) 945-6517, Fax No. (204) 948-2578.

Yours truly,

Ernie Armitt
Director of Mines

Enclosure

cc Doina Priscu, Chief Mining Engineer

/tlz
QLSIGN1.DOC

QUARRY LEASE

Quarry
Lease No. QL-2067

THIS LEASE made in duplicate this 20th day of November, 2009

BETWEEN:

Her Majesty the Queen in right of the
Province of Manitoba, represented by the
Minister of Science, Technology, Energy
and Mines

(the "Minister")

of the First Part

- and -

VICTORY NICKEL INC.
80 RICHMOND ST W, SUITE 1802
TORONTO ON M5H 2A4

(the "Lessee")

of the Second Part

The parties agree as follows:

1. In this Lease:

(a) "Act" means The Mines and Minerals Act, Cap. M162 C.C.S.M., as amended, revised or substituted from time to time;

(b) "regulations" means regulations made pursuant to the Act, and as amended, revised or substituted from time to time;

2. Subject and pursuant to the Act and regulations, the Minister conveys to the lessee the exclusive right to explore for, develop, and produce the following quarry minerals, namely

ROCK OR STONE (PROCESSED STONE- LIMESTONE) _____

that are the property of the Crown and are found on or under the land described as:

**ALL THAT PORTION OF UNSURVEYED TOWNSHIP 59 RANGE 12 WPM CONTAINED
WITHIN THE FOLLOWING LIMITS DETERMINED BY GRID LINES FROM NAD 83 (CSRS**

98) BEING IN UTM 6° ZONE 14, EXPRESSED IN METRES AND FURTHER DESCRIBED AS FOLLOWS:

COMMENCING AT A POINT AT THE INTERSECTION OF UTM GRID LINES 484973 E AND 5996120 N; THENCE ELY IN A STRAIGHT LINE TO THE INTERSECTION OF UTM GRID LINES 485733 E AND 5996120 N; THENCE SLY IN A STRAIGHT LINE TO THE INTERSECTION OF UTM GRID LINES 485733 E AND 5995200 N; THENCE WLY IN A STRAIGHT LINE TO THE INTERSECTION OF UTM GRID LINES 484973 E AND 5995200 N; THENCE NLY IN A STRAIGHT LINE TO THE POINT OF COMMENCEMENT.

(the "Lands") and being 69.92 hectares, more or less, for a term of 10 years, commencing the 2nd day of November, 2009 renewable in accordance with the Act.

3. The Lessee shall comply with the Act and regulations; including, without restricting the generality of the foregoing, the payment of rent, royalty and rehabilitation levy prescribed thereunder.
4. The Lessee shall and does hereby indemnify and save harmless the Minister against any and all actions, suits, claims or demands that may be brought or made against the Minister for or by reason of any act or thing done or omitted to be done by the Lessee or its agents with respect to the Lands.
5. To be effective and binding, any waiver by the Minister of a breach by the Lessee of any term or condition of this Lease, the Act or the regulations must be in writing. Any such waiver shall extend only to the events of breach enumerated therein and shall not limit or affect the Minister's rights with respect to any other breach.
6. If the Lessee defaults, breaches, fails to perform or observe any term or condition of this Lease, the Act or the regulations, and any such event is not remedied within such notice period as the Minister may give, the Minister may cancel this Lease. Notwithstanding any such cancellation by the Minister, the rights of the Minister against the Lessee shall not be prejudiced and the Minister shall have the full remedies against the Lessee as if the Lease remained in full force and effect.
7. Any notice to a party hereto shall be in writing and may be delivered personally, sent by telegram, telex, telecopier or other means of electronic communication, or may be forwarded by mail subject to Canada Post confirmation of delivery to that party at the following address:

To the Minister:

Science, Technology, Energy and Mines
Unit 360-1395 Ellice Avenue
Winnipeg, Manitoba
R3G 3P2

To the Lessee:

VICTORY NICKEL INC.
80 RICHMOND ST W, SUITE 1802
TORONTO ON M5H 2A4

8. This lease shall be interpreted in accordance with the laws of Manitoba.
9. Any amendments to this Lease shall be in writing and signed by both parties.
10. The Lessee shall not assign this lease except with the prior written consent of the Minister which shall not be unreasonably withheld. Any obligations of the Lessee outstanding at the date of any assignment shall remain the responsibility of the Lessee, to the extent the obligations are not performed by the permitted assignee.
11. This Lease shall enure to the benefit of and be binding upon the heirs, executors, administrators, successors and permitted assigns of the parties.

12. **Additional clauses:**

Mining operations shall not commence on this lease until a Mine Closure Plan has been submitted by the lessee, accompanied by the required financial security deposit and approved by the Director of Mines.

It is the lessee's responsibility to locate all utilities, (including but not limited to gas, electric and telecommunications) that may exist within the limits of this disposition prior to any excavation. "Call Before You Dig" and "611 Cable Locate Service". The lessee shall comply with all requirements imposed by the utility company.

The lessee shall comply with The Workplace Safety and Health Act and Regulation.

In witness whereof the Minister and the Lessee have executed this Lease on the dates shown below their respective signatures.

Signed, sealed and delivered
in the presence of:

Her Majesty the Queen in right of the Province Of
Manitoba

Renee Masson
Witness

[Signature]
Minister of Science, Technology, Energy and Mines


Authorized Signing Authority
Ernest Arnold, P.Eng.
Director of Mines

Dec 11 2009
Date

David Tomalty
Witness


[Signature]
Lessee VICTORY NICKEL INC.

NOV 20 2009
Date

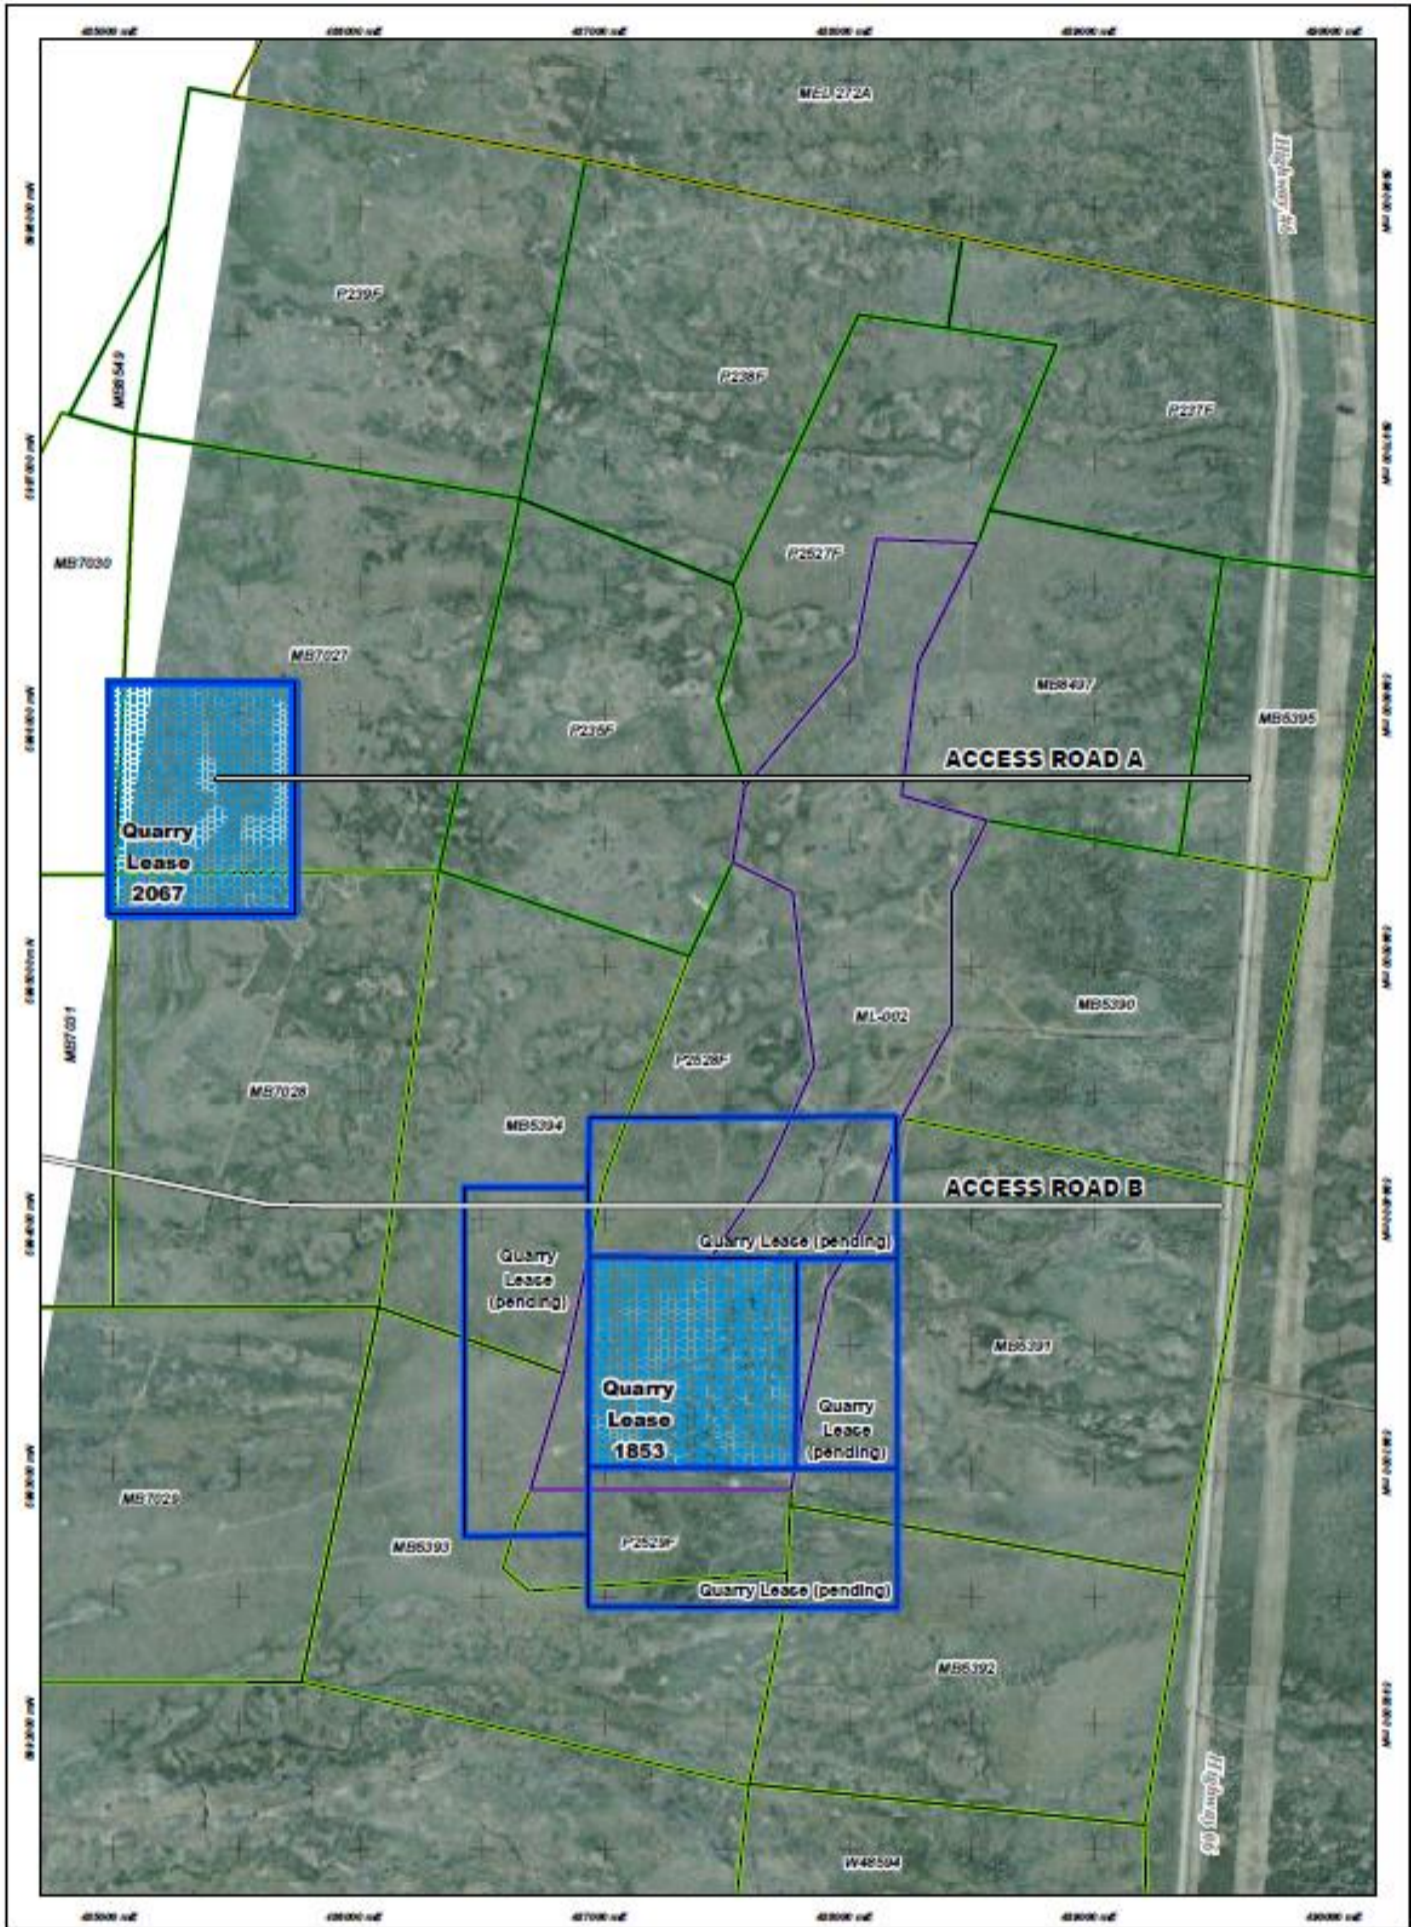

Graphics by:

 Zone 14 Geoproc Solutions Inc.
 www.zone14.com Winnipeg, Manitoba



-  VNI Quarry: Complete
-  VNI Quarry: Pending
-  VNI Exploration Lease
-  VNI Lease
-  VNI Claims, Optioned (Xstrata)
-  VNI Claims

VICTORY NICKEL INC.

MINAGO PROJECT - SOUTH BLOCK AREA
 Minago River Area, Manitoba - G3J03

Property and Access

DATUM: NAD 83, ZONE 14

APPENDIX 2.8-A

Waste Rock

	Page
Appendix 2.8-A1: Phase I and Phase II Drill Log Summaries	2.8-2
Appendix 2.8-A2: Phase I Static and Metal Test Results & Phase II Grainsize, Static & Metal Test Results	2.8-18
Appendix 2.8-A3: Shake Flask Extraction Test Results	2.8-47
Appendix 2.8-A4: Kinetic Test Results	2.8-50

APPENDIX 2.8-A1

Phase I and Phase II Drill Log Summaries

Phase I Drill Log Summary

Summary of Static Geochemical Samples Minago Project May 2007

SAMPLE TYPE

1. Overburden (OB)/Altered Rock formation (AR)
2. Frac Sand (FS) formation/Altered Rock formation (AR)
3. Frac Sand (FS) formation/Limestone formation (LS)
4. Limestone (LS) formation/Overburden (OB)
5. Ore (ORE)/Altered Rock (AR) formation
6. Limestone (LS) formation/Altered Rock (AR) formation
7. Ore (ORE)/Limestone (LS) formation
8. OB
9. LS
10. FS
11. AR
12. ORE
13. OB/LS/FS/AR/ORE

Samples 1 – 7 are composite on the basis of their formation thicknesses as discussed.

Sample # 13 is a composite sample.

SAMPLE WEIGHT

2.0 Kilogram (minimum)

Labelled #1 N0727 "OB/AR" ; #1 N0728 "OB/AR" ; etc.

- Drillhole N0728 and N0729 represent the southern and northwestern portions of the proposed pit shell;

hole 28 includes non- to sparsely mineralised serpentinite unlikely to be milled; and the overall rocktype distribution in the 2 holes combined may approximate the proportions sent to the waste pile for the western end of the deposit/pt.

- Drillhole 27 should estimate the maximum acid generation potential of material classified as uneconomic

(i.e. due to insufficient grade-thickness, discontinuous lensy mineralisation, or unacceptable levels of internal dilution from granitoid intrusives).

- The clay till sample obtained effervesces vigorously in dilute HCl.

SAMPLING NOTES: AR is the weathered cap of Proterozoic rock regardless of lithology
The AR in hole N0729 is granitic which weathers deeper than other rocktypes
The OB unit is unusually thin in N0728 (4m).
In general core length of OB in holes to date is 10-11m, so 10m has been used
ORE for the purposes of this study is all Proterozoic/Achean material
contained within the pit shell, regardless of nickel content
The first 3 holes chosen for sampling are at the rim of the pit, containing little mineralised ultramafic rock. This is appropriate, since the bulk of the mineralised material will end up as tailings rather than in a waste pile
It is suggested that the final 2 holes selected be resource holes which encounter the sulphide bearing pelitic msed and sulphide iron formation units observed in the initial holes of the program -NE side of the pit
A sample ratio of 3:1 for OB/AR for example means 3 parts OB to 1 part AR
1500g OB and 500g AR for 2kg minimum sample size-NOT 1/3 AR

Sample #/composition	N0727	N0727	N0727	N0728	N0728	N0728	N0729	N0729	N0729	N0736	N0736	N0736
	weight ratio kg	total wt kg	weight ratio kg	total wt kg	weight ratio kg	total wt kg	weight ratio kg	total wt kg	weight ratio kg	total wt kg	weight ratio kg	total wt kg
1- OB/AR	1:1.7	1:1.7	2.7	2.5:1	0.1:2.5	2.6	27:5:1	2.85	2.75:0.1	0.03:1	0.06:2.0	2.06
2- FS/AR	1:1.25	1:1.25	2.25	2.5:1	0.1:2.5	2.6	1:2	2.1	0.7:1.4	0.05:1	0.1:2.0	2.1
3- FS/LS	1:7	0.25:1.75	2.0	1.7	0.3:2.1	2.4	1:7	2.8	0.35:2.45	0.15:1	0.3:2	2.3
4- LS/OB	10:1	2.0:0.2	2.2	7:1	2.1:0.3	2.4	5.5:1	2.6	2.2:0.4	1.0:0.08	2.0:0.16	2.16
5- ORE/AR	11:6:1	2.32:0.2	2.52	66:1	1.98:0.03	2.01	12:1	2.6	2.4:0.2	0.26:1	0.52:2	2.52
6- LS/AR	5:6:1	1.96:0.35	2.31	18:1	1.98:0.11	2.09	3:6:1	2.3	1.8:0.5	0.35:1	0.7:2	2.7
7- ORE/LS	2:1:1	1.47:0.7	2.17	3:7:1	1.85:0.5	2.35	3:3:1	2.15	1.65:0.5	0.75:1	1.0(0.23)F+0.46Gran+0.29SPT):1:33	2.33
8- OB	1	2.91	2.01	1	2.33	>2	1	2.1	2.1	1	2.75	2.75
9- LS	1	2.72	2.72	1	2.48	2.48	1	2.3	2.3	1	2.43	2.43
10- FS	1	2.8	2.8	1	2.36	2.36	1	2.25	2.25	1	2.4	2.4
11- AR	1	2.12	2.12	1	2.23	2.23	1	2.65	2.65	1	2.5	2.5
12- ORE	1	>2	>2	1	>2	>2	1	>2	>2	1	2.75(0.62)F+1.32Gran+0.8(SPT)	2.75
13- OB/LS/FS/AR/ORE		.07(.68)/.09(.12)/1.4	2.36	.11(.71)/.1(.04)/3.65	0.05:0.35:0.05:0.02:1.83	2.275	.11(.61)/.09(.17)/2.01	2.88	0.11:0.61:0.09:0.17:2.01	0.03:0.35:0.05:1:0.26	0.06:0.7:0.1:2:0.52	3.38

Abbreviated lithology distribution	depth (m) N0727	length (m)	notes	depth (m) N0728	length (m)	notes	depth (m) N0729	length (m)	notes	depth (m) N0736	length (m)	notes
OB	8.65	7	1-2m peat	4.1	10	see above	11	10	10	5	5	5
LS	76.65	68		75.55	71		71.9	61	61	71	66	66
FS (SS)	86	9		85.75	10		80.9	9	9	80.75	9.75	9.75
AR	98.12	12		89.5	4		97	17	17	270.5	189.75	189.75
ORE	239	140		455	385		298	201	201	320	49.5	49.5

N0728 ORE=57% spt, 28% aligran, 13% gran dyke, 2% maf mvolc (spt weakly to mod. well mineralised throughout)

N0728 ORE=24% spt, 12% amph, 64% gran/gran gneiss (spt contains only trace sulphides)

N0729 ORE=50% gran/gran gneiss, 50% amph

N0736 ORE=23% iron formation, 48% granite, 29% spt

N0736 AR=26% mafic gneisses, 74% granite gneiss

Drillhole N0727 Lithology Log

DDH	From (m)	To (m)	Unit	Lithology
N0727	0.00	8.10	1	Overburden
N0727	8.10	76.45	2	Dolomite
N0727	76.45	86.00	3	Sandstone
N0727	86.00	88.35	5	Granite
N0727	88.35	116.84	4	Serpentinite
N0727	116.84	122.49	5	Granite
N0727	122.49	133.92	4	Serpentinite
N0727	133.92	135.90	5	Granite
N0727	135.90	186.61	4	Serpentinite
N0727	186.61	206.34	5	Granite
N0727	206.34	213.12	4	Serpentinite
N0727	213.12	218.74	5	Granite
N0727	218.74	228.52	4	Serpentinite
N0727	228.52	233.00	5	Granite
N0727	233.00	239.00	4	Serpentinite

Drillhole N0729 Lithology Log

DDH	From (m)	To (m)	Unit	Lithology
N0729	0.00	10.60	1	Overburden
N0729	10.60	71.90	2	Dolomite
N0729	71.90	80.90	3	Sandstone
N0729	80.90	91.30	11	Regolith
N0729	91.30	98.40	5	Granite
N0729	98.40	107.00	6	Amphibolite
N0729	107.00	117.45	5	Granite
N0729	117.45	135.60	6	Amphibolite
N0729	135.60	141.10	5	Granite
N0729	141.10	200.00	6	Amphibolite
N0729	200.00	244.00	5	Granite
N0729	244.00	298.00	6	Amphibolite

Drillhole N0729 Lithology Log

DDH	From (m)	To (m)	Unit	Lithology
N0729	0.00	10.60	1	Overburden
N0729	10.60	71.90	2	Dolomite
N0729	71.90	80.90	3	Sandstone
N0729	80.90	91.30	11	Regolith
N0729	91.30	98.40	5	Granite
N0729	98.40	107.00	6	Amphibolite
N0729	107.00	117.45	5	Granite
N0729	117.45	135.60	6	Amphibolite
N0729	135.60	141.10	5	Granite
N0729	141.10	200.00	6	Amphibolite
N0729	200.00	244.00	5	Granite
N0729	244.00	298.00	6	Amphibolite

Drillhole N0728 Assay Log

2.8-7

DDH	Sample #	From (m)	To (m)	Length (m)	Sample Type	Description	Cu (ppm)	Ni (ppm)	Ni (%)	SG
N0727	925371	98.19	99.13	0.94	CORE	ALTGRAN msom. chloritic, nil ss	43	1150		
N0727	925372	99.13	100.63	1.50	CORE	ALTM silv-grn and assimilated granitoid, nil-tr ss, 1/2m ground	120	1390		
N0727	925373	100.63	101.46	0.83	CORE	ALTGRAN 10% ALTM nil-tr ss	61	1610		
N0727	925374	101.46	102.66	1.20	CORE	ALTGRAN +calcsil? skarn	58	1500		
N0727	925375	102.66	103.85	1.19	CORE	ALTGRAN minor assim. ALTM tr ss	120	3550		
N0727	925376	103.85	104.37	0.52	CORE	30cm altum 20cm um or chl-mvolc, tr ss	34	3080		
N0727	925377	104.37	104.88	0.51	CORE	sauss rock, poss calcsil skarn, tr cp on fr's, tr mill diss.	81	2840		
N0727	925378	104.88	105.74	0.86	CORE	altgran bleached, chltzd near fr's	34	2510		
N0727	925379	105.74	106.97	1.23	CORE	pale fg spt 25cm altum, 19cm phlog altum ground, nil-tr ss	28	2870		
N0727	925380				STD	WPR-1	1550	2820		
N0727	925381	106.97	107.82	0.85	CORE	spt fg light grn nil-tr ss	35	3030		
N0727	925382	107.82	108.67	0.85	CORE	spt fg grey, 2-3%ss	7	>5000	1.6	
N0727	925383	108.67	109.89	1.22	CORE	spt fg grey-grn, fine patchy hem, tr ss	3	>5000	0.86	
N0727	925384	109.89	111.20	1.31	CORE	spt fg lt grn, tr ss	34	>5000	0.87	
N0727	925385	111.20	111.51	0.31	CORE	altum 10% gran, nil-tr ss	83	3950		
N0727	925386	111.51	112.40	0.89	CORE	altgran bleached chltzd, nil-tr ss	75	1410		
N0727	925387	112.40	112.94	0.54	CORE	altum, nil-tr ss	89	1290		
N0727	925388	112.94	113.86	0.92	CORE	altum/altgran hybrid, nil-tr ss GAP BELOW is 6-7cm brown clay	240	1210		
N0727	925389	113.86	114.36	0.50	CORE	spt fg dark grn, contam. 1-2% interstitial pn	650	1480		2.63
N0727	925390				BLANK	LIMESTONE	13	23		
N0727	925391	114.36	115.67	1.31	CORE	altum, silv-grn phlog and limonite, nil-tr ss	180	230		
N0727	925392	115.67	116.84	1.17	CORE	gran and spt intr. bx with 40% peg frag, nil-tr ss	57	910		
N0727	925393	116.84	117.36	0.52	CORE	gran dyke, minor chl, nil-tr ss	30	410		
N0727	925394	117.36	118.84	1.48	CORE	altgran msom. sheared, mFZ at bottom, tr ss on fr's	57	250		
N0727	925395	118.84	119.57	0.73	CORE	altgran msom. chl, nil-tr ss	30	490		
N0727	925396	119.57	121.10	1.53	CORE	gran dyke, fresh no infills	20	120		
N0727	925397	121.10	122.49	1.39	CORE	altgran mod. chl, <1%cp on fr's	63	540		
N0727	925398	122.49	123.80	1.31	CORE	maf mvolc? 10% gran	190	810		
N0727	925399	123.80	124.75	0.95	CORE	altgran tr ss on fr's	51	500		
N0727	925400	124.75	126.15	1.40	CORE	maf mvol? dark red brown fg	140	1020		
N0727	925401	126.15	126.90	0.75	CORE	maf mvol fg dark red-brown hemtzd	120	1290		
N0727	925402	126.90	127.53	0.63	CORE	altum grn-brown	43	570		
N0727	925403	127.53	128.68	1.15	CORE	altum phlog-tc	270	3710		
N0727	925404				STD	IGS-22	1090	>5000	1.27	
N0727	925405	128.68	130.02	1.34	CORE	spt fg dk grn, some hem trem, 2% ss	370	>5000	1.26	
N0727	925406	130.02	131.41	1.39	CORE	spt as above 3-4% ss	49	>5000	1	
N0727	925407	131.41	132.34	0.93	CORE	spt as above 2-3% ss	61	>5000	0.89	
N0727	925408	132.34	133.17	0.83	CORE	spt c-txt red-brn pseud. 2% ss	41	>5000	1.24	
N0727	925409				BLANK	LIMESTONE	<1	30		
N0727	925410	133.17	133.92	0.75	CORE	spt+altum-tc, tr ss, ann on fr's	200	>5000	1.21	2.35
N0727	925411	133.92	135.06	1.14	CORE	altgran + altum proportions?? Junior geol!	13	1750		
N0727	925412	135.06	135.90	0.84	CORE	as above	17	4530		

Drillhole N0728 Assay Log

DDH	Sample #	From (m)	To (m)	Length (m)	Sample Type	Description	Cu (ppm)	Ni (ppm)	Ni (%)	SG
N0727	925413	135.90	136.48	0.58	CORE	altum 5% altgran, minor ann	130	>5000	1	
N0727	925414	136.48	137.81	1.33	CORE	spt fg, mottled med tp dk grn, hemtized patches, 2% ss	8	4980		
N0727	925415	137.81	139.27	1.46	CORE	spt as above	23	>5000	0.84	
N0727	925416	139.27	140.07	0.80	CORE	spt 30% trem for top 20cm, tr ss	24	>5000	0.88	
N0727	925417				BLANK	LIMESTONE	2	24		
N0727	925418	140.07	140.90	0.83	CORE	spt c-txt, hem pseudomorphs, tr ss, mill on fr's	130	3000		
N0727	925419	140.90	141.65	0.75	CORE	altgran+altum, tr ss on fr's	140	3400		
N0727	925420	141.65	143.00	1.35	CORE	altum +altgran, 1%ss, tr cp on fr's	160	3220		
N0727	925421	143.00	143.39	0.39	CORE	spt fg med grn, ~1% ss	98	4280		
N0727	925422	143.39	143.68	0.29	CORE	altgran, hemtized, clay fr-fills	50	3840		
N0727	925423	143.68	145.01	1.33	CORE	spt mg c-txt, top 10cm altum, 1-2% ss	44	>5000	0.94	
N0727	925424	145.01	146.18	1.17	CORE	spt mg c-txt, med grn tr ss	14	>5000	0.72	
N0727	925425	146.18	146.80	0.62	CORE	altgran 65%, altum 35%, nil-tr ss	9	3900		
N0727	925426				STD	WPR-1	1500	2800		
N0727	925427	146.80	148.44	1.64	CORE	altum-trem hemtized, tr ss	400	>5000	0.89	
N0727	925428	148.44	149.68	1.24	CORE	altum as above tr ss	310	3000		
N0727	925429	149.68	150.44	0.76	CORE	altgran tr mill from fr's, and altum phlog-tc, tr ss	71	4090		
N0727	925430	150.44	150.71	0.27	CORE	spt med to dk grn, some trem, tr ann on fr's	32	>5000	1.03	2.46
N0727	925431	150.71	152.37	1.66	CORE	spt as above, minor ann	19	>5000	1.41	
N0727	925432	152.37	153.08	0.71	CORE	altum, 25% altgran	150	4890		
N0727	925433	153.08	154.10	1.02	CORE	spt med to dk grn, minor fr-hosted mill, some tc-ann fr's, 1-2% ss	20	>5000	0.76	
N0727	925434				BLANK	LIMESTONE	1	16		
N0727	925435	154.10	155.09	0.99	CORE	spt dk grn 2% ss	37	>5000	1.03	
N0727	925436	155.09	156.17	1.08	CORE	spt med to dk grn, minor cp, 2% ss	770	>5000	1.15	
N0727	925437	156.17	157.61	1.44	CORE	spt lt to dk grn, 2% ss	780	>5000	0.88	
N0727	925438	157.61	159.22	1.61	CORE	spt with tc alt, 2% ss	310	4680		
N0727	925439	159.22	159.60	0.38	CORE	spt 50% altum, ~1% ss	100	1690		
N0727	925440	159.60	160.05	0.45	CORE	altgran-hem and altum tc-phlog	32	750		
N0727	925441	160.05	161.76	1.71	CORE	spt fg dk grn, talcose, tr ss	250	3650		
N0727	925442	161.76	163.18	1.42	CORE	spt as above tr ss	220	3730		
N0727	925443	163.18	164.00	0.82	CORE	spt as above, 1-2% ss	530	>5000	0.57	
N0727	925444	164.00	164.72	0.72	CORE	spt, mg grey-grn, talcose 1% ss	510	4300		
N0727	925445				STD	IGS-22	1070	>5000	1.27	
N0727	925446	164.72	166.18	1.46	CORE	spt as above faint c-txt, 2-3% ss mainly pn	610	>5000	0.63	
N0727	925447	166.18	166.60	0.42	CORE	spt as above, 50% altum, ~1% ss	270	4120		
N0727	925448	166.60	167.80	1.20	CORE	spt as above, altum fr-related at end, 1-2% ss, lesser mt	610	>5000	0.83	
N0727	925449	167.80	169.33	1.53	CORE	spt as above, 3-4% ss, minor mt	820	>5000	1.16	
N0727	925450	169.33	170.40	1.07	CORE	spt fg grey-grn, 3-4% ss, 2% mt, some intergrowths	1040	>5000	1.13	2.43
N0727	925451				BLANK	LIMESTONE	9	71		
N0727	925452	170.40	171.85	1.45	CORE	spt fg grey-grn, tr cp, 1-2% ss, 3-4% mt	1160	>5000	1.1	
N0727	925453	171.85	172.94	1.09	CORE	spt as abovediss cp on tc-fr's, 1-2% ss similar mt	750	>5000	0.9	
N0727	925454	172.94	174.45	1.51	CORE	spt as above, tr cp on fr's, 1-2% ss, 3-4% mt	830	>5000	1.1	

Drillhole N0728 Assay Log

DDH	Sample #	From (m)	To (m)	Length (m)	Sample Type	Description	Cu (ppm)	Ni (ppm)	Ni (%)	SG
N0727	925455	174.45	175.97	1.52	CORE	spt fg dk grn, 1% ss, 5% mt	590	>5000	0.71	
N0727	925456				STD	WPR-1	1500	2860		
N0727	925457	175.97	176.57	0.60	CORE	spt vfg dk grn-blk3-4% ss, some mt intergrowths, cpy films on fr's	1000	>5000	1.04	
N0727	925458	176.57	176.82	0.25	CORE	altum, 10cm spt, solid cp film at 176.57m	530	>5000	0.72	
N0727	925459	176.82	178.04	1.22	CORE	spt fg-mg, dk grn3-5% ss talcose	820	>5000	1.14	
N0727	925460	178.04	179.00	0.96	CORE	spt as above, 2-3% ss	700	>5000	1.18	
N0727	925461	179.00	180.15	1.15	CORE	spt as above 2-3% ss	1030	>5000	1.21	
N0727	925462	180.15	181.33	1.18	CORE	spt as above, 1-2% ss	1100	>5000	1.29	
N0727	925463	181.33	182.22	0.89	CORE	spt, 50% altum-1% ss	890	>5000	0.94	
N0727	925464	182.22	182.93	0.71	CORE	altum-phlog	210	>5000	0.88	
N0727	925465	182.93	183.45	0.52	CORE	altum hem clay fr-fills	9	450		
N0727	925466	183.45	184.13	0.68	CORE	altum phlog-tc	4	4140		
N0727	925467	184.13	185.29	1.16	CORE	spt fg, greyish, minor ann from fr's, tr ss	16	3630		
N0727	925468				BLANK	LIMESTONE	3	31		
N0727	925469	185.29	186.00	0.71	CORE	spt vfg, mottled red-brn to grn, tr ss	8	1950		
N0727	925470	186.00	186.61	0.61	CORE	spt trem bearing, 40% altum, tr ss	67	2550		2.37
N0727	925471	186.61	188.00	1.39	CORE	altum/altum, gap below is fresh granitoid unsampled	7	450		
N0727	925472	196.40	197.56	1.16	CORE	altum, tr mill from low angle fr	2	140		
N0727	925473	197.56	198.43	0.87	CORE	altum, tr mill on fr's	8	1320		
N0727	925474	198.43	199.54	1.11	CORE	altum, tr ss on fr's	3	740		
N0727	925475	199.54	200.86	1.32	CORE	altum, 40% altum tc-phlog	42	1300		
N0727	925476	200.86	202.44	1.58	CORE	altum hem clay fr-fills	11	1180		
N0727	925477	202.44	203.81	1.37	CORE	altum as above	2	180		
N0727	925478	203.81	205.27	1.46	CORE	altum as above	2	180		
N0727	925479	205.27	206.34	1.07	CORE	altum as above	<1	190		
N0727	925480	206.34	207.04	0.70	CORE	altum, 5% altum	2	670		
N0727	925481	207.04	207.94	0.90	CORE	spt, c-txt cg, hemtzd tr ss	<1	2250		
N0727	925482	207.94	209.20	1.26	CORE	spt c-txt, lt to dk grn, tr ss	<1	2190		
N0727	925483				STD	WPR-1	1570	2930		
N0727	925484	209.20	210.73	1.53	CORE	spt, c-txt cg, dk grn, tr ss	<1	2520		
N0727	925485	210.73	211.94	1.21	CORE	spt as above	<1	1600		
N0727	925486	211.94	213.12	1.18	CORE	spt fg, mottled with lt grn patches, tr ss	45	1850		
N0727	925487	213.12	213.48	0.36	CORE	altum hemtzd, clay fr-fills, cpy on fr's ~1%	15	330		
N0727	925488				BLANK	LIMESTONE	<1	9		
N0727	925489	213.48	215.00	1.52	CORE	gran mg	<1	31		
N0727	925490				STD	GBM-1	550	>5000	1.23	
N0727	925491	215.00	216.33	1.33	CORE	altum hem clay fr-fills	6	230		2.57
N0727	925492	216.33	218.00	1.67	CORE	altum as above	9	420		
N0727	925493	218.00	218.74	0.74	CORE	altum as above	12	520		
N0727	925494	218.74	220.10	1.36	CORE	spt c-txt and altum tc-trem	18	1820		
N0727	925495	220.10	220.36	0.26	CORE	altum hemtzd	4	270		
N0727	925496	220.36	221.61	1.25	CORE	spt c-txt lt to dk grn, tr ss	15	2040		

Drillhole N0728 Assay Log

DDH	Sample #	From (m)	To (m)	Length (m)	Sample Type	Description	Cu (ppm)	Ni (ppm)	Ni (%)	SG
N0727	925497	221.61	221.91	0.30	CORE	spt as above, 10% altum	19	2080		
N0727	925498	221.91	224.00	2.09	CORE	spt as above, 10% altum	13	1820		
N0727	925499				STD	GBM-1	1250	>5000	1.24	
N0727	925500	224.00	225.00	1.00	CORE	spt dk grn, mill on fr's, tr ss throughout, followed by 926401				
N0727	926401	225.00	227.00	2.00	CORE	altum + spt dk grn, tr ss, mill on a single fracture	5	2030		
N0727	926402	227.00	228.52	1.52	CORE	spt lt to med grn serp-tc pseudomorphs, tr ss	1	1470		
N0727	926403	228.52	229.73	1.21	CORE	altgran hemtzd	20	2070		
N0727	926404	229.73	231.27	1.54	CORE	altgran hemtzd	30	200		
N0727	926405	231.27	233.00	1.73	CORE	altgran hemtzd	20	290		
N0727	926406	233.00	233.97	0.97	CORE	altgran+altum tc-phlog	16	210		
N0727	926407	233.97	235.17	1.20	CORE	spt cg rel c-txt dk grn to red-brown	4	1190		
N0727	926408				STD	IGS-22	1	2080		1.32
N0727	926409	235.17	236.00	0.83	CORE	spt cg rel c-txt dk grn to red-brown	960	>5000		
N0727	926410	236.00	237.24	1.24	CORE	spt cg rel c-txt dk grn to red-brown, final 20cm altum	<1	1950		
N0727	926411	237.24	239.00	1.76	CORE	spt med grn to brown, tr ss mill on a fr	<1	1430		
							<1	1150		

Drillhole N0729 Assay Log

DDH	Sample #	From (m)	To (m)	Length (m)	Sample Type	Description	Cu (ppm)	Ni (ppm)	Ni (%)	SG
N0728	926412	85.75	86.33	0.58	CORE	ALTUM, light grey, phlog+chl, silicified, granular, 3% disseminated sulphide	820	>5000	0.89	
N0728	926413	86.33	87.06	0.73	CORE	ALTGRAN, fg, faded green, highly bleached	450	2540		
N0728	926414	87.06	88.13	1.07	CORE	ALTGRAN, fg, faded green + pink, highly bleached	280	2640		
N0728	926415	88.13	89.00	0.87	CORE	ALTGRAN, fg, faded green + pink, highly bleached, trace sulphide on a fractu	360	1490		
N0728	926416	89.00	89.57	0.57	CORE	ALTGRAN, fg, faded green + pink, bleached, coarse grained calcite on fractu	120	1680		2.24
N0728	926417	89.57	90.60	1.03	CORE	Volcanic (mafic meta), vfg, reddish black to greenish black, randomly orien	130	1830		
N0728	926418	90.60	91.30	0.70	CORE	Volcanic (mafic meta), vfg, reddish black to greenish black, randomly orien	71	1550		
N0728	926419	91.30	92.09	0.79	CORE	Volcanic (mafic meta), vfg, reddish black to greenish black, randomly orien	73	1410		
N0728	926420	92.09	92.93	0.84	CORE	Volcanic (mafic meta), vfg, reddish black to greenish black, randomly orien	68	1820		
N0728	926421	92.93	93.85	0.92	CORE	Volcanic (mafic meta), vfg, reddish black to greenish black, randomly orien	90	1310		
N0728	926422	93.85	94.57	0.72	CORE	Volcanic (mafic meta), vfg, reddish black to greenish black, randomly orien	99	1160		
N0728	926423				STD	WPR-1	1630	2590		
N0728	926424	94.57	95.27	0.70	CORE	Volcanic (mafic meta), vfg, reddish black to greenish black, randomly orien	73	1160		
N0728	926425	95.27	96.00	0.73	CORE	Volcanic (mafic meta), vfg, reddish black to greenish black, randomly orien	140	1390		
N0728	926426	96.00	97.00	1.00	CORE	ALTGRAN dyke, dk green+brownish green, random grey specks, ~5% sulphide on	88	1530		
N0728	926427	97.00	97.38	0.38	CORE	Volcanic (mafic meta), vfg, reddish black to greenish black, fg sulphide on	210	1740		
N0728	926428	97.38	98.00	0.62	CORE	ALTGRAN dyke, dk green+brownish green, random grey specks, abundant milleri	57	2230		
N0728	926429	98.00	98.50	0.50	CORE	Volcanic (mafic meta), vfg, reddish black to greenish black, fg sulphide on	100	2290		
N0728	926430	98.50	99.40	0.90	CORE	Volcanic (mafic meta), vfg, reddish black to greenish black, fg sulphide on	94	2100		
N0728	926431	99.40	99.72	0.32	CORE	ALTGRAN dyke, dk green+brownish green, random grey specks, ~5% sulphide on	68	1860		
N0728	926432	99.72	100.52	0.80	CORE	Volcanic (mafic meta), vfg, reddish black to greenish black, randomly orien	140	1840		
N0728	926433	100.52	101.00	0.48	CORE	ALTUM dyke, light green with red hematized patches, common vugs 3mm wide	98	260		
N0728	926434	101.00	101.90	0.90	CORE	Volcanic (mafic meta), vfg, reddish black to greenish black, randomly orien	84	2250		
N0728	926435	101.90	102.23	0.33	CORE	Volcanic (mafic meta), vfg, reddish black to greenish black, randomly orien	180	3340		
N0728	926436	102.23	103.00	0.77	CORE	SPT, fg, light green hematized, contaminated	89	>5000	1	2.24
N0728	926437				STD	WPR-1	1610	2550		
N0728	926438	103.00	104.00	1.00	CORE	SPT, light to medium green hematized splotchy texture, tr. sulph., 40 cm cor	57	>5000	1.36	
N0728	926439	104.00	104.84	0.84	CORE	SPT, light to medium green hematized splotchy texture, tr. sulph., random mt	6	>5000	1.24	
N0728	926440	104.84	105.64	0.80	CORE	Fault Zone, vfg, broken ALTUM (talc, phlog, chlorite)	130	>5000	1.22	
N0728	926441	105.64	106.24	0.60	CORE	SPT, fg, medium green, talc splotches, tr. sulph.	82	>5000	1.56	
N0728	926442	106.24	107.54	1.30	CORE	SPT, fg, dark green, moderately hematized, 1-2% sulph.	400	>5000	1.69	
N0728	926443				BLANK	LIMESTONE	3	85		
N0728	926444	107.54	108.47	0.93	CORE	SPT, fg, lighter green, 1-2% sulph	11	>5000	1.11	
N0728	926445	108.47	109.90	1.43	CORE	ALTUM, very broken up, light bluish green, talc+phlog+chlorite	44	2350		
N0728	926446	109.90	110.85	0.95	CORE	ALTUM, first 35cm tremolite rich rock=light pink/green, remainder=very brok	13	1330		
N0728	926447	110.85	112.17	1.32	CORE	SPT, cumulate, medium green, hematized, tr. sulph.	6	1510		
N0728	926448	112.17	112.76	0.59	CORE	SPT, cumulate, medium green, hematized, tr. sulph., talc rich	9	1650		
N0728	926449	112.76	113.88	1.12	CORE	SPT, medium green, cumulate, common talcose veinlets of random orientation,	9	2000		
N0728	926450	113.88	114.65	0.77	CORE	FGRAN 62cm: hem. pink, mgrained, green clay filled fract common, ALTUM 15cm	23	860		
N0728	926451	114.65	115.38	0.73	CORE	SPT, medium green, mgrained pseudomorphs(cumulate), frequent talcose veinle	30	1570		
N0728	926452				STD	WPR-1	1610	2580		
N0728	926453	115.38	116.49	1.11	CORE	SPT, cumulate, pervasively hem. pseudomorphs, light gr matrix, random mt fl	17	2170		
N0728	926454	116.49	117.30	0.81	CORE	SPT, light green, cumulate, hem. pseudomorphs, random mt flecks, talcose, t	40	2120		
N0728	926455	117.30	118.33	1.03	CORE	ALTUM, light green, talc-tremolite rich, random mt flecks	65	1700		
N0728	926456	118.33	119.72	1.39	CORE	Granitic Dyke, pink, mgrained, 12 cm pure qtz	32	190		2.62

Drillhole N0729 Assay Log

DDH	Sample #	From (m)	To (m)	Length (m)	Sample Type	Description	Cu (ppm)	Ni (ppm)	Ni (%)	SG
N0728	926457	119.72	120.01	0.29	CORE	ALTUM, fg, very talcose, light blue-pink	12	380		
N0728	926458	120.01	120.70	0.69	CORE	SPT, cumulate, light to medium green, talcose matrix, yellow serpentine spe	100	1910		
N0728	926459	120.70	121.80	1.10	CORE	SPT, fg, dk green, abundant millerite on rare fractures, abundant talcose l	52	2240		
N0728	926460	121.80	122.95	1.15	CORE	SPT, medium green, fg, talcose, tr. sulph.	28	1920		
N0728	926461	122.95	124.42	1.47	CORE	SPT, medium green, fg, talcose, tr. sulph.	23	2410		
N0728	926462				STD	GBM-1	450	>5000	1.22	
N0728	926463	124.42	125.73	1.31	CORE	SPT, medium green, fg, talcose, tr. sulph.	28	2560		
N0728	926464	125.73	127.28	1.55	CORE	SPT, dk green, fg, talcose lenses, tr. sulph.	24	2470		
N0728	926465				BLANK	LIMESTONE				
N0728	926466	127.28	128.49	1.21	CORE	SPT, dk green, fg, talcose lenses, abundant millerite on rare fractures, 15	100	2070		
N0728	926467	128.49	129.60	1.11	CORE	SPT, med. green, cumulate, talcose mat., pervasively hem. pseudomorphs, den	66	2130		
N0728	926468				STD	IGS-22	1040	>5000	1.26	
N0728	926469	129.60	130.37	0.77	CORE	SPT, light green, cumulate, talcose matrix, tr. sulph.	180	1570		
N0728	926470	130.37	131.43	1.06	CORE	FRAN, mgrained, pink/dk reddish pink, common green clay filled fractures,	50	560		
N0728	926471	131.43	133.00	1.57	CORE	SPT, cumulate, medium green, pervasively hem. pseudomorphs, tr. sulph.	47	2220		
N0728	926472	133.00	134.35	1.35	CORE	ALTUM: 60%, fg, soft phlog+chl, ~60 lost core, SPT: 40% dk green talcose, t	12	1740		
N0728	926473	134.35	135.36	1.01	CORE	SPT, dk green, mgrained, very talcose, tr. sulph.	4	2040		
N0728	926474	135.36	137.00	1.64	CORE	SPT, fg, dk green, minor millerite on rare fractures, speckled with fine ta	10	2150		
N0728	926475	137.00	138.30	1.30	CORE	SPT, fg, dk green, speckled with fine talc., ~30cm ALTUM: phlog+tc-trem	17	2650		
N0728	926476	138.30	139.75	1.45	CORE	SPT, fg, medium green, tr. sulph.	2	1960		
N0728	926477	139.75	140.66	0.91	CORE	Granitic Dyke: 50%, pervasive hem., ALTUM:50%, light bluish green, phlog	8	1140		
N0728	926478	140.66	142.00	1.34	CORE	SPT, fg, light to medium green, 15cm tremolite rich rock, tr. sulph.	2	1840		
N0728	926479	142.00	143.00	1.00	CORE	SPT, fg, light green, tr. sulph.	4	2210		
N0728	926480				STD	WPR-1	1640	2600		2.42
N0728	926481	143.00	144.15	1.15	CORE	SPT, fg, light green, tr. sulph.	4	2440		
N0728	926482	144.15	145.20	1.05	CORE	SPT, fg, light green, tr. sulph.	2	2470		
N0728	926483	145.20	146.15	0.95	CORE	SPT, fg, light green, tr. sulph.	2	2570		
N0728	926484	146.15	147.50	1.35	CORE	SPT, fg, light green, tr. sulph.	3	2500		
N0728	926485	147.50	148.13	0.63	CORE	SPT, fg, medium green, very broken, solid sulph. fracture filling of pentla	3	2200		
N0728	926486				BLANK	LIMESTONE	3	13		
N0728	926487	148.13	148.61	0.48	CORE	SPT, mgrained, medium green, very broken, abundant millerite on rare fractu	7	2220		
N0728	926488	148.61	149.30	0.69	CORE	SPT, mgrained, light green, abundant sulphide on rare fractures	9	1810		
N0728	926489	149.30	149.75	0.45	CORE	Granitic Dyke: pervasively hem., green clay filled fracture, ALTUM: light b	7	1120		
N0728	926490	149.75	151.40	1.66	CORE	SPT, fg, dk green, abundant millerite on rare fractures	23	2030		
N0728	926491	151.40	151.87	0.46	CORE	SPT, dk green, coarse dk pseudomorphs, 10% talc filled fracture swarm, rare	13	1940		
N0728	926492	151.87	153.34	1.47	CORE	Granitic Dyke: 60%, pink/light green, altered, rare fract. filled with clay	13	250		
N0728	926493	153.34	153.90	0.56	CORE	SPT, medium green, dense fracture swarm infilled with talc, millerite on ra	37	1780		
N0728	926494	153.90	155.04	1.14	CORE	SPT, fg medium green, tr. sulph.	56	1910		
N0728	926495	155.04	156.67	1.63	CORE	SPT, dk green, abundant millerite on rare fractures, 10cm granite	22	2280		
N0728	926496	156.67	157.95	1.28	CORE	SPT, light green, fg, tr. sulph., 10cm typical ALTUM	3	1960		
N0728	926497	157.95	158.64	0.69	CORE	SPT:70%, light green, medium grain, tr. sulph., ALTUM:25%, soft, light green+brown	5	1530		
N0728	926498	158.64	159.50	0.86	CORE	SPT, medium green, fg, splotches of talc, abundant millerite on 2 fractures	17	2100		
N0728	926499				STD	IGS-22	970	>5000	1.22	
N0728	926500	159.50	161.00	1.50	CORE	SPT, fg, medium green, talcose, tr. sulph.	22	2510		
N0728	926501	161.00	162.26	1.26	CORE	SPT, fg, medium green, tr. sulph. but abundant millerite on one fracture	41	2120		

2.8-12

Drillhole N0729 Assay Log

DDH	Sample #	From (m)	To (m)	Length (m)	Sample Type	Description	Cu (ppm)	Ni (ppm)	Ni (%)	SG
N0728	926502	162.26	163.35	1.09	CORE	Granite:65%,pink,mgrained,abundant millerite on 2 fractures,ALTUM:35%,ligh	12	370		
N0728	926503	163.35	163.73	0.38	CORE	SPT, fg, medium green, abundant millerite on 3 fractures,fracture swarm inf	34	1750		
N0728	926504				BLANK	LIMESTONE	4	2		
N0728	926505	163.73	164.62	0.89	CORE	SPT, m grained, medium green, tr. sulph.	13	2520		
N0728	926506	164.62	165.85	1.23	CORE	SPT, fg, dk green, abundant millerite on 2 fractures	5	2570		
N0728	926507	165.85	167.22	1.37	CORE	SPT, fg, dk green, tr. sulph.	4	2740		
N0728	926508	167.22	168.78	1.56	CORE	SPT, fg, dk green, tr. sulph.	4	2530		
N0728	926509				BLANK	LIMESTONE	4	1400		
N0728	926510	168.78	170.22	1.44	CORE	SPT, fg, dk green, tr. sulph.	4	2670		
N0728	926511	170.22	171.38	1.16	CORE	SPT, fg, dk green, millerite on 1 fracture	4	2490		
N0728	926512	171.38	172.14	0.76	CORE	SPT, fg, dk green, abundant millerite on 3 fractures	8	2200		
N0728	926513	172.14	173.12	0.98	CORE	SPT, m green+reddish brown, hem., cut by dense fracture swarm infilled with	13	1230		
N0728	926514	173.12	173.88	0.76	CORE	SPT:50%, fg, green tr. sulph., ALTUM:50%, patch of hematized tremolite	65	1600		
N0728	926515	173.88	175.90	2.02	CORE	Granite, pink, m grained, 10 cm soft ALTUM	14	98		
N0728	926516	175.90	177.90	2.00	CORE	Pinkish, FGRAN, haematized, serp infills,	10	140		2.58
N0728	926517				STD	WPR-1	1670	2560		
N0728	926518	177.90	179.00	1.10	CORE	Greenish brown, pervasively haematized, mg, pseudomorphs, ALTUM, tr sulph	27	1070		
N0728	926519	179.00	182.00	3.00	CORE	70% FGRAN +30% ALTUM, tr of py on frac, nil on rock	12	320		
N0728	926520	182.00	185.00	3.00	CORE	70% FGRAN +30% ALTUM, tr of py and cpy on frac, nil on rock	17	200		
N0728	926521	185.00	188.00	3.00	CORE	ALTGRAN, cataclastite from 187.3 to 188, nil sulph.	6	310		
N0728	926522	188.00	191.00	3.00	CORE	50% ALTRAN, 50 % pinkish granite, nil sulph.	8	64		
N0728	926523	191.00	194.00	3.00	CORE	Pinkish, kspat rich, syenitic granitoid, nil sulph.	8	18		
N0728	926524	194.00	197.00	3.00	CORE	Pinkish, kspat rich, syenitic granitoid, nil sulph	8	9		
N0728	926525	197.00	200.00	3.00	CORE	Pinkish, kspat rich, syenitic granitoid, nil sulph	8	5		
N0728	926526	200.00	203.00	3.00	CORE	Pinkish, kspat rich, syenitic granitoid, nil sulph	13	8		
N0728	926527	203.00	206.00	3.00	CORE	Pinkish, kspat rich, syenitic granitoid, nil sulph	10	47		
N0728	926528	206.00	207.56	1.56	CORE	50% ALTGRAN, 50% syenite, nil sulph	10	160		
N0728	926529				STD	FGRAN, sub vertical fracture, millerite on the granite fracture	1620	2500		
N0728	926530	207.56	209.57	2.01	CORE	WPR-1	46	580		
N0728	926531	209.57	212.00	2.43	CORE	Phlo, trem, ALTUM with asso contaminated granite, tr sulph	9	180		
N0728	926532	212.00	215.00	3.00	CORE	ALTGRAN, nil sulph	7	29		
N0728	926533	215.00	218.00	3.00	CORE	ALTGRAN, nil sulph	10	29		
N0728	926534	218.00	221.00	3.00	CORE	ALTGRAN, nil sulph	12	5		
N0728	926535	221.00	224.00	3.00	CORE	ALTGRAN, nil sulph	7	6		2.61
N0728	926536	224.00	227.00	3.00	CORE	ALTGRAN, nil sulph	10	8		
N0728	926537	227.00	230.00	3.00	CORE	Broken core, strongly bleached, cataclastite fault rocks, ALTGRAN, nil sulph	11	37		
N0728	926538	230.00	233.00	3.00	CORE	50 % pinkish GRAN, 50 % Cataclastite, nil sulph	11	56		
N0728	926539	233.00	236.00	3.00	CORE	Pinkish green contaminated granite, nil sulph	16	32		
N0728	926540	236.00	238.90	2.90	CORE	Pinkish, K-spar rich syenite	11	93		
N0728	926541	238.90	240.03	1.13	CORE	Greenish brown, pervasively haematized, contaminated ultramafics, tr sulph,	21	730	1.21	
N0728	926542				STD	GBM-1	390	>5000		
N0728	926543	240.03	240.90	0.87	CORE	Greenish brown, pervasively haematized, contaminated ultramafics, tr sulph,	33	690		
N0728	926544	240.90	242.00	1.10	CORE	ALTGRAN, nil sulph	16	130		
N0728	926545	242.00	243.84	1.84	CORE	ALTGRAN, nil sulph	12	81		
N0728	926546	243.84	245.00	1.16	CORE	Greenish brown, pervasively haematized, contaminated ultramafics, tr sulph,	65	440		

2.8-13

Drillhole N0729 Assay Log

DDH	Sample #	From (m)	To (m)	Length (m)	Sample Type	Description	Cu (ppm)	Ni (ppm)	Ni (%)	SG
N0728	926547	245.00	245.94	0.94	CORE	Greenish brown, pervasively haematized, contaminated ultramafics, tr sulp,	170	2990		
N0728	926548	245.94	248.00	2.06	CORE	FRAN, serp infills, tr sulp on frac not on rock	35	170		
N0728	926549	248.00	251.00	3.00	CORE	Pinkish, massive syenite, nil sulp	12	19		
N0728	926550	251.00	254.00	3.00	CORE	Pinkish, massive syenite, nil sulp	13	8		
N0728	926551	254.00	257.00	3.00	CORE	70% Granitic dyke, 30% Amphibolite	30	42		
N0728	926552	257.00	260.00	3.00	CORE	60% Amphibolite, 30% GRAN, 10% ALTGRAN	12	260		
N0728	926553	260.00	263.00	3.00	CORE	Pinkish, massive, syenite with 30%bleached ALTGRAN, nil sulp	12	28		
N0728	926554	263.00	266.00	3.00	CORE	90% Amphibolite+10% GRAN	13	260		
N0728	926555				STD	WPR-1	1620	2570		
N0728	926556	266.00	269.00	3.00	CORE	90% Amphibolite+10% GRAN	16	130		2.87
N0728	926557	269.00	272.00	3.00	CORE	80% Amphibolite + 20% GRAN	29	16		
N0728	926558	272.00	275.00	3.00	CORE	Greenish black chloritized amphibolite	110	38		
N0728	926559	275.00	278.00	3.00	CORE	Greenish black chloritized amphibolite	69	75		
N0728	926560	278.00	281.00	3.00	CORE	Greenish black chloritized amphibolite	23	120		
N0728	926561	281.00	284.00	3.00	CORE	Greenish black chloritized amphibolite	14	100		
N0728	926601	368.36	369.67	1.31	CORE	70% Greenish black chloritized amphibolite, 30% GRAN	<1	410		2.61
N0728	926602	369.67	371.00	1.33	CORE	70% Greenish black chloritized amphibolite, 30% GRAN	12	440		
N0728	926603	371.00	372.55	1.55	CORE	Greenish black chloritized amphibolite	85	750		
N0728	926604	372.55	374.00	1.45	CORE	90% Greenish black chloritized amphibolite, 10% GRAN	7	400		
N0728	926605	374.00	375.40	1.40	CORE	Greenish black chloritized amphibolite	250	610		
N0728	926606	375.40	377.00	1.60	CORE	60% GRAN, 40% AM	12	190		
N0728	926607	377.00	378.56	1.56	CORE	FZ, 70% AM, 30% GRAN	10	430		
N0728	926608				PULP	PULP "B" 925723	<1	2450		
N0728	926609	378.56	380.00	1.44	CORE	Greenish black chloritized amphibolite	1	600		
N0728	926610	380.00	381.44	1.44	CORE	Greenish black chloritized amphibolite	<1	600		
N0728	926611	381.44	383.17	1.73	CORE	Greenish black chloritized amphibolite	<1	690		
N0728	926612	354.35	355.81	1.46	CORE	90% Greenish black chloritized amphibolite, 10% GRAN	57	620		
N0728	926613	355.81	357.26	1.45	CORE	Greenish black chloritized amphibolite	47	730		
N0728	926614	357.26	358.50	1.24	CORE	Greenish black chloritized amphibolite	<1	510		
N0728	926615	358.50	360.09	1.59	CORE	80%Greenish black chloritized amphibolite, 20% gran	24	400		
N0728	926616	360.09	361.82	1.73	CORE	Chloritized amphibolite cut by 3 minor GRAN veinlets	25	160		
N0728	926617	361.82	363.15	1.33	CORE	Chloritized amphibolite cut by a 5 cm minor GRAN veinlet.	41	200		
N0728	926618	363.15	364.63	1.48	CORE	Chloritized amphibolite asso with 5% GRAN xenolith	40	350		
N0728	926619				PULP	PULP "B" 925812	180	4370		
N0728	926620	364.63	366.07	1.44	CORE	Greenish black chloritized amphibolite	35	740		
N0728	926621	366.07	367.10	1.03	CORE	Greenish black chloritized amphibolite	25	620		2.57
N0728	926622	367.10	367.90	0.80	CORE	Greenish black chloritized amphibolite	14	620		

**Phase II
Sample
Selection**

**Summary of Phase II Static Tests Sample Selection
Minago Project
August 2008**

Numeric Code	Alpha Code	Description	# Samples		
			BHK holes	N holes	SUBTOTAL
1	OVB	Overburden			0
2	PZD	Dolomite			0
3	PZS	Sandstone			0
4	SPT	Serpentinite	10	22	32
5	GT	Granite	16	17	33
6	AMP	Amphibolite	1	3	4
7	PYX	Pyroxenite			0
8	PER	Peridotite			0
9	SCH	Schist			0
10	LC	Lost Core			0
11	R	Regolith		1	1
12	MD	Mafic Dike		3	3
13	MSD	Metasediment		6	6
14	MMV	Mafic Metavolcanic		2	2
TOTAL			27	54	81

Summary of Phase II Static Test Samples Selected
 BHK Drill Hole Intersections
 Minago Project

Sample #	Code	Hole ID	From (ft.)	To (ft.)	Length	Sample #	Ni ppm	Ni %	Pt ppm	Pd ppm	Cu ppm	Co ppm	Au ppm	Ag ppm
1	SPT	BHK 41-R1-90	607	610.35	3.35	259758	1420		<0.005	0.005	8	74	<0.001	<0.5
2	SPT	BHK 41-R1-90	1051.5	1056.2	4.7	365627	>10000	1.16	0.126	0.239	505	167	0.048	<0.5
3	GT	BHK 41-R1-90	1080	1083	3	365633	178		<0.005	0.003	180	8	0.001	<0.5
4	GT	BHK 42-90	767	774	7	49092	28		<0.005	0.005	19	6	<0.001	<0.5
5	GT	BHK 42-90	962	967	5	49125	12		<0.005	<0.001	5	4	0.002	<0.5
6	GT	BHK 42-90	962	967	5	49125	12		<0.005	<0.001	5	4	0.002	<0.5
7	GT	BHK 42-R2-90	1089	1094	5	365507	34		<0.005	0.001	17	18	<0.001	<0.5
8	GT	BHK 42-R2-90	1166	1172	6	365525	38		<0.005	<0.001	19	5	<0.001	<0.5
9	GT	BHK 43-90	927	937	10	49427	334		<0.005	<0.001	12	8	<0.001	<0.5
10	GT	BHK 49-R9-90	463.75	467.5	3.75	258551	40		<0.005	<0.001	15	6	<0.001	<0.5
11	GT	BHK 49-R9-90	495.5	505.5	10	258555	7		<0.005	<0.001	17	7	<0.001	<0.5
12	GT	BHK 49-R9-90	739	746.5										
13	SPT	BHK 49-R9-90	746.5	749.9	3.4	258612	4540		0.072	0.142	26	96	0.011	<0.5
14	SPT	BHK 49-R9-90	818.5	821.5	3	258774	>10000	1.61	0.186	0.403	1050	190	0.028	0.9
15	GT	BHK 49-R9-90	833.2	835	1.8	258779	649		<0.005	0.01	57	6	0.013	<0.5
16	SPT	BHK 49-R9-90	927	932	5	258618	2620		0.048	0.095	94	111	0.002	<0.5
17	GT	BHK 49-R9-90	1015.5	1017	1.5	258637	104		<0.005	<0.001	20	7	<0.001	<0.5
18	AMP	BHK 52-90	660	665	5	49809	129		0.007	0.006	68	17	<0.001	<0.5
19	SPT	BHK 52-90	744	749	5	49816	1660		0.007	0.005	17	70	0.001	<0.5
20	SPT	BHK 52-90	776	781	5	49822	2400		0.007	0.004	6	61	<0.001	<0.5
21	SPT	BHK 52-90	801	806	5	49828	4880		0.04	0.063	20	97	0.016	<0.5
22	SPT	BHK 52-90	811	815	4	49830	6270		0.042	0.081	20	88	0.009	<0.5
23	GT	BHK 52-90	817	820	3	49832	640		0.005	0.003	23	7	<0.001	<0.5
24	GT	BHK 52-90	856.5	865	8.5	49842	143		0.005	0.002	14	2	<0.001	<0.5
25	GT	BHK 52-90	865	870	5	49843	1315		0.005	0.014	29	2	<0.001	<0.5
26	SPT	BHK 52-90	1110	1115.5	5.5	49904	1725		<0.005	0.001	20	55	<0.001	<0.5
27	GT	BHK 52-90	1128	1133	5	49907	49		<0.005	<0.001	14	3	<0.001	<0.5

Summary of Phase II Static Test Samples Selected
N Drillcore Intersections
Minago Project

Code	DDH	Sample #	From (m)	To (m)	Length (m)	Sample Type	Description	Cu (ppm)	Ni (ppm)	Ni (%)	SG
GT	N0702	924204	117.50	119.00	1.50	CORE	Granite	59	230		
SPT	N0702	924224	141.50	142.74	1.24	CORE	SPT	11	1920		
SPT/GT	N0702	924234	151.60	152.40	0.80	CORE	SPT	10	1840		
GT	N0702	924235	152.40	153.70	1.30	CORE	Granite	13	2180		
MSD	N0705	924548	99.5	100.6	1.1	CORE	Met Sed	250	580		
MD	N0705	924551	101.6	102.6	1	CORE	Alt UM	71	250		
GT	N0705	924558	107.35	108.35	1	CORE	Gran Gneiss	240	62		2.49
GT	N0706	924350	102.50	103.25	0.75	CORE	alt'd granite	36	2450		
GT	N0706	924424	178.30	179.70	1.40	CORE	Gran Gneiss	30	5		
GT	N0707	924591	109.30	110.80	1.50	CORE	Alt Gran	23	500		
SPT	N0707	924626	143.6	145.1	1.5	CORE	Alt UM +SPT	21	>5000	1.32	
MD	N0707	924669	191	192.5	1.5	CORE	Molson Dyke	41	81		
SPT	N0707	924686	209	210.5	1.5	CORE	SPT	5	4250		
SPT	N0707	924709	233	234.2	1.2	CORE	Alt Gran+millrite	<1	2460		
SPT	N0707	924724	257	258.5	1.5	CORE	Alt Ultramafic	9	1110		
MSD	N0710	924730	126.1	126.6	0.5	CORE	Iron Fm	300	230		
MSD	N0710	924738	135.4	136.2	0.8	CORE	Iron Fm+Meta Se	83	93		2.66
SPT	N0710	924747	144	145.5	1.5	CORE	Alt. Ultramafic+FR	12	2200		
SPT	N0710	924762	164	165.5	1.5	CORE		<1	3490		
SPT	N0710	924772	177	177.6	0.6	CORE	1-2% pn	1210	>5000	1.03	
SPT	N0710	924827	240.5	242	1.5	CORE	SPT	1	2700		
GT	N0710	924890	312.3	312.9	0.6	CORE	EGRAN	8	960		
MSD	N0712	925841	197	198.5	1.5	CORE	spt	64	3880		
SPT	N0712	925856	214.5	215.45	0.95	CORE	alt'd gran	34	1010		
SPT	N0712	925866	225.5	227	1.5	CORE	spt	340	>5000	0.81	
MMV	N0712	925884	249.5	251	1.5	CORE	amph	72	200		
GT	N0713	924964	203.2	204.7	1.5	CORE	granite, nil sulphid	7	170		
GT	N0713	924981	221	222.5	1.5	CORE	40% alt um, nil su	24	1670		
SPT	N0713	925017	255.51	257	1.49	CORE	2-3% fgr diss sulph	<1	>5000	0.67	
SPT	N0713	925075	317	318.53	1.53	CORE	peridotite, 1-2% fg	77	3350		
GT	N0713	925116	371.04	371.7	0.66	CORE	foliated mafic dyk	93	380		
GT	N0713	925132	436.3	437.27	0.97	CORE	granite, nil sulphid	5	27		2.64
MSD	N0701	924169	185	186.4	1.4	CORE	banded to 25 cm of near massive py; sulph			0.221	
MSD	N0701	924159	173.45	174.9	1.45	CORE	disseminated to thin layers of pyritic sulph			0.315	
SPT	N0719	925999	492.02	493.47	1.45	CORE	Dark green serp	3	2840		
GT	N0720	925273	249.3	251	1.7	CORE	granite, nil sulphid	12	260		
SPT	N0720	925276	254.84	256.33	1.49	CORE	altered um, partly	10	2300		
GT	N0724	929308	171.18	171.96	0.78	CORE	90% amphibolite w	43	110		2.87
AMP	N0724	929311	185.68	186.84	1.16	CORE	100% amphibolite	97	73		
AMP	N0724	929314	190	190.84	0.84	CORE	100% Amphibolite	100	78		
AMP	N0724	929318	196.15	197	0.85	CORE	100% Amphibolite	77	200		
GT	N0725	925315	138.64	139.56	0.92	CORE	altgran bleached	7	100		
MMV	N0726	926231	109.00	110.00	1.00	CORE	Amphibolite with f	39	150		
SPT	N0726	926235	125.94	126.72	0.78	CORE	Contaminated ultr	15	880		
SPT	N0726	926243	133.69	134.54	0.85	CORE	Amphibolite with t	170	1390		
GT	N0726	926297	215.81	218	2.19	CORE	EGRAN, with serp	32	520		
SPT	N0726	926312	284.39	285.4	1.01	CORE	Med green, trem a	160	2950		
R	N0730	926397	94.53	95.23	0.7	CORE	regolith chl-phlog	28	1000		
SPT	N0730	929407	104.25	105.25	1	CORE	Alt TJUM 25cm mic	11	1560		
SPT	N0730	929433	135.5	137	1.5	CORE	grey-grm spt sim t	31	2150		
MD	N0730	929437	141	143	2	CORE	mvolc nil sulph	200	180		
GT	N0730	929488	197.7	198.8	1.1	CORE	alt'd gran	38	300		
SPT	N0730	929490	200	201.5	1.5	CORE	fg purple-limegrn	17	1640		
GT	N0733	929497	164.00	165.00	1.00	CORE	sim to prev	8	280		

APPENDIX 2.8-A2

**Phase I Static Test and Metal Results
Phase II Grainsize, Static, and Metal Test Results**

Phase I Static Test and Metal Results

Table A2.8.1 Geochemical Sample Description for Phase I Static Testing

No.	Drill Hole	ARD Sample #	Composition ¹					Description	Rock Type by Lithology	Rock Type by Code	Mass (kg)
			OB	LS	FS	AR	ORE				
1	N0727	OB/AR	1.0				1.7	Overburden-Alteration	glacial lacustrine clay-granite,serpentinite	1-5,4	2.70
2	N0727	FS/AR			1.0	1.3		Frac Sand-Alteration	sandstone-granite,serpentinite	3-5,4	2.25
3	N0727	FS/LS			1.0	7.0		Frac Sand-Limestone Composite	sandstone-dolomite	3-2	2.00
4	N0727	LS/OB	1.0	10.0				Limestone-Overburden Composite	dolomite-glacial lacustrine clay	2-1	2.20
5	N0727	ORE/AR				1.0	11.6	Ore-Alteration Composite	granite,serpentinite-granite,serpentinite	5,4-5,4	2.52
6	N0727	LS/AR		5.6		1.0		Limestone-Alteration Composite	dolomite-granite,serpentinite	2-5,4	2.31
7	N0727	ORE/LS		1.0			2.1	Ore-Limestone Composite	granite,serpentinite-dolomite	5,4-2	2.17
8	N0727	OB	1.0					Overburden	glacial lacustrine clay	1	2.01
9	N0727	LS		1.0				Limestone	dolomite	2	2.72
10	N0727	FS			1.0			Frac Sand	sandstone	3	2.80
11	N0727	AR					1.0	Alteration	granite,serpentinite	5,4	2.12
12	N0727	ORE ²					1.0	Ore	granite,serpentinite	5,4	na
13	N0727	OB/LS/FS/AR/ORE	0.05	0.49	0.07	0.08	1.0	Overburden-Limestone-Frac Sand-Alteration-Ore Composite	glacial lacustrine clay-dolomite-sandstone-granite,serpentinite-granite,serpentinite	1-2-3-5,4-5,4	2.36
14	N0728	OB/AR	25.0				1.0	Overburden-Alteration Composite	glacial lacustrine clay-serpentinite	1-4	2.60
15	N0728	FS/AR				25.0	1.0	Frac Sand-Alteration Composite	sandstone-serpentinite	3-4	2.60
16	N0728	FS/LS		7.0	1.0			Frac Sand-Limestone Composite	sandstone-dolomite	3-2	2.40
17	N0728	LS/OB	1.0	7.0				Limestone-Overburden Composite	dolomite-glacial lacustrine clay	2-1	2.40
18	N0728	ORE/AR				1.0	66.0	Ore-Alteration Composite	mafic dike,serpentinite,granite,mafic metavolcanic,amphibolite-serpentinite	7,4,5,9,6-4	2.01
19	N0728	LS/AR		18.0			1.0	Limestone-Alteration Composite	dolomite-serpentinite	2-4	2.09
20	N0728	ORE/LS		1.0			3.7	Ore-Limestone Composite	mafic dike,serpentinite,granite,mafic metavolcanic,amphibolite-dolomite	7,4,5,9,6-2	2.35
21	N0728	OB	1.0					Overburden	glacial lacustrine clay	1	>2.00
22	N0728	LS		1.0				Limestone	dolomite	2	2.48
23	N0728	FS			1.0			Frac Sand	sandstone	3	2.36
24	N0728	AR					1.0	Alteration	serpentinite	4	2.23
25	N0728	ORE ²					1.0	Ore	mafic dike,serpentinite,granite,mafic	7,4,5,9,6	na
26	N0728	OB/LS/FS/AR/ORE	0.03	0.19	0.03	0.01	1.0	Overburden-Limestone-Frac Sand-Alteration-Ore Composite	glacial lacustrine clay-dolomite-sandstone-serpentinite-mafic dike,serpentinite,granite,mafic metavolcanic,amphibolite	1-2-3-4-7,4,5,9,6	2.28
27	N0729	OB/AR	27.5				1.0	Overburden-Alteration Composite	glacial lacustrine clay-regolith,granite	1-11,5	2.85
28	N0729	FS/AR			1.0	2.0		Frac Sand-Alteration Composite	sandstone-regolith,granite	3-11,5	2.10
29	N0729	FS/LS		7.0	1.0			Frac Sand-Limestone Composite	sandstone-dolomite	3-2	2.80
30	N0729	LS/OB		3.6			1.0	Limestone-Overburden Composite	dolomite-glacial lacustrine clay	2-1	2.60
31	N0729	ORE/AR				1.0	12.0	Ore-Alteration Composite	amphibolite,granite-regolith,granite	6,5-11,5	2.60
32	N0729	LS/AR		3.6		1.0		Limestone-Alteration Composite	dolomite-regolith,granite	2-11,5	2.30
33	N0729	ORE/LS		1.0			3.3	Ore-Limestone Composite	amphibolite,granite-dolomite	6,5-2	2.15
34	N0729	OB	1					Overburden	glacial lacustrine clay	1	2.10
35	N0729	LS		1.0				Limestone	dolomite	2	2.30
36	N0729	FS			1.0			Frac Sand	sandstone	3	2.25
37	N0729	AR					1.0	Alteration	regolith,granite	11,5	2.65
38	N0729	ORE ²					1.0	Ore	amphibolite,granite	6,5	na
39	N0729	OB/LS/FS/AR/ORE	0.05	0.30	0.04	0.08	1.0	Overburden-Limestone-Frac Sand-Alteration-Ore Composite	glacial lacustrine clay-dolomite-sandstone-regolith,granite- amphibolite,granite	1-2-3-11,5-6,5	2.98
40	N0736	OB/AR	0.03				1.0	Overburden-Alteration Composite	glacial lacustrine clay-??	1-?	2.06
41	N0736	FS/AR			0.05	1.0		Frac Sand-Alteration Composite	sandstone-??	3-?	2.10
42	N0736	FS/LS		1.0	0.15			Frac Sand-Limestone Composite	sandstone-dolomite	3-2	2.30
43	N0736	LS/OB	0.08	1.0				Limestone-Alteration Composite	dolomite-??	2-?	2.16
44	N0736	ORE/AR				1.0	0.26	Ore-Alteration Composite	??-??	??	2.52
45	N0736	LS/AR		0.35		1.0		Limestone-Alteration Composite	dolomite-??	2-?	2.70
46	N0736	ORE/LS		1.0			0.75	Ore-Limestone Composite	??-dolomite	??-2	2.33
47	N0736	OB	1.0					Overburden	glacial lacustrine clay	1	2.75
48	N0736	LS		1.0				Limestone	dolomite	2	2.43
49	N0736	FS			1.0			Frac Sand	sandstone	3	2.40
50	N0736	AR					1.0	Alteration	??	?	2.50
51	N0736	ORE					1.0	Ore	??	?	2.75
52	N0736	OB/LS/FS/AR/ORE	0.03	0.35	0.05	1.0	0.26	Overburden-Limestone-Frac Sand-Alteration-Ore Composite	glacial lacustrine clay-dolomite-sandstone-??-??	1-2-3-?-?	3.38

Notes:

- 1 Lithologies: OB=overburden, LS=dolomite, FS=sandstone, AR=altered Precambrian basement, ORE=Precambrian basement
- 2 no sample collected

CLIENT : David Machaina
PROJECT : Minago (Nuinsco Resources Ltd.)
CEMI Project # : 0714
Test : Modified Acid-Base Accounting
Date : April 17/23, 2007

Sample ID	Paste pH	TIC %	CaCO ₃ NP	S(T) %	S(SO ₄) %	S(S-2) %	AP	NP	Net NP	Fizz Test
#1-NO727-OB/AR	8.11	0.91	75.8	0.16	0.01	0.15	4.7	55.1	50.4	Moderate
#1-NO728-OB/AR	8.05	2.36	196.7	0.04	<0.01	0.04	1.3	196.0	194.8	Strong
#2-NO727-FS/AR	8.89	1.09	90.8	0.08	<0.01	0.08	2.5	99.4	96.9	Slight
#2-NO728-FS/AR	9.07	1.21	100.8	0.06	<0.01	0.06	1.9	95.8	93.9	Slight
#3-NO727-FS/LS	8.87	10.49	874.2	0.08	<0.01	0.08	2.5	824.1	821.6	Strong
#3-NO728-FS/LS	8.75	10.77	897.5	0.04	<0.01	0.04	1.3	837.2	836.0	Strong
#3-NO729-FS/LS	8.82	10.63	885.8	0.07	<0.01	0.07	2.2	854.3	852.1	Strong
#4-NO727-LB/OB	8.34	11.09	924.2	0.07	<0.01	0.07	2.2	903.3	901.1	Strong
#4-NO728-LB/OB	8.23	10.68	890.0	0.04	<0.01	0.04	1.3	864.3	863.1	Strong
#5-NO727-ORE/AR	9.70	0.29	24.2	0.3	0.02	0.28	8.8	59.0	50.3	None
#5-NO728-ORE/AR	9.67	0.52	43.3	0.08	<0.01	0.08	2.5	41.4	38.9	Slight
#5-NO729-ORE/AR	9.40	0.22	18.3	0.12	<0.01	0.12	3.8	40.7	37.0	Slight
#6-NO727-LS/AR	8.66	10.69	890.8	0.1	<0.01	0.10	3.1	919.0	915.9	Strong
#6-NO728-LS/AB	8.51	12.06	1005.0	0.02	<0.01	0.02	0.6	967.3	966.7	Strong
#6-NO729-LS/AR	8.51	9.83	819.2	0.09	<0.01	0.09	2.8	809.7	806.9	Strong
#7-NO727-ORE/LS	9.63	5.25	437.5	0.23	<0.01	0.23	7.2	412.9	405.7	Strong
#7-NO728-ORE/LS	9.60	3.13	260.8	0.08	<0.01	0.08	2.5	245.1	242.6	Moderate
#8-NO727-OB	7.88	2.46	205.0	0.04	<0.01	0.04	1.3	198.6	197.4	Strong
#8-NO728-OB	7.88	2.46	205.0	0.03	<0.01	0.03	0.9	193.6	192.7	Strong
#8-NO729-OB	7.98	2.65	220.8	0.04	<0.01	0.04	1.3	229.8	228.6	Strong
#9-NO727-LS	8.80	12.02	1001.7	0.1	<0.01	0.10	3.1	831.7	828.6	Strong
#9-NO728-LS	8.69	12.5	1041.7	0.04	<0.01	0.04	1.3	665.7	664.5	Strong
#9-NO729-LS	8.79	12.25	1020.8	0.03	<0.01	0.03	0.9	738.1	737.2	Strong
#10-NO727-FS	9.16	1.69	140.8	0.13	<0.01	0.13	4.1	141.4	137.3	Moderate
#10-NO728-FS	8.89	1.04	86.7	0.02	<0.01	0.02	0.6	83.1	82.5	Moderate
#10-NO729-FS	8.95	1.52	126.7	0.19	<0.01	0.19	5.9	122.2	116.3	Moderate
#11-NO727-AR	8.06	0.11	9.2	0.34	0.01	0.33	10.3	10.2	-0.1	None
#11-NO728-AR	7.99	0.34	28.3	0.69	0.04	0.65	20.3	30.8	10.5	None
#11-NO729-AR	8.55	1.04	86.7	0.14	<0.01	0.14	4.4	86.3	81.9	Slight
#13-NO727-OB/LS/FS/AR/ORE	9.65	3.29	274.2	0.24	0.01	0.23	7.2	231.7	224.5	Moderate
#13-NO728-OB/LS/FS/AR/ORE	9.66	2.18	181.7	0.07	<0.01	0.07	2.2	122.8	120.6	Moderate
Duplicates										
#1-NO727-OB/AR		0.9		0.15	<0.01					
#1-NO728-OB/AR	8.06							197.3		Strong
#3-NO729-FS/LS		10.61		0.06	-					
#6-NO728-LS/AB	8.58							968.6		Strong
#8-NO728-OB		2.46		0.04	<0.01					
#10-NO727-FS		1.7		0.13	<0.01					
#13-NO728-OB/LS/FS/AR/ORE	9.66							138.8		Moderate

Note:

AP = Acid potential in tonnes CaCO₃ equivalent per 1000 tonnes of material. AP is determined from calculated sulphide sulphur content: S(T) - S(SO₄).

NP = Neutralization potential in tonnes CaCO₃ equivalent per 1000 tonnes of material.

NET NP = NP - AP

Carbonate NP is calculated from TIC originating from carbonates and is expressed in kg CaCO₃/tonne.

CLIENT : David Machina
 PROJECT : Minigo (Nunimo Resources Ltd.)
 CBM Project # : 074
 Date : April 16, 2007

Sample ID	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Co	Cr	Cu	Fe	Hg	K	La	Mg	Mn	Mo	Na	Ni	P	Pb	S	Sb	Sc	Sr	Th	U	V	W	Zn	Zr	
#1-N0728-OB/AR	<-0.2	1.95	<-5	114	0.9	<-5	5.62	<-1	12	49	35	3.19	<-1	0.33	25	2.42	372	<-2	0.04	163	442	3	0.02	8	6	59	9	0.08	20	<-10	53	22	
#2-N0728-OB/AR	<-0.2	1.88	<-5	74	0.8	<-5	2.25	<-1	5	107	37	1.89	<-1	0.64	16	2.13	282	<-2	0.04	118	109	<-2	0.06	11	4	24	<-5	0.09	21	<-10	37	13	
#3-N0728-FS/AR	0.8	0.31	<-5	<-10	<-0.5	<-5	2.11	<-1	3	166	19	0.64	<-1	0.07	<-10	1.51	106	3	0.01	94	36	<-2	0.05	10	<-1	10	<-5	0.01	16	<-10	4	<-10	
#4-N0728-FS/LS	0.4	0.12	<-5	<-10	<-0.5	<-5	>15.00	<-1	<-1	55	8	0.41	<-1	0.07	<-10	10.84	200	<-2	0.02	11	148	3	0.13	6	<-1	60	<-5	<-0.01	23	<-10	3	<-10	
#5-N0728-FS/LS	0.5	0.1	<-5	<-10	<-0.5	<-5	>15.00	<-1	<-1	59	3	0.38	<-1	0.06	<-10	10.96	184	<-2	0.02	7	81	<-2	0.15	7	<-1	56	<-5	<-0.01	22	<-10	1	<-10	
#6-N0728-LB/OB	0.2	0.25	<-5	19	<-0.5	<-5	>15.00	<-1	<-1	8	3	0.54	<-1	0.08	<-10	11.13	189	<-2	0.03	5	137	<-2	0.06	<-5	1	55	<-5	0.01	17	<-10	7	<-10	
#7-N0728-LB/OB	0.4	0.29	<-5	21	<-0.5	<-5	>15.00	<-1	<-1	16	5	0.76	<-1	0.09	15	10.85	335	<-2	0.03	10	274	<-2	0.09	<-5	1	55	<-5	0.01	20	<-10	5	<-10	
#8-N0728-ORE/AR	<-0.2	1.16	<-5	80	0.9	<-5	1.24	<-1	35	295	20	2.66	<-1	0.38	21	14.76	348	<-2	0.17	4370	175	3	0.27	11	6	26	7	0.02	14	13	26	<-10	16
#9-N0728-ORE/AR	<-0.2	1.35	<-5	357	0.9	<-5	1.24	<-1	23	174	33	3.63	<-1	0.13	70	6.69	253	<-2	0.11	269	360	3	0.09	15	6	50	24	0.05	50	<-10	33	<-10	
#10-N0728-LS/AR	<-0.2	1.35	<-5	357	0.9	<-5	>15.00	<-1	<-1	23	174	3.63	<-1	0.13	70	6.69	253	<-2	0.11	269	360	3	0.09	15	6	50	24	0.05	50	<-10	33	<-10	
#11-N0728-LS/AR	<-0.2	1.17	<-5	10	<-0.5	<-5	>15.00	<-1	<-1	3	4	0.97	<-1	0.02	16	12.42	403	<-2	0.04	55	145	<-2	0.04	10	<-1	53	<-5	0.01	15	<-10	9	<-10	
#12-N0728-LS/AR	<-0.2	0.85	<-5	77	<-0.5	<-5	>15.00	<-1	8	217	6	1.44	<-1	0.36	14	11.39	323	<-2	0.05	107	159	<-2	0.12	13	3	69	<-5	0.03	26	<-10	11	5	
#13-N0728-ORE/LS	<-0.2	0.92	<-5	103	0.6	<-5	5.54	<-1	23	243	10	1.95	<-1	0.45	47	8.04	307	<-2	0.07	652	189	<-2	0.05	12	2	42	<-5	0.03	29	<-10	13	8	
#14-N0728-ORE/LS	<-0.2	1.99	<-5	139	0.9	<-5	6.81	<-1	15	58	17	3.04	<-1	0.43	32	2.34	482	<-2	0.04	41	582	4	0.02	9	6	66	1	0.11	24	<-10	53	<-10	
#15-N0728-OB	<-0.2	1.88	<-5	128	0.8	<-5	6.95	<-1	13	54	26	2.87	<-1	0.41	30	2.37	469	<-2	0.04	39	551	8	0.01	6	5	63	11	0.1	18	<-10	50	<-10	
#16-N0728-LS	0.2	0.1	<-5	<-10	<-0.5	<-5	>15.00	<-1	<-1	3	1	0.43	<-1	0.07	<-10	12.51	220	<-2	0.02	27	169	<-2	0.16	6	<-1	58	<-5	<-0.01	21	<-10	<-1	2	
#17-N0728-LS	0.5	0.04	<-5	<-10	<-0.5	<-5	>15.00	<-1	<-1	1	4	0.43	<-1	0.04	<-10	12.72	317	<-2	0.02	5	101	<-2	0.07	5	<-1	53	<-5	<-0.01	18	<-10	<-1	1	
#18-N0728-FS	0.7	0.05	<-5	<-10	<-0.5	<-5	3.06	<-1	1	188	22	0.55	<-1	0.02	<-10	1.72	103	4	0.01	43	24	5	0.12	9	<-1	9	<-5	<-0.01	24	<-10	<-1	3	
#19-N0728-FS	0.5	0.05	<-5	<-10	<-0.5	<-5	2.6	<-1	1	193	10	0.54	<-1	0.04	<-10	1.49	82	3	0.01	15	13	3	0.17	6	<-1	8	<-5	<-0.01	18	<-10	<-1	5	
#20-N0728-FS	<-0.2	0.1	<-5	<-10	<-0.5	<-5	2.6	<-1	1	193	10	0.54	<-1	0.04	<-10	1.49	82	3	0.01	15	13	3	0.17	6	<-1	8	<-5	<-0.01	18	<-10	<-1	5	
#21-N0728-AR	<-0.2	0.75	5	73	0.6	<-5	0.27	<-1	14	41	151	0.79	<-1	0.31	51	0.5	107	<-2	0.02	183	61	3	0.29	<-5	3	18	12	0.02	31	<-10	24	18	
#22-N0728-AR	<-0.2	2.46	7	46	2.3	<-5	0.81	<-1	123	237	480	3.42	<-1	0.3	201	5.01	199	<-2	0.07	4061	333	8	0.71	20	9	56	19	0.01	82	13	63	<-10	
#23-N0728-AR	<-0.2	2.59	<-5	121	1.4	<-5	2.6	<-1	65	981	68	4.79	<-1	0.37	44	4.85	440	<-2	0.12	647	218	3	0.13	30	11	94	<-5	0.06	19	11	79	<-10	
#24-N0728-OB/LS/FS/AR/ORE	0.6	1.47	<-5	198	0.8	<-5	5.55	<-1	57	59	108	3.05	<-1	0.49	28	12.7	315	<-2	0.17	2684	222	2	0.24	7	3	38	7	0.04	38	<-10	22		
#25-N0728-OB/LS/FS/AR/ORE	<-0.2	1.07	<-5	75	0.8	<-5	4.2	<-1	22	310	16	2.15	<-1	0.37	52	6.74	310	<-2	0.06	495	424	<-2	0.04	16	4	42	10	0.05	31	<-10	28		

CLIENT : David Machaina
PROJECT : Minago (Nuinsco Resources Ltd.)
CEMI Project # : 0714
Test : Modified Acid-Base Accounting
Date : April 17/23, 2007

Sample ID	Paste pH	TIC %	CaCO3 NP	S(T) %	S(SO4) %	S(S-2) %	AP	NP	Net NP	Fizz Test
#1-NOT29 OB/AR 2.75/0.1	7.85	2.52	210.0	0.06	<0.01	0.06	1.9	209.5	207.6	Strong
#2-NOT29 FS/AR 0.71/1.4	8.81	0.71	59.2	0.12	<0.01	0.12	3.8	48.8	45.1	Slight
#4-NOT29 LS/OB 2.2/0.4	8.06	11.16	930.0	0.05	<0.01	0.05	1.6	917.5	915.9	Strong
#7-NOT29 ORE/LS 1.65/0.5	9.68	2.25	187.5	0.08	<0.01	0.08	2.5	185.5	183.0	Moderate
#13-NOT29-OB/LS/FS/AR/ORE	9.28	2.14	178.3	0.13	<0.01	0.13	4.1	179.8	175.7	Moderate
Duplicates										
#1-NOT29 OB/AR 2.75/0.1	8.03	2.52		0.05	<0.01			210.8		Strong

Note:

AP = Acid potential in tonnes CaCO3 equivalent per 1000 tonnes of material. AP is determined from calculated sulphide sulphur content: S(T) - S(SO4).

NP = Neutralization potential in tonnes CaCO3 equivalent per 1000 tonnes of material.

NET NP = NP - AP

Carbonate NP is calculated from TIC originating from carbonates and is expressed in kg CaCO3/tonne.

CLIENT : David Machina
 PROJECT : Minigo (Nunisco Resources Ltd.)
 CBM Project # : 0714, by Aqua Regia Digestion with ICP Finish
 Date : April 16, 2007

Sample ID	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Co	Cr	Cu	Fe	Hg	K	La	Mg	Mn	Mo	Na	Ni	P	Pb	S	Sb	Sc	Sr	Th	Ti	U	V	W	Zn	Zr	
	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm		
#1-NO729	<0.2	0.88	<5	6.22	<0.5	<5	1.5	<1	17	144	34	1.55	<1	0.19	20	2.13	258	<2	0.03	208	450	6	0.04	<5	3	7	<10	28	<10	<10	<10	17		
#2-NO729	<0.2	1.81	<5	156	0.9	<5	1.5	<1	17	414	33	2.38	<1	0.55	59	3.05	250	<2	0.07	208	355	6	0.09	12	5	43	7	0.06	36	<10	29	15		
#4-NO729	<0.2	0.15	<5	13	<0.5	<5	>15.00	<1	<1	16	1	0.43	<1	0.07	<10	11.71	184	<2	0.02	7	144	3	0.11	<5	<1	55	<5	<0.01	1.4	<10	4	2	2	
#7-NO729	<0.2	1.48	<5	262	<0.5	<5	4.26	<1	14	300	17	2.25	<1	0.72	49	4.31	211	<2	0.09	123	507	37	0.08	19	3	31	13	0.12	35	<10	37	<10	44	8
#13-NO729-OBALS/FSA/OORE	<0.2	1.24	<5	248	<0.5	<5	4.15	<1	19	483	37	2.39	<1	0.84	54	4.11	220	<2	0.08	206	334	9	0.11	20	2	32	11	0.1	34	<10	43	<10	36	10

Vision, Nis, & Inc.
 H:\URS\S\944824\Victory Nickel\Geochem\Geochem_AR0_ML\Report\Appendices\Appendix B'
 AppendixB: nNunisco Static Testing Apr 13, 07 (Apr 24, 07) v2.xls - Merge

CLIENT : Keith Mountjoy
PROJECT : Minago (Nuinco Resources Ltd.)
CEMI Project # : 0714
Test : Modified Acid-Base Accounting
Date : May 29, 2007

Sample ID	Paste pH	TIC %	CaCO3 NP	S(T) %	S(SO4) %	S(S-2) %	AP	NP	Net NP	Fizz Test
N0736 #1 - OB/AR	9.22	0.13	10.8	0.16	<0.01	0.16	5.0	28.4	23.4	None
N0736 #2 - FS/AR	8.96	0.16	13.3	0.18	<0.01	0.18	5.6	20.5	14.9	None
N0736 #3 - FS/LS	8.87	11.7	975.0	0.09	<0.01	0.09	2.8	964.2	961.4	Moderate
N0736 #4 LS/OB	8.28	11.7	975.0	0.06	<0.01	0.06	1.9	954.8	952.9	Moderate
N0736 #5 - ORE/AR	9.22	0.1	8.3	0.33	0.01	0.32	10.0	20.3	10.3	None
N0736 #6 - LS/AR	9.27	2.95	245.8	0.12	<0.01	0.12	3.8	231.6	227.9	Slight
N0736 #7 - ORE/LS	8.83	7.68	640.0	1.24	<0.01	1.24	38.8	648.9	610.2	Moderate
N0736 #8 OB	7.73	2.4	200.0	0.12	0.02	0.10	3.1	194.8	191.7	Moderate
N0736 #9 LS	8.89	11.9	991.7	0.09	<0.01	0.09	2.8	970.5	967.7	Moderate
N0736 #10 FS	8.86	0.92	76.7	0.22	<0.01	0.22	6.9	68.3	61.4	Slight
N0736 #11 AR	9.64	0.08	6.7	0.19	<0.01	0.19	5.9	17.9	12.0	None
N0736 #12 ORE	9.13	0.2	16.7	4.12	0.03	4.09	127.8	37.9	-89.9	None
N0736 #13 - OB/LS/FS/AR/ORE	9.03	2.49	207.5	0.62	<0.01	0.62	19.4	200.4	181.0	Moderate
Duplicates										
N0736 #1 - OB/AR	9.35	0.14		0.14	<0.01			24.3		None
N0736 #10 FS		0.89		0.22	<0.01					
N0736 #13 - OB/LS/FS/AR/ORE	9.28							201.7		Moderate

Note:

AP = Acid potential in tonnes CaCO3 equivalent per 1000 tonnes of material. AP is determined from calculated sulphide sulphur content: S(T) - S(SO4).

NP = Neutralization potential in tonnes CaCO3 equivalent per 1000 tonnes of material.

NET NP = NP - AP

Carbonate NP is calculated from TIC originating from carbonates and is expressed in kg CaCO3/tonne.

Sulphate-S by 25% HCl leach followed by ICP finish.

Sulphide S = Total S - Sulphate S

CLIENT : Keith Mounjroy
 PROJECT : Mirage (Nuniseo Resources Ltd.)
 CEMLI Project # : 0714
 Title : Air by Aqua Regia Digestion with ICP Finish
 Date : June 1, 2007

Sample ID	Ag	Al	As	Ba	Be	Bi	Cd	Co	Cr	Cu	Fe	Hg	K	La	Mg	Mn	Mo	Na	Ni	P	Pb	S	Sb	Sc	Sr	Th	Ti	U	V	W	Zn	Zr
	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g	µg/g
N0736 #1 - OB/AR	<0.2	1.88	<0.2	61	<0.5	<0.5	0.84	13	156	19	2.71	<1	0.75	10.6	2.13	177	<2	0.32	22	597	<2	0.14	<5	6	24	20	22	28	<10	<10	40	14
N0736 #2 - FS/AR	<0.2	1.43	<5	120	0.6	<5	0.61	1	114	19	2.36	<1	0.64	69	1.37	184	3	0.08	22	540	<2	0.17	5	6	24	20	22	28	<10	<10	40	14
N0736 #3 - FS/LS	<0.2	0.17	<5	<10	<0.5	<5	>15.00	1	16	2	0.35	<1	0.1	<10	10.64	130	<2	0.02	5	64	<2	0.12	<5	<1	47	7	10	130	5	<10	4	2
N0736 #4 - LS/OB	<0.2	0.14	<5	<10	<0.5	<5	>15.00	1	11	1	0.33	<1	0.07	<10	10.47	152	<2	0.02	5	61	<2	0.08	<5	<1	31	8	<10	123	5	<10	3	2
N0736 #5 - ORE/AR	<0.2	1.43	<5	70	0.9	<5	0.4	26	140	23	2.34	<1	0.63	74	2.43	201	<2	0.1	461	465	<2	0.31	<5	4	24	17	20	20	30	<10	38	13
N0736 #6 - ORE/AR	<0.2	1.43	<5	70	0.9	<5	0.4	26	140	23	2.34	<1	0.63	74	2.43	201	<2	0.1	461	465	<2	0.31	<5	4	24	17	20	20	30	<10	38	13
N0736 #7 - ORE/LS	<0.2	0.5	<5	58	<0.5	<5	11.3	1	20	116	2.42	<1	0.28	13	9.16	187	3	0.04	699	110	3	1.28	7	1	14	9	107	20	<10	18	5	1
N0736 #8 - OB	<0.2	1.42	<5	100	0.6	<5	5.86	1	43	16	2.18	<1	0.28	27	2.01	342	<2	0.03	27	429	5	0.11	<5	4	34	15	53	39	<10	51	24	1
N0736 #9 - LS	<0.2	0.12	<5	<10	<0.5	<5	>15.00	2	12	3	0.32	<1	0.07	<10	10.72	137	<2	0.02	7	63	4	0.12	6	<1	33	6	<10	129	3	<10	4	1
N0736 #10 - FS	0.6	0.13	<5	<10	<0.5	<5	1.37	1	10	53	0.79	<1	0.06	30	0.85	72	<2	0.01	27	40	2	0.21	<5	1	<1	<5	<10	28	4	<10	19	4
N0736 #11 - AR	<0.2	0.97	<5	56	<0.5	<5	0.5	1	61	31	1.65	<1	0.43	58	1.14	160	<2	0.08	27	527	2	0.18	<5	4	10	13	14	38	<10	40	10	4
N0736 #12 - ORE	<0.2	1.08	<5	53	0.6	<5	0.4	3	38	21	6.09	<1	0.55	37	6.09	274	<2	0.07	199	170	7	3.88	9	3	11	10	18	38	12	40	11	1
N0736 #13 - ORE/LS/FS/AR/ORE	<0.2	1.08	<5	53	0.6	<5	4.22	1	89	44	2.23	<1	0.44	51	4.32	155	<2	0.86	378	374	2	0.82	<5	4	25	18	61	39	<10	25	12	

Table A2.8.2
Total Metal Concentrations
Phase I Static Test Results
Minago Project

Sample #	Rock Type	Comp Ratio	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Co	Cr	Cu	Fe	Hg	K	La	Mg	Mn
			ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	%
#8-N0727-OB	1	1	<0.2	1.99	<5	139	0.9	<5	6.81	<1	15	58	27	3.04	<1	0.43	32	2.34	482
#8-N0728-OB	1	1	<0.2	1.84	<5	135	0.8	<5	6.57	<1	13	54	25	2.79	1	0.39	30	2.29	412
#8-N0729-OB	1	1	<0.2	1.88	<5	128	0.8	<5	6.95	<1	13	54	26	2.87	<1	0.41	30	2.37	469
#8-N0736-OB	1	1	<0.2	1.42	<5	100	0.6	<5	5.86	1	12	43	16	2.18	1	0.28	27	2.01	342
Minimum			0.00	1.42	<5	100.00	0.60	<5	5.86	1.00	12.00	43.00	16.00	2.18	1.00	0.28	27.00	2.01	342.00
Maximum			0.00	1.99	<5	139.00	0.90	<5	6.95	1.00	15.00	58.00	27.00	3.04	1.00	0.43	32.00	2.37	482.00
#9-N0727-LS	2	1	0.2	0.1	<5	<10	<0.5	<5	>15.00	<1	<1	3	1	0.43	<1	0.07	<10	12.51	220
#9-N0728-LS	2	1	0.5	0.04	<5	<10	<0.5	<5	>15.00	<1	<1	1	4	0.43	<1	0.03	<10	12.72	317
#9-N0729-LS	2	1	0.5	0.07	<5	<10	<0.5	<5	>15.00	<1	<1	2	<1	0.26	<1	0.04	<10	12.78	162
#9-N0736-LS	2	1	<0.2	0.12	<5	<10	<0.5	<5	>15.00	<1	2	12	3	0.32	<1	0.07	<10	10.72	137
Minimum			0.20	0.04	<5	<10	<0.5	<5	>15.0	<1	2.00	1.00	1.00	0.26	<1	0.03	<10	10.72	137.00
Maximum			0.50	0.12	<5	<10	<0.5	<5	>15.0	<1	2.00	12.00	4.00	0.43	<1	0.07	<10	12.78	317.00
#10-N0727-FS	3	1	0.7	0.05	<5	<10	<0.5	<5	3.06	<1	1	188	22	0.55	<1	0.02	<10	1.72	103
#10-N0728-FS	3	1	0.8	0.23	<5	12	<0.5	<5	2.03	<1	2	126	18	0.55	<1	0.04	<10	1.09	103
#10-N0729-FS	3	1	<0.2	0.1	<5	<10	<0.5	<5	2.6	<1	1	193	10	0.54	<1	0.04	<10	1.49	82
#10-N0736-FS	3	1	0.6	0.13	<5	<10	<0.5	<5	1.37	<1	10	53	25	0.79	<1	0.06	30	0.85	72
Minimum			0.60	0.05	<5	12.00	<0.5	<5	1.37	<1	1.00	53.00	10.00	0.54	<1	0.02	30.00	0.85	72.00
Maximum			0.80	0.23	<5	12.00	<0.5	<5	3.06	<1	10.00	193.00	25.00	0.79	<1	0.06	30.00	1.72	103.00
#11-N0727-AR	5,4	1	<0.2	0.75	5	73	0.6	<5	0.27	<1	14	41	151	0.79	<1	0.31	51	0.5	107
#11-N0728-AR	4	1	<0.2	2.46	7	46	2.3	<5	0.81	<1	123	237	480	3.42	<1	0.3	201	5.01	199
#11-N0729-AR	11,5	1	<0.2	2.59	<5	121	1.4	<5	2.6	<1	65	981	68	4.79	<1	0.37	44	4.85	440
#11-N0736-AR	?	1	<0.2	0.97	<5	56	<0.5	<5	0.5	1	12	61	31	1.65	<1	0.43	58	1.14	160
Minimum			0.00	0.75	5.00	46.00	0.60	<5	0.27	1.00	12.00	41.00	31.00	0.79	<1	0.30	44.00	0.50	107.00
Maximum			0.00	2.59	7.00	121.00	2.30	<5	2.60	1.00	123.00	981.00	480.00	4.79	<1	0.43	201.00	5.01	440.00
#12-N0736-ORE	?	1	<0.2	1.18	<5	83	0.6	<5	0.4	3	38	211	130	6.37	<1	0.55	37	6.09	274
#1-N0727-OB/AR	1-4,5	1:1.7	<0.2	1.99	<5	162	1.3	<5	2.61	<1	15	78	35	3.19	<1	0.89	20	1.56	490
#1-N0728-OB/AR	1-4	25:1	<0.2	1.85	<5	114	0.9	<5	5.62	<1	12	49	21	2.97	<1	0.33	25	2.42	372
#1-N0729-OB/AR	1-5,11	27.5:1	<0.2	0.86	<5	64	<0.5	<5	6.22	<1	7	144	14	1.55	<1	0.19	20	2.13	258
#1-N0736-OB/AR	1-?	0.03:1	<0.2	1.86	<5	61	1	<5	0.64	1	14	126	17	2.71	<1	0.75	104	2.13	177
Minimum			0.00	0.86	<5	61.00	0.90	<5	0.64	1.00	7.00	49.00	14.00	1.55	<1	0.19	20.00	1.56	177.00
Maximum			0.00	1.99	<5	162.00	1.30	<5	6.22	1.00	15.00	144.00	35.00	3.19	<1	0.89	104.00	2.42	490.00
#2-N0727-FS/AR	3-4,5	1:1.25	<0.2	1.32	<5	74	0.8	<5	2.25	<1	5	107	37	1.89	<1	0.64	16	2.13	282
#2-N0728-FS/AR	3-4	25:1	0.8	0.31	<5	<10	<0.5	<5	2.11	<1	3	166	19	0.64	<1	0.04	<10	1.51	106
#2-N0729-FS/AR	3-5,11	1:2	<0.2	1.81	<5	156	0.9	<5	1.5	<1	17	414	33	2.38	<1	0.55	59	3.05	250
#2-N0736-FS/AR	3-?	0.05:1	<0.2	1.43	<5	120	0.6	<5	0.61	1	13	114	19	2.36	1	0.64	69	1.37	184
Minimum			0.80	0.31	<5	74.00	0.60	<5	0.61	1.00	3.00	107.00	19.00	0.64	1.00	0.04	16.00	1.37	106.00
Maximum			0.80	1.81	<5	156.00	0.90	<5	2.25	1.00	17.00	414.00	37.00	2.38	1.00	0.64	69.00	3.05	282.00

Notes: Lithologies: OB=overburden, LS=dolomite, FS=sandstone, AR=altered Precambrian basement, ORE=Precambrian basement
Rock Types: 1=glacial lacustrine clay, 2=dolomite, 3=sandstone, 4=serpentinite, 5=granite, 6=amphibolite, 7=mafic dike, 9=mafic metavolcanic, 11=regolith

Table A2.8.2 (Cont.'d)
Total Metal Concentrations
Phase I Static Test Results
Minago Project

Sample #	Rock Type	Comp Ratio	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
#8-N0727-OB	1	1	<2	0.04	41	582	4	0.02	9	6	66	11	0.11	24	<10	53	<10	66	35
#8-N0728-OB	1	1	<2	0.04	35	514	6	0.02	9	5	69	9	0.1	14	<10	48	<10	62	25
#8-N0729-OB	1	1	<2	0.04	38	551	8	0.01	6	5	63	11	0.1	18	<10	50	<10	65	34
#8-N0736-OB	1	1	<2	0.03	27	429	5	0.11	<5	4	34	15	0.08	<10	53	39	<10	51	24
Minimum			<2	0.03	27.00	429.00	4.00	0.01	6.00	4.00	34.00	9.00	0.08	14.00	53.00	39.00	<10	51.00	24.00
Maximum			<2	0.04	41.00	582.00	8.00	0.11	9.00	6.00	69.00	15.00	0.11	24.00	53.00	53.00	<10	66.00	35.00
#9-N0727-LS	2	1	<2	0.02	27	169	<2	0.16	6	<1	58	<5	<0.01	21	<10	2	<10	<1	2
#9-N0728-LS	2	1	<2	0.02	5	101	<2	0.07	5	<1	52	<5	<0.01	18	<10	1	<10	<1	1
#9-N0729-LS	2	1	<2	0.02	3	75	<2	0.03	<5	<1	53	<5	<0.01	24	<10	2	<10	<1	1
#9-N0736-LS	2	1	<2	0.02	7	63	4	0.12	6	<1	33	6	<0.01	<10	129	3	<10	4	1
Minimum			<2	0.02	3.00	63.00	4.00	0.03	5.00	<1	33.00	6.00	<0.01	18.00	129.00	1.00	<10	4.00	1.00
Maximum			<2	0.02	27.00	169.00	4.00	0.16	6.00	<1	58.00	6.00	<0.01	24.00	129.00	3.00	<10	4.00	2.00
#10-N0727-FS	3	1	4	0.01	43	24	5	0.12	9	<1	9	<5	<0.01	<10	<10	3	<10	<1	3
#10-N0728-FS	3	1	2	0.01	45	43	<2	<0.01	8	<1	11	<5	0.01	21	<10	5	<10	2	4
#10-N0729-FS	3	1	3	0.01	15	13	3	0.17	6	<1	8	<5	<0.01	18	<10	3	<10	<1	5
#10-N0736-FS	3	1	<2	0.01	27	40	2	0.21	<5	1	<1	<5	<0.01	<10	28	4	<10	19	4
Minimum			2.00	0.01	15.00	13.00	2.00	0.12	6.00	1.00	8.00	<5	0.01	18.00	28.00	3.00	<10	2.00	3.00
Maximum			4.00	0.01	45.00	43.00	5.00	0.21	9.00	1.00	11.00	<5	0.01	21.00	28.00	5.00	<10	19.00	5.00
#11-N0727-AR	5.4	1	<2	0.02	183	61	3	0.29	<5	3	18	12	0.02	31	<10	18	<10	24	18
#11-N0728-AR	4	1	<2	0.07	4061	333	8	0.71	20	9	56	19	0.01	82	13	63	<10	82	13
#11-N0729-AR	11.5	1	<2	0.12	647	218	3	0.13	30	11	94	<5	0.06	19	11	79	<10	56	13
#11-N0736-AR	?	1	<2	0.08	27	527	2	0.18	<5	4	10	13	0.04	<10	14	38	<10	40	10
Minimum			<2	0.02	27.00	61.00	2.00	0.13	20.00	3.00	10.00	12.00	0.01	19.00	11.00	18.00	<10	24.00	10.00
Maximum			<2	0.12	4061.00	527.00	8.00	0.71	30.00	11.00	94.00	19.00	0.06	82.00	14.00	79.00	<10	82.00	18.00
#12-N0736-ORE	?	1	4	0.07	1899	170	7	3.98	9	3	<1	10	0.04	<10	18	36	12	40	11
#1-N0727-OB/AR	1-4.5	1:1.7	<2	0.04	74	566	5	0.14	10	8	39	9	0.15	17	<10	62	<10	63	25
#1-N0728-OB/AR	1-4	25:1	<2	0.04	163	442	3	0.02	8	6	59	9	0.08	20	<10	49	<10	53	22
#1-N0729-OB/AR	1-5.11	27.5:1	2	0.03	28	460	2	0.04	<5	3	47	6	0.06	11	<10	28	<10	26	17
#1-N0736-OB/AR	1-?	0.03:1	<2	0.12	22	697	<2	0.14	<5	6	33	20	0.03	<10	28	72	<10	36	14
Minimum			2.00	0.03	22.00	442.00	2.00	0.02	8.00	3.00	33.00	6.00	0.03	11.00	28.00	28.00	<10	26.00	14.00
Maximum			2.00	0.12	163.00	697.00	5.00	0.14	10.00	8.00	59.00	20.00	0.15	20.00	28.00	72.00	<10	63.00	25.00
#2-N0727-FS/AR	3-4.5	1:1.25	<2	0.04	118	109	<2	0.06	11	4	24	<5	0.09	21	<10	38	<10	37	13
#2-N0728-FS/AR	3-4	25:1	3	0.01	94	36	<2	0.05	10	<1	10	<5	0.01	16	<10	4	<10	<1	4
#2-N0729-FS/AR	3-5.11	1:2	<2	0.07	208	355	6	0.09	12	5	43	7	0.06	36	<10	32	<10	29	15
#2-N0736-FS/AR	3-?	0.05:1	3	0.08	22	540	<2	0.17	5	6	24	20	0.03	<10	22	46	<10	40	14
Minimum			3.00	0.01	22.00	36.00	6.00	0.05	5.00	4.00	10.00	7.00	0.01	16.00	22.00	4.00	< 10	29.00	4.00
Maximum			3.00	0.08	208.00	540.00	6.00	0.17	12.00	6.00	43.00	20.00	0.09	36.00	22.00	46.00	< 10	40.00	15.00

Notes: Lithologies: OB=overburden, LS=dolomite, FS=sandstone, AR=altered Precambrian basement, ORE=Precambrian basement
Rock Types: 1=glacial lacustrine clay, 2=dolomite, 3=sandstone, 4=serpentinite, 5=granite, 6=amphibolite, 7=mafic dike, 9=mafic metavolcanic, 11=regolith

Table A2.8.2 (Cont.'d)
Total Metal Concentrations
Phase I Geochemical Assessment
Minago Project

Sample #	Rock Type	Comp Ratio	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm
#3-N0727-FS/LS	3-2	1:7	0.4	0.12	<5	<10	<0.5	<5	>15.00	<1	<1	55	8	0.41	<1	0.07	<10	10.84	200
#3-N0728-FS/LS	3-2	1:7	0.9	0.06	<5	<10	<0.5	<5	>15.00	<1	<1	50	4	0.33	<1	0.04	<10	10.96	167
#3-N0729-FS/LS	3-2	1:7	0.5	0.1	<5	<10	<0.5	<5	>15.00	<1	<1	59	3	0.38	<1	0.06	<10	10.96	184
#3-N0736-FS/LS	3-2	0.15:1	<0.2	0.17	<5	<10	<0.5	<5	>15.00	<1	1	16	2	0.35	<1	0.1	<10	10.64	130
Minimum			0.4	0.06	<5	<10	<0.5	<5	>15.00	<1	1	16	2	0.33	<1	0.04	<10	10.64	130
Maximum			0.9	0.17	<5	<10	<0.5	<5	>15.00	<1	1	59	8	0.41	<1	0.1	<10	10.96	200
#4-N0727-LS/OB	2-1	10:1	0.2	0.25	<5	19	<0.5	<5	>15.00	<1	<1	8	3	0.54	<1	0.08	<10	11.13	189
#4-N0728-LS/OB	2-1	7:1	0.4	0.29	<5	21	<0.5	<5	>15.00	<1	<1	16	5	0.76	<1	0.09	15	10.85	335
#4-N0729-LS/OB	2-1	5.5:1	<0.2	0.15	<5	13	<0.5	<5	>15.00	<1	<1	16	1	0.43	<1	0.07	<10	11.71	194
#4-N0736-LS/OB	2-1	1.0:0.08	<0.2	0.14	<5	<10	<0.5	<5	>15.00	<1	1	11	1	0.33	<1	0.07	<10	10.47	152
Minimum			0.2	0.14	<5	13	<0.5	<5	>15.00	<1	1	8	1	0.33	<1	0.07	15	10.47	152
Maximum			0.4	0.29	<5	21	<0.5	<5	>15.00	<1	1	16	5	0.76	<1	0.09	15	11.71	335
#5-N0727-ORE/AR	4.5-4.5	11.6:1	<0.2	1.36	<5	88	0.7	<5	0.55	<1	75	107	305	3.98	<1	0.38	21	14.76	348
#5-N0728-ORE/AR	4.5,7,9-4	66:1	<0.2	1.16	<5	80	0.9	<5	1.24	<1	35	295	20	2.66	<1	0.36	103	7.06	326
#5-N0729-ORE/AR	5.6-5.11	12:1	<0.2	1.84	<5	357	0.6	<5	0.8	<1	23	474	33	2.73	1	1.13	70	2.67	253
#5-N0736-ORE/AR	?-?	0.26:1	<0.2	1.43	<5	70	0.9	<5	0.4	1	26	140	23	2.34	<1	0.63	74	2.43	201
Minimum			0	1.16	<5	70	0.6	<5	0.4	1	23	107	20	2.34	1	0.36	21	2.43	201
Maximum			0	1.84	<5	357	0.9	<5	1.24	1	75	474	305	3.98	1	1.13	103	14.76	348
#6-N0727-LS/AR	2-4.5	5.6:1	0.5	0.25	<5	19	<0.5	<5	>15.00	<1	<1	23	14	0.58	<1	0.17	11	10.92	242
#6-N0728-LS/AB	2-4	18:1	<0.2	0.17	<5	10	<0.5	<5	>15.00	<1	<1	3	4	0.97	<1	0.02	16	12.42	403
#6-N0729-LS/AR	2-5,11	3.6:1	<0.2	0.85	<5	77	<0.5	<5	>15.00	<1	8	217	6	1.44	<1	0.36	14	11.39	323
#6-N0736-LS/AR	2-?	0.35:1	<0.2	1.26	<5	69	0.7	<5	4.76	1	10	52	22	1.81	1	0.65	77	3.83	169
Minimum			0.5	0.17	<5	10	0.7	<5	4.76	1	8	3	4	0.58	1	0.02	11	3.83	169
Maximum			0.5	1.26	<5	77	0.7	<5	4.76	1	10	217	22	1.81	1	0.65	77	12.42	403
#7-N0727-ORE/LS	4.5-2	2.1:1	<0.2	1.48	<5	236	0.7	<5	8.94	<1	116	41	76	2.52	<1	0.59	21	12.59	327
#7-N0728-ORE/LS	4.5,6,7,9-2	3.7:1	<0.2	0.92	<5	103	0.6	<5	5.54	<1	23	243	10	1.95	<1	0.45	47	8.04	307
#7-N0729-ORE/LS	5.6-2	3.3:1	<0.2	1.48	<5	262	<0.5	<5	4.26	<1	14	300	17	2.25	<1	0.72	49	4.31	211
#7-N0736-ORE/LS	7-2	0.75:1	<0.2	0.5	<5	58	<0.5	<5	11.3	1	20	118	120	2.42	<1	0.28	13	9.16	187
Minimum			0	0.5	<5	58	0.6	<5	4.26	1	14	41	10	1.95	<1	0.28	13	4.31	187
Maximum			0	1.48	<5	262	0.7	<5	11.3	1	116	300	120	2.52	<1	0.72	49	12.59	327
#13-N0727-OB/LS/FS/AR/ORE	1-2-3-4.5-4.5	0.05:0.49:0.07:0.08:1	0.6	1.47	<5	198	0.8	<5	5.55	<1	57	59	108	3.05	<1	0.49	26	12.7	315
#13-N0728-OB/LS/FS/AR/ORE	1-2-3-4-4.5,6,7,9	0.03:0.19:0.03:0.01:1	<0.2	1.07	<5	75	0.8	<5	4.2	<1	22	310	16	2.15	<1	0.37	52	6.74	310
#13-N0729-OB/LS/FS/AR/ORE	1-2-3-5,11-5.6	0.05:0.3:0.04:0.08:1	<0.2	1.24	<5	248	<0.5	<5	4.15	<1	19	483	37	2.39	<1	0.84	54	4.11	220
#13-N0736-OB/LS/FS/AR/ORE	1-2-3-?-?	0.03:0.35:0.05:1:0.26	<0.2	1.08	<5	38	0.6	<5	4.22	1	12	69	44	2.23	<1	0.44	51	4.52	155
Minimum			0.6	1.07	<5	38	0.6	<5	4.15	1	12	59	16	2.15	<1	0.37	26	4.11	155
Maximum			0.6	1.47	<5	248	0.8	<5	5.55	1	57	483	108	3.05	<1	0.84	54	12.7	315

Notes: Lithologies: OB=overburden, LS=dolomite, FS=sandstone, AR=altered Precambrian basement, ORE=Precambrian basement
Rock Types: 1=glacial lacustrine clay, 2=dolomite, 3=sandstone, 4=serpentinite, 5=granite, 6=amphibolite, 7=mafic dike, 9=mafic meta volcanic, 11=regolith

Table A2.8.2 (Cont.'d)
Total Metal Concentrations
Phase I Geochemical Assessment
Minago Project

Sample #	Rock Type	Comp Ratio	Mo	Na	Ni	P	Pb	S	Sb	Sc	Sr	Th	Ti	Tl	U	V	W	Zn	Zr
			ppm	%	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm
#3-NO727-FS/LS	3-2	1:7	<2	0.02	11	148	3	0.13	6	<1	60	<5	<0.01	23	<10	3	<10	<1	2
#3-NO728-FS/LS	3-2	1:7	<2	0.02	3	55	<2	0.05	7	<1	64	<5	<0.01	22	<10	2	<10	<1	1
#3-NO729-FS/LS	3-2	1:7	<2	0.02	7	81	<2	0.1	7	<1	56	<5	<0.01	25	<10	3	<10	1	2
#3-NO736-FS/LS	3-2	0.15:1	<2	0.02	5	64	<2	0.12	<5	<1	47	7	<0.01	<10	130	5	<10	4	2
Minimum			<2	0.02	3	55	3	0.05	6	<1	47	7	<0.01	22	130	2	<10	1	1
Maximum			<2	0.02	11	148	3	0.13	7	<1	64	7	<0.01	25	130	5	<10	4	2
#4-NO727-LS/OB	2-1	10:1	<2	0.03	5	137	<2	0.09	<5	1	55	<5	0.01	17	<10	7	<10	1	5
#4-NO728-LS/OB	2-1	7:1	<2	0.03	10	274	<2	0.06	<5	1	55	<5	0.01	20	<10	8	<10	5	5
#4-NO729-LS/OB	2-1	5.5:1	<2	0.02	7	144	3	0.11	<5	<1	55	<5	<0.01	14	<10	4	<10	2	2
#4-NO736-LS/OB	2-1	1.0:0.08	<2	0.02	5	61	<2	0.08	<5	<1	31	8	<0.01	<10	123	5	<10	3	2
Minimum			0	0.02	5	61	3	0.06	<5	1	31	8	0.01	14	123	4	<10	1	2
Maximum			0	0.03	10	274	3	0.11	<5	1	55	8	0.01	20	123	8	<10	5	5
#5-NO727-ORE/AR	4,5-4,5	11.6:1	<2	0.17	4370	175	3	0.27	11	6	26	7	0.02	14	13	26	<10	16	6
#5-NO728-ORE/AR	4,5,7,9-4	66:1	<2	0.07	848	520	3	0.05	12	6	50	24	0.05	50	<10	33	<10	34	9
#5-NO729-ORE/AR	5,6-5,11	12:1	<2	0.1	229	326	5	0.09	15	4	32	15	0.11	27	16	51	<10	48	15
#5-NO736-ORE/AR	?-?	0.26:1	<2	0.1	461	465	<2	0.31	<5	4	24	17	0.03	<10	20	30	<10	38	13
Minimum			<2	0.07	229	175	3	0.05	11	4	24	7	0.02	14	13	26	<10	16	6
Maximum			<2	0.17	4370	520	5	0.31	15	6	50	24	0.11	50	20	51	<10	48	15
#6-NO727-LS/AR	2-4,5	5.6:1	<2	0.03	36	150	<2	0.15	9	<1	54	<5	0.01	16	<10	5	<10	1	3
#6-NO728-LS/AB	2-4	18:1	<2	0.04	55	145	<2	0.04	10	1	53	<5	0.01	15	<10	9	<10	<1	2
#6-NO729-LS/AR	2-5,11	3.6:1	<2	0.05	107	159	<2	0.12	13	3	69	<5	0.03	26	<10	22	<10	11	5
#6-NO736-LS/AR	2-?	0.35:1	<2	0.08	18	410	<2	0.1	<5	4	23	21	0.03	<10	69	35	<10	34	13
Minimum			<2	0.03	18	145	<2	0.04	9	1	23	21	0.01	15	69	5	<10	1	2
Maximum			<2	0.08	107	410	<2	0.15	13	4	69	21	0.03	26	69	35	<10	34	13
#7-NO727-ORE/LS	4,5-2	2.1:1	<2	0.16	3111	209	<2	0.27	8	2	42	<5	0.03	29	<10	18	<10	13	8
#7-NO728-ORE/LS	4,5,6,7,9-2	3.7:1	<2	0.07	652	198	<2	0.05	12	3	34	18	0.04	33	<10	21	<10	21	8
#7-NO729-ORE/LS	5,6-2	3.3:1	<2	0.09	123	507	37	0.08	19	3	31	13	0.12	35	<10	37	<10	44	8
#7-NO736-ORE/LS	?-2	0.75:1	3	0.04	669	110	3	1.28	7	1	14	9	0.02	<10	107	20	<10	18	5
Minimum			3	0.04	123	110	3	0.05	7	1	14	9	0.02	29	107	18	<10	13	5
Maximum			3	0.16	3111	507	37	1.28	19	3	42	18	0.12	35	107	37	<10	44	8
#13-NO727-OB/LS/FS/AR/ORE	1-2-3-4,5-4,5	0.05:0.49:0.07:0.08:1	<2	0.17	2664	222	2	0.24	7	3	38	7	0.04	38	<10	22	<10	23	6
#13-NO728-OB/LS/FS/AR/ORE	1-2-3-4-4,5,6,7,9	0.03:0.19:0.03:0.01:1	<2	0.06	495	424	<2	0.04	16	4	42	10	0.05	31	<10	28	<10	28	7
#13-NO729-OB/LS/FS/AR/ORE	1-2-3-5,11-5,6	0.05:0.3:0.04:0.08:1	<2	0.08	206	334	9	0.11	20	2	32	11	0.1	34	<10	43	<10	36	10
#13-NO736-OB/LS/FS/AR/ORE	1-2-3-?-?	0.03:0.35:0.05:1:0.26	<2	0.06	378	374	2	0.62	<5	4	25	18	0.02	<10	61	36	<10	25	12
Minimum			<2	0.06	206	222	2	0.04	7	2	25	7	0.02	31	61	22	<10	23	6
Maximum			<2	0.17	2664	424	9	0.62	20	4	42	18	0.1	38	61	43	<10	36	12

Notes: Lithologies: OB=overburden, LS=dolomite, FS=sandstone, AR=altered Precambrian basement, ORE=Precambrian basement
Rock Types: 1=glacial lacustrine clay, 2=dolomite, 3=sandstone, 4=serpentinite, 5=granite, 6=amphibolite, 7=mafic dike, 9=mafic metavolcanic, 11=regolith

Phase II Grainsize, Static Test and Metal Results

BHK Drillcore Samples
Phase II Static Testing
Minago Project

Code	Hole ID	From (ft.)	To (ft.)	Length (ft.)	Sample #	Au ppm	Pt ppm	Pd ppm	Cu ppm	Ni ppm	Ni %	Co ppm	Ag ppm
SPT	BHK 41-R1-90	607	610.35	3.35	259758	<0.001	<0.005	0.005	8	1,420		74	<0.5
SPT	BHK 41-R1-90	1,051.5	1,056.2	4.7	365627	0.048	0.126	0.239	505	>10000	1.16	167	<0.5
GT	BHK 41-R1-90	1,080	1,083	3	365633	0.001	<0.005	0.003	180	178		8	<0.5
GT	BHK 42-90	767	774	7	49092	<0.001	<0.005	0.005	19	28		6	<0.5
GT	BHK 42-90	962	967	5	49125	0.002	<0.005	<0.001	5	12		4	<0.5
GT	BHK 42-R2-90	1,089	1,094	5	365507	<0.001	<0.005	0.001	17	34		18	<0.5
GT	BHK 42-R2-90	1,166	1,172	6	365525	<0.001	<0.005	<0.001	19	38		5	<0.5
GT	BHK 43-90	927	937	10	49427	<0.001	<0.005	<0.001	12	334		8	<0.5
GT	BHK 49-R9-90	463.75	467.5	3.75	258551	<0.001	<0.005	<0.001	15	40		6	<0.5
	BHK 49-R9-90	467.5	495.5	28	258554	<0.001	<0.005	<0.001	24	8		2	<0.5
GT	BHK 49-R9-90	495.5	505.5	10	258555	<0.001	<0.005	<0.001	17	7		7	<0.5
GT	BHK 49-R9-90	739	746.5										
SPT	BHK 49-R9-90	746.5	749.9	3.4	258612	0.011	0.072	0.142	26	4,540		96	<0.5
SPT	BHK 49-R9-90	818.5	821.5	3	258774	0.028	0.186	0.403	1050	>10000	1.61	190	0.9
GT	BHK 49-R9-90	833.2	835	1.8	258779	0.013	<0.005	0.01	57	649		6	<0.5
SPT	BHK 49-R9-90	927	932	5	258618	0.002	0.048	0.095	94	2,620		111	<0.5
GT	BHK 49-R9-90	1,015.5	1,017.0	1.5	258637	<0.001	<0.005	<0.001	20	104		7	<0.5
GT	BHK 50-90	399.75	405	5.25	365663	0.006	0.136	0.452	20	7,720		125	<0.5
AMP	BHK 52-90	660	665	5	49809	<0.001	0.007	0.006	68	129		17	<0.5
SPT	BHK 52-90	744	749	5	49816	0.001	0.007	0.005	17	1,660		70	<0.5
SPT	BHK 52-90	776	781	5	49822	<0.001	0.007	0.004	6	2,400		61	<0.5
SPT	BHK 52-90	801	806	5	49828	0.016	0.04	0.063	20	4,880		97	<0.5
SPT	BHK 52-90	811	815	4	49830	0.009	0.042	0.081	20	6,270		88	<0.5
GT	BHK 52-90	817	820	3	49832	<0.001	0.005	0.003	23	640		7	<0.5
GT	BHK 52-90	856.5	865	8.5	49842	<0.001	0.005	0.002	14	143		2	<0.5
GT	BHK 52-90	865	870	5	49843	<0.001	0.005	0.014	29	1,315		2	<0.5
SPT	BHK 52-90	1,110	1,116	5.5	49904	<0.001	<0.005	0.001	20	1,725		55	<0.5
GT	BHK 52-90	1,128	1,133	5	49907	<0.001	<0.005	<0.001	14	49		3	<0.5

TOTAL # SAMPLES 28

SAMPLES TESTED 21

Bolded and shaded samples were static tested

Table A2.8.4
N Drillcore Samples
Phase II Static Testing
Minago Project

Code	DDH	Sample #	From (m)	To (m)	Length (m)	Sample Type	Description	Cu (ppm)	Ni (ppm)	Ni (%)	SG
GT	N0702	924204	117.50	119.00	1.50	CORE	Granite	59	230		
SPT	N0702	924224	141.50	142.74	1.24	CORE	SPT	11	1,920		
SPT/GT	N0702	924234	151.60	152.40	0.80	CORE	SPT	10	1,840		
GT	N0702	924235	152.40	153.70	1.30	CORE	Granite	13	2,180		
MSD	N0705	924548	99.5	100.6	1.1	CORE	Met Sed	250	580		
MD	N0705	924551	101.6	102.6	1	CORE	Alt UM	71	250		
GT	N0705	924558	107.35	108.35	1	CORE	Gran Gneiss	240	62		2.49
GT	N0706	924350	102.50	103.25	0.75	CORE	alt'd granite	36	2,450		
GT	N0706	924424	178.30	179.70	1.40	CORE	Gran Gneiss	30	5		
GT	N0707	924591	109.30	110.80	1.50	CORE	Alt Gran	23	500		
SPT	N0707	924626	143.6	145.1	1.5	CORE	Alt UM +SPT	21	>5000	1.32	
MD	N0707	924669	191	192.5	1.5	CORE	Molson Dyke	41	81		
SPT	N0707	924686	209	210.5	1.5	CORE	SPT	5	4,250		
SPT	N0707	924709	233	234.2	1.2	CORE	Alt Gran+millrite	<1	2,460		
SPT	N0707	924724	257	258.5	1.5	CORE	Alt Ultramafic	9	1,110		
MSD	N0710	924730	126.1	126.6	0.5	CORE	Iron Fm	300	230		
MSD	N0710	924738	135.4	136.2	0.8	CORE	Iron Fm+Meta Sed	83	93		2.66
SPT	N0710	924747	144	145.5	1.5	CORE	Alt. Ultramafic+FRGR	12	2,200		
SPT	N0710	924762	164	165.5	1.5	CORE		<1	3,490		
SPT	N0710	924772	177	177.6	0.6	CORE	1-2% pn	1210	>5000	1.03	
SPT	N0710	924827	240.5	242	1.5	CORE	SPT	1	2,700		
GT	N0710	924890	312.3	312.9	0.6	CORE	FRGRAN	8	960		
MSD	N0712	925841	197	198.5	1.5	CORE	spt	64	3,880		
SPT	N0712	925856	214.5	215.45	0.95	CORE	alt'd gran	34	1,010		
SPT	N0712	925866	225.5	227	1.5	CORE	spt	340	>5000	0.81	
MMV	N0712	925884	249.5	251	1.5	CORE	amph	72	200		
GT	N0713	924964	203.2	204.7	1.5	CORE	granite, nil sulphide	7	170		
GT	N0713	924981	221	222.5	1.5	CORE	40% alt um, nil sulph	24	1,670		
SPT	N0713	925017	255.51	257	1.49	CORE	2-3% fgr diss sulphide, 2-3% fgr diss magnetite	<1	>5000	0.67	
SPT	N0713	925075	317	318.53	1.53	CORE	peridotite, 1-2% fgr diss sulphide	77	3,350		
GT	N0713	925116	371.04	371.7	0.66	CORE	foliated mafic dyke, 15% granite, 2-3% pyrite	93	380		
GT	N0713	925132	436.3	437.27	0.97	CORE	granite, nil sulphide	5	27		2.64
SPT	N0714	928023	172.5	174	1.5	CORE	spt 1-2%ss, tr-1% mt			0.6	
SPT	N0714	928367	489.45	491	1.55	CORE	grey-grm spt banded talc? alt'n tr-1% ss			0.52	
SPT	N0716	928708	168.43	169.28	0.85	CORE	ALTUM			0.31	
GT	N0716	928710	170	171.42	1.42	CORE	FRGRAN+ALTUM			0.08	
SPT	N0717	928414	144.15	145.45	1.3	CORE	spt. patches of trem in med green spt (sper			0.19	
MSD	N0717	929147	367.25	368.6	1.35	CORE	gran gneiss 1-2% py			0.003	
MSD	N0717	929149	370.4	370.7	0.3	CORE	fefmtn, 75% py			0.33	
MSD	N0701	924169	185	186.4	1.4	CORE	banded to 25 cm of near massive py:sulph 2-025%, massive py from 185.75 to 186.00m			0.221	
MSD	N0717	929151	371.42	372.4	0.98	CORE	as above 3-4% py			0.038	
MSD	N0701	924159	173.45	174.9	1.45	CORE	disseminated to thin layers of pyritic sulphide 2-3%			0.315	
GT	N-07-18	929194	240.55	242.20	1.65	CORE	frag alt'd gran			0.034	
SPT	N-07-18	929206	257	258.5	1.5	CORE	c-bxt grm spt, nil-tr sulph			0.32	
SPT	N0719	925999	492.02	493.47	1.45	CORE	Dark green serp, fg, 1-2% sulph	3	2,840		
GT	N0720	925273	249.3	251	1.7	CORE	granite, nil sulphide	12	260		
SPT	N0720	925276	254.84	256.33	1.49	CORE	altered um, partly zoned, hematized, some dark pseudomorphs, nil sulphide	10	2,300		
GT	N0724	929308	171.18	171.96	0.78	CORE	90% amphibolite with tr of sulp., 10 % felsic dykes.	43	110		2.87
AMP	N0724	929311	185.68	186.84	1.16	CORE	100% amphibolite with traces of sulph.	97	73		
AMP	N0724	929314	190	190.84	0.84	CORE	100% Amphibolite with 1% sulp.	100	78		
AMP	N0724	929318	196.15	197	0.85	CORE	100% Amphibolite with 1% sulp.	77	200		
GT	N0725	925315	138.64	139.56	0.92	CORE	altgran bleached	7	100		
MMV	N0726	926231	109.00	110.00	1.00	CORE	Amphibolite with fine sulfide disseminations, no adjacent sample.	39	150		
SPT	N0726	926235	125.94	126.72	0.78	CORE	Contaminated ultramafics, mottled green, tr sulp, slightly magnetic	15	880		
SPT	N0726	926243	133.69	134.54	0.85	CORE	Amphibolite with traces of fine sulfide disseminations.	170	1,390		
GT	N0726	926297	215.81	218	2.19	CORE	FRGRAN, with serp infills, nil sulp	32	520		
SPT	N0726	926312	284.39	285.4	1.01	CORE	Med green, trem altered SPT, tr sulp, mag diss and talc stringers.	160	2,950		
R	N0730	926397	94.53	95.23	0.7	CORE	regolith ch-phlog blebby sulph weathd contaminated UM?	28	1,000		
SPT	N0730	929407	104.25	105.25	1	CORE	ALTUM 25cm mica at LCT nil vis sulph	11	1,560		
SPT	N0730	929433	135.5	137	1.5	CORE	grey-grm spt sim to prev	31	2,150		
MD	N0730	929437	141	143	2	CORE	mvolc nil sulph	200	180		
GT	N0730	929488	197.7	198.8	1.1	CORE	alt'd gran	38	300		
SPT	N0730	929490	200	201.5	1.5	CORE	fg purple-limegrn mass spt, tr sulph	17	1,640		
GT	N0733	929497	164.00	165.00	1.00	CORE	sim to prev	8	280		

TOTAL # SAMPLES 64
SAMPLES TESTED 30
Bolded and shaded samples static tested

CLIENT : David Machaina
PROJECT : Minago (Nuinsco Resources Ltd.)
CEMI Project # : 0714
Test : Screen Assay
Date : June 28, 2007

HC-1 AR

Sieve Designation	Aperture (mm)	Weight Retained		
		(g)	(%)	Cumulative (%)
+1/4"	6.300	16.02	16.2%	16.2%
-1/4" + 10	1.700	39.79	40.2%	56.3%
-10 + 35	0.425	19.84	20.0%	76.4%
- 35 + 100	0.150	6.44	6.5%	82.9%
-100 + 270	0.053	11.09	11.2%	94.1%
-270	-0.053	5.87	5.9%	100.0%
TOTAL		99.05	100.0%	

HC-2 ORE/AR

Sieve Designation	Aperture (mm)	Weight Retained		
		(g)	(%)	Cumulative (%)
+1/4"	6.300	35.78	35.9%	35.9%
-1/4" + 10	1.700	45.83	45.9%	81.8%
-10 + 35	0.425	8.76	8.8%	90.6%
- 35 + 100	0.150	1.90	1.9%	92.5%
-100 + 270	0.053	4.79	4.8%	97.3%
-270	-0.053	2.70	2.7%	100.0%
TOTAL		99.76	100.0%	

HC-3 ORE/LS

Sieve Designation	Aperture (mm)	Weight Retained		
		(g)	(%)	Cumulative (%)
+1/4"	6.300	28.25	28.4%	28.4%
-1/4" + 10	1.700	45.02	45.3%	73.8%
-10 + 35	0.425	11.75	11.8%	85.6%
- 35 + 100	0.150	2.88	2.9%	88.5%
-100 + 270	0.053	6.05	6.1%	94.6%
-270	-0.053	5.38	5.4%	100.0%
TOTAL		99.33	100.0%	

HC-4 OB/LS/FS/AR/ORE

Sieve Designation	Aperture (mm)	Weight Retained		
		(g)	(%)	Cumulative (%)
+1/4"	6.300	19.63	19.6%	19.6%
-1/4" + 10	1.700	45.74	45.8%	65.4%
-10 + 35	0.425	15.44	15.5%	80.9%
- 35 + 100	0.150	4.00	4.0%	84.9%
-100 + 270	0.053	2.60	2.6%	87.5%
-270	-0.053	12.50	12.5%	100.0%
TOTAL		99.91	100.0%	

CLIENT : David Machaina
PROJECT : Minago (Nuinsco Resources Ltd.)
CEMI Project # : 0714
Test : Modified Acid-Base Accounting
Date : June 19, 2007

Sample ID	Paste pH	TIC %	CaCO3 NP	S(T) %	S(SO4) %	S(S-2) %	AP	NP	Net NP	Fizz Test
HC-1 AR	8.49	0.35	29.2	0.28	<0.01	0.28	8.8	31.9	23.2	Slight
HC-2 ORE/AR	9.69	0.24	20.0	0.16	<0.01	0.16	5.0	39.0	34.0	None
HC-3 ORE/LS	9.54	4.55	379.2	0.35	<0.01	0.35	10.9	443.5	432.6	Strong
HC-4 OB/LS/FS/AR/ORE	9.45	2.62	218.3	0.73	<0.01	0.73	22.8	238.1	215.3	Moderate
Duplicates										
HC-1 AR	8.60	0.36		0.27	0.01			29.7		Slight

Note:

AP = Acid potential in tonnes CaCO3 equivalent per 1000 tonnes of material. AP is determined from calculated sulphide sulphur content: S(T) - S(SO4).

NP = Neutralization potential in tonnes CaCO3 equivalent per 1000 tonnes of material.

NET NP = NP - AP

Carbonate NP is calculated from TIC originating from carbonates and is expressed in kg CaCO3/tonne.

CLIENT : David Machina
 PROJECT : Minage (Munisco Resources Ltd.)
 TAILING PILE # : 100001 by Aquas Regia Digestion with ICP Finish
 DATE : June 28, 2007

Sample ID	Ag	Al	As	Ba	Bi	B	Ca	Cd	Co	Cr	Cu	Fe	Hg	K	La	Mg	Mn	Mo	Na	Ni	P	Pb	S	Sb	Sc	Sr	Th	Ti	U	V	W	Zn	Zr
	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	
HC-1 AR	<0.2	1.64	<5	65	1.2	<5	0.98	<1	44	344	171	2.66	<1	0.31	80	2.79	224	<2	0.07	1003	315	<2	0.23	21	4	16	31	<10	51	<10	43	13	
HC-2 OREAR	<0.2	1.17	<5	105	0.7	<5	0.62	<1	30	248	48	2.75	<1	0.46	87	6.22	268	<2	0.09	1428	398	3	0.11	8	4	42	16	<10	29	<10	34	9	
HC-3 ORELS	0.7	1.13	<5	151	0.5	<5	9.18	<1	22	214	52	2.28	<1	0.46	30	8.99	254	<2	0.08	913	481	<2	0.42	6	2	48	<5	<10	26	<10	22	5	
HC-4 OBL/SF/S/AR/ORE	0.9	1.2	<5	133	0.6	<5	4.83	<1	28	261	89	3.15	<1	0.48	42	7.42	265	<2	0.09	1104	359	9	0.75	9	3	44	<5	<10	34	<10	32	8	

CLIENT : Nuinsco Resources Ltd.
PROJECT : Minago (Nuinsco Resources Ltd.)
CEMI Project # : 0714
Test : Modified and Sobek Acid-Base Accounting
Date : September 16, 2008

Sample ID	Paste pH	TIC %	CaCO3 P	S(T) N	S(SO4) %	S(S-2) %	Insoluble S %	AP %	Modified NP	Net NP	Fizz Test
HC #1	8.25	0.37	30.8	0.31	<0.01	0.29	0.02	9.1	31.8	22.7	Slight
HC #2	8.53	0.27	22.5	0.37	<0.01	0.31	0.06	9.7	45.9	36.2	Slight
HC #3	8.50	4.2	350.0	0.56	<0.01	0.56	<0.01	17.5	355.8	338.3	Moderate
HC #4	8.44	2.53	210.8	0.42	<0.01	0.4	0.02	12.5	211.3	198.8	Moderate
Duplicate											
HC #1	8.27	0.37		0.32	<0.01	0.27			31.1		Slight

Note:

AP = Acid potential in tonnes CaCO3 equivalent per 1000 tonnes of material. AP is determined from sulphide sulphur content.

NP = Neutralization potential in tonnes CaCO3 equivalent per 1000 tonnes of material.

NET NP = NP - AP

Carbonate NP is calculated from TIC originating from carbonate minerals and is expressed in kg CaCO3/tonne.

Sulphate sulphur determined by 25% HCL with gravimetric finish

Sulphide sulphur determined by Sobek 1:7 nitric acid with gravimetric finish

Insoluble S is acid insoluble S (Total S - (Sulphate S + Sulphide S)).

HC #1 = AR Composite (N0727+N0728+N0729+N036)

HC #2 = ORE/AR Composite (N0727+N0728+N0729+N036)

HC #3 = ORE/LS Composite (N0727+N0728+N0729+N036)

HC #4 = OB/LS/FS/AR/ORE Composite (N0727+N0728+N0729+N036)

CLIENT : Nuinisco Resources Ltd.
 PROJECT : Minago (Nuinisco Resources Ltd.)
 CEMI Project# : 0714
 Test : Metals by Aqua Regia Digestion with ICP-MS Finish
 Date : September 25, 2008

Sample ID	Ag ppm	Al %	As ppm	Ba ppm	Ba ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Co ppm	Cr ppm	Cs ppm	Cu ppm	Fe %	Ga ppm	Ga ppm	Hf ppm	Hg ppm	In ppm	K %	La ppm	Li ppm	Mg %	Mn ppm	Mo ppm	Na %
HC #1	0.2	2.3	<0.5	59	1	0.4	0.75	<0.1	178	53.2	336	0.8	136.5	2.77	8	0.2	0.4	<0.1	0.01	0.34	86	105.2	2.69	246	1.1	0.02
HC #2	0.2	1.34	<0.5	104	1	0.5	0.54	<0.1	128	52.9	201	2.1	96.6	3.49	5	0.2	0.3	<0.1	0.02	0.41	62	99.3	7.58	324	1.9	0.03
HC #3	0.2	0.99	<0.5	127	<1	0.4	5.73	<0.1	56	25.4	159	1.8	121.8	2.4	4	0.1	0.2	<0.1	0.01	0.35	27	53.4	7.4	247	2.7	0.03
HC #4	0.2	1.26	<0.5	122	1	0.3	3.74	<0.1	90	37.8	191	1.8	77.4	2.69	5	0.2	0.2	<0.1	0.01	0.43	46	76.1	7.45	258	1.9	0.03

HC #1 = AR Composite (N07Z+N0728+N0729+N036)
 HC #2 = OREAR Composite (N07Z+N0728+N0729+N036)
 HC #3 = ORELS Composite (N07Z+N0728+N0729+N036)
 HC #4 = OBLFS/ARORE Composite (N07Z+N0728+N0729+N036)

CLIENT
PROJECT
CEMI Project #
Test
Date

Sample ID	Nb ppm	Ni ppm	P %	Ph ppm	Pb ppm	Bi ppm	Be ppb	S %	Sb ppm	Sc ppm	Se ppm	Sn ppm	Sr ppm	Ta ppm	Ta ppm	Te ppm	Th ppm	Ti %	Ti ppm	U ppm	V ppm	W ppm	Y ppm	Zn ppm	Zr ppm
HC #1	0.1	>1000.0	0.022	4	16.3	-5	-5	0.22	<-0.1	5.3	<-0.5	0.4	39	<-0.1	<-0.1	<-0.1	9.2	0.028	0.2	4.8	34	0.1	7.3	47	11.5
HC #2	0.1	>1000.0	0.031	2.5	28.8	-5	-5	0.31	<-0.1	4.4	<-0.5	0.3	31	<-0.1	<-0.1	0.1	13.5	0.04	0.3	4.2	24	0.1	5.6	34	10.3
HC #3	0.2	>1000.0	0.023	3.5	23.6	-5	-5	0.52	<-0.1	2.2	<-0.5	0.3	25	<-0.1	<-0.1	0.1	10.5	0.046	0.3	4.2	20	0.1	3.8	25	6.6
HC #4	0.2	>1000.0	0.034	3	24.8	-5	-5	0.43	<-0.1	3.4	<-0.5	0.3	30	<-0.1	<-0.1	<-0.1	10.8	0.044	0.3	3.8	26	0.1	4.9	33	8.3

HC #1 = AR Composite (N
HC #2 = OREAR Campo
HC #3 = ORELS Campo
HC #4 = OBLFS/RCO

Table A2.8.5
Total Metal Concentrations
Phase II Static Testing
Minago Project

Sample #	Rock Type	Code	Rock Drill Hole #	From (ft)	To (ft)	Length (ft)	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Co	Cr	Cu	Fe	Hg	K	La	Mg	Mn	Sample #
							ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	%	ppm	%	ppm	%	ppm	
49809	Amphibolite	AMP	BHK 52-90	660	665	5.00	0.1	3.16	2.5	76	2.1	2.5	0.36	1	16	213	75	2.69	0.5	0.78	61	4.39		49809
929318	Amphibolite	AMP	N0724	196.15	197	0.85	0.8	1.18	2.5	166	0.25	2.5	0.66	1	31	308	75	2.22	0.5	0.72	5	1.7	215	929318
	Average						0.5	2.2	2.5	121.0	1.2	2.5	0.5	1.0	23.5	260.5	75.0	2.5	0.5	0.8	33.0	3.0	215.0	
925273	Granite	GT	N0720	249.3	251	1.70	0.1	0.75	2.5	204	0.5	2.5	0.18	0.5	6	173	6	0.9	0.5	0.64	79	1.12	110	925273
929488	Granite	GT	N0730	197.7	198.8	1.10	0.1	4.09	2.5	22	1.2	2.5	0.18	1	7	23	34	2.01	0.5	0.19	23	13.7	176	929488
365633	Granite	GT	BHK 41-R1-90	1080	1083	3.00	0.1	0.98	5	126	0.7	2.5	0.76	0.5	6	129	39	1.37	0.5	0.2	154	2.75	111	365633
49092	Granite	GT	BHK 42-90	767	774	7.00	0.1	0.89	2.5	65	0.7	2.5	0.19	0.5	4	132	7	0.86	0.5	0.35	40	0.94	86	49092
49125	Granite	GT	BHK 42-90	962	967	5.00	0.1	0.5	2.5	108	0.6	2.5	0.29	0.5	2	143	0.5	0.79	0.5	0.28	60	0.87	102	49125
365507	Granite	GT	BHK 42-R1-90	1089	1094	5.00	0.1	1.33	2.5	223	0.5	2.5	0.76	1	14	124	3	2.27	1	0.91	84	1.81	250	365507
365525	Granite	GT	BHK 42-R2-90	1156	1172	16.00	0.1	0.56	2.5	132	0.5	2.5	0.35	0.5	3	127	13	1.18	0.5	0.33	94	0.74	125	365525
49427	Granite	GT	BHK 43-90	927	937	10.00	0.1	1.3	2.5	74	0.9	2.5	0.1	1	11	211	2	1.79	0.5	0.52	29	2.48	91	49427
258551	Granite	GT	BHK 49-R9-90	463.75	467.5	3.75	0.1	1.27	10	89	1.2	2.5	0.42	0.5	5	89	4	1.59	0.5	0.56	292	1.46	124	258551
258637	Granite	GT	BHK 49-R9-90	1015.5	1017	1.50	0.1	3.15	2.5	286	1.3	2.5	0.26	0.5	3	40	18	1.19	0.5	0.27	48	9.99	858	258637
258779	Granite	GT	BHK 49-R9-90	833.2	835	1.80	0.6	2.13	2.5	66	0.9	2.5	0.15	1	24	79	112	2.4	0.5	0.25	18	7.56	263	258779
49832	Granite	GT	BHK 52-90	817	820	3.00	0.4	0.79	2.5	60	0.7	2.5	0.03	0.5	3	152	14	0.8	0.5	0.21	10	1.18	81	49832
49842	Granite	GT	BHK 52-90	856.5	865	8.50	0.1	0.51	2.5	376	0.25	2.5	0.05	0.5	2	143	4	0.86	0.5	0.23	37	0.56	69	49842
49843	Granite	GT	BHK 52-90	865	870	5.00	0.1	2.18	2.5	44	0.8	2.5	0.08	0.5	4	82	8	1.18	0.5	0.23	54	4.77	77	49843
49907	Granite	GT	BHK 52-90	1126	1133	7.00	0.1	0.78	5	109	0.5	2.5	0.12	0.5	4	130	3	1.27	0.5	0.36	93	0.98	113	49907
924235	Granite	GT	N0702	162.4	163.7	1.30	0.8	4.26	2.5	36	2.2	2.5	0.08	1	30	53	5	2.6	0.5	0.15	16	8.45	297	924235
924558	Granite	GT	N0705	107.35	108.35	1.00	0.3	1.15	2.5	77	0.7	2.5	0.21	0.5	12	115	323	1.39	0.5	0.54	41	0.73	185	924558
924350	Granite	GT	N0706	102.5	103.25	0.75	0.1	4.53	2.5	138	2.2	2.5	0.58	1	10	66	36	4.06	0.5	0.39	63	8.32	173	924350
924424	Granite	GT	N0706	178.3	179.7	1.40	0.05	0.82	2.5	117	0.25	2.5	0.15	1	5	104	26	2.16	0.5	0.41	36	0.48	247	924424
924591	Granite	GT	N0707	109.3	110.6	1.30	0.1	1.39	6	79	0.7	2.5	0.88	0.5	4	68	15	1.11	0.5	0.74	143	1.44	119	924591
924890	Granite	GT	N0710	312.3	312.9	0.60	0.1	4.77	2.5	224	2.5	2.5	0.1	1	15	64	0.5	2.19	0.5	0.31	58	12.49	338	924890
924964	Granite	GT	N0713	203.2	204.7	1.50	0.2	1.48	2.5	196	0.7	2.5	0.13	0.5	7	101	6	1.12	0.5	0.32	46	2.42	93	924964
925132	Granite	GT	N0713	436.3	437.27	0.97	0.1	0.66	2.5	118	0.5	2.5	0.09	0.5	3	105	1	0.86	0.5	0.34	119	0.86	81	925132
929308	Granite	GT	N0724	171.18	171.96	0.78	0.6	2.26	2.5	11	0.7	2.5	1.56	2	23	291	32	4.46	0.5	0.11	14	2.68	558	929308
925315	Granite	GT	N0725	138.64	139.56	0.92	0.1	1.99	6	79	1	2.5	0.12	0.5	7	80	3	1.23	0.5	0.73	119	2.49	126	925315
926297	Granite	GT	N0726	215.81	218	2.19	1.5	2.32	2.5	85	2	2.5	0.13	1	5	149	19	1.79	0.5	0.22	27	4.65	75	926297
929497	Granite	GT	N0733	164	165	1.00	0.1	2.68	2.5	40	2	2.5	0.1	0.5	4	66	4	1.5	0.5	0.2	38	7.37	146	929497
258554	Granite	GT	258554	485.00	495.50	10.50	0.1	0.99	5	111	0.7	2.5	0.26	0.5	6	144	2	1.34	0.5	0.57	136	0.95	167	258554
	Average						0.23	1.80	3.29	117.68	0.98	2.50	0.30	0.71	8.18	113.68	26.43	1.65	0.52	0.38	70.39	3.72	187.18	
924551	Mafic Dike	MD	N0705	101.6	102.6	1.00	0.1	1.27	10	89	1.2	2.5	0.42	0.5	5	89	4	1.59	0.5	0.56	292	1.46	124	924551
929437	Mafic Dike	MD	N0730	141	143	2.00	0.1	3.54	2.5	38	1	2.5	0.46	2	35	96	201	5.51	0.5	0.1	18	10.22	350	929437
	Average						0.1	2.4	6.3	63.5	1.1	2.5	0.4	1.3	20.0	92.5	102.5	3.6	0.5	0.3	155.0	5.8	237.0	
925884	Mafic Metavolcanic	MMV	N0712	249.5	251	1.50	0.8	1.12	2.5	181	0.25	2.5	0.42	1	17	216	54	2.2	0.5	0.83	38	1.45	221	925884
924159	Metasediment	MSD	N0701	173.45	174.9	1.45	0.3	2.02	2.5	198	1.9	2.5	0.72	2	27	148	64	4.61	0.5	1.36	39	2.09	414	924159
924548	Metasediment	MSD	N0705	99.5	100.8	1.30	0.1	1.08	2.5	53	0.9	2.5	0.12	0.5	27	122	254	1.19	1	0.7	61	0.69	133	924548
924738	Metasediment	MSD	N0710	135.4	136.2	0.80	0.9	3.13	2.5	62	1.4	2.5	0.1	4	18	140	58	9.15	0.5	1.14	45	2.3	520	924738
925841	Metasediment	MSD	N0712	197	198.5	1.50	1	0.9	2.5	127	0.25	2.5	0.68	2	106	380	47	4.38	0.5	0.58	5	>15.00	364	925841
	Average						0.575	1.7825	<3	110	1.1125	<3	0.405	2.125	44.5	197.5	105.75	4.8325	<1	0.945	<38	>5.02	357.75	
926397	Regolith	R	N0730	94.53	95.23	0.70	1.3	0.56	5	30	0.5	2.5	12.33	1	97	170	24	2.73	0.5	0.01	22	8.57	583	926397
365627	Serpentinite	SPT	BHK 41-R1-90	1051.5	1056.2	4.70	0.1	0.48	2.5	194	0.25	2.5	0.16	2	170	302	479	5.65	0.5	0.44	53	>15.00	451	365627
258612	Serpentinite	SPT	BHK 49-R9-90	746.5	749.9	3.40	0.1	0.53	2.5	116	0.8	2.5	1.78	1	112	284	11	3.75	0.5	0.28	120	>15.00	468	258612
924724	Serpentinite	SPT	N0707	257	258.5	1.50	0.1	0.74	2.5	57	1.1	2.5	5.58	0.5	97	202	7	1.8	0.5	0.43	29	6.1	412	924724
258774	Serpentinite	SPT	BHK 49-R9-90	818.5	821.5	3.00	0.6	0.66	2.5	170	0.6	2.5	0.81	1	158	250	835	3.17	0.5	0.44	58	>15.00	383	258774
49816	Serpentinite	SPT	BHK 52-90	744	749	5.00	0.1	0.97	8	417	0.6	2.5	2.27	2	66	565	0.5	5.48	0.5	0.41	210	>15.00	682	49816
49828	Serpentinite	SPT	BHK 52-90	801	806	5.00	0.1	0.59	5	202	0.25	2.5	1.7	2										

Table A2.8.5 (Cont.'d)
Total Metal Concentrations
Phase II Static Testing
Minago Project

Sample #	Rock Type	Rock Code	Drill Hole #	From (ft)	To (ft)	Length (ft)	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm
365627	Serpentinite	SPT	BHK 41-R1-90	1051.5	1056.2	4.70	<0.2	0.48	<5	194	<0.5	<5	0.16	2	170	302	479	5.65	<1	0.44	53	>15.00	451
258612	Serpentinite	SPT	BHK 49-R9-90	746.5	749.9	3.40	<0.2	0.53	<5	116	0.8	<5	1.78	1	112	284	11	3.75	<1	0.28	120	>15.00	468
924724	Serpentinite	SPT	N0707	257	258.5	1.50	<0.2	0.74	<5	57	1.1	<5	5.58	<1	97	202	7	1.8	<1	0.43	29	6.1	412
258774	Serpentinite	SPT	BHK 49-R9-90	818.5	821.5	3.00	0.6	0.66	<5	170	0.6	<5	0.81	1	158	250	835	3.17	<1	0.44	58	>15.00	383
49816	Serpentinite	SPT	BHK 52-90	744	749	5.00	<0.2	0.97	8	417	0.6	<5	2.27	2	66	565	<1	5.48	<1	0.41	210	>15.00	682
49828	Serpentinite	SPT	BHK 52-90	801	806	5.00	<0.2	0.59	5	202	<0.5	<5	1.7	2	79	557	3	5	<1	0.15	75	>15.00	631
49830	Serpentinite	SPT	BHK 52-90	811	815	4.00	0.2	0.44	<5	30	<0.5	<5	1.63	2	93	495	3	5.33	<1	0.05	54	>15.00	604
49904	Serpentinite	SPT	BHK 52-90	1110	1115.5	5.50	<0.2	1.45	<5	242	1.6	<5	0.22	1	38	467	14	2.27	<1	0.84	65	5.74	157
924686	Serpentinite	SPT	N0707	233	243.2	10.20	<0.2	0.21	<5	72	<0.5	<5	1.17	2	56	230	<1	5.21	<1	0.2	90	>15.00	605
925856	Serpentinite	SPT	N0712	214.5	215.45	0.95	0.7	3.65	<5	630	1.6	<5	0.08	1	18	96	23	2.36	<1	1.23	60	9.08	327
925017	Serpentinite	SPT	N0713	371.04	371.7	0.66	0.9	0.56	6	91	<0.5	<5	0.3	2	79	512	<1	4.44	<1	0.3	24	>15.00	364
925276	Serpentinite	SPT	N0720	254.84	256.33	1.49	0.6	0.56	<5	66	1.2	<5	1.54	1	146	191	1	3.23	<1	0.27	23	11.94	283
926243	Serpentinite	SPT	N0726	133.69	134.54	0.85	1.3	0.99	7	17	<0.5	<5	1.42	1	79	887	157	3.83	<1	0.15	18	9.66	326
929407	Serpentinite	SPT	N0730	104.25	105.25	1.00	<0.2	0.76	<5	36	0.7	<5	0.05	1	69	222	9	3.22	<1	0.15	19	>15.00	455
	Minimum						<0.2	0.21	<5	17	<0.5	<5	0.05	<1	18	96	<1	1.8	<1	0.05	18	5.74	157
	Average						0.4	0.9	3.6	167.1	0.7	2.5	1.3	1.4	90.0	375.7	110.3	3.9	0.5	0.4	64.1	12.7	439.1
	Maximum						1.3	3.65	8	630	1.6	<5	5.58	2	170	887	835	5.65	<1	1.23	210	>15	682
924234	Serp/Gran	SPT/GT	N0702	161.6	162.4	0.80	0.4	0.82	5	50	0.5	<5	0.02	1	42	317	<1	2.99	<1	0.15	15	>15.00	284

Table A2.8.5 (Cont.'d)
Total Metal Concentrations
Phase II Static Testing
Minago Project

Rock Type	Rock Code	Drill Hole #	From (ft)	To (ft)	Length (ft)	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Se ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
Amphibolite	AMP	BHK 52-90	660	665	5.00	<2	0.3	128	717	<2	<0.1	0.09	8	12	<1	27	0.05	<10	18	93	<10	34	12
Amphibolite	AMP	N0724	196.15	197	0.85	4	0.11	199	430	<2	<0.1	0.12	20	3	3	<5	0.21	<10	24	57	<10	27	3
Minimum						2	0.11	128	430	<2	<0.1	0.09	8	3	<1	<5	0.05	<10	18	57	<10	27	3
Average						2.5	0.205	163.5	573.5	1	0.05	0.105	14	7.5	1.75	14.75	0.13	0.5	21	75	5	30.5	7.5
Maximum						4	0.3	199	717	<2	<0.1	0.12	20	12	3	27	0.21	<10	24	93	<10	34	12
Granite	GT	N0720	249.3	251	1.70	2	0.05	267	111	8	0.4	0.02	5	1	<1	20	0.04	<10	35	7	<10	28	37
Granite	GT	N0730	197.7	198.8	1.10	<2	0.69	396	108	<2	<0.1	0.03	<5	1	<1	6	0.02	<10	25	7	<10	19	7
Granite	GT	BHK 41-R1-90	1080	1083	3.00	<2	0.11	258	615	6	<0.1	0.03	<5	1	38	34	0.06	<10	15	14	<10	26	18
Granite	GT	BHK 42-90	767	774	7.00	<2	0.04	51	274	<2	<0.1	0.02	<5	1	<1	11	0.02	<10	13	7	<10	23	12
Granite	GT	BHK 42-90	962	967	5.00	2	0.07	9	245	6	<0.1	0.01	<5	1	15	22	0.02	<10	18	7	<10	31	19
Granite	GT	BHK 42-R1-90	1089	1094	5.00	<2	0.09	38	1846	<2	<0.1	0.04	7	5	<1	18	0.1	13	11	53	<10	54	12
Granite	GT	BHK 42-R2-90	1156	1172	16.00	<2	0.05	25	534	9	<0.1	0.05	<5	1	<1	33	0.04	<10	20	12	<10	51	15
Granite	GT	BHK 43-90	927	937	10.00	<2	0.09	261	348	5	<0.1	0.03	<5	2	<1	20	0.03	<10	19	16	<10	42	17
Granite	GT	BHK 49-R9-90	463.75	467.5	3.75	<2	0.09	34	1495	2	<0.1	0.05	<5	2	27	47	0.01	26	24	24	<10	26	33
Granite	GT	BHK 49-R9-90	1015.5	1017	1.50	<2	0.09	32	212	<2	<0.1	0.03	<5	1	<1	19	0.03	<10	<10	10	<10	21	4
Granite	GT	BHK 49-R9-90	833.2	835	1.80	<2	0.22	2036	223	<2	<0.1	0.14	<5	1	<1	14	0.03	<10	12	11	<10	27	6
Granite	GT	BHK 52-90	817	820	3.00	2	0.08	409	34	5	<0.1	0.02	<5	1	<1	12	0.01	<10	42	3	<10	24	10
Granite	GT	BHK 52-90	856.5	865	8.50	2	0.07	61	133	3	<0.1	0.01	<5	1	<1	15	0.04	<10	17	8	<10	22	12
Granite	GT	BHK 52-90	865	870	5.00	<2	0.31	1150	184	<2	<0.1	0.01	<5	1	<1	13	0.01	<10	10	10	<10	23	5
Granite	GT	BHK 52-90	1126	1133	7.00	<2	0.31	1150	184	<2	<0.1	0.01	<5	1	<1	13	0.01	<10	10	10	<10	23	5
Granite	GT	N0702	162.4	163.7	1.30	<2	0.4	1931	86	<2	0.4	0.01	<5	1	<1	14	0.01	<10	39	12	<10	18	5
Granite	GT	N0705	107.35	108.35	1.00	<2	0.04	52	537	<2	<0.1	0.15	5	2	<1	15	0.04	12	36	18	<10	49	25
Granite	GT	N0706	102.5	103.25	0.75	<2	0.17	1884	754	<2	<0.1	0.11	<5	2	12	27	0.05	<10	39	22	<10	40	43
Granite	GT	N0706	178.3	179.7	1.40	2	0.06	15	557	4	<0.1	0.36	8	2	<1	10	0.06	<10	38	19	<10	42	15
Granite	GT	N0707	109.3	110.6	1.30	<2	0.11	369	779	<2	<0.1	0.06	<5	1	<1	24	0.02	<10	20	15	<10	44	35
Granite	GT	N0710	312.3	312.9	0.60	<2	0.5	995	39	<2	1.6	0.04	<5	2	<1	7	0.02	<10	31	21	<10	19	5
Granite	GT	N0713	203.2	204.7	1.50	<2	0.16	179	390	<2	<0.1	0.04	<5	1	<1	22	0.03	<10	49	14	<10	23	11
Granite	GT	N0713	436.3	437.27	0.97	<2	0.05	37	212	5	1.7	0.02	<5	1	<1	19	0.04	<10	29	11	<10	24	22
Granite	GT	N0724	171.18	171.96	0.78	<2	0.08	110	442	<2	<0.1	0.14	19	10	1	<5	0.18	<10	32	119	<10	41	10
Granite	GT	N0725	138.64	139.56	0.92	<2	0.2	122	529	<2	2.5	0.05	6	1	<1	28	0.02	<10	31	21	<10	43	15
Granite	GT	N0726	215.81	218	2.19	<2	0.22	381	376	<2	<0.1	0.23	<5	3	1	10	0.01	17	30	14	<10	10	8
Granite	GT	N0733	164	165	1.00	<2	0.56	322	177	<2	<0.1	0.01	5	1	<1	6	0.01	<10	21	10	<10	15	10
Granite	GT	258554	485.00	495.50	10.50	2	0.06	16	820	3	<0.1	0.02	<5	1	<1	27	0.03	11	<10	19	<10	54	25
Minimum						<2	0.04	9	34	2	<0.1	0.01	<5	1	<1	5	0.01	<10	<10	3.00	<10	10	4
Average						1.21	0.18	449.64	437.29	2.61	0.28	0.06	3.84	1.75	3.75	18.16	0.04	3.23	23.82	18.36	5.00	31	16
Maximum						2	0.69	2036	1846	9	2.5	0	19	10	38	47	0	26	49	119	<10	54	43
Mafic Dike	MD	N0705	101.6	102.6	1.00	<2	0.09	34	1495	2	2.9	0.05	<5	2	27	47	0.01	26	24	24	<10	26	33
Mafic Dike	MD	N0730	141	143	2.00	<2	0.59	219	430	<2	<0.1	0.03	12	23	<1	<5	0.12	<10	33	178	<10	31	8
Minimum						<2	0.09	34	430	<2	<0.1	0.03	<5	2	<1	<5	0.01	<10	24	24	<10	26	8
Maximum						<1	0.34	126.5	962.5	1.5	1.475	0.04	7.25	12.5	13.75	24.75	0.065	13.25	28.5	101	5	28.5	20.5
						<2	0.59	219	1495	2	2.9	0.05	12	23	27	47	0.12	26	33	178	<10	31	33
Mafic Metavolcanic	MMV	N0712	249.5	251	1.50	<2	0.06	136	872	5	2.1	0.47	12	3	<1	13	0.14	<10	24	34	<10	42	12
Metasediment	MSD	N0701	173.45	174.9	1.45	<2	0.09	198	574	<2	<0.1	0.18	9	8	<1	7	0.08	<10	20	80	<10	105	12
Metasediment	MSD	N0705	99.5	100.8	1.30	<2	0.04	401	145	<2	<0.1	0.17	7	2	<1	11	0.03	<10	14	20	<10	37	13
Metasediment	MSD	N0710	135.4	136.2	0.80	15	0.09	93	450	8	2.4	4.75	10	7	8	8	0.15	<10	40	140	15	75	29
Metasediment	MSD	N0712	197	198.5	1.50	<2	0.1	3586	35	5	2.3	0.34	10	4	2	<5	0.02	<10	38	8	<10	11	4
Minimum						<1	0.08	1069.5	301	3.75	1.2	1.36	9	5.25	2.75	7.125	0.07	<10	28	62	7.5	57	14.5
Average						<1	0.08	1069.5	301	3.75	1.2	1.36	9	5.25	2.75	7.125	0.07	<10	28	62	7.5	57	14.5
Maximum						<1	0.08	1069.5	301	3.75	1.2	1.36	9	5.25	2.75	7.125	0.07	<10	28	62	7.5	57	14.5
Regolith	R	N0730	94.53	95.23	0.70	<2	0.05	1258	31	4	3	0.19	5	2	86	6	0.01	<10	47	10	<10	9	4

Table A2.8.5 (Cont.'d)
Total Metal Concentrations
Phase II Static Testing
Minago Project

Rock Type	Rock Code	Drill Hole #	From (ft)	To (ft)	Length (ft)	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Se ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
Serpentinite	SPT	BHK 41-R1-90	1051.5	1056.2	4.70	<2	0.05	>10000	67	19	0.3	0.72	<5	5	<1	<5	0.01	<10	15	9	<10	4	3
Serpentinite	SPT	BHK 49-R9-90	746.5	749.9	3.40	<2	0.05	3459	102	9	<0.1	0.02	6	5	<1	13	0.02	15	24	11	<10	22	3
Serpentinite	SPT	N0707	257	258.5	1.50	<2	0.06	853	53	<2	1.2	0.09	5	3	<1	5	0.01	<10	42	7	<10	8	9
Serpentinite	SPT	BHK 49-R9-90	818.5	821.5	3.00	<2	0.05	>110000	66	15	<0.1	0.76	<5	4	<1	6	0.01	<10	15	9	<10	7	3
Serpentinite	SPT	BHK 52-90	744	749	5.00	<2	0.19	1565	167	10	<0.1	0.01	17	6	224	23	0.04	15	26	27	<10	14	4
Serpentinite	SPT	BHK 52-90	801	806	5.00	<2	0.1	4118	62	7	<0.1	0.01	15	6	164	<5	0.03	<10	15	20	<10	18	3
Serpentinite	SPT	BHK 52-90	811	815	4.00	<2	0.09	6863	48	8	<0.1	0.03	11	5	<1	<5	0.02	10	17	18	<10	19	3
Serpentinite	SPT	BHK 52-90	1110	1115.5	5.50	<2	0.12	869	62	<2	<0.1	0.04	13	2	<1	6	0.02	<10	24	11	<10	29	6
Serpentinite	SPT	N0707	233	243.2	10.20	<2	0.08	2979	51	7	<0.1	0.17	7	5	<1	7	0.01	<10	30	9	<10	9	3
Serpentinite	SPT	N0712	214.5	215.45	0.95	<2	0.21	968	119	<2	<0.1	0.05	<5	2	3	11	0.08	<10	32	21	<10	35	19
Serpentinite	SPT	N0713	371.04	371.7	0.66	<2	0.1	5462	54	7	4.6	0.29	13	6	1	<5	0.02	<10	30	19	<10	11	3
Serpentinite	SPT	N0720	254.84	256.33	1.49	<2	0.13	2416	35	4	2.4	0.1	8	3	1	<5	0.01	<10	38	6	<10	13	3
Serpentinite	SPT	N0726	133.69	134.54	0.85	<2	0.16	1295	39	7	4	0.37	24	4	4	<5	0.03	<10	27	37	<10	5	5
Serpentinite	SPT	N0730	104.25	105.25	1.00	<2	0.1	1612	34	<2	<0.1	0.02	12	2	<1	<5	0.01	11	10	6	<10	18	2
Minimum						<2	0.05	853	34	<2	<0.1	0.01	<5	2	<1	<5	0.01	<10	10	6	<10	4	2
Average						1.0	0.1	>3266.1	68.5	6.9	0.9	0.2	9.9	4.1	28.6	6.3	0.02	4.0	24.6	15.0	5.0	15.1	4.9
Maximum						<2	0.21	> 110000	167	19	4.6	0.76	24	6	224	23	0.08	15	42	37	<10	35	19
Serp/Gran	SPT/GT	N0702	161.6	162.4	0.80	<2	0.11	1731	32	<2	<0.1	0.02	<5	4	<1	<5	0.02	<10	14	15	<10	31	2

CLIENT : David Machaina
 PROJECT : Minago (Nuinsco Resources Ltd.)
 CEMI Project # : 0714
 Test : Modified Acid-Base Accounting
 Date : Sept 18, 2007

Sample ID	Paste pH	TIC %	CaCO3 NP	S(T) %	S(SO4) %	S(S-2) %	AP	NP	Net NP	Fizz Test
49092	8.77			0.03			0.9	11.1	10.2	none
49125	9.38			0.02			0.6	19.2	18.6	none
49427	9.38			0.04			1.3	14.2	12.9	none
49809	9.35			0.09			2.8	28.7	25.9	none
49816	8.87			0.02			0.6	167.7	167.1	none
49828	8.95			0.03			0.9	154.9	154.0	slight
49830	8.96			0.04			1.3	153.0	151.8	none
49832	9.18			0.02			0.6	10.4	9.8	none
49842	9.26			0.02			0.6	11.8	11.2	none
49843	9.25			0.02			0.6	36.4	35.7	none
49904	8.83			0.06			1.9	33.4	31.5	none
49907	9.25			0.03			0.9	15.1	14.2	none
258551	8.85			0.07			2.2	20.3	18.1	none
258554	9.02			0.03			0.9	13.0	12.1	none
258612	8.55	1.09	90.8	0.03	<0.01	0.03	0.9	151.1	150.1	none
258637	8.95			0.04			1.3	87.2	85.9	none
258774	7.10			0.74			23.1	86.3	63.2	none
258779	7.99			0.14			4.4	28.0	23.6	none
365507	9.45			0.05			1.6	28.3	26.7	none
365525	9.35			0.05			1.6	17.9	16.3	none
365627	7.17	0.06	5.0	0.8	0.22	0.58	18.1	54.8	36.7	none
365663	9.25			0.04			1.3	47.2	46.0	none
924159	8.63			0.17			5.3	28.3	23.0	none
924234	9.17	<0.01	<0.8	0.03	<0.01	0.03	0.9	56.9	56.0	none
924235	9.02			0.02			0.6	66.0	65.3	none
924350	8.77			0.13			4.1	44.6	40.5	none
924424	8.28			0.39			12.2	9.7	-2.5	none
924548	7.89			0.17			5.3	6.8	1.5	none
924551	8.30			0.2			6.3	28.2	22.0	none
924558	8.35			0.16			5.0	62.9	57.9	none
924591	9.27			0.07			2.2	29.6	27.5	none
924686	8.20			0.19			5.9	133.9	127.9	none
924724	8.95	3.57	297.5	0.1	<0.01	0.10	3.1	272.4	269.3	slight
924738	7.69			5.12			160.0	9.0	-151.0	none
924890	9.30			0.05			1.6	58.8	57.2	none
924964	9.47			0.05			1.6	22.6	21.1	none
925017	8.80			0.3			9.4	81.0	71.7	none
925132	9.66			0.03			0.9	10.7	9.7	none
925273	9.72	0.07	5.8	0.04	<0.01	0.04	1.3	10.9	9.7	none
925276	9.18			0.11			3.4	100.6	97.2	none
925315	8.98			0.06			1.9	20.7	18.9	none
925841	8.35			0.37			11.6	89.3	77.8	none
925856	9.16			0.07			2.2	48.9	46.7	none
925884	9.25			0.46			14.4	21.0	6.6	none
926243	9.27			0.38			11.9	94.0	82.1	none
926297	8.99			0.24			7.5	28.0	20.5	none
926397	8.95			0.16			5.0	549.1	544.1	moderate
929308	9.28			0.16			5.0	48.4	43.4	slight
929318	9.68			0.12			3.8	19.0	15.2	none
929407	8.95			0.04			1.3	61.9	60.7	none
929437	9.40			0.05			1.6	53.9	52.3	none
929488	9.23	0.03	2.5	0.04	<0.01	0.04	1.3	72.2	71.0	none
929497	9.18			0.02			0.6	47.4	46.7	none
Duplicates										
49092	8.76							11.0		none
924234	9.16							57.3		none
924738	7.70							8.9		none
926243	9.28			0.4				94.1		none
926297	8.95							28.1		none
258612		1.12		0.03	<0.01					
49843				0.02						
365525				0.07						
924235				0.03						
924724		3.59			<0.01					
924890				0.05						
929407				0.03						
929488		0.04			<0.01					

Note:

AP = Acid potential in tonnes CaCO3 equivalent per 1000 tonnes of material. AP is determined from calculated sulphide sulphur content: S(T) - S(SO4) unless SO4-S not determined.

NP = Neutralization potential in tonnes CaCO3 equivalent per 1000 tonnes of material.

NET NP = NP - AP

Carbonate NP is calculated from TIC originating from carbonates and is expressed in kg CaCO3/tonne.

CLIENT : David Machaina
PROJECT : Minago (Nuinsco Resources Ltd.)
CEMI Project # : 0714
Test : Metals by Aqua Regia Digestion with ICP Finish
Date : Sept 18, 2007

Sample ID	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm
49092	<0.2	0.89	<5	65	0.7	<5	0.19	<1	4	132
49125	<0.2	0.5	<5	108	0.6	<5	0.29	<1	2	143
49427	<0.2	1.3	<5	74	0.9	<5	0.1	1	11	211
49809	<0.2	3.16	<5	76	2.1	<5	0.36	1	16	213
49816	<0.2	0.97	8	417	0.6	<5	2.27	2	66	565
49828	<0.2	0.59	5	202	<0.5	<5	1.7	2	79	557
49830	0.2	0.44	<5	30	<0.5	<5	1.63	2	93	495
49832	0.4	0.79	<5	60	0.7	<5	0.03	<1	3	152
49842	<0.2	0.51	<5	376	<0.5	<5	0.05	<1	2	143
49843	<0.2	2.18	<5	44	0.8	<5	0.08	<1	4	82
49904	<0.2	1.45	<5	242	1.6	<5	0.22	1	38	467
49907	<0.2	0.78	5	109	0.5	<5	0.12	<1	4	130
258551	<0.2	1.27	10	89	1.2	<5	0.42	<1	5	89
258554	<0.2	0.99	5	111	0.7	<5	0.26	<1	6	144
258612	<0.2	0.53	<5	116	0.8	<5	1.78	1	112	284
258637	<0.2	3.15	<5	286	1.3	<5	0.26	<1	3	40
258774	0.6	0.66	<5	170	0.6	<5	0.81	1	158	250
258779	0.6	2.13	<5	66	0.9	<5	0.15	1	24	79
365507	<0.2	1.33	<5	223	0.5	<5	0.76	1	14	124
365525	<0.2	0.56	<5	132	0.5	<5	0.35	<1	3	127
365627	<0.2	0.48	<5	194	<0.5	<5	0.16	2	170	302
365633	<0.2	0.98	5	126	0.7	<5	0.76	<1	6	129
924159	0.3	2.02	<5	198	1.9	<5	0.72	2	27	148
924234	0.4	0.82	5	50	0.5	<5	0.02	1	42	317
924235	0.8	4.26	<5	36	2.2	<5	0.08	1	30	53
924350	<0.2	4.53	<5	138	2.2	<5	0.58	1	10	66
924424	<0.2	0.82	<5	117	<0.5	<5	0.15	1	5	104
924551	0.4	2.26	<5	199	2	<5	0.73	2	27	161
924558	0.3	1.15	<5	77	0.7	<5	0.21	<1	12	115
924591	<0.2	1.39	6	79	0.7	<5	0.88	<1	4	68
924686	<0.2	0.21	<5	72	<0.5	<5	1.17	2	56	230
924724	<0.2	0.74	<5	57	1.1	<5	5.58	<1	97	202
924738	0.9	3.13	<5	62	1.4	<5	0.1	4	18	140
924890	<0.2	4.77	<5	224	2.5	<5	0.1	1	15	64
924964	0.2	1.48	<5	196	0.7	<5	0.13	<1	7	101
925017	0.9	0.56	6	91	<0.5	<5	0.3	2	79	512
925132	<0.2	0.66	<5	118	0.5	<5	0.09	<1	3	105
925273	<0.2	0.75	<5	204	0.5	<5	0.18	<1	6	173
925276	0.6	0.56	<5	66	1.2	<5	1.54	1	146	191
925315	<0.2	1.99	6	79	1	<5	0.12	<1	7	80
925841	1	0.9	<5	127	<0.5	<5	0.68	2	106	380
925856	0.7	3.65	<5	630	1.6	<5	0.08	1	18	96
925884	0.8	1.12	<5	181	<0.5	<5	0.42	1	17	216
926243	1.3	0.99	7	17	<0.5	<5	1.42	1	79	887
926297	1.5	2.32	<5	85	2	<5	0.13	1	5	149
926397	1.3	0.56	5	30	0.5	<5	12.33	1	97	170
929308	0.6	2.26	<5	11	0.7	<5	1.56	2	23	291
929318	0.8	1.18	<5	166	<0.5	<5	0.66	1	31	308
929407	<0.2	0.76	<5	36	0.7	<5	0.05	1	69	222
929437	<0.2	3.54	<5	38	1	<5	0.46	2	35	96
929488	<0.2	4.09	<5	22	1.2	<5	0.18	1	7	23
929497	<0.2	2.68	<5	40	2	<5	0.1	<1	4	66
924548	<0.2	1.08	<5	53	0.9	<5	0.12	<1	27	122

CLIENT
PROJECT
CEMI Project #
Test
Date

Sample ID	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm
49092	7	0.86	<1	0.35	40	0.94	86	<2	0.04	51
49125	<1	0.79	<1	0.28	60	0.87	102	2	0.07	9
49427	2	1.79	<1	0.52	29	2.48	91	<2	0.09	261
49809	75	2.69	<1	0.78	61	4.39	147	<2	0.3	128
49816	<1	5.48	<1	0.41	210	>15.00	682	<2	0.19	1565
49828	3	5	<1	0.15	75	>15.00	631	<2	0.1	4118
49830	3	5.33	<1	0.05	54	>15.00	604	<2	0.09	6863
49832	14	0.8	<1	0.21	10	1.18	81	2	0.08	409
49842	4	0.86	<1	0.23	37	0.56	69	2	0.07	61
49843	8	1.18	<1	0.23	54	4.77	77	<2	0.31	1150
49904	14	2.27	<1	0.84	65	5.74	157	<2	0.12	869
49907	3	1.27	<1	0.36	93	0.98	113	<2	0.07	40
258551	4	1.59	<1	0.56	292	1.46	124	<2	0.09	34
258554	2	1.34	<1	0.57	136	0.95	167	2	0.06	16
258612	11	3.75	<1	0.28	120	>15.00	468	<2	0.05	3459
258637	18	1.19	<1	0.27	48	9.99	858	<2	0.09	32
258774	835	3.17	<1	0.44	58	>15.00	383	<2	0.05	>10000
258779	112	2.4	<1	0.25	18	7.56	263	<2	0.22	2036
365507	3	2.27	1	0.91	84	1.81	250	<2	0.09	38
365525	13	1.18	<1	0.33	94	0.74	125	<2	0.05	25
365627	479	5.65	<1	0.44	53	>15.00	451	<2	0.05	>10000
365633	39	1.37	<1	0.2	154	2.75	111	<2	0.11	258
924159	64	4.61	<1	1.36	39	2.09	414	<2	0.09	198
924234	<1	2.99	<1	0.15	15	>15.00	284	<2	0.11	1731
924235	5	2.6	<1	0.15	16	8.45	297	<2	0.4	1931
924350	36	4.06	<1	0.39	63	8.32	173	<2	0.17	1884
924424	26	2.16	<1	0.41	36	0.48	247	2	0.06	15
924551	61	4.84	<1	1.46	37	2.17	421	<2	0.09	189
924558	323	1.39	<1	0.54	41	0.73	185	<2	0.04	52
924591	15	1.11	<1	0.74	143	1.44	119	<2	0.11	369
924686	<1	5.21	<1	0.2	90	>15.00	605	<2	0.08	2979
924724	7	1.8	<1	0.43	29	6.1	412	<2	0.06	853
924738	58	9.15	<1	1.14	45	2.3	520	15	0.09	93
924890	<1	2.19	<1	0.31	58	12.49	338	<2	0.5	995
924964	6	1.12	<1	0.32	46	2.42	93	<2	0.16	179
925017	<1	4.44	<1	0.3	24	>15.00	364	<2	0.1	5462
925132	1	0.86	<1	0.34	119	0.86	81	<2	0.05	37
925273	6	0.9	<1	0.64	79	1.12	110	2	0.05	267
925276	1	3.23	<1	0.27	23	11.94	283	<2	0.13	2416
925315	3	1.23	<1	0.73	119	2.49	126	<2	0.2	122
925841	47	4.38	<1	0.58	<10	>15.00	364	<2	0.1	3586
925856	23	2.36	<1	1.23	60	9.08	327	<2	0.21	968
925884	54	2.2	<1	0.83	38	1.45	221	<2	0.06	136
926243	157	3.83	<1	0.15	18	9.66	326	<2	0.16	1295
926297	19	1.79	<1	0.22	27	4.65	75	<2	0.22	381
926397	24	2.73	<1	0.01	22	8.57	583	<2	0.05	1258
929308	32	4.46	<1	0.11	14	2.68	558	<2	0.08	110
929318	75	2.22	<1	0.72	<10	1.7	215	4	0.11	199
929407	9	3.22	<1	0.15	19	>15.00	455	<2	0.1	1612
929437	201	5.51	<1	0.1	18	10.22	350	<2	0.59	219
929488	34	2.01	<1	0.19	23	13.7	176	<2	0.69	396
929497	4	1.5	<1	0.2	38	7.37	146	<2	0.56	322
924548	254	1.19	1	0.7	61	0.69	133	<2	0.04	401

CLIENT
PROJECT
CEMI Project #
Test
Date

Sample ID	P ppm	Pb ppm	Se ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm
49092	274	<2	<0.1	0.02	<5	1	<1	11	0.02	<10
49125	245	6	<0.1	0.01	<5	1	15	22	0.02	<10
49427	348	5	<0.1	0.03	<5	2	<1	20	0.03	<10
49809	717	<2	<0.1	0.09	8	12	<1	27	0.05	<10
49816	167	10	<0.1	0.01	17	6	224	23	0.04	15
49828	62	7	<0.1	0.01	15	6	164	<5	0.03	<10
49830	48	8	<0.1	0.03	11	5	<1	<5	0.02	10
49832	34	5	<0.1	0.02	<5	1	<1	12	0.01	<10
49842	133	3	<0.1	0.01	<5	1	<1	15	0.04	<10
49843	184	<2	<0.1	0.01	<5	1	<1	13	0.01	<10
49904	62	<2	<0.1	0.04	13	2	<1	6	0.02	<10
49907	487	<2	<0.1	0.02	5	1	<1	21	0.04	<10
258551	1495	2	<0.1	0.05	<5	2	27	47	0.01	26
258554	820	3	<0.1	0.02	<5	1	<1	27	0.03	11
258612	102	9	<0.1	0.02	6	5	<1	13	0.02	15
258637	212	<2	<0.1	0.03	<5	1	<1	19	0.03	<10
258774	66	15	<0.1	0.76	<5	4	<1	6	0.01	<10
258779	223	<2	<0.1	0.14	<5	1	<1	14	0.03	<10
365507	1846	<2	<0.1	0.04	7	5	<1	18	0.1	13
365525	534	9	<0.1	0.05	<5	1	<1	33	0.04	<10
365627	67	19	0.3	0.72	<5	5	<1	<5	0.01	<10
365633	615	6	<0.1	0.03	<5	1	38	34	0.06	<10
924159	574	<2	<0.1	0.18	9	8	<1	7	0.08	<10
924234	32	<2	<0.1	0.02	<5	4	<1	<5	0.02	<10
924235	86	<2	0.4	0.01	<5	1	<1	14	0.01	<10
924350	754	<2	<0.1	0.11	<5	2	12	27	0.05	<10
924424	557	4	<0.1	0.36	8	2	<1	10	0.06	<10
924551	577	<2	2.9	0.18	9	9	<1	6	0.08	<10
924558	537	<2	<0.1	0.15	5	2	<1	15	0.04	12
924591	779	<2	<0.1	0.06	<5	1	<1	24	0.02	<10
924686	51	7	<0.1	0.17	7	5	<1	7	0.01	<10
924724	53	<2	1.2	0.09	5	3	<1	5	0.01	<10
924738	450	8	2.4	4.75	10	7	8	8	0.15	<10
924890	39	<2	1.6	0.04	<5	2	<1	7	0.02	<10
924964	390	<2	<0.1	0.04	<5	1	<1	22	0.03	<10
925017	54	7	4.6	0.29	13	6	1	<5	0.02	<10
925132	212	5	1.7	0.02	<5	1	<1	19	0.04	<10
925273	111	8	0.4	0.02	5	1	<1	20	0.04	<10
925276	35	4	2.4	0.1	8	3	1	<5	0.01	<10
925315	529	<2	2.5	0.05	6	1	<1	28	0.02	<10
925841	35	5	2.3	0.34	10	4	2	<5	0.02	<10
925856	119	<2	<0.1	0.05	<5	2	3	11	0.08	<10
925884	872	5	2.1	0.47	12	3	<1	13	0.14	<10
926243	39	7	4	0.37	24	4	4	<5	0.03	<10
926297	376	<2	3	0.23	<5	3	1	10	0.01	17
926397	31	4	3.7	0.19	5	2	86	6	0.01	<10
929308	442	<2	<0.1	0.14	19	10	1	<5	0.18	<10
929318	430	<2	<0.1	0.12	20	3	3	<5	0.21	<10
929407	34	<2	<0.1	0.02	12	2	<1	<5	0.01	11
929437	430	<2	<0.1	0.03	12	23	<1	<5	0.12	<10
929488	108	<2	<0.1	0.03	<5	1	<1	6	0.02	<10
929497	177	<2	<0.1	0.01	5	1	<1	6	0.01	<10
924548	145	<2	<0.1	0.17	7	2	<1	11	0.03	<10

CLIENT
PROJECT
CEMI Project #
Test
Date

Sample ID	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
49092	13	7	<10	23	12
49125	18	7	<10	31	19
49427	19	16	<10	42	17
49809	18	93	<10	34	12
49816	26	27	<10	14	4
49828	15	20	<10	18	3
49830	17	18	<10	19	3
49832	42	3	<10	24	10
49842	17	8	<10	22	12
49843	10	10	<10	23	5
49904	24	11	<10	29	6
49907	17	17	<10	37	13
258551	24	24	<10	26	33
258554	<10	19	<10	54	25
258612	24	11	<10	22	3
258637	<10	10	<10	21	4
258774	15	9	<10	7	3
258779	12	11	<10	27	6
365507	11	53	<10	54	12
365525	20	12	<10	51	15
365627	15	9	<10	4	3
365633	15	14	<10	26	18
924159	20	80	<10	105	12
924234	14	15	<10	31	2
924235	39	12	<10	18	5
924350	39	22	<10	40	43
924424	38	19	<10	42	15
924551	34	84	<10	101	12
924558	36	18	<10	49	25
924591	20	15	<10	44	35
924686	30	9	<10	9	3
924724	42	7	<10	8	9
924738	40	140	15	75	29
924890	31	21	<10	19	5
924964	49	14	<10	23	11
925017	30	19	<10	11	3
925132	29	11	<10	24	22
925273	35	7	<10	28	37
925276	38	6	<10	13	3
925315	31	21	<10	43	15
925841	38	8	<10	11	4
925856	32	21	<10	35	19
925884	24	34	<10	42	12
926243	27	37	<10	5	5
926297	30	14	<10	10	8
926397	47	10	<10	9	4
929308	32	119	<10	41	10
929318	24	57	<10	27	3
929407	10	6	<10	18	2
929437	33	178	<10	31	8
929488	25	7	<10	19	7
929497	21	10	<10	15	10
924548	14	20	<10	37	13

APPENDIX 2.8-A3

Shake Flask Extraction Results

Phase I – Shake Flask Extraction Results

CLIENT : David Machaina
PROJECT : Minago (Nuinsco Resources Ltd.)
CEMI Project # : 0714
Test : 24 Hour NanoPure Water Leach Extraction Test at 3:1 Liquid to Solid Ratio
Date : June 12, 2007

Leachate Analysis

Sample ID			#1-NO727-OB/AR	#2-NO729-FS/AR	#10-NO727-FS	#10-NO729-FS	Blank
Parameter	Method	Units					
Volume Nanopure water		mL	750	750	750	750	750
Sample Weight		g	250	250	250	250	250
pH	meter		8.15	8.52	7.88	7.90	6.26
Redox	meter	mV	313	292	314	322	333
Conductivity	meter	uS/cm	328	266	123	169	<1
Acidity (to pH 4.5)	titration	mg CaCO3/L	#N/A	#N/A	#N/A	#N/A	#N/A
Total Acidity (to pH 8.3)	titration	mg CaCO3/L	1.4	#N/A	1.7	1.8	1.4
Alkalinity	titration	mg CaCO3/L	81.2	100.4	42.5	46.7	1.1
Sulphate	Turbidity	mg/L	125	27	21	37	<1
Ion Balance							
Major Anions	Calc	meq/L	4.23	2.57	1.29	1.71	#N/A
Major Cations	Calc	meq/L	4.16	3.06	1.31	1.86	#N/A
Difference	Calc	meq/L	0.07	-0.49	-0.03	-0.16	#N/A
Balance (%)	Calc	%	0.9%	-8.7%	-1.0%	-4.5%	#N/A
Dissolved Metals							
Hardness CaCO3		mg/L	93.4	7	52.2	75.4	<0.5
Aluminum Al	ICP-MS	mg/L	0.115	0.53	0.0235	0.0207	<0.0002
Antimony Sb	ICP-MS	mg/L	0.00034	0.00014	0.00299	0.00025	<0.00005
Arsenic As	ICP-MS	mg/L	0.0009	0.001	0.0011	0.0006	<0.0001
Barium Ba	ICP-MS	mg/L	0.0357	0.00213	0.0193	0.0315	0.00004
Beryllium Be	ICP-MS	mg/L	0.00007	0.00007	<0.00005	<0.00005	<0.00005
Bismuth Bi	ICP-MS	mg/L	<0.00005	<0.00005	<0.00005	<0.00005	<0.00005
Boron B	ICP-MS	mg/L	0.461	0.804	0.03	0.047	<0.008
Cadmium Cd	ICP-MS	mg/L	0.00004	0.00001	0.00003	0.00003	<0.00001
Calcium Ca	ICP-MS	mg/L	24.1	1.69	10.9	16	<0.05
Chromium Cr	ICP-MS	mg/L	<0.0002	0.002	<0.0002	0.0004	0.0002
Cobalt Co	ICP-MS	mg/L	0.00044	0.0001	0.00129	0.00124	<0.00002
Copper Cu	ICP-MS	mg/L	0.0044	0.0018	0.0024	0.0009	0.0002
Iron Fe	ICP-MS	mg/L	0.062	0.128	0.007	<0.005	<0.005
Lead Pb	ICP-MS	mg/L	0.0002	0.00011	0.00033	0.00003	0.00003
Lithium Li	ICP-MS	mg/L	0.0235	0.0599	0.0062	0.008	<0.0002
Magnesium Mg	ICP-MS	mg/L	8.07	0.68	6.04	8.62	<0.05
Manganese Mn	ICP-MS	mg/L	0.0268	0.00158	0.0062	0.00562	0.00005
Mercury Hg	CVAA	ug/L	<0.05	<0.05	<0.05	<0.05	<0.05
Molybdenum Mo	ICP-MS	mg/L	0.0114	0.00469	0.0091	0.0102	<0.00002
Nickel Ni	ICP-MS	mg/L	0.005	0.002	0.0284	0.0096	<0.0005
Phosphorus P	ICP-MS	mg/L	<0.1	<0.1	<0.1	<0.1	<0.1
Potassium K	ICP-MS	mg/L	10.6	10.9	2.84	4.03	<0.05
Selenium Se	ICP-MS	mg/L	0.0013	0.0006	0.0057	0.0009	<0.0005
Silicon Si	ICP-MS	mg/L	1.57	4.11	0.62	0.79	<0.05
Silver Ag	ICP-MS	mg/L	<0.00001	0.00003	<0.00001	0.00006	<0.00001
Sodium Na	ICP-MS	mg/L	46.4	60.7	4.59	5.83	<0.05
Strontium Sr	ICP-MS	mg/L	0.148	0.0248	0.0733	0.115	0.00004
Sulphur (S)	ICP-MS	mg/L	36.1	7.6	4.9	10.5	<0.1
Thallium Tl	ICP-MS	mg/L	<0.00005	<0.00005	<0.00005	<0.00005	<0.00005
Tin Sn	ICP-MS	mg/L	<0.00005	<0.00005	0.00006	<0.00005	<0.00005
Titanium Ti	ICP-MS	mg/L	0.0051	0.0062	0.0013	0.0025	<0.0005
Uranium U	ICP-MS	mg/L	0.00261	0.00109	0.00432	0.00346	<0.00001
Vanadium V	ICP-MS	mg/L	0.00175	0.00904	0.00031	0.00063	<0.00005
Zinc Zn	ICP-MS	mg/L	0.0009	0.0007	<0.0005	<0.0005	<0.0005
Zirconium Zr	ICP-MS	mg/L	<0.005	<0.005	<0.005	<0.005	<0.005

Phase II – Shake Flask Extraction Results
--

CLIENT : Nuinsco Resources Ltd.
PROJECT : Minago (Nuinsco Resources Ltd.)
CEMI Project # : 0714
Test : 24 Hour NanoPure Water Leach Extraction Test at 3:1 Liquid to Solid Ratio
Date : August 27, 2008

Leachate Analysis

Sample ID			HC #1	HC #2	HC #3	HC #4
Parameter	Method	Units				
Volume Nanopure water		mL	3000	3000	3000	3000
Sample Weight		g	977.56	984.02	978.7	980.09
pH	meter		7.9	7.96	7.97	7.97
Redox	meter	mV	340	342	348	357
Conductivity	meter	uS/cm	90	89	72	92
Acidity (to pH 4.5)	titration	mg CaCO3/L	na	na	na	na
Total Acidity (to pH 8.3)	titration	mg CaCO3/L	1.8	1.6	1.4	1.5
Alkalinity	titration	mg CaCO3/L	45.2	43.7	38.4	42.9
Sulphate	Turbidity	mg/L	4	5	3	6
Dissolved Metals						
Hardness CaCO3		mg/L	39.5	31.1	31.2	39.8
Aluminum Al	ICP-MS	ug/L	22.9	33.9	76.6	175
Antimony Sb	ICP-MS	ug/L	0.13	0.04	0.04	0.05
Arsenic As	ICP-MS	ug/L	0.49	0.27	0.4	0.64
Barium Ba	ICP-MS	ug/L	7.86	4.49	6.15	8.44
Beryllium Be	ICP-MS	ug/L	<0.01	<0.01	<0.01	0.01
Bismuth Bi	ICP-MS	ug/L	<0.005	<0.005	0.008	0.007
Boron B	ICP-MS	ug/L	<50	205	78	111
Cadmium Cd	ICP-MS	ug/L	0.024	0.021	0.027	0.026
Calcium Ca	ICP-MS	ug/L	10300	5830	5420	8830
Chromium Cr	ICP-MS	ug/L	0.2	0.2	0.4	0.6
Cobalt Co	ICP-MS	ug/L	0.113	0.112	0.216	0.378
Copper Cu	ICP-MS	ug/L	1.65	0.35	1.73	4.71
Iron Fe	ICP-MS	ug/L	5	29	72	147
Lead Pb	ICP-MS	ug/L	0.086	0.083	0.166	0.214
Lithium Li	ICP-MS	ug/L	14.7	17.2	9.1	12.5
Magnesium Mg	ICP-MS	ug/L	3350	4020	4300	4310
Manganese Mn	ICP-MS	ug/L	0.98	0.93	0.94	2.01
Mercury Hg	CVAA	ug/L	<0.01	<0.01	<0.01	<0.01
Molybdenum Mo	ICP-MS	ug/L	0.34	0.13	0.17	0.44
Nickel Ni	ICP-MS	ug/L	2.8	9.26	7.85	17.4
Phosphorus P	ICP-MS	ug/L	2	<2	3	4
Potassium K	ICP-MS	ug/L	6420	6720	3510	6360
Selenium Se	ICP-MS	ug/L	0.11	0.8	0.4	0.3
Silicon Si	ICP-MS	ug/L	1560	3190	1860	2860
Silver Ag	ICP-MS	ug/L	<0.005	<0.005	<0.005	<0.005
Sodium Na	ICP-MS	ug/L	390	3790	2290	910
Strontium Sr	ICP-MS	ug/L	115	68.2	42.2	67.9
Sulphur (S)	ICP-MS	ug/L	<3000	<3000	<3000	<3000
Thallium Tl	ICP-MS	ug/L	0.03	0.037	0.023	0.026
Tin Sn	ICP-MS	ug/L	0.01	0.02	0.01	0.01
Titanium Ti	ICP-MS	ug/L	2.2	<0.5	1.9	4.5
Uranium U	ICP-MS	ug/L	0.098	0.05	0.283	0.592
Vanadium V	ICP-MS	ug/L	1.6	1.4	1	1.5
Zinc Zn	ICP-MS	ug/L	0.3	0.3	1	1.1
Zirconium Zr	ICP-MS	ug/L	<0.1	<0.1	<0.1	<0.2

HC #1 = AR Composite (N0727+N0728+N0729+N0736)

HC #2 = ORE/AR Composite (N0727+N0728+N0729+N0736)

HC #3 = ORE/LS Composite (N0727+N0728+N0729+N0736)

HC #4 = OB/LS/FS/AR/ORE Composite (N0727+N0728+N0729+N0736)

APPENDIX 2.8-A4

Kinetic Test Results for Waste Rock

Cell No.	Sample ID	Sample Type	Method Reference	Column Dimensions			Dry Wt. of Sample (kg)	Column Packing		Pore Volume (mL)	Total Volume of Initial Flushings (mL)	Flushing Rate/Weekly Input* (mL)	Temp (°C)	Sampling Frequency	Start-up date	Sampling Day	Operation Procedure	Sample prep for flushings
				Inner Diameter (cm)	Length (cm)	Distance from Top of column to Sample (cm)		Other Materials Used	Column Material									
1	AR Composite (N0727+N0728+N0729+N036)	Waste Rock	MEND	10.20	25.50		1.00	Plexiglas perforated disk & nylon mesh	Plexiglas	750	500	20-22 °C	Weekly	12-Jun	Wednesday	Flood Leach	none	
2	ORE/AR Composite (N0727+N0728+N0729+N036)	Waste Rock	MEND	10.20	25.50		1.00	Plexiglas perforated disk & nylon mesh	Plexiglas	750	500	20-22 °C	Weekly	12-Jun	Wednesday	Flood Leach	none	
3	ORE/LS Composite (N0727+N0728+N0729+N036)	Waste Rock	MEND	10.20	25.50		1.00	Plexiglas perforated disk & nylon mesh	Plexiglas	750	500	20-22 °C	Weekly	12-Jun	Wednesday	Flood Leach	none	
4	OB/LS/FS/AR/ORE Composite (N0727+N0728+N0729+N036)	Waste Rock	MEND	10.20	25.50		1.00	Plexiglas perforated disk & nylon mesh	Plexiglas	750	500	20-22 °C	Weekly	12-Jun	Wednesday	Flood Leach	none	

HC 1

Sample = AR Composite

Date	Cycle No.	Volume mL		pH	ORP mV	Cond. umhos/cm	Acidity (pH 4.5) mgCaCO3/L	Acidity (pH 8.3) mgCaCO3/L	Alkalinity mgCaCO3/L	Sulphate mg/L	Hardness CaCO3 mg/L
		Input	Output								
12-Jun-07	1	750	520	7.72	374	611	#N/A	2.3	40.5	262	88.3
20-Jun-07	2	500	405	7.62	364	832	#N/A	2.6	30.2	341	
27-Jun-07	3	500	425	7.63	380	647	#N/A	2.4	28.8	255	72.3
4-Jul-07	4	500	480	7.88	358	463	#N/A	2.3	37.9	161	
11-Jul-07	5	500	415	7.77	359	405	#N/A	2.9	36.0	161	30.4
18-Jul-07	6	500	430	7.93	366	430	#N/A	2.4	45.7	181	
25-Jul-07	7	500	460	8.09	370	302	#N/A	2.4	47.8	96	14.5
1-Aug-07	8	500	470	7.82	366	266	#N/A	2.4	46.1	42	
8-Aug-07	9	500	465	8.08	317	230	#N/A	1.2	42.4	50	8.8
15-Aug-07	10	500	455	8.02	370	24	#N/A	2.4	41.5	54	
22-Aug-07	11	500	435	7.88	379	187	#N/A	3.1	38.1	55	10.3
29-Aug-07	12	500	445	8.09	363	148	#N/A	3.6	32.8	40	
5-Sep-07	13	500	430	7.84	394	168	#N/A	2.3	34.8	47	10.6
12-Sep-07	14	500	435	8.08	380	140	#N/A	3.2	38.4	40	
19-Sep-07	15	500	445	8.05	376	144	#N/A	#N/A	39.5	44	8.8
26-Sep-07	16	500	455	7.97	394	137	#N/A	3.2	27.7	28	
3-Oct-07	17	500	460	7.89	391	150	#N/A	3.9	31.4	34	8.9
10-Oct-07	18	500	470	7.56	431	148	#N/A	2.8	30.6	29	
17-Oct-07	19	500	430	7.44	415	106	#N/A	2.7	22.9	22	7.8
24-Oct-07	20	500	465	7.64	428	113	#N/A	2.4	28.5	23	
31-Oct-07	21	500	470	7.78	378	121	#N/A	3.4	32.4	21	16.3
7-Nov-07	22	500	465	7.62	423	124	#N/A	2.7	27.4	21	
14-Nov-07	23	500	460	7.62	424	131	#N/A	2.8	31.6	27	13.2
21-Nov-07	24	500	475	7.43	476	99	#N/A	3.1	23.7	20	
28-Nov-07	25	500	465	7.43	424	84	#N/A	3.2	24.4	13	9.9
5-Dec-07	26	500	465	7.57	449	89	#N/A	3.1	26.4	17	
12-Dec-07	27	500	490	7.68	396	79	#N/A	2.3	21.9	14	11.7
19-Dec-07	28	500	470	7.55	458	78	#N/A	2.3	22.2	13	
26-Dec-07	29	500	465	7.56	398	80	#N/A	2.0	22.0	18	13.3
2-Jan-08	30	500	470	7.44	458	72	#N/A	2.4	17.6	15	
9-Jan-08	31	500	500	7.48	399	82	#N/A	#N/A	#N/A	14	17
16-Jan-08	32	500	465	7.30	481	79	#N/A	3.7	20.9	16	
23-Jan-08	33	500	480	7.36	403	76	#N/A	3.6	20.8	13	15.5
30-Jan-08	34	500	450	7.32	434	86	#N/A	4.2	22.9	17	
6-Feb-08	35	500	440	7.41	459	73	#N/A	2.9	20.3	15	16.8
13-Feb-08	36	500	445	7.33	448	71	#N/A	4.2	18.2	17	
20-Feb-08	37	500	455	7.52	443	73	#N/A	3.2	18.1	12	17.9
27-Feb-08	38	500	445	7.41	429	73	#N/A	3.8	18.3	14	
5-Mar-08	39	500	450	7.50	423	85	#N/A	3.8	22.2	20	22
12-Mar-08	40	500	455	7.46	431	114	#N/A	3.2	30.2	21	
19-Mar-08	41	500	465	7.61	426	101	#N/A	3.2	32.7	15	26.7
26-Mar-08	42	500	470	7.55	423	114	#N/A	3.6	41.4	16	
2-Apr-08	43	500	415	7.71	430	101	#N/A	2.6	39.2	13	32
9-Apr-08	44	500	415	7.59	424	117	#N/A	2.8	39.3	16	
16-Apr-08	45	500	405	7.57	422	106	#N/A	3.1	35.2	15	29.7
23-Apr-08	46	500	400	7.61	434	116	#N/A	3.3	39.9	16	
30-Apr-08	47	500	400	7.71	417	121	#N/A	2.4	40.2	16	37.2
7-May-08	48	500	400	7.70	398	120	#N/A	3.0	39.7	15	
14-May-08	49	500	415	7.75	382	111	#N/A	2.8	39.2	10	37.6
21-May-08	50	500	395	7.57	378	86	#N/A	3.1	29.1	8	
28-May-08	51	500	460	7.64	395	83	#N/A	3.2	34.4	9	30
4-Jun-08	52	500	460	8.17	370	49	#N/A	2.8	23.3	6	
11-Jun-08	53	500	460	7.60	419	60	#N/A	3.0	27.3	9	25.7
18-Jun-08	54	500	475	7.47	389	57	#N/A	3.7	29.2	8	
25-Jun-08	55	500	465	7.51	393	71	#N/A	4.4	29.5	7	26.3
2-Jul-08	56	500	455	7.50	397	67	#N/A	2.6	22.7	9	
9-Jul-08	57	500	470	7.62	388	85	#N/A	2.5	28.5	13	31.8
16-Jul-08	58	500	475	7.39	402	59	#N/A	2.9	21.9	8	
23-Jul-08	59	500	465	7.45	419	68	#N/A	2.9	25.2	9	26.4
30-Jul-08	60	500	480	7.54	403	71	#N/A	2.3	29.6	9	
6-Aug-08	61	500	485	7.61	394	81	#N/A	2.7	32.6	9	31.4
13-Aug-08	62	500	470	7.52	369	71	#N/A	2.6	25.8	5	
20-Aug-08	63	500	470	7.52	324	70	#N/A	2.5	27.0	9	29

Cell Terminated

Sept 19/07 Acidity 9.4 Suspect titrator error.

Jan 9/08 Acidity 5.3, Alkalinity 126.2. Suspect instrument error, not repeated.

HC 1

Sample = AR Compo

Date	Cycle No.	Al mg/L	Sb mg/L	As mg/L	Ba mg/L	Be mg/L	Bi mg/L	B mg/L	Cd mg/L	Ca mg/L	Cr mg/L	Co mg/L	Cu mg/L	Fe mg/L	Pb mg/L
12-Jun-07	1	0.174	0.00015	0.0005	0.0141	<0.00005	<0.00005	0.452	0.00005	20.8	0.0005	0.00334	0.0016	0.072	0.00004
20-Jun-07	2														
27-Jun-07	3	0.0439	0.0001	0.0007	0.00832	<0.00005	<0.00005	0.403	0.00004	19.8	<0.0002	0.00117	0.0036	0.017	0.00004
4-Jul-07	4														
11-Jul-07	5	0.109	0.00013	0.0006	0.0045	<0.00005	<0.00005	0.405	0.00003	8.11	0.0007	0.00045	0.0012	0.088	0.00017
18-Jul-07	6														
25-Jul-07	7	0.112	0.00014	0.0004	0.00265	<0.00005	<0.00005	0.441	0.00003	3.58	0.0005	0.00024	0.0015	0.024	0.00003
1-Aug-07	8														
8-Aug-07	9	0.0317	0.00018	0.0012	0.00202	<0.00005	<0.00005	0.34	0.00002	2.19	0.0003	0.00009	0.0019	0.01	0.00005
15-Aug-07	10														
22-Aug-07	11	0.0745	0.00013	0.0006	0.00259	<0.00005	<0.00005	0.325	0.00001	2.5	0.0009	0.00025	0.0006	0.051	0.00013
29-Aug-07	12														
5-Sep-07	13	0.152	0.00013	0.0006	0.00321	<0.00005	<0.00005	0.309	0.00003	2.63	0.0011	0.00025	0.0013	0.065	0.00014
12-Sep-07	14														
19-Sep-07	15	0.054	0.00018	0.0007	0.00299	<0.00005	<0.00005	0.296	0.00001	2.14	<0.0002	0.00015	0.0003	0.013	0.00614
26-Sep-07	16														
3-Oct-07	17	0.0428	0.00014	0.0005	0.0027	<0.00005	<0.00005	0.178	0.00001	2.21	0.0003	0.00015	0.0007	0.028	0.00003
10-Oct-07	18														
17-Oct-07	19	0.0543	0.00009	0.0009	0.00282	<0.00001	<0.000005	0.135	0.000017	2.04	0.0004	0.00011	0.00111	0.016	0.000308
24-Oct-07	20														
31-Oct-07	21	0.0178	0.00057	0.0014	0.00242	<0.00001	<0.000005	0.122	<0.000005	3.93	0.0001	0.00006	0.00009	0.005	0.000008
7-Nov-07	22														
14-Nov-07	23	0.0147	0.00011	0.0003	0.00438	<0.00001	<0.000005	0.161	<0.000005	3.47	0.0001	0.00012	0.00299	0.005	0.000016
21-Nov-07	24														
28-Nov-07	25	0.0395	0.00009	0.0003	0.00306	<0.00001	<0.000005	0.09	<0.000005	2.51	0.0004	0.00018	0.0014	0.021	0.000049
5-Dec-07	26														
12-Dec-07	27	0.0435	0.0001	0.0002	0.0033	<0.00001	<0.000005	0.072	<0.000005	3.12	0.0004	0.00012	0.00044	0.013	0.000208
19-Dec-07	28														
26-Dec-07	29	0.0165	0.00009	0.0002	0.00366	<0.00001	<0.000005	0.074	0.000028	3.42	0.0002	0.00012	0.00068	0.007	0.0145
2-Jan-08	30														
9-Jan-08	31	0.0125	0.00008	0.0002	0.00423	<0.00001	<0.000005	0.079	<0.000005	4.48	0.0001	0.00013	0.00026	0.004	0.000005
16-Jan-08	32														
23-Jan-08	33	0.016	0.00007	0.0002	0.00382	<0.00001	<0.000005	0.054	<0.000005	3.97	0.0001	0.00013	0.00061	0.006	0.00149
30-Jan-08	34														
6-Feb-08	35	0.0314	0.00008	0.0002	0.00438	<0.00001	<0.000005	0.061	<0.000005	4.42	0.0003	0.00016	0.00184	0.014	0.0085
13-Feb-08	36														
20-Feb-08	37	0.0181	0.00006	0.0002	0.00421	<0.00001	<0.000005	0.073	<0.000005	4.53	<0.0001	0.00022	0.0004	0.005	0.00001
27-Feb-08	38														
5-Mar-08	39	0.0187	0.00007	0.0002	0.00494	<0.00001	0.000006	0.074	<0.000005	5.72	0.0002	0.00012	0.00071	0.006	0.000337
12-Mar-08	40														
19-Mar-08	41	0.0132	0.0001	0.0005	0.00545	<0.00001	<0.000005	0.106	0.000006	6.64	<0.0001	0.00014	0.00067	0.003	0.000014
26-Mar-08	42														
2-Apr-08	43	0.0349	0.00011	0.0003	0.00636	<0.00001	<0.000005	0.113	<0.000005	7.86	0.0003	0.00015	0.00058	0.007	0.000026
9-Apr-08	44														
16-Apr-08	45	0.0197	0.00012	0.0003	0.00687	<0.00001	<0.000005	0.132	0.000008	7.45	0.0002	0.00019	0.00097	0.006	0.000184
23-Apr-08	46														
30-Apr-08	47	0.0176	0.00013	0.0003	0.0088	<0.00001	<0.000005	0.118	<0.000005	9.13	0.0002	0.00014	0.0007	0.007	0.000011
7-May-08	48														
14-May-08	49	0.017	0.00012	0.0003	0.00881	<0.00001	<0.000005	0.107	<0.000005	8.84	0.0002	0.00015	0.00069	0.004	<0.000005
21-May-08	50														
28-May-08	51	0.018	0.0001	0.0002	0.00716	<0.00001	<0.000005	0.074	<0.000005	7.16	0.0001	0.00012	0.00186	0.004	0.000013
4-Jun-08	52														
11-Jun-08	53	0.018	0.00012	0.0002	0.00584	<0.00001	<0.000005	<0.05	0.00002	6.45	0.0002	0.00016	0.00271	0.008	0.0191
18-Jun-08	54														
25-Jun-08	55	0.0138	0.00007	0.0002	0.00595	<0.00001	<0.000005	0.051	<0.000005	6.38	0.0003	0.00011	0.00064	0.004	0.000013
2-Jul-08	56														
9-Jul-08	57	0.025	0.00007	0.0002	0.00723	<0.00001	<0.000005	0.06	<0.000005	8.23	0.0002	0.00013	0.00203	0.015	0.000091
16-Jul-08	58														
23-Jul-08	59	0.0179	0.00006	0.0002	0.00546	<0.00001	<0.000005	<0.05	<0.000005	6.75	0.0002	0.00011	0.00072	0.006	0.000015
30-Jul-08	60														
6-Aug-08	61	0.0105	0.00008	0.0002	0.00626	<0.00001	0.000044	<0.05	0.000015	7.81	<0.0001	0.00012	0.00047	0.003	0.000086
13-Aug-08	62														
20-Aug-08	63	0.0119	0.00006	0.0001	0.00557	<0.00001	<0.000005	<0.05	0.000013	7.11	<0.0001	9.7E-05	0.0005	0.002	0.00004

Cell Terminated

Sept 19/07 Acidity 9.4
Jan 9/08 Acidity 5.3, A

HC 1

Sample = AR Compo

Date	Cycle No.	Li mg/L	Mg mg/L	Mn mg/L	Hg ug/L	Mo mg/L	Ni mg/L	P mg/L	K mg/L	Se mg/L	Si mg/L	Ag mg/L	Na mg/L	Sr mg/L	S mg/L
12-Jun-07	1	0.0583	8.85	0.003	<0.05	0.0208	0.23	<0.1	13.4	0.0095	1.49	<0.00001	108	0.329	97.8
20-Jun-07	2														
27-Jun-07	3	0.0485	5.55	0.0018	<0.05	0.0284	0.028	<0.1	8.44	0.0092	1.07	<0.00001	98.7	0.297	83.3
4-Jul-07	4														
11-Jul-07	5	0.0372	2.46	0.0011	<0.05	0.0211	0.0106	<0.1	8.64	0.0072	1.47	<0.00001	66.6	0.126	47.9
18-Jul-07	6														
25-Jul-07	7	0.0319	1.34	0.0005	<0.05	0.0138	0.0065	<0.1	7.24	0.0045	1.46	<0.00001	57.4	0.0528	30.3
1-Aug-07	8														
8-Aug-07	9	0.0268	0.8	0.0004	<0.05	0.00858	0.0028	<0.1	6.37	0.003	1.25	<0.00001	40.2	0.0344	19.4
15-Aug-07	10														
22-Aug-07	11	0.0216	0.98	0.0005	<0.05	0.00632	0.0052	<0.1	5.54	0.0026	1.43	0.00002	40.5	0.0339	20.1
29-Aug-07	12														
5-Sep-07	13	0.0288	0.97	0.0007	<0.05	0.00627	0.0055	<0.1	6.83	0.0024	1.33	0.00001	37.8	0.0402	20.5
12-Sep-07	14														
19-Sep-07	15	0.0273	0.83	0.0004	<0.05	0.00432	0.0036	<0.1	7.35	0.0013	1.27	<0.00001	34	0.0335	15.4
26-Sep-07	16														
3-Oct-07	17	0.024	0.81	0.0003	<0.05	0.00296	0.0034	<0.1	6.05	0.0013	1.05	<0.00001	22.3	0.0353	11.7
10-Oct-07	18														
17-Oct-07	19	0.0184	0.65	0.0004	<0.01	0.0018	0.0025		5.79	0.00066	0.922	<0.000005	15.4	0.0264	7
24-Oct-07	20														
31-Oct-07	21	0.0202	1.57	0.0002	<0.01	0.00229	0.002	<0.002	6.8	0.00065	1	<0.000005	15	0.0386	9
7-Nov-07	22														
14-Nov-07	23	0.0287	1.12	0.0004	<0.01	0.00199	0.0032	<0.002	7.86	0.00075	0.968	<0.000005	17.2	0.0494	10
21-Nov-07	24														
28-Nov-07	25	0.0199	0.89	0.0004	<0.01	0.00111	0.0038	<0.002	6.1	0.00048	1.26	0.000005	9.28	0.0381	4
5-Dec-07	26														
12-Dec-07	27	0.018	0.94	0.0004	<0.01	0.00098	0.0031	<0.002	6.14	0.00045	0.765	<0.000005	6.69	0.0433	6
19-Dec-07	28														
26-Dec-07	29	0.0181	1.15	0.0005	<0.01	0.00095	0.0034	<0.002	6.19	0.00034	0.729	0.000055	7.14	0.0478	5
2-Jan-08	30														
9-Jan-08	31	0.0199	1.41	0.0004	<0.01	0.00114	0.0039	<0.002	6.63	0.00052	0.739	<0.000005	6.65	0.0568	7
16-Jan-08	32														
23-Jan-08	33	0.0183	1.37	0.0004	<0.01	0.00091	0.0036	<0.002	5.67	0.00025	0.691	<0.000005	4.74	0.0546	5
30-Jan-08	34														
6-Feb-08	35	0.0181	1.41	0.0006	0.02	0.00088	0.0042	<0.002	6.38	0.00026	0.766	0.000006	4.95	0.0595	6
13-Feb-08	36														
20-Feb-08	37	0.0191	1.61	0.0008	<0.01	<0.00005	0.0118	<0.002	6.24	0.00026	0.765	<0.000005	5.05	0.0626	7
27-Feb-08	38														
5-Mar-08	39	0.0214	1.89	0.0006	<0.01	0.00115	0.0033	<0.002	7.11	0.00023	0.808	<0.000005	4.37	0.0768	7
12-Mar-08	40														
19-Mar-08	41	0.0277	2.46	0.0006	<0.01	0.00122	0.0032	<0.002	8.36	0.00026	1.42	<0.000005	4.85	0.0942	6
26-Mar-08	42														
2-Apr-08	43	0.0336	3.01	0.0008	<0.01	0.00114	0.0045	<0.002	10.9	0.00032	1.36	<0.000005	4.73	0.106	6
9-Apr-08	44														
16-Apr-08	45	0.032	2.7	0.0005	<0.01	0.00114	0.0037	<0.002	11.2	0.00039	1.51	<0.000005	3.87	0.103	6
23-Apr-08	46														
30-Apr-08	47	0.0364	3.5	0.0005	0.01	0.00118	0.004	<0.002	11.7	0.00034	1.55	0.000008	2.85	0.134	6
7-May-08	48														
14-May-08	49	0.0311	3.76	0.0004	<0.01	0.00087	0.0041	<0.002	10.8	0.0003	1.51	<0.000005	1.85	0.127	5
21-May-08	50														
28-May-08	51	0.0249	2.95	0.0004	<0.01	0.0007	0.0032	<0.002	8.24	0.00045	1.16	<0.000005	1.11	0.105	3
4-Jun-08	52														
11-Jun-08	53	0.0159	2.34	0.0007	<0.01	0.00052	0.004	<0.002	6.24	0.00029	0.948	<0.000005	0.72	0.0826	<3
18-Jun-08	54														
25-Jun-08	55	0.018	2.52	0.0005	<0.01	0.00052	0.0029	<0.002	5.65	0.00036	1.01	0.000012	0.56	0.0845	3
2-Jul-08	56														
9-Jul-08	57	0.0194	2.73	0.0006	<0.01	0.00066	0.0034	<0.002	6.28	0.00039	1.06	0.000012	0.53	0.106	4
16-Jul-08	58														
23-Jul-08	59	0.0152	2.32	0.0005	<0.01	0.00049	0.0031	0.002	5.09	0.00033	0.741	<0.000005	0.43	0.0846	3
30-Jul-08	60														
6-Aug-08	61	0.0184	2.9	0.0005	<0.01	0.00063	0.003	<0.002	5.84	0.00012	1.03	<0.000005	0.43	0.102	3
13-Aug-08	62														
20-Aug-08	63	0.0167	2.74	0.0003	<0.01	0.00053	0.0025	<0.002	5.37	0.00016	0.895	<0.000005	0.37	0.0928	4

Cell Terminated

Sept 19/07 Acidity 9.4
Jan 9/08 Acidity 5.3, A

HC 1

Sample = AR Compo

Date	Cycle No.	Tl mg/L	Sn mg/L	Ti mg/L	U mg/L	V mg/L	Zn mg/L	Zr mg/L	Major Anions	Major Cations	Diff	Diff (%)
12-Jun-07	1	0.00007	<0.00005	0.0064	0.00213	0.0018	<0.0005	<0.005	6.27	6.80	0.54	4.1%
20-Jun-07	2											
27-Jun-07	3	<0.00005	<0.00005	0.0013	0.00146	0.0021	0.0019	<0.005	5.89	5.95	0.06	0.5%
4-Jul-07	4											
11-Jul-07	5	<0.00005	0.00035	0.0028	0.00113	0.0036	0.0019	<0.005	4.07	3.72	-0.35	-4.5%
18-Jul-07	6											
25-Jul-07	7	<0.00005	<0.00005	0.0013	0.00146	0.0048	0.0006	<0.005	2.96	2.97	0.01	0.2%
1-Aug-07	8											
8-Aug-07	9	<0.00005	0.00005	<0.0005	0.00081	0.0043	0.001	<0.005	1.89	2.09	0.20	5.0%
15-Aug-07	10											
22-Aug-07	11	<0.00005	<0.00005	0.0013	0.00083	0.0032	<0.0005	<0.005	1.91	2.11	0.20	5.0%
29-Aug-07	12											
5-Sep-07	13	<0.00005	0.00007	0.0059	0.0007	0.0032	0.0013	<0.005	1.67	2.03	0.35	9.6%
12-Sep-07	14											
19-Sep-07	15	<0.00005	0.00007	0.0005	0.00055	0.002	<0.0005	<0.005	1.71	1.84	0.13	3.8%
26-Sep-07	16											
3-Oct-07	17	<0.00005	<0.00005	0.0007	0.00059	0.0027	<0.0005	<0.005	1.34	1.30	-0.03	-1.3%
10-Oct-07	18											
17-Oct-07	19	0.000018	0.00003	<0.0005	0.00023	0.0022	0.0013	<0.0001	0.92	0.97	0.06	3.0%
24-Oct-07	20											
31-Oct-07	21	0.000019	0.00003	<0.0005	0.00032	0.0015	0.0007	<0.0001	1.09	1.15	0.07	2.9%
7-Nov-07	22											
14-Nov-07	23	0.000025	0.00003	<0.0005	0.00051	0.002	0.0007	<0.0001	1.19	1.21	0.02	0.8%
21-Nov-07	24											
28-Nov-07	25	0.000023	0.00002	<0.0005	0.00026	0.0018	0.0004	<0.0001	0.76	0.76	0.00	-0.1%
5-Dec-07	26											
12-Dec-07	27	0.000017	0.00002	0.0007	0.00029	0.0013	0.0008	<0.0001	0.73	0.68	-0.05	-3.5%
19-Dec-07	28											
26-Dec-07	29	0.000026	0.00001	<0.0005	0.00027	0.001	0.0009	<0.0001	0.81	0.73	-0.08	-5.2%
2-Jan-08	30											
9-Jan-08	31	0.000022	<0.00001	<0.0005	0.00031	0.0008	0.0004	<0.0001	#N/A	0.80	#N/A	#N/A
16-Jan-08	32											
23-Jan-08	33	0.000022	<0.00001	<0.0005	0.00024	0.0007	0.0007	<0.0001	0.69	0.66	-0.03	-1.9%
30-Jan-08	34											
6-Feb-08	35	0.000024	<0.00001	<0.0005	0.00024	0.0008	0.0012	<0.0001	0.72	0.71	0.00	-0.3%
13-Feb-08	36											
20-Feb-08	37	0.000025	<0.00001	0.0006	0.00026	0.0006	0.0007	<0.0001	0.61	0.74	0.13	9.3%
27-Feb-08	38											
5-Mar-08	39	0.000027	<0.00001	<0.0005	0.00026	0.0007	0.0004	<0.0001	0.86	0.81	-0.05	-2.9%
12-Mar-08	40											
19-Mar-08	41	0.000031	<0.00001	<0.0005	0.00072	0.0013	0.0005	<0.0001	0.97	0.96	-0.01	-0.4%
26-Mar-08	42											
2-Apr-08	43	0.000031	0.00001	0.0013	0.0005	0.0015	0.0007	<0.0001	1.05	1.12	0.07	3.2%
9-Apr-08	44											
16-Apr-08	45	0.00004	<0.00001	<0.0005	0.00044	0.0016	0.0017	<0.0001	1.02	1.05	0.03	1.6%
23-Apr-08	46											
30-Apr-08	47	0.000042	<0.00001	<0.0005	0.00063	0.0017	0.0002	<0.0001	1.14	1.17	0.03	1.3%
7-May-08	48											
14-May-08	49	0.000037	<0.00001	<0.0005	0.00059	0.0016	0.0005	<0.0001	0.99	1.11	0.12	5.5%
21-May-08	50											
28-May-08	51	0.000026	<0.00001	<0.0005	0.00051	0.001	0.0002	<0.0001	0.88	0.86	-0.02	-0.9%
4-Jun-08	52											
11-Jun-08	53	0.000024	<0.00001	<0.0005	0.00027	<0.0002	0.0021	<0.0001	0.73	0.71	-0.03	-1.9%
18-Jun-08	54											
25-Jun-08	55	0.000022	<0.00001	<0.0005	0.0004	0.0009	0.0007	<0.0001	0.74	0.69	-0.04	-2.8%
2-Jul-08	56											
9-Jul-08	57	0.000027	0.00001	<0.0005	0.00048	0.001	0.0028	<0.0001	0.84	0.82	-0.02	-1.3%
16-Jul-08	58											
23-Jul-08	59	0.00002	<0.00001	<0.0005	0.00027	0.0008	0.0004	<0.0001	0.69	0.68	-0.01	-1.1%
30-Jul-08	60											
6-Aug-08	61	0.000023	<0.00001	<0.0005	0.00039	0.0009	0.0006	<0.0001	0.84	0.80	-0.04	-2.6%
13-Aug-08	62											
20-Aug-08	63	0.000029	<0.00001	<0.0005	0.00042	0.0007	0.0002	<0.0001	0.73	0.73	0.01	0.5%

Cell Terminated

Sept 19/07 Acidity 9.4
Jan 9/08 Acidity 5.3, A

HC 2

Sample = ORE/AR Composite

Date	Cycle	Volume mL		pH	ORP mV	Cond. umhos/cm	Acidity (pH 4.5) mgCaCO3/L	Acidity (pH 8.3) mgCaCO3/L	Alkalinity mgCaCO3/L	Sulphate mg/L	Hardness CaCO3 mg/L
	No.	Input	Output								
12-Jun-07	1	750	605	9.22	275	323	#N/A	#N/A	71.5	80	5.7
20-Jun-07	2	500	395	8.91	296	536	#N/A	#N/A	78.8	87	
27-Jun-07	3	500	415	8.72	330	462	#N/A	#N/A	60.9	190	8.8
4-Jul-07	4	500	475	8.34	327	379	#N/A	#N/A	45.9	129	
11-Jul-07	5	500	415	8.59	323	483	#N/A	#N/A	53.8	188	13.3
18-Jul-07	6	500	435	8.54	333	501	#N/A	#N/A	62.0	159	
25-Jul-07	7	500	450	8.49	349	264	#N/A	#N/A	39.5	87	6.3
1-Aug-07	8	500	450	8.14	345	252	#N/A	1.7	38.0	48	
8-Aug-07	9	500	460	8.35	302	232	#N/A	#N/A	36.8	70	5.6
15-Aug-07	10	500	435	8.42	355	24	#N/A	#N/A	37.3	47	
22-Aug-07	11	500	430	8.43	354	176	#N/A	#N/A	37.1	38	4.9
29-Aug-07	12	500	445	8.52	345	149	#N/A	#N/A	34.5	39	
5-Sep-07	13	500	435	8.24	366	135	#N/A	0.9	31.5	42	3.9
12-Sep-07	14	500	495	8.15	377	108	#N/A	2.3	34.8	34	
19-Sep-07	15	500	450	8.26	352	103	#N/A	#N/A	31.3	34	3.9
26-Sep-07	16	500	440	8.30	384	149	#N/A	#N/A	29.4	27	
3-Oct-07	17	500	440	8.13	378	137	#N/A	2.4	29.0	27	4.5
10-Oct-07	18	500	465	8.22	396	123	#N/A	1.1	27.9	21	
17-Oct-07	19	500	415	7.57	403	118	#N/A	2.6	26.5	22	3.9
24-Oct-07	20	500	460	8.15	402	113	#N/A	1.5	31.3	23	
31-Oct-07	21	500	450	7.71	383	105	#N/A	3.0	23.4	17	3.1
7-Nov-07	22	500	460	7.90	399	99	#N/A	1.9	28.1	14	
14-Nov-07	23	500	450	7.81	410	99	#N/A	2.4	27.5	16	3.5
21-Nov-07	24	500	435	7.79	455	96	#N/A	2.5	23.6	21	
28-Nov-07	25	500	480	7.75	413	103	#N/A	2.9	29.7	16	3.6
5-Dec-07	26	500	460	7.72	436	84	#N/A	2.8	23.9	13	
12-Dec-07	27	500	515	7.76	404	84	#N/A	2.1	26.8	12	3.4
19-Dec-07	28	500	455	7.71	443	79	#N/A	1.8	23.9	11	
26-Dec-07	29	500	510	7.71	396	77	#N/A	1.8	24.2	19	3.4
2-Jan-08	30	500	465	7.72	440	71	#N/A	2.0	21.1	10	
9-Jan-08	31	500	510	7.61	410	76	#N/A	2.3	26.0	16	4.3
16-Jan-08	32	500	475	7.67	463	92	#N/A	3.2	26.9	15	
23-Jan-08	33	500	465	7.59	397	73	#N/A	3.3	21.8	9	3.8
30-Jan-08	34	500	445	7.72	417	71	#N/A	3.3	20.9	15	
6-Feb-08	35	500	435	7.69	444	70	#N/A	2.5	20.2	13	5.7
13-Feb-08	36	500	455	7.72	429	64	#N/A	3.3	20.3	13	
20-Feb-08	37	500	490	7.60	436	67	#N/A	3.1	20.9	12	5.6
27-Feb-08	38	500	450	7.70	407	59	#N/A	4.3	15.9	9	
5-Mar-08	39	500	450	7.63	411	55	#N/A	3.1	15.6	8	4.5
12-Mar-08	40	500	455	7.67	414	67	#N/A	2.5	18.2	13	
19-Mar-08	41	500	465	7.80	410	66	#N/A	2.7	21.2	10	5.6
26-Mar-08	42	500	455	7.64	406	61	#N/A	2.9	17.7	9	
2-Apr-08	43	500	425	7.67	419	56	#N/A	2.2	17.8	8	6.8
9-Apr-08	44	500	410	7.41	416	62	#N/A	2.6	17.8	12	
16-Apr-08	45	500	420	7.43	417	72	#N/A	2.7	15.3	14	9.9
23-Apr-08	46	500	425	7.47	431	87	#N/A	2.7	14.6	20	
30-Apr-08	47	500	410	7.43	404	88	#N/A	2.3	13.1	21	15.2
7-May-08	48	500	420	7.62	387	97	#N/A	2.8	14.1	21	
14-May-08	49	500	410	7.52	374	91	#N/A	2.4	13.0	24	19.7
21-May-08	50	500	400	7.63	372	106	#N/A	2.7	18.3	21	
28-May-08	51	500	460	7.45	389	74	#N/A	3.0	11.3	20	18.8
4-Jun-08	52	500	450	7.64	399	61	#N/A	2.7	11.0	16	
11-Jun-08	53	500	475	7.51	415	54	#N/A	2.5	11.1	15	13.9
18-Jun-08	54	500	475	7.62	377	44	#N/A	3.4	11.4	13	
25-Jun-08	55	500	470	7.61	382	58	#N/A	3.5	12.3	10	13.8
2-Jul-08	56	500	465	7.49	386	50	#N/A	2.4	8.8	12	
9-Jul-08	57	500	470	7.46	378	55	#N/A	2.4	10.4	12	12.9
16-Jul-08	58	500	460	7.44	393	47	#N/A	2.8	9.9	11	
23-Jul-08	59	500	465	7.38	412	54	#N/A	2.7	11.4	11	13.8
30-Jul-08	60	500	490	7.41	398	52	#N/A	2.3	14.7	8	
6-Aug-08	61	500	465	7.42	386	47	#N/A	2.6	16.1	7	12
13-Aug-08	62	500	480	7.38	363	48	#N/A	2.3	11.1	8	
20-Aug-08	63	500	455	7.37	319	44	#N/A	2.6	11.7	7	12.8

Cell Terminated

Sept 19/07 Acidity 6.6 Suspect titrator error.

HC 2

Sample = ORE/AR C

Date	Cycle No.	Al mg/L	Sb mg/L	As mg/L	Ba mg/L	Be mg/L	Bi mg/L	B mg/L	Cd mg/L	Ca mg/L	Cr mg/L	Co mg/L	Cu mg/L	Fe mg/L	Pb mg/L
12-Jun-07	1	0.287	0.00017	0.0019	0.00143	<0.00005	<0.00005	1.99	0.00004	1.19	0.0003	0.00009	0.0018	0.18	0.00006
20-Jun-07	2														
27-Jun-07	3	0.452	0.0001	0.0012	0.00175	0.00008	<0.00005	1.9	0.00002	1.88	0.0007	0.00025	0.0018	0.26	0.00012
4-Jul-07	4														
11-Jul-07	5	0.52	0.00009	0.0015	0.00296	<0.00005	<0.00005	1.65	<0.00001	2.58	0.0019	0.00053	0.0013	0.343	0.00013
18-Jul-07	6														
25-Jul-07	7	0.214	0.00006	0.0002	0.00144	<0.00005	<0.00005	1.13	<0.00001	1.41	0.0005	0.0002	0.0029	0.101	0.00168
1-Aug-07	8														
8-Aug-07	9	0.23	0.00006	0.0009	0.00147	<0.00005	<0.00005	1.04	<0.00001	1.1	0.0011	0.00024	0.0002	0.124	0.00008
15-Aug-07	10														
22-Aug-07	11	0.0959	0.00005	0.0008	0.00136	<0.00005	<0.00005	0.946	<0.00001	1	0.0007	0.00015	0.0004	0.08	0.00005
29-Aug-07	12														
5-Sep-07	13	0.284	<0.00005	0.0007	0.00126	0.00009	<0.00005	0.794	<0.00001	0.63	0.0012	0.00026	0.0008	0.142	0.00011
12-Sep-07	14														
19-Sep-07	15	0.0842	<0.00005	0.0003	0.0009	<0.00005	<0.00005	0.708	<0.00001	0.85	<0.0002	0.00013	0.0001	0.044	0.00004
26-Sep-07	16														
3-Oct-07	17	0.118	0.00011	0.0083	0.00092	<0.00005	<0.00005	0.596	<0.00001	0.66	0.0006	0.00052	0.0023	0.181	0.00988
10-Oct-07	18														
17-Oct-07	19	0.214	0.00008	0.0019	0.00106	0.00001	<0.00005	0.54	<0.00005	0.56	0.0011	0.000384	0.0014	0.157	0.000185
24-Oct-07	20														
31-Oct-07	21	0.0655	0.00006	0.0009	0.00055	<0.00001	<0.00005	0.497	<0.00005	0.65	0.0004	0.00013	0.0002	0.054	0.000063
7-Nov-07	22														
14-Nov-07	23	0.0621	0.00005	0.0006	0.00052	<0.00001	<0.00005	0.41	<0.00005	0.74	0.0004	0.00017	0.0011	0.054	0.000051
21-Nov-07	24														
28-Nov-07	25	0.0774	0.00005	0.0003	0.00079	<0.00001	<0.00005	0.388	<0.00005	0.57	0.0005	0.000217	0.0007	0.065	0.000046
5-Dec-07	26														
12-Dec-07	27	0.043	0.00006	0.0003	0.00063	<0.00001	<0.00005	0.283	<0.00005	0.68	0.0005	0.000081	0.0002	0.03	0.00084
19-Dec-07	28														
26-Dec-07	29	0.0158	0.00003	0.0002	0.00055	<0.00001	<0.00005	0.267	<0.00005	0.68	<0.0001	0.000031	0.0003	0.011	0.000078
2-Jan-08	30														
9-Jan-08	31	0.0174	0.00003	0.0002	0.0009	<0.00001	<0.00005	0.308	<0.00005	0.93	0.0001	0.000049	0.0002	0.016	0.000012
16-Jan-08	32														
23-Jan-08	33	0.0491	0.00003	0.0003	0.00074	<0.00001	<0.00005	0.269	0.000013	0.69	0.0004	0.000132	0.0004	0.042	0.000075
30-Jan-08	34														
6-Feb-08	35	0.123	0.00003	0.0001	0.0015	<0.00001	<0.00005	0.285	0.000013	0.89	0.0008	0.000539	0.0018	0.158	0.000393
13-Feb-08	36														
20-Feb-08	37	0.0187	0.00003	0.0001	0.00083	<0.00001	<0.00005	0.269	<0.00005	1.06	<0.0001	0.000081	0.0003	0.013	0.000017
27-Feb-08	38														
5-Mar-08	39	0.0303	<0.00002	6E-05	0.00082	<0.00001	0.000025	0.22	<0.00005	0.84	0.0002	0.0001	0.0005	0.025	0.000023
12-Mar-08	40														
19-Mar-08	41	0.0236	0.00003	0.0001	0.00086	<0.00001	<0.00005	0.256	<0.00005	1.05	0.0003	0.000062	0.0004	0.015	0.000607
26-Mar-08	42														
2-Apr-08	43	0.0806	0.00003	0.0002	0.001	0.00001	<0.00005	0.222	<0.00005	1.24	0.0005	0.000235	0.0004	0.065	0.000038
9-Apr-08	44														
16-Apr-08	45	0.0755	0.00004	0.0029	0.00178	<0.00001	<0.00005	0.205	<0.00005	1.86	0.0006	0.00035	0.0009	0.08	0.000027
23-Apr-08	46														
30-Apr-08	47	0.0314	0.00003	0.0002	0.00219	<0.00001	<0.00005	0.18	<0.00005	2.84	0.0002	0.000206	0.0003	0.031	0.000011
7-May-08	48														
14-May-08	49	0.0512	0.00002	5E-05	0.00262	0.00001	<0.00005	0.212	0.000014	3.44	0.0003	0.000321	0.0008	0.041	0.000364
21-May-08	50														
28-May-08	51	0.0227	0.00002	2E-05	0.00245	<0.00001	<0.00005	0.145	<0.00005	3.19	0.0001	0.000151	0.0008	0.021	0.000021
4-Jun-08	52														
11-Jun-08	53	0.0121	0.00002	2E-05	0.00233	<0.00001	<0.00005	0.163	0.000041	2.49	<0.0001	0.00009	0.0014	0.009	0.00485
18-Jun-08	54														
25-Jun-08	55	0.0115	<0.00002	4E-05	0.00183	<0.00001	<0.00005	0.156	<0.00005	2.35	0.0003	0.000072	0.0007	0.03	0.000007
2-Jul-08	56														
9-Jul-08	57	0.0271	0.00002	4E-05	0.00211	<0.00001	<0.00005	0.151	<0.00005	2.36	0.0002	0.000101	0.0007	0.027	0.000081
16-Jul-08	58														
23-Jul-08	59	0.0125	<0.00002	0.0001	0.00191	<0.00001	<0.00005	0.152	<0.00005	2.56	0.0002	0.000065	0.0003	0.008	0.000021
30-Jul-08	60														
6-Aug-08	61	0.0122	0.00003	<0.00002	0.00171	<0.00001	<0.00005	0.14	0.00002	2.13	<0.0001	0.000061	0.0006	0.009	0.0199
13-Aug-08	62														
20-Aug-08	63	0.0108	<0.00002	9E-05	0.00165	<0.00001	<0.00005	0.127	0.000026	2.28	0.0002	0.000082	0.0005	0.008	0.000259

Cell Terminated

Sept 19/07 Acidity 6.6

HC 2

Sample = ORE/AR C

Date	Cycle No.	Li mg/L	Mg mg/L	Mn mg/L	Hg ug/L	Mo mg/L	Ni mg/L	P mg/L	K mg/L	Se mg/L	Si mg/L	Ag mg/L	Na mg/L
12-Jun-07	1	0.0088	0.67	0.0009	<0.05	0.0187	0.0031	<0.1	4.44	0.0032	2.78	<0.00001	76.1
20-Jun-07	2												
27-Jun-07	3	0.0084	1	0.0017	<0.05	0.0121	0.007	<0.1	4.23	0.0088	2.97	0.00002	91.8
4-Jul-07	4												
11-Jul-07	5	0.0107	1.67	0.0024	<0.05	0.0048	0.015	<0.1	6.01	0.0097	3.56	0.00001	92.5
18-Jul-07	6												
25-Jul-07	7	0.006	0.67	0.0008	<0.05	0.0017	0.006	<0.1	3.56	0.0071	1.93	<0.00001	51.6
1-Aug-07	8												
8-Aug-07	9	0.0059	0.68	0.001	<0.05	0.0012	0.0074	<0.1	3.4	0.0068	2.05	<0.00001	45.2
15-Aug-07	10												
22-Aug-07	11	0.005	0.58	0.0005	<0.05	0.001	0.0047	<0.1	2.73	0.0058	1.88	<0.00001	41.9
29-Aug-07	12												
5-Sep-07	13	0.006	0.58	0.0009	<0.05	0.0009	0.0084	<0.1	3.03	0.0056	2.1	<0.00001	33.5
12-Sep-07	14												
19-Sep-07	15	0.005	0.42	0.0005	<0.05	0.0007	0.004	<0.1	2.81	0.0043	1.49	<0.00001	29.9
26-Sep-07	16												
3-Oct-07	17	0.0058	0.7	0.0011	<0.05	0.0006	0.0148	<0.1	2.36	0.0037	2.02	<0.00001	24.5
10-Oct-07	18												
17-Oct-07	19	0.0056	0.6	0.0009	<0.01	0.0005	0.0107		2.5	0.003	2.08	<0.000005	22.4
24-Oct-07	20												
31-Oct-07	21	0.005	0.37	0.0005	<0.01	0.0004	0.0039	<0.002	2.37	0.0023	1.5	<0.000005	19.9
7-Nov-07	22												
14-Nov-07	23	0.0055	0.4	0.0005	0.01	0.0004	0.0045	0.003	2.61	0.002	1.41	<0.000005	18.5
21-Nov-07	24												
28-Nov-07	25	0.0068	0.52	0.0005	<0.01	0.0004	0.0078	<0.002	2.76	0.002	1.61	<0.000005	19
5-Dec-07	26												
12-Dec-07	27	0.006	0.41	0.0004	<0.01	0.0003	0.0033	<0.002	2.65	0.0015	1.25	<0.000005	13.4
19-Dec-07	28												
26-Dec-07	29	0.0055	0.4	0.0003	<0.01	0.0003	0.0018	<0.002	2.62	0.0014	1.14	<0.000005	13.2
2-Jan-08	30												
9-Jan-08	31	0.0065	0.47	0.0004	<0.01	0.0004	0.0028	<0.002	3.07	0.0014	1.14	<0.000005	13.1
16-Jan-08	32												
23-Jan-08	33	0.0061	0.51	0.0005	<0.01	0.0003	0.005	<0.002	2.98	0.0014	1.28	<0.000005	11.9
30-Jan-08	34												
6-Feb-08	35	0.0081	0.85	0.0012	<0.01	0.0002	0.0155	<0.002	3.04	0.0013	1.83	0.000008	12.2
13-Feb-08	36												
20-Feb-08	37	0.0078	0.71	0.0005	<0.01	<0.00005	0.006	<0.002	3.31	0.0013	1.3	<0.000005	12
27-Feb-08	38												
5-Mar-08	39	0.0064	0.59	0.0004	<0.01	0.0002	0.0055	<0.002	2.89	0.0011	0.98	<0.000005	8.68
12-Mar-08	40												
19-Mar-08	41	0.0082	0.73	0.0004	<0.01	0.0003	0.0034	<0.002	3.45	0.0012	1.63	<0.000005	9.83
26-Mar-08	42												
2-Apr-08	43	0.0106	0.89	0.0008	0.02	0.0002	0.0117	0.005	4.07	0.0011	1.31	0.000007	7.66
9-Apr-08	44												
16-Apr-08	45	0.0133	1.29	0.0008	<0.01	0.0002	0.0214	<0.002	5.02	0.0012	1.54	<0.000005	8.4
23-Apr-08	46												
30-Apr-08	47	0.0177	1.96	0.0009	0.02	0.0002	0.0407	<0.002	5.59	0.0014	1.25	0.000006	7.51
7-May-08	48												
14-May-08	49	0.0197	2.69	0.001	0.01	0.0002	0.0608	0.003	6.15	0.0015	1.34	<0.000005	7.33
21-May-08	50												
28-May-08	51	0.015	2.62	0.0008	<0.01	0.0002	0.0319	<0.002	5.08	0.0014	1.15	<0.000005	5.24
4-Jun-08	52												
11-Jun-08	53	0.0115	1.88	0.0007	<0.01	0.0001	0.0195	<0.002	4.32	0.0009	1.04	<0.000005	4.13
18-Jun-08	54												
25-Jun-08	55	0.0119	1.93	0.0006	<0.01	0.0001	0.0132	<0.002	3.79	0.001	1.17	0.000012	3.23
2-Jul-08	56												
9-Jul-08	57	0.0108	1.69	0.0008	<0.01	0.0001	0.0111	<0.002	3.61	0.0009	1.1	0.000006	2.83
16-Jul-08	58												
23-Jul-08	59	0.0108	1.8	0.0005	<0.01	0.0001	0.01	<0.002	3.73	0.0009	0.959	<0.000005	2.95
30-Jul-08	60												
6-Aug-08	61	0.0101	1.63	0.0006	<0.01	9E-05	0.0105	<0.002	3.35	0.0007	1.12	<0.000005	2.41
13-Aug-08	62												
20-Aug-08	63	0.01	1.72	0.0006	<0.01	9E-05	0.0108	<0.002	3.39	0.0007	1	<0.000005	2.21

Cell Terminated

Sept 19/07 Acidity 6.6

HC 2

Sample = ORE/AR C

Date	Cycle No.	Sr mg/L	S mg/L	Tl mg/L	Sn mg/L	Ti mg/L	U mg/L	V mg/L	Zn mg/L	Zr mg/L	Major Anions	Major Cations	Diff	Diff (%)
12-Jun-07	1	0.0123	27.7	<0.00005	0.00005	0.0018	0.0003	0.013	0.0006	<0.005	3.10	3.54	0.44	6.6%
20-Jun-07	2													
27-Jun-07	3	0.0223	93.5	<0.00005	0.00007	0.0054	0.0016	0.0117	0.0032	<0.005	5.18	4.28	-0.90	-9.5%
4-Jul-07	4													
11-Jul-07	5	0.0365	63	<0.00005	0.00015	0.0053	0.0011	0.0089	0.0017	<0.005	4.99	4.44	-0.55	-5.8%
18-Jul-07	6													
25-Jul-07	7	0.0149	25.9	<0.00005	0.00006	0.002	0.0005	0.0071	0.0008	<0.005	2.60	2.46	-0.14	-2.8%
1-Aug-07	8													
8-Aug-07	9	0.0123	23	<0.00005	0.0001	0.0022	0.0004	0.0067	0.001	<0.005	2.20	2.16	-0.03	-0.7%
15-Aug-07	10													
22-Aug-07	11	0.0091	19.8	<0.00005	<0.00005	0.0015	0.0004	0.0052	0.0016	<0.005	1.53	1.99	0.46	12.9%
29-Aug-07	12													
5-Sep-07	13	0.0077	15.1	<0.00005	0.00008	0.0028	0.0004	0.0064	0.0011	<0.005	1.50	1.61	0.11	3.5%
12-Sep-07	14													
19-Sep-07	15	0.0081	12.6	<0.00005	<0.00005	0.0012	0.0003	0.0054	<0.0005	<0.005	1.33	1.45	0.11	4.1%
26-Sep-07	16													
3-Oct-07	17	0.0074	11.2	<0.00005	<0.00005	0.0011	0.0004	0.0049	<0.0005	<0.005	1.14	1.22	0.07	3.1%
10-Oct-07	18													
17-Oct-07	19	0.006	9	0.00001	0.00014	0.0021	0.0003	0.0049	0.0012	0.0005	0.99	1.12	0.13	6.0%
24-Oct-07	20													
31-Oct-07	21	0.0061	7	0.000008	0.00002	<0.0005	0.0003	0.0037	0.0008	0.0001	0.82	0.99	0.17	9.3%
7-Nov-07	22													
14-Nov-07	23	0.0062	8	0.000006	0.00001	0.0007	0.0003	0.0034	0.0004	0.0002	0.88	0.94	0.06	3.2%
21-Nov-07	24													
28-Nov-07	25	0.0075	6	0.000012	0.00002	<0.0005	0.0003	0.0036	0.0002	0.0002	0.93	0.97	0.04	2.2%
5-Dec-07	26													
12-Dec-07	27	0.0078	6	0.000008	0.00001	0.0005	0.0002	0.0023	0.0004	<0.0001	0.79	0.72	-0.07	-4.5%
19-Dec-07	28													
26-Dec-07	29	0.0076	5	0.000012	<0.00001	<0.0005	0.0002	0.0022	0.0004	<0.0001	0.88	0.71	-0.17	-10.8%
2-Jan-08	30													
9-Jan-08	31	0.0092	5	0.000012	<0.00001	<0.0005	0.0002	0.0022	0.0008	<0.0001	0.85	0.73	-0.12	-7.6%
16-Jan-08	32													
23-Jan-08	33	0.0082	5	0.000011	<0.00001	<0.0005	0.0002	0.0023	0.0016	<0.0001	0.62	0.67	0.05	3.5%
30-Jan-08	34													
6-Feb-08	35	0.0107	6	0.000014	0.00001	0.0013	0.0002	0.0022	0.002	0.0002	0.67	0.72	0.05	3.4%
13-Feb-08	36													
20-Feb-08	37	0.012	5	0.000014	<0.00001	<0.0005	0.0002	0.0017	0.0016	<0.0001	0.67	0.72	0.05	3.6%
27-Feb-08	38													
5-Mar-08	39	0.0102	4	0.000013	<0.00001	<0.0005	0.0002	0.0015	0.0007	<0.0001	0.48	0.54	0.06	6.3%
12-Mar-08	40													
19-Mar-08	41	0.0131	4	0.000015	<0.00001	<0.0005	0.0002	0.0019	0.0003	<0.0001	0.63	0.63	0.00	-0.4%
26-Mar-08	42													
2-Apr-08	43	0.0147	5	0.000017	0.00001	0.0008	0.0001	0.0022	0.0005	0.0001	0.52	0.57	0.05	4.5%
9-Apr-08	44													
16-Apr-08	45	0.0231	7	0.000022	0.00001	0.0009	0.0002	0.0016	0.0009	<0.0001	0.60	0.69	0.10	7.4%
23-Apr-08	46													
30-Apr-08	47	0.0352	9	0.000031	<0.00001	<0.0005	0.0002	0.0011	0.0005	<0.0001	0.70	0.77	0.07	5.0%
7-May-08	48													
14-May-08	49	0.0445	10	0.000033	<0.00001	<0.0005	0.0002	0.0014	0.0015	<0.0001	0.76	0.87	0.11	6.7%
21-May-08	50													
28-May-08	51	0.043	9	0.000024	<0.00001	<0.0005	0.0003	0.001	0.0007	<0.0001	0.64	0.73	0.09	6.5%
4-Jun-08	52													
11-Jun-08	53	0.0333	6	0.000022	<0.00001	<0.0005	0.0002	0.0007	0.0054	<0.0001	0.54	0.57	0.03	3.1%
18-Jun-08	54													
25-Jun-08	55	0.0295	5	0.00002	<0.00001	<0.0005	0.0002	0.0011	0.0002	<0.0001	0.45	0.51	0.06	6.2%
2-Jul-08	56													
9-Jul-08	57	0.0309	5	0.000022	<0.00001	<0.0005	0.0002	0.001	0.0016	<0.0001	0.46	0.47	0.01	1.5%
16-Jul-08	58													
23-Jul-08	59	0.03	5	0.00002	<0.00001	<0.0005	0.0002	0.001	0.0002	<0.0001	0.46	0.50	0.04	4.5%
30-Jul-08	60													
6-Aug-08	61	0.0275	4	0.00002	<0.00001	<0.0005	0.0002	0.001	0.0006	<0.0001	0.47	0.43	-0.04	-4.0%
13-Aug-08	62													
20-Aug-08	63	0.0266	4	0.000026	<0.00001	<0.0005	0.0002	0.0009	0.0014	<0.0001	0.38	0.44	0.06	7.1%

Cell Terminated

Sept 19/07 Acidity 6.6

HC 3

Sample = ORE/LS Composite

Date	Cycle No.	Volume mL		pH	ORP mV	Cond. umhos/cm	Acidity (pH 4.5) mgCaCO3/L	Acidity (pH 8.3) mgCaCO3/L	Alkalinity mgCaCO3/L	Sulphate mg/L	Hardness CaCO3 mg/L
		Input	Output								
12-Jun-07	1	750	625	9.13	271	344	#N/A	#N/A	62.2	130	13.3
20-Jun-07	2	500	405	9.11	286	487	#N/A	#N/A	83.8	92	
27-Jun-07	3	500	410	9.08	307	308	#N/A	#N/A	70.6	90	7.6
4-Jul-07	4	500	495	8.32	332	326	#N/A	#N/A	56.3	93	
11-Jul-07	5	500	420	8.43	327	311	#N/A	#N/A	62.0	110	13.9
18-Jul-07	6	500	410	8.72	326	282	#N/A	#N/A	81.1	66	
25-Jul-07	7	500	440	8.66	342	172	#N/A	#N/A	43.0	39	11.5
1-Aug-07	8	500	440	8.2	349	176	#N/A	1.4	39.4	29	
8-Aug-07	9	500	445	8.42	305	161	#N/A	#N/A	34.7	28	10.5
15-Aug-07	10	500	440	8.27	369	24	#N/A	0.7	34.5	29	
22-Aug-07	11	500	415	8.42	361	134	#N/A	#N/A	36.5	29	10.5
29-Aug-07	12	500	425	8.29	364	120	#N/A	1.7	36.2	26	
5-Sep-07	13	500	430	8.31	371	110	#N/A	#N/A	36.3	25	9.3
12-Sep-07	14	500	440	8.24	379	93	#N/A	1.9	36.4	21	
19-Sep-07	15	500	435	8.17	368	76	#N/A	1.4	36.0	14	11.2
26-Sep-07	16	500	435	8.22	389	120	#N/A	1.9	32.6	14	
3-Oct-07	17	500	445	7.91	386	106	#N/A	3.1	31.7	14	11.1
10-Oct-07	18	500	450	7.98	406	101	#N/A	1.6	27.2	13	
17-Oct-07	19	500	420	7.50	407	96	#N/A	2.9	29.5	11	11.1
24-Oct-07	20	500	460	7.93	416	89	#N/A	1.6	28.2	11	
31-Oct-07	21	500	445	7.63	396	84	#N/A	2.8	25.5	13	12.4
7-Nov-07	22	500	445	7.64	414	79	#N/A	2.1	26.1	9	
14-Nov-07	23	500	455	7.54	423	71	#N/A	2.5	23.3	10	12.7
21-Nov-07	24	500	445	7.55	461	80	#N/A	2.6	22.6	14	
28-Nov-07	25	500	455	7.64	413	85	#N/A	3.0	29.3	11	14.9
5-Dec-07	26	500	460	7.65	438	71	#N/A	2.7	27.0	9	
12-Dec-07	27	500	460	7.66	411	68	#N/A	2.1	26.0	7	13.2
19-Dec-07	28	500	455	7.75	445	65	#N/A	1.9	25.7	6	
26-Dec-07	29	500	455	7.36	405	52	#N/A	1.7	22.3	8	11.6
2-Jan-08	30	500	450	7.53	445	52	#N/A	2.0	20.3	8	
9-Jan-08	31	500	515	7.53	405	66	#N/A	2.2	26.7	6	17.2
16-Jan-08	32	500	460	7.43	467	48	#N/A	3.2	17.7	5	
23-Jan-08	33	500	470	7.38	408	60	#N/A	3.4	21.5	7	15.3
30-Jan-08	34	500	435	7.37	428	58	#N/A	3.4	21.5	9	
6-Feb-08	35	500	440	7.53	447	57	#N/A	2.6	20.7	7	15.3
13-Feb-08	36	500	450	7.40	440	57	#N/A	3.4	21.2	11	
20-Feb-08	37	500	450	7.44	442	58	#N/A	3.1	16.7	9	16.6
27-Feb-08	38	500	455	7.38	425	50	#N/A	3.2	16.2	6	
5-Mar-08	39	500	450	7.41	422	49	#N/A	3.4	18.5	8	15.9
12-Mar-08	40	500	445	7.50	417	52	#N/A	2.5	18.4	5	
19-Mar-08	41	500	460	7.62	414	53	#N/A	2.6	21.1	6	16.3
26-Mar-08	42	500	465	7.43	415	49	#N/A	2.9	17.5	5	
2-Apr-08	43	500	450	7.46	428	45	#N/A	2.2	17.7	2	16.1
9-Apr-08	44	500	435	7.46	416	42	#N/A	2.3	24.9	7	
16-Apr-08	45	500	440	7.46	413	50	#N/A	2.7	17.1	6	17.1
23-Apr-08	46	500	435	7.53	425	54	#N/A	2.4	17.5	6	
30-Apr-08	47	500	445	7.52	400	58	#N/A	2.2	17.6	8	19.8
7-May-08	48	500	480	7.64	382	55	#N/A	2.4	16.5	10	
14-May-08	49	500	480	7.56	375	51	#N/A	2.1	14.0	7	19.3
21-May-08	50	500	460	7.61	364	47	#N/A	2.6	15.2	6	
28-May-08	51	500	455	7.50	385	38	#N/A	2.9	14.6	6	14.6
4-Jun-08	52	500	460	7.63	404	34	#N/A	2.8	13.5	6	
11-Jun-08	53	500	465	7.61	406	34	#N/A	2.4	14.5	8	14.4
18-Jun-08	54	500	470	7.63	375	29	#N/A	3.0	14.0	5	
25-Jun-08	55	500	470	7.58	381	37	#N/A	3.3	14.9	5	14.2
2-Jul-08	56	500	475	7.58	385	36	#N/A	2.1	13.1	5	
9-Jul-08	57	500	465	7.50	382	41	#N/A	2.2	13.7	8	14.1
16-Jul-08	58	500	470	7.47	394	36	#N/A	2.5	14.2	6	
23-Jul-08	59	500	465	7.48	409	41	#N/A	2.4	14.3	5	15.4
30-Jul-08	60	500	480	7.45	401	39	#N/A	1.9	17.7	5	
6-Aug-08	61	500	465	7.52	388	41	#N/A	2.3	21.4	4	15.6
13-Aug-08	62	500	460	7.45	366	39	#N/A	2.1	13.7	3	
20-Aug-08	63	500	465	7.51	326	37	#N/A	2.2	15.3	3	15.1

Cell Terminated

April 2, 2008 Pb 0.00363. Repeat = 0.00329, suspect contamination.

HC 3

Sample = ORE/LS Co

Date	Cycle No.	Al mg/L	Sb mg/L	As mg/L	Ba mg/L	Be mg/L	Bi mg/L	B mg/L	Cd mg/L	Ca mg/L	Cr mg/L	Co mg/L	Cu mg/L	Fe mg/L
12-Jun-07	1	0.0757	0.00022	0.001	0.00455	<0.00005	<0.00005	0.973	0.00003	2.53	<0.0002	0.00007	0.0011	0.058
20-Jun-07	2													
27-Jun-07	3	0.171	0.00025	0.0021	0.00186	<0.00005	<0.00005	0.932	0.00001	1.27	<0.0002	0.00018	0.0022	0.162
4-Jul-07	4													
11-Jul-07	5	0.229	0.00022	0.0014	0.00339	<0.00005	<0.00005	0.834	<0.00001	1.92	0.001	0.00053	0.0028	0.303
18-Jul-07	6													
25-Jul-07	7	0.144	0.00009	0.0007	0.00238	<0.00005	<0.00005	0.462	<0.00001	1.96	0.0004	0.00027	0.0005	0.129
1-Aug-07	8													
8-Aug-07	9	0.328	0.00008	0.001	0.0027	<0.00005	<0.00005	0.392	<0.00001	1.65	0.0009	0.00045	0.0016	0.186
15-Aug-07	10													
22-Aug-07	11	0.058	0.00007	0.0008	0.00222	<0.00005	<0.00005	0.386	<0.00001	1.79	0.0006	0.00017	0.0005	0.078
29-Aug-07	12													
5-Sep-07	13	0.062	0.00008	0.0007	0.00187	<0.00005	<0.00005	0.337	<0.00001	1.57	<0.0002	0.00014	0.0007	0.051
12-Sep-07	14													
19-Sep-07	15	0.0953	0.00008	0.0007	0.00202	<0.00005	<0.00005	0.281	<0.00001	1.76	<0.0002	0.0003	0.0007	0.109
26-Sep-07	16													
3-Oct-07	17	0.0901	0.0001	0.0008	0.00208	<0.00005	0.00025	0.241	<0.00001	1.81	0.0004	0.00047	0.0011	0.099
10-Oct-07	18													
17-Oct-07	19	0.073	0.00007	0.0007	0.00195	<0.00001	<0.000005	0.225	<0.000005	1.88	0.0003	0.000187	0.0007	0.058
24-Oct-07	20													
31-Oct-07	21	0.0414	0.00005	0.0006	0.00214	<0.00001	<0.000005	0.207	<0.000005	2.19	0.0002	0.000132	0.0003	0.043
7-Nov-07	22													
14-Nov-07	23	0.0368	0.00004	0.0004	0.00224	<0.00001	<0.000005	0.144	<0.000005	2.29	0.0002	0.000178	0.0007	0.046
21-Nov-07	24													
28-Nov-07	25	0.0691	0.00006	0.0003	0.00314	<0.00001	<0.000005	0.178	<0.000005	2.36	0.0004	0.000456	0.0005	0.08
5-Dec-07	26													
12-Dec-07	27	0.0758	0.00006	0.0006	0.00243	<0.00001	<0.000005	0.129	<0.000005	2.2	0.0006	0.000303	0.0004	0.073
19-Dec-07	28													
26-Dec-07	29	0.0217	0.00003	0.0002	0.00224	0.00002	<0.000005	0.093	0.000011	2.06	<0.0001	0.000106	0.0005	0.02
2-Jan-08	30													
9-Jan-08	31	0.0125	0.00004	0.0002	0.00319	<0.00001	<0.000005	0.111	<0.000005	3.1	<0.0001	0.000069	0.0004	0.01
16-Jan-08	32													
23-Jan-08	33	0.0331	0.00003	0.0002	0.00281	<0.00001	<0.000005	0.103	<0.000005	2.56	0.0002	0.000163	0.0005	0.034
30-Jan-08	34													
6-Feb-08	35	0.0339	0.00003	0.0002	0.003	<0.00001	<0.000005	0.094	<0.000005	2.67	0.0002	0.000111	0.0013	0.032
13-Feb-08	36													
20-Feb-08	37	0.0387	0.00003	0.0002	0.00329	<0.00001	<0.000005	0.094	<0.000005	2.82	0.0001	0.000158	0.0007	0.033
27-Feb-08	38													
5-Mar-08	39	0.0292	0.00002	0.0001	0.00295	<0.00001	<0.000005	0.079	<0.000005	2.75	0.0001	0.000149	0.0006	0.03
12-Mar-08	40													
19-Mar-08	41	0.0306	0.00002	0.0001	0.00297	<0.00001	<0.000005	0.086	<0.000005	2.73	0.0002	0.000117	0.0003	0.021
26-Mar-08	42													
2-Apr-08	43	0.0605	0.00004	0.0002	0.003	<0.00001	<0.000005	0.071	0.000059	2.7	0.0008	0.00012	0.0011	0.027
9-Apr-08	44													
16-Apr-08	45	0.021	0.00003	0.0002	0.0032	<0.00001	<0.000005	0.073	0.000005	2.94	<0.0001	0.0001	0.0004	0.02
23-Apr-08	46													
30-Apr-08	47	0.0206	0.00003	0.0001	0.00389	<0.00001	<0.000005	0.074	<0.000005	3.47	<0.0001	0.000114	0.0005	0.018
7-May-08	48													
14-May-08	49	0.0162	<0.00002	0.0002	0.00355	<0.00001	<0.000005	0.064	<0.000005	3.24	<0.0001	0.000077	<0.00005	0.011
21-May-08	50													
28-May-08	51	0.019	0.00002	8E-05	0.00277	<0.00001	<0.000005	0.053	<0.000005	2.46	<0.0001	0.000081	0.0011	0.013
4-Jun-08	52													
11-Jun-08	53	0.023	<0.00002	9E-05	0.00301	<0.00001	<0.000005	<0.05	<0.000005	2.53	<0.0001	0.000074	0.0022	0.016
18-Jun-08	54													
25-Jun-08	55	0.0167	<0.00002	0.0001	0.00268	<0.00001	<0.000005	0.051	<0.000005	2.42	0.0005	0.000068	0.0005	0.012
2-Jul-08	56													
9-Jul-08	57	0.0195	0.00002	9E-05	0.00293	<0.00001	<0.000005	0.062	<0.000005	2.57	0.0002	0.000095	0.001	0.019
16-Jul-08	58													
23-Jul-08	59	0.0149	0.00002	0.0002	0.00273	<0.00001	<0.000005	<0.05	<0.000005	2.81	<0.0001	0.000059	0.0004	0.009
30-Jul-08	60													
6-Aug-08	61	0.0144	0.00002	8E-05	0.00282	<0.00001	<0.000005	0.051	0.000016	2.76	<0.0001	0.000061	0.0004	0.009
13-Aug-08	62													
20-Aug-08	63	0.0163	<0.00002	7E-05	0.00262	0.00001	0.000005	<0.05	0.000012	2.63	<0.0001	0.000059	0.0003	0.008

Cell Terminated

April 2, 2008 Pb 0.003

HC 3

Sample = ORE/LS Co

Date	Cycle No.	Pb mg/L	Li mg/L	Mg mg/L	Mn mg/L	Hg ug/L	Mo mg/L	Ni mg/L	P mg/L	K mg/L	Se mg/L	Si mg/L	Ag mg/L	Na mg/L	Sr mg/L
12-Jun-07	1	0.00002	0.0089	1.69	0.0005	<0.05	0.0114	0.0049	<0.1	4.5	0.0027	1.47	<0.00001	77.5	0.0215
20-Jun-07	2														
27-Jun-07	3	0.00007	0.0059	1.07	0.0007	<0.05	0.0085	0.008	<0.1	2.53	0.0028	2.31	0.00002	64.8	0.0123
4-Jul-07	4														
11-Jul-07	5	0.00015	0.0101	2.2	0.0021	<0.05	0.0041	0.0209	<0.1	3.77	0.0037	3.06	<0.00001	62.2	0.019
18-Jul-07	6														
25-Jul-07	7	0.00007	0.0051	1.59	0.0018	<0.05	0.0011	0.011	<0.1	2.24	0.0024	1.33	<0.00001	32.2	0.011
1-Aug-07	8														
8-Aug-07	9	0.00012	0.0066	1.55	0.0012	<0.05	0.0008	0.0163	<0.1	2.51	0.0022	1.9	<0.00001	29.2	0.0129
15-Aug-07	10														
22-Aug-07	11	0.00005	0.0048	1.45	0.0006	<0.05	0.0007	0.0078	<0.1	2.19	0.0017	1.32	<0.00001	29.9	0.0128
29-Aug-07	12														
5-Sep-07	13	0.00008	0.0067	1.3	0.0005	<0.05	0.0007	0.0053	<0.1	2.72	0.0012	1.23	<0.00001	23.9	0.0145
12-Sep-07	14														
19-Sep-07	15	0.00006	0.0082	1.66	0.0008	<0.05	0.0005	0.0128	<0.1	2.68	0.0011	1.25	<0.00001	20.6	0.0145
26-Sep-07	16														
3-Oct-07	17	0.00017	0.0084	1.59	0.001	<0.05	0.0005	0.0141	<0.1	2.32	0.0008	1.16	<0.00001	16.5	0.0148
10-Oct-07	18														
17-Oct-07	19	0.0013	0.008	1.55	0.0006	<0.01	0.0004	0.0068		2.77	0.0009	1.15	<0.000005	14.9	0.0171
24-Oct-07	20														
31-Oct-07	21	0.000054	0.0072	1.68	0.0005	<0.01	0.0003	0.0051	<0.002	2.58	0.0007	0.999	<0.000005	11.7	0.0191
7-Nov-07	22														
14-Nov-07	23	0.000131	0.0062	1.69	0.0008	<0.01	0.0003	0.0077	0.003	2.41	0.0006	0.839	<0.000005	9.06	0.0168
21-Nov-07	24														
28-Nov-07	25	0.000089	0.0085	2.19	0.001	<0.01	0.0003	0.0137	<0.002	2.73	0.0008	1.16	0.000012	10.8	0.0219
5-Dec-07	26														
12-Dec-07	27	0.000086	0.0072	1.87	0.0008	<0.01	0.0002	0.0102	0.002	2.59	0.0007	1.05	<0.000005	6.78	0.0186
19-Dec-07	28														
26-Dec-07	29	0.000067	0.0051	1.56	0.0006	<0.01	0.0002	0.0033	<0.002	2.02	0.0005	0.643	<0.000005	5.09	0.0168
2-Jan-08	30														
9-Jan-08	31	0.000052	0.0071	2.3	0.0007	<0.01	0.0004	0.0029	<0.002	2.68	0.0008	0.742	<0.000005	5.85	0.0225
16-Jan-08	32														
23-Jan-08	33	0.000037	0.0058	2.16	0.0008	<0.01	0.0003	0.0054	<0.002	2.26	0.0008	0.756	<0.000005	5.06	0.0197
30-Jan-08	34														
6-Feb-08	35	0.00005	0.0077	2.1	0.0007	0.01	0.0002	0.0059	<0.002	2.41	0.0005	0.812	<0.000005	4.77	0.0215
13-Feb-08	36														
20-Feb-08	37	0.000036	0.0069	2.33	0.0009	<0.01	0.0003	0.0065	0.002	2.4	0.0005	0.803	<0.000005	4.52	0.0213
27-Feb-08	38														
5-Mar-08	39	0.000037	0.0061	2.18	0.0009	<0.01	0.0002	0.006	<0.002	2.2	0.0005	0.622	<0.000005	3.3	0.02
12-Mar-08	40														
19-Mar-08	41	0.000035	0.0063	2.3	0.0008	<0.01	0.0002	0.005	<0.002	2.06	0.0005	0.841	<0.000005	3.04	0.0198
26-Mar-08	42														
2-Apr-08	43	#N/A	0.0072	2.27	0.0007	<0.01	0.0002	0.0053	0.004	2.4	0.0005	0.697	<0.000005	2.7	0.0206
9-Apr-08	44														
16-Apr-08	45	0.000013	0.0077	2.36	0.0007	<0.01	0.0002	0.0055	<0.002	2.33	0.0004	0.731	<0.000005	2.67	0.0212
23-Apr-08	46														
30-Apr-08	47	0.00002	0.0086	2.71	0.0007	0.01	0.0003	0.0061	<0.002	2.39	0.0004	0.755	<0.000005	2.36	0.0263
7-May-08	48														
14-May-08	49	0.000026	0.006	2.72	0.0008	<0.01	0.0003	0.0049	<0.002	1.96	0.0004	0.661	<0.000005	2.29	0.0232
21-May-08	50														
28-May-08	51	0.000048	0.0048	2.04	0.0007	<0.01	0.0001	0.0043	<0.002	1.53	0.0003	0.557	<0.000005	1.84	0.0173
4-Jun-08	52														
11-Jun-08	53	0.000067	0.0044	1.96	0.0008	<0.01	0.0001	0.0038	<0.002	1.6	0.0004	0.56	<0.000005	2.11	0.0175
18-Jun-08	54														
25-Jun-08	55	0.000042	0.0049	1.97	0.0007	<0.01	0.0001	0.0033	<0.002	1.51	0.0004	0.527	0.000007	1.54	0.016
2-Jul-08	56														
9-Jul-08	57	0.000095	0.0051	1.87	0.0008	<0.01	0.0001	0.0044	<0.002	1.7	0.0005	0.608	<0.000005	1.6	0.018
16-Jul-08	58														
23-Jul-08	59	0.0023	0.0048	2.04	0.0007	<0.01	0.0001	0.0029	<0.002	1.72	0.0005	0.49	<0.000005	1.61	0.0178
30-Jul-08	60														
6-Aug-08	61	0.00695	0.0051	2.13	0.0007	<0.01	0.0001	0.0033	<0.002	1.71	0.0004	0.591	<0.000005	1.51	0.0177
13-Aug-08	62														
20-Aug-08	63	0.000072	0.0046	2.08	0.0006	<0.01	0.0001	0.0029	<0.002	1.51	0.0004	0.513	0.000006	1.29	0.0169

Cell Terminated

April 2, 2008 Pb 0.003

HC 3

Sample = ORE/LS Co

Date	Cycle No.	S mg/L	Tl mg/L	Sn mg/L	Ti mg/L	U mg/L	V mg/L	Zn mg/L	Zr mg/L	Major Anions	Major Cations	Diff	Diff (%)
12-Jun-07	1	43.5	<0.00005	<0.00005	0.0011	0.00046	0.0053	<0.0005	<0.005	3.95	3.75	-0.20	-2.6%
20-Jun-07	2												
27-Jun-07	3	48.3	<0.00005	0.00005	0.0027	0.00214	0.0055	0.0008	<0.005	3.29	3.03	-0.25	-4.0%
4-Jul-07	4												
11-Jul-07	5	28.5	<0.00005	0.00014	0.0033	0.00353	0.0042	0.0017	<0.005	3.53	3.08	-0.45	-6.9%
18-Jul-07	6												
25-Jul-07	7	11.5	<0.00005	<0.00005	0.0031	0.00129	0.003	0.0005	<0.005	1.67	1.69	0.01	0.4%
1-Aug-07	8												
8-Aug-07	9	12.7	<0.00005	0.00005	0.0055	0.00101	0.0027	0.0006	<0.005	1.28	1.54	0.27	9.5%
15-Aug-07	10												
22-Aug-07	11	13.6	<0.00005	<0.00005	0.0011	0.00092	0.002	<0.0005	<0.005	1.33	1.56	0.23	7.9%
29-Aug-07	12												
5-Sep-07	13	9.7	<0.00005	0.00006	0.0011	0.00103	0.0022	<0.0005	<0.005	1.25	1.29	0.05	1.9%
12-Sep-07	14												
19-Sep-07	15	6.4	<0.00005	<0.00005	0.0008	0.00099	0.0017	<0.0005	<0.005	1.01	1.19	0.18	8.1%
26-Sep-07	16												
3-Oct-07	17	5.8	<0.00005	0.00019	0.0013	0.00119	0.0016	0.001	<0.005	0.93	1.00	0.07	3.8%
10-Oct-07	18												
17-Oct-07	19	5	0.000013	0.00007	0.0009	0.00098	0.0017	0.0004	0.0001	0.82	0.94	0.12	6.9%
24-Oct-07	20												
31-Oct-07	21	4	0.000013	0.00005	<0.0005	0.00072	0.0011	0.0004	<0.0001	0.78	0.82	0.04	2.6%
7-Nov-07	22												
14-Nov-07	23	6	0.00001	0.00006	0.0006	0.00065	0.0011	0.0004	<0.0001	0.67	0.71	0.04	2.5%
21-Nov-07	24												
28-Nov-07	25	4	0.000015	0.00003	0.0007	0.00086	0.0016	0.0003	<0.0001	0.82	0.84	0.02	1.3%
5-Dec-07	26												
12-Dec-07	27	4	0.000011	0.00001	0.0015	0.00061	0.0012	0.0003	0.0001	0.67	0.62	-0.04	-3.2%
19-Dec-07	28												
26-Dec-07	29	<3	0.000015	0.00001	<0.0005	0.0005	0.0009	0.0008	<0.0001	0.61	0.50	-0.11	-9.7%
2-Jan-08	30												
9-Jan-08	31	4	0.000015	<0.00001	<0.0005	0.00086	0.0007	0.0006	<0.0001	0.66	0.67	0.01	0.5%
16-Jan-08	32												
23-Jan-08	33	3	0.000013	<0.00001	0.0007	0.00051	0.0008	0.0006	<0.0001	0.58	0.58	0.01	0.7%
30-Jan-08	34												
6-Feb-08	35	3	0.000017	<0.00001	<0.0005	0.00073	0.0007	0.0015	<0.0001	0.56	0.58	0.01	1.3%
13-Feb-08	36												
20-Feb-08	37	4	0.000016	<0.00001	0.001	0.0005	0.0008	0.0005	<0.0001	0.52	0.59	0.07	6.3%
27-Feb-08	38												
5-Mar-08	39	3	0.000012	<0.00001	<0.0005	0.00045	0.0006	0.0002	<0.0001	0.54	0.52	-0.02	-1.9%
12-Mar-08	40												
19-Mar-08	41	<3	0.000013	<0.00001	0.0006	0.00044	0.0008	0.0004	<0.0001	0.55	0.51	-0.04	-3.4%
26-Mar-08	42												
2-Apr-08	43	3	0.000015	<0.00001	0.0007	0.00046	0.0008	0.0061	<0.0001	0.40	0.50	0.11	11.8%
9-Apr-08	44												
16-Apr-08	45	3	0.000016	<0.00001	<0.0005	0.00056	0.0007	0.0004	<0.0001	0.47	0.52	0.05	5.1%
23-Apr-08	46												
30-Apr-08	47	3	0.000021	<0.00001	<0.0005	0.00061	0.0007	0.0003	<0.0001	0.52	0.56	0.04	3.9%
7-May-08	48												
14-May-08	49	4	0.000014	<0.00001	<0.0005	0.0008	0.0007	0.0002	<0.0001	0.43	0.54	0.11	11.5%
21-May-08	50												
28-May-08	51	<3	0.00001	<0.00001	<0.0005	0.00053	0.0006	0.0002	<0.0001	0.42	0.41	-0.01	-0.8%
4-Jun-08	52												
11-Jun-08	53	<3	0.000011	<0.00001	<0.0005	0.00061	0.0004	0.0015	<0.0001	0.46	0.42	-0.04	-4.2%
18-Jun-08	54												
25-Jun-08	55	<3	0.000012	<0.00001	<0.0005	0.00059	0.0007	0.0008	<0.0001	0.40	0.39	-0.01	-1.7%
2-Jul-08	56												
9-Jul-08	57	<3	0.000014	0.00001	<0.0005	0.00053	0.0007	0.0015	<0.0001	0.44	0.40	-0.05	-5.4%
16-Jul-08	58												
23-Jul-08	59	<3	0.000012	<0.00001	<0.0005	0.0005	0.0007	0.0004	<0.0001	0.39	0.42	0.03	3.9%
30-Jul-08	60												
6-Aug-08	61	<3	0.000012	<0.00001	<0.0005	0.00054	0.0006	0.0005	<0.0001	0.51	0.42	-0.09	-9.5%
13-Aug-08	62												
20-Aug-08	63	<3	0.000018	<0.00001	<0.0005	0.00048	0.0004	0.0003	<0.0001	0.37	0.40	0.03	3.9%

Cell Terminated

April 2, 2008 Pb 0.003

HC 4

Sample = OB/LS/FS/AR/ORE Composite

Date	Cycle No.	Volume mL		pH	ORP mV	Cond. umhos/cm	Acidity (pH 4.5) mgCaCO3/L	Acidity (pH 8.3) mgCaCO3/L	Alkalinity mgCaCO3/L	Sulphate mg/L	Hardness CaCO3 mg/L
		Input	Output								
12-Jun-07	1	750	600	8.96	272	319	#N/A	#N/A	61.2	90	12.8
20-Jun-07	2	500	405	8.38	313	662	#N/A	#N/A	53.3	175	
27-Jun-07	3	500	435	8.49	337	590	#N/A	#N/A	48.3	221	20.5
4-Jul-07	4	500	495	8.60	326	422	#N/A	#N/A	48.9	144	
11-Jul-07	5	500	425	8.04	351	485	#N/A	1.9	42.5	174	20.5
18-Jul-07	6	500	435	8.50	344	398	#N/A	#N/A	45.0	147	
25-Jul-07	7	500	465	8.63	351	267	#N/A	#N/A	42.6	85	12.8
1-Aug-07	8	500	470	8.41	343	276	#N/A	#N/A	42.7	61	
8-Aug-07	9	500	470	8.61	299	260	#N/A	#N/A	43.9	70	9.4
15-Aug-07	10	500	460	8.35	366	24	#N/A	#N/A	39.9	57	
22-Aug-07	11	500	440	8.51	356	179	#N/A	#N/A	39.6	49	9.3
29-Aug-07	12	500	440	8.38	364	157	#N/A	#N/A	35.2	39	
5-Sep-07	13	500	435	8.52	362	150	#N/A	#N/A	36.1	47	9.7
12-Sep-07	14	500	435	8.40	369	129	#N/A	#N/A	36.4	37	
19-Sep-07	15	500	455	8.53	361	118	#N/A	#N/A	39.0	39	8.5
26-Sep-07	16	500	445	8.52	375	174	#N/A	#N/A	34.6	30	
3-Oct-07	17	500	455	8.26	377	161	#N/A	1.9	35.6	34	8
10-Oct-07	18	500	480	8.45	388	150	#N/A	#N/A	36.0	24	
17-Oct-07	19	500	435	7.57	412	147	#N/A	3.1	34.7	23	7.6
24-Oct-07	20	500	465	8.26	405	120	#N/A	1.1	35.8	24	
31-Oct-07	21	500	460	7.71	401	121	#N/A	3.0	28.5	20	8.6
7-Nov-07	22	500	460	7.89	411	113	#N/A	2.3	29.8	21	
14-Nov-07	23	500	465	7.76	431	115	#N/A	2.4	28.4	21	8.7
21-Nov-07	24	500	455	7.78	458	106	#N/A	2.7	24.4	19	
28-Nov-07	25	500	475	7.81	417	113	#N/A	2.8	30.0	23	11
5-Dec-07	26	500	475	7.73	436	105	#N/A	2.9	28.1	21	
12-Dec-07	27	500	485	7.66	417	92	#N/A	2.2	25.2	16	10.9
19-Dec-07	28	500	460	7.69	452	94	#N/A	1.9	24.6	16	
26-Dec-07	29	500	470	7.42	417	96	#N/A	2.0	24.5	20	12.4
2-Jan-08	30	500	470	7.63	448	87	#N/A	2.3	23.9	14	
9-Jan-08	31	500	495	7.70	408	104	#N/A	2.4	30.5	20	18.1
16-Jan-08	32	500	470	7.50	471	78	#N/A	3.2	20.5	14	
23-Jan-08	33	500	460	7.48	413	85	#N/A	4.0	22.6	15	16.3
30-Jan-08	34	500	450	7.57	427	92	#N/A	3.7	24.6	19	
6-Feb-08	35	500	445	7.70	445	90	#N/A	2.8	24.2	19	18.7
13-Feb-08	36	500	435	7.62	438	78	#N/A	3.9	22.8	12	
20-Feb-08	37	500	465	7.48	442	71	#N/A	3.2	18.2	14	16.9
27-Feb-08	38	500	455	7.54	421	71	#N/A	3.4	20.1	12	
5-Mar-08	39	500	445	7.47	421	69	#N/A	4.0	17.7	12	18.5
12-Mar-08	40	500	435	7.56	419	78	#N/A	2.5	20.9	14	
19-Mar-08	41	500	460	7.66	416	75	#N/A	2.8	22.3	13	21.5
26-Mar-08	42	500	480	7.46	419	69	#N/A	3.1	20.2	12	
2-Apr-08	43	500	470	7.47	429	60	#N/A	2.6	18.3	12	20.3
9-Apr-08	44	500	475	7.48	413	72	#N/A	2.5	17.0	10	
16-Apr-08	45	500	470	7.50	418	81	#N/A	3.1	21.5	16	25.9
23-Apr-08	46	500	465	7.53	430	81	#N/A	2.8	21.8	15	
30-Apr-08	47	500	470	7.53	405	80	#N/A	2.4	20.5	14	25.6
7-May-08	48	500	470	7.66	391	82	#N/A	2.8	23.0	14	
14-May-08	49	500	475	7.57	380	68	#N/A	2.4	18.1	10	24.6
21-May-08	50	500	455	7.66	374	95	#N/A	3.0	26.8	16	
28-May-08	51	500	470	7.58	393	64	#N/A	3.1	22.5	11	23.6
4-Jun-08	52	500	465	7.62	415	60	#N/A	3.3	21.5	10	
11-Jun-08	53	500	480	7.67	413	62	#N/A	2.8	26.0	11	27.7
18-Jun-08	54	500	470	7.64	383	62	#N/A	3.6	27.4	12	
25-Jun-08	55	500	475	7.61	390	76	#N/A	3.8	26.0	11	27.1
2-Jul-08	56	500	465	7.60	393	64	#N/A	2.3	16.1	10	
9-Jul-08	57	500	480	7.57	389	81	#N/A	2.6	22.2	16	27.3
16-Jul-08	58	500	470	7.52	399	64	#N/A	2.7	20.3	13	
23-Jul-08	59	500	475	7.49	414	73	#N/A	2.9	17.9	13	26.1
30-Jul-08	60	500	490	7.43	409	59	#N/A	2.3	16.2	9	
6-Aug-08	61	500	485	7.52	395	66	#N/A	2.4	22.0	11	23.8
13-Aug-08	62	500	480	7.45	375	68	#N/A	2.4	15.6	9	
20-Aug-08	63	500	485	7.36	338	62	#N/A	2.6	15.9	9	23.3

Cell Terminated

April 2, 2008 Pb 0.0103. Repeat = 0.00940. Suspect contamination.

HC 4

Sample = OB/LS/FS/A

Date	Cycle No.	Al mg/L	Sb mg/L	As mg/L	Ba mg/L	Be mg/L	Bi mg/L	B mg/L	Cd mg/L	Ca mg/L	Cr mg/L	Co mg/L	Cu mg/L	Fe mg/L
12-Jun-07	1	0.497	0.00016	0.0008	0.00436	0.00007	<0.00005	1.05	0.00002	2.45	0.001	0.00027	0.0032	0.336
20-Jun-07	2													
27-Jun-07	3	0.244	0.00011	0.0012	0.00483	<0.00005	<0.00005	1.08	0.00002	4.92	<0.0002	0.00035	0.0037	0.19
4-Jul-07	4													
11-Jul-07	5	0.453	0.0001	0.0008	0.00586	0.00013	<0.00005	0.986	0.00001	4.59	0.0007	0.00041	0.0012	0.378
18-Jul-07	6													
25-Jul-07	7	0.341	0.00006	0.0005	0.00408	<0.00005	<0.00005	0.729	<0.00001	2.79	0.0008	0.00036	0.0015	0.242
1-Aug-07	8													
8-Aug-07	9	0.186	0.00008	0.0006	0.00255	<0.00005	<0.00005	0.74	<0.00001	2.3	0.0004	0.00013	0.0007	0.103
15-Aug-07	10													
22-Aug-07	11	0.0647	0.00005	0.0005	0.00194	<0.00005	<0.00005	0.632	<0.00001	2.29	0.0005	0.00012	0.0005	0.081
29-Aug-07	12													
5-Sep-07	13	0.215	0.00007	0.0008	0.00215	<0.00005	<0.00005	0.571	<0.00001	2.33	0.0003	0.00021	0.0012	0.15
12-Sep-07	14													
19-Sep-07	15	0.13	0.00006	0.0008	0.00184	<0.00005	<0.00005	0.517	<0.00001	2.05	<0.0002	0.00019	0.0011	0.082
26-Sep-07	16													
3-Oct-07	17	0.0631	0.00022	0.0017	0.00161	<0.00005	<0.00005	0.465	<0.00001	1.95	<0.0002	0.00015	0.0025	0.073
10-Oct-07	18													
17-Oct-07	19	0.104	0.00005	0.0008	0.00177	<0.00001	<0.00005	0.43	<0.00005	1.77	0.0003	0.000166	0.001	0.098
24-Oct-07	20													
31-Oct-07	21	0.062	0.00006	0.0007	0.00172	<0.00001	<0.00005	0.388	<0.00005	2.09	0.0002	0.00013	0.001	0.055
7-Nov-07	22													
14-Nov-07	23	0.0478	0.00005	0.0003	0.00169	<0.00001	<0.00005	0.32	<0.00005	2.11	0.0002	0.000102	0.0013	0.042
21-Nov-07	24													
28-Nov-07	25	0.128	0.00005	0.0002	0.00314	<0.00001	<0.00005	0.266	<0.00005	2.4	0.0006	0.000339	0.0007	0.132
5-Dec-07	26													
12-Dec-07	27	0.0792	0.00006	0.0002	0.00275	<0.00001	<0.00005	0.201	<0.00005	2.55	0.0003	0.000175	0.0009	0.071
19-Dec-07	28													
26-Dec-07	29	0.0364	0.00006	0.0003	0.00256	<0.00001	<0.00005	0.229	0.000045	2.8	0.0001	0.00009	0.0009	0.031
2-Jan-08	30													
9-Jan-08	31	0.0283	0.00005	0.0003	0.00337	<0.00001	<0.00005	0.266	<0.00005	4.21	0.0001	0.000074	0.0007	0.023
16-Jan-08	32													
23-Jan-08	33	0.0297	0.00004	0.0001	0.00301	<0.00001	<0.00005	0.187	<0.00005	3.48	0.0002	0.000092	0.001	0.027
30-Jan-08	34													
6-Feb-08	35	0.0694	0.00004	0.0001	0.00419	<0.00001	0.00006	0.228	<0.00005	4.17	0.0002	0.000205	0.0013	0.102
13-Feb-08	36													
20-Feb-08	37	0.033	0.00003	0.0001	0.00302	<0.00001	<0.00005	0.192	<0.00005	3.67	<0.0001	0.000092	0.0006	0.026
27-Feb-08	38													
5-Mar-08	39	0.0266	0.00003	0.0001	0.00323	<0.00001	<0.00005	0.169	<0.00005	4.12	<0.0001	0.000077	0.0004	0.02
12-Mar-08	40													
19-Mar-08	41	0.0211	0.00005	0.0001	0.00351	<0.00001	<0.00005	0.215	<0.00005	4.48	0.0004	0.00007	0.0006	0.014
26-Mar-08	42													
2-Apr-08	43	0.0476	0.00004	0.0001	0.00357	<0.00001	<0.00005	0.143	0.000028	4.31	0.0003	0.000101	0.0008	0.031
9-Apr-08	44													
16-Apr-08	45	0.0267	0.00003	0.0001	0.00463	<0.00001	<0.00005	0.175	<0.00005	5.71	<0.0001	0.000103	0.001	0.021
23-Apr-08	46													
30-Apr-08	47	0.0193	0.00004	0.0002	0.00457	<0.00001	<0.00005	0.154	<0.00005	5.47	<0.0001	0.000079	0.0009	0.016
7-May-08	48													
14-May-08	49	0.0203	0.00004	9E-05	0.00432	<0.00001	<0.00005	0.15	<0.00005	5.15	<0.0001	0.000066	0.0003	0.013
21-May-08	50													
28-May-08	51	0.0249	0.00004	0.0002	0.00455	<0.00001	<0.00005	0.125	<0.00005	4.85	<0.0001	0.000083	0.0013	0.017
4-Jun-08	52													
11-Jun-08	53	0.0304	0.00004	0.0001	0.00489	<0.00001	<0.00005	0.141	<0.00005	5.89	<0.0001	0.000111	0.0018	0.027
18-Jun-08	54													
25-Jun-08	55	0.0311	0.00003	0.0001	0.00515	<0.00001	<0.00005	0.147	0.00005	5.67	0.0003	0.000092	0.0012	0.044
2-Jul-08	56													
9-Jul-08	57	0.0635	0.00003	0.0001	0.00584	<0.00001	<0.00005	0.115	<0.00005	6.07	0.0002	0.000125	0.0027	0.048
16-Jul-08	58													
23-Jul-08	59	0.0182	0.00003	0.0001	0.00486	<0.00001	<0.00005	0.097	<0.00005	5.8	0.0001	0.000054	0.0004	0.011
30-Jul-08	60													
6-Aug-08	61	0.0164	0.00003	4E-05	0.00428	<0.00001	<0.00005	0.081	0.000016	5.17	0.0001	0.000067	0.0006	0.012
13-Aug-08	62													
20-Aug-08	63	0.0183	0.00002	5E-05	0.00426	<0.00001	<0.00005	0.074	0.000014	4.96	<0.0001	0.000059	0.001	0.013

Cell Terminated

April 2, 2008 Pb 0.010

HC 4

Sample = OB/LS/FS/A

Date	Cycle No.	Pb mg/L	Li mg/L	Mg mg/L	Mn mg/L	Hg ug/L	Mo mg/L	Ni mg/L	P mg/L	K mg/L	Se mg/L	Si mg/L	Ag mg/L
12-Jun-07	1	0.00012	0.0112	1.63	0.0033	<0.05	0.0104	0.0086	<0.1	5.51	0.0009	2.59	<0.00001
20-Jun-07	2												
27-Jun-07	3	0.00009	0.0096	2	0.0035	<0.05	0.013	0.0248	<0.1	5.67	0.002	1.78	<0.00001
4-Jul-07	4												
11-Jul-07	5	0.0002	0.0102	2.19	0.0032	<0.05	0.0062	0.0163	<0.1	6.55	0.0034	2.86	0.00002
18-Jul-07	6												
25-Jul-07	7	0.00022	0.007	1.42	0.0031	<0.05	0.0027	0.0165	<0.1	4.27	0.0021	1.78	<0.00001
1-Aug-07	8												
8-Aug-07	9	0.00007	0.0071	0.89	0.0011	<0.05	0.0023	0.0073	<0.1	4.67	0.0023	1.65	<0.00001
15-Aug-07	10												
22-Aug-07	11	0.00007	0.005	0.87	0.0008	<0.05	0.0017	0.0059	<0.1	3.42	0.0019	1.41	<0.00001
29-Aug-07	12												
5-Sep-07	13	0.00009	0.0073	0.96	0.0013	<0.05	0.0019	0.0097	<0.1	4.43	0.002	1.72	<0.00001
12-Sep-07	14												
19-Sep-07	15	0.00008	0.0062	0.82	0.0011	<0.05	0.0014	0.0082	<0.1	4.31	0.0011	1.34	<0.00001
26-Sep-07	16												
3-Oct-07	17	0.00015	0.0067	0.77	0.0008	<0.05	0.0014	0.0069	<0.1	3.6	0.0017	1.31	<0.00001
10-Oct-07	18												
17-Oct-07	19	0.000058	0.007	0.77	0.001	<0.01	0.001	0.0074		4.26	0.00084	1.44	<0.000005
24-Oct-07	20												
31-Oct-07	21	0.000046	0.0075	0.82	0.0009	<0.01	0.0008	0.0063	<0.002	4.24	0.0004	1.3	<0.000005
7-Nov-07	22												
14-Nov-07	23	0.000338	0.008	0.84	0.0008	<0.01	0.0009	0.0051	0.003	4.83	0.00027	1.15	0.00001
21-Nov-07	24												
28-Nov-07	25	0.000612	0.0091	1.23	0.0015	<0.01	0.0008	0.0149	<0.002	4.6	0.0003	1.49	<0.000005
5-Dec-07	26												
12-Dec-07	27	0.000103	0.0082	1.1	0.0012	<0.01	0.0006	0.0085	0.003	4.79	0.00021	1.11	<0.000005
19-Dec-07	28												
26-Dec-07	29	0.00114	0.0089	1.3	0.0009	<0.01	0.0006	0.005	<0.002	5.23	0.00013	1.13	<0.000005
2-Jan-08	30												
9-Jan-08	31	0.000019	0.0111	1.85	0.0008	<0.01	0.0008	0.0053	<0.002	6.44	0.0003	1.13	<0.000005
16-Jan-08	32												
23-Jan-08	33	0.000034	0.0087	1.86	0.0011	<0.01	0.0005	0.0061	<0.002	5.16	0.00014	1.02	<0.000005
30-Jan-08	34												
6-Feb-08	35	0.000054	0.0114	2.01	0.0014	0.03	0.0006	0.01	<0.002	6.55	0.00014	1.32	0.000007
13-Feb-08	36												
20-Feb-08	37	0.000255	0.0093	1.88	0.001	<0.01	0.0005	0.0053	<0.002	5.09	0.00015	1.02	<0.000005
27-Feb-08	38												
5-Mar-08	39	0.00003	0.0089	1.99	0.0009	<0.01	0.0005	0.0047	<0.002	4.79	0.00009	0.876	<0.000005
12-Mar-08	40												
19-Mar-08	41	0.0004	0.01	2.49	0.0008	<0.01	0.0005	0.0049	<0.002	6.67	0.00015	1.07	<0.000005
26-Mar-08	42												
2-Apr-08	43	#N/A	0.0099	2.31	0.0009	<0.01	0.0004	0.0061	0.004	5.16	0.00012	0.943	<0.000005
9-Apr-08	44												
16-Apr-08	45	0.000053	0.0112	2.83	0.0012	<0.01	0.0005	0.0068	<0.002	6.29	0.00012	1.19	<0.000005
23-Apr-08	46												
30-Apr-08	47	0.000401	0.0118	2.9	0.0009	0.01	0.0005	0.0056	<0.002	5.75	0.00015	1.13	<0.000005
7-May-08	48												
14-May-08	49	0.00473	0.0105	2.85	0.0011	<0.01	0.0004	0.0054	0.002	5.51	0.00012	1.12	<0.000005
21-May-08	50												
28-May-08	51	0.000024	0.0105	2.78	0.0009	<0.01	0.0005	0.0059	<0.002	5.25	0.00011	1.2	<0.000005
4-Jun-08	52												
11-Jun-08	53	0.000028	0.0114	3.14	0.0012	<0.01	0.0004	0.0072	<0.002	6.13	0.00013	1.52	<0.000005
18-Jun-08	54												
25-Jun-08	55	0.000017	0.013	3.14	0.001	<0.01	0.0004	0.0066	<0.002	5.51	0.00026	1.45	0.000011
2-Jul-08	56												
9-Jul-08	57	0.000132	0.0109	2.95	0.0011	<0.01	0.0006	0.0075	0.003	5.17	0.00014	1.38	<0.000005
16-Jul-08	58												
23-Jul-08	59	0.000018	0.0099	2.83	0.0009	<0.01	0.0004	0.0052	0.002	4.86	0.00018	0.967	<0.000005
30-Jul-08	60												
6-Aug-08	61	0.000855	0.0083	2.65	0.0009	<0.01	0.0004	0.0056	<0.002	4.24	0.00005	0.973	<0.000005
13-Aug-08	62												
20-Aug-08	63	0.000061	0.0088	2.65	0.0008	<0.01	0.0004	0.0049	<0.002	4.06	0.0001	0.883	<0.000005

Cell Terminated

April 2, 2008 Pb 0.010

HC 4

Sample = OB/LS/FS/A

Date	Cycle No.	Na mg/L	Sr mg/L	S mg/L	Tl mg/L	Sn mg/L	Ti mg/L	U mg/L	V mg/L	Zn mg/L	Zr mg/L	Major Anions	Major Cations	Diff	Diff (%)
12-Jun-07	1	72.5	0.0191	30.8	<0.00005	<0.00005	0.0087	0.00087	0.0116	0.0009	<0.005	3.10	3.55	0.45	6.8%
20-Jun-07	2														
27-Jun-07	3	104	0.0509	65.9	<0.00005	0.00007	0.0064	0.00184	0.0072	0.0039	<0.005	5.57	5.08	-0.49	-4.6%
4-Jul-07	4														
11-Jul-07	5	87.2	0.0509	55.5	<0.00005	0.0001	0.0131	0.00128	0.0068	0.0016	<0.005	4.47	4.37	-0.11	-1.2%
18-Jul-07	6														
25-Jul-07	7	51	0.02	25.9	<0.00005	0.00005	0.0092	0.00135	0.006	0.0018	<0.005	2.62	2.58	-0.04	-0.8%
1-Aug-07	8														
8-Aug-07	9	48.5	0.0188	23.8	<0.00005	0.00017	0.0039	0.00128	0.0061	0.0013	<0.005	2.34	2.42	0.08	1.7%
15-Aug-07	10														
22-Aug-07	11	41	0.0145	18.9	<0.00005	<0.00005	0.0022	0.00093	0.0043	0.0008	<0.005	1.81	2.06	0.24	6.3%
29-Aug-07	12														
5-Sep-07	13	34.9	0.0169	17.6	<0.00005	0.00006	0.0055	0.00086	0.0047	0.0009	<0.005	1.70	1.83	0.13	3.5%
12-Sep-07	14														
19-Sep-07	15	31.1	0.0148	13	<0.00005	<0.00005	0.0032	0.00097	0.0045	<0.0005	<0.005	1.59	1.63	0.04	1.2%
26-Sep-07	16														
3-Oct-07	17	26.7	0.0149	12.2	<0.00005	<0.00005	0.0019	0.00104	0.0042	0.002	<0.005	1.42	1.41	-0.01	-0.3%
10-Oct-07	18														
17-Oct-07	19	25.3	0.0129	10	0.000007	0.00012	0.0025	0.00093	0.0041	0.0011	0.0002	1.17	1.36	0.19	7.4%
24-Oct-07	20														
31-Oct-07	21	20	0.015	7	0.000009	0.00003	0.0015	0.00093	0.0028	0.0014	<0.0001	0.99	1.15	0.16	7.6%
7-Nov-07	22														
14-Nov-07	23	18	0.016	10	0.000005	0.00006	0.0016	0.00092	0.0025	0.0006	0.0002	1.00	1.08	0.08	3.6%
21-Nov-07	24														
28-Nov-07	25	15.6	0.0206	7	0.000011	0.00002	0.0037	0.00097	0.0025	0.0002	0.0002	1.08	1.02	-0.06	-3.0%
5-Dec-07	26														
12-Dec-07	27	10.1	0.0213	7	0.000008	0.00002	0.003	0.00082	0.0019	0.0004	0.0001	0.84	0.78	-0.06	-3.6%
19-Dec-07	28														
26-Dec-07	29	11.6	0.0248	8	0.000013	0.00001	0.0007	0.00071	0.0018	0.004	<0.0001	0.91	0.88	-0.02	-1.3%
2-Jan-08	30														
9-Jan-08	31	10.7	0.0327	9	0.000013	<0.00001	<0.0005	0.00097	0.0015	0.0003	<0.0001	1.03	0.99	-0.03	-1.7%
16-Jan-08	32														
23-Jan-08	33	6.96	0.0294	6	0.000011	<0.00001	0.0009	0.00056	0.0013	0.0013	<0.0001	0.76	0.76	0.00	-0.2%
30-Jan-08	34														
6-Feb-08	35	7.48	0.0356	7	0.000015	<0.00001	0.0019	0.00057	0.0015	0.0009	<0.0001	0.88	0.87	-0.01	-0.8%
13-Feb-08	36														
20-Feb-08	37	5.4	0.0296	6	0.000011	<0.00001	0.0009	0.00046	0.0013	0.001	<0.0001	0.66	0.70	0.05	3.5%
27-Feb-08	38														
5-Mar-08	39	3.71	0.0311	6	0.000011	<0.00001	0.0007	0.00037	0.0011	0.0005	<0.0001	0.60	0.65	0.05	3.9%
12-Mar-08	40														
19-Mar-08	41	3.31	0.0375	6	0.000013	<0.00001	0.0013	0.00046	0.0008	0.0007	<0.0001	0.72	0.74	0.03	1.8%
26-Mar-08	42														
2-Apr-08	43	2.27	0.0365	5	0.000014	<0.00001	0.0019	0.00049	0.0011	0.0027	<0.0001	0.62	0.64	0.02	1.7%
9-Apr-08	44														
16-Apr-08	45	2.5	0.045	6	0.000017	<0.00001	0.0007	0.00047	0.0011	0.0009	<0.0001	0.76	0.79	0.02	1.6%
23-Apr-08	46														
30-Apr-08	47	1.89	0.0457	5	0.000018	<0.00001	0.0006	0.00053	0.0012	0.0006	<0.0001	0.70	0.74	0.04	2.8%
7-May-08	48														
14-May-08	49	1.75	0.0422	6	0.000016	<0.00001	0.0006	0.00059	0.0012	0.0004	<0.0001	0.57	0.71	0.14	10.8%
21-May-08	50														
28-May-08	51	1.27	0.0424	4	0.000014	<0.00001	0.0005	0.00074	0.0011	0.0004	<0.0001	0.68	0.66	-0.02	-1.3%
4-Jun-08	52														
11-Jun-08	53	1.38	0.0493	4	0.000018	<0.00001	0.001	0.0008	0.001	0.0007	<0.0001	0.75	0.77	0.02	1.3%
18-Jun-08	54														
25-Jun-08	55	1	0.0461	4	0.000017	<0.00001	0.0008	0.00079	0.0013	0.0011	<0.0001	0.75	0.73	-0.02	-1.6%
2-Jul-08	56														
9-Jul-08	57	1	0.0522	5	0.000017	0.00001	0.0014	0.00066	0.001	0.0029	<0.0001	0.78	0.72	-0.06	-3.8%
16-Jul-08	58														
23-Jul-08	59	0.7	0.046	5	0.000016	<0.00001	0.0006	0.00057	0.0009	0.0006	<0.0001	0.63	0.68	0.05	3.7%
30-Jul-08	60														
6-Aug-08	61	0.6	0.0404	4	0.000017	<0.00001	<0.0005	0.00048	0.0008	0.0003	<0.0001	0.67	0.61	-0.06	-4.5%
13-Aug-08	62														
20-Aug-08	63	0.6	0.04	5	0.000019	<0.00001	<0.0005	0.00045	0.0007	0.0004	<0.0001	0.50	0.60	0.09	8.2%

Cell Terminated

April 2, 2008 Pb 0.010

**HUMIDITY CELL HC-1
CALCULATED LOADING RATES**

2.8-68

(mg/kg/wk)

MINAGO PROJECT

Date	Cycle No.	Volume		pH	ORP mV	Cond. umhos/cm	Acidity (pH 4.5) mgCaCO3/L	Acidity (pH 8.3) mg/kg/wk	Alkalinity mg/kg/wk	Sulphate	Hardness
		Input mL	Output L							mg/kg/wk	CaCO3 mg/L
12-Jun-07	1	750	0.52	7.72	374	611	#N/A	1.2	21.1	136	88.3
20-Jun-07	2	500	0.41	7.62	364	832	#N/A	1.1	12.2	138	
27-Jun-07	3	500	0.43	7.63	380	647	#N/A	1.0	12.2	108	72.3
4-Jul-07	4	500	0.48	7.88	358	463	#N/A	1.1	18.2	77	
11-Jul-07	5	500	0.42	7.77	359	405	#N/A	1.2	14.9	67	30.4
18-Jul-07	6	500	0.43	7.93	366	430	#N/A	1.0	19.6	78	
25-Jul-07	7	500	0.46	8.09	370	302	#N/A	1.1	22.0	44	14.5
1-Aug-07	8	500	0.47	7.82	366	266	#N/A	1.1	21.7	20	
8-Aug-07	9	500	0.47	8.08	317	230	#N/A	0.5	19.7	23	8.8
15-Aug-07	10	500	0.46	8.35	366	24	#N/A	1.1	18.9	25	
22-Aug-07	11	500	0.44	8.51	356	179	#N/A	1.4	16.6	24	10.3
29-Aug-07	12	500	0.44	8.38	364	157	#N/A	1.6	14.6	18	
5-Sep-07	13	500	0.44	8.52	362	150	#N/A	1.0	15.0	20	10.6
12-Sep-07	14	500	0.44	8.40	369	129	#N/A	1.4	16.7	17	
19-Sep-07	15	500	0.46	8.53	361	118	#N/A	1.4	17.6	20	8.8
26-Sep-07	16	500	0.45	8.52	375	174	#N/A	1.4	12.6	13	
3-Oct-07	17	500	0.46	8.26	377	161	#N/A	1.8	14.4	16	8.9
10-Oct-07	18	500	0.48	8.45	388	150	#N/A	1.3	14.4	14	
17-Oct-07	19	500	0.44	7.57	412	147	#N/A	1.2	9.8	9	7.8
24-Oct-07	20	500	0.47	8.26	405	120	#N/A	1.1	13.3	11	
31-Oct-07	21	500	0.45	7.71	401	121	#N/A	1.6	15.2	10	16.3
7-Nov-07	22	500	0.47	7.62	423	124	#N/A	1.3	12.8	10	
14-Nov-07	23	500	0.46	7.62	424	131	#N/A	1.3	14.5	12	13.2
21-Nov-07	24	500	0.48	7.43	476	99	#N/A	1.5	11.2	10	
28-Nov-07	25	500	0.47	7.43	424	84	#N/A	1.5	11.4	6	9.9
5-Dec-07	26	500	0.47	7.57	449	89	#N/A	1.4	12.3	8	
12-Dec-07	27	500	0.49	7.68	396	79	#N/A	1.1	10.7	7	11.7
19-Dec-07	28	500	0.47	7.55	458	78	#N/A	1.1	10.4	6	
26-Dec-07	29	500	0.47	7.56	398	80	#N/A	0.9	10.2	8	13.3
2-Jan-08	30	500	0.47	7.44	458	72	#N/A	1.1	8.3	7	
9-Jan-08	31	500	0.50	7.48	399	82	#N/A			7	17
16-Jan-08	32	500	0.47	7.30	481	79	#N/A	1.7	9.7	7	
23-Jan-08	33	500	0.48	7.36	403	76	#N/A	1.7	10.0	6	15.5
30-Jan-08	34	500	0.45	7.32	434	86	#N/A	1.9	10.3	8	
6-Feb-08	35	500	0.44	7.41	459	73	#N/A	1.3	8.9	7	16.8
13-Feb-08	36	500	0.45	7.33	448	71	#N/A	1.9	8.1	8	
20-Feb-08	37	500	0.46	7.52	443	73	#N/A	1.5	8.2	5	17.9
27-Feb-08	38	500	0.45	7.41	429	73	#N/A	1.7	8.1	6	
5-Mar-08	39	500	0.45	7.50	423	85	#N/A	1.7	10.0	9	22
12-Mar-08	40	500	0.46	7.46	431	114	#N/A	1.5	13.7	10	
19-Mar-08	41	500	0.47	7.61	426	101	#N/A	1.5	15.2	7	26.7
26-Mar-08	42	500	0.47	7.55	423	114	#N/A	3.6	41.4	8	
2-Apr-08	43	500	0.42	7.71	430	101	#N/A	2.6	39.2	5	32
9-Apr-08	44	500	0.42	7.59	424	117	#N/A	2.8	39.3	7	
16-Apr-08	45	500	0.41	7.57	422	106	#N/A	3.1	35.2	6	29.7
23-Apr-08	46	500	0.40	7.61	434	116	#N/A	3.3	39.9	6	
30-Apr-08	47	500	0.40	7.71	417	121	#N/A	2.4	40.2	6	37.2
7-May-08	48	500	0.40	7.70	398	120	#N/A	3.0	39.7	6	
14-May-08	49	500	0.42	7.75	382	111	#N/A	2.8	39.2	4	37.6
21-May-08	50	500	0.40	7.57	378	86	#N/A	3.1	29.1	3	
28-May-08	51	500	0.46	7.64	395	83	#N/A	3.2	34.4	4	30
4-Jun-08	52	500	0.46	8.17	370	49	#N/A	2.8	23.3	3	
11-Jun-08	53	500	0.46	7.60	419	60	#N/A	3.0	27.3	4	25.7
18-Jun-08	54	500	0.475	7.47	389	57	#N/A	3.7	29.2	4	
25-Jun-08	55	500	0.465	7.51	393	71	#N/A	4.4	29.5	3	26.3
2-Jul-08	56	500	0.455	7.5	397	67	#N/A	2.6	22.7	4	
9-Jul-08	57	500	0.47	7.62	388	85	#N/A	2.5	28.5	6	31.8
16-Jul-08	58	500	0.475	7.39	402	59	#N/A	2.9	21.9	4	
23-Jul-08	59	500	0.465	7.45	419	68	#N/A	2.9	25.2	4	26.4
30-Jul-08	60	500	0.48	7.54	403	71	#N/A	2.3	29.6	4	
6-Aug-08	61	500	0.485	7.61	394	81	#N/A	2.7	32.6	4	31.4
13-Aug-08	62	500	0.47	7.52	369	71	#N/A	2.6	25.8	2	
20-Aug-08	63	500	0.47	7.52	324	70	#N/A	2.5	27.0	4	29

HUMIDITY CELL HC-1
CALCULATED LOADING RATES
(mg/kg/wk)

2.8-69

MINAGO PROJECT

Date	Cycle No.	Al	Sb	As	Ba	Be	Bi	B	Cd	Ca	Cr	Co	Cu
		mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk
12-Jun-07	1	0.090	0.0001	0.0003	0.007	0.00003	0.00003	0.235	0.000026	10.816	0.00026	0.002	0.001
20-Jun-07	2	0.0546						0.2032		9.6155	0.000173	0.00112	0.0012
27-Jun-07	3	0.019	0.0000	0.0003	0.004	0.00002	0.00002	0.171	0.000017	8.415	0.00009	0.000	0.002
4-Jul-07	4	0.0319						0.1697		5.8903	0.000188	0.00034	0.001
11-Jul-07	5	0.045	0.0001	0.0002	0.002	0.00002	0.00002	0.168	0.000012	3.366	0.00029	0.00019	0.000
18-Jul-07	6	0.0484						0.1855		2.5062	0.00026	0.00015	0.0006
25-Jul-07	7	0.052	0.0001	0.0002	0.001	0.00002	0.00002	0.203	0.000014	1.647	0.00023	0.00011	0.001
1-Aug-07	8	0.0331						0.1805		1.3326	0.000185	0.00008	0.0008
8-Aug-07	9	0.015	0.0001	0.0006	0.001	0.00002	0.00002	0.158	0.000009	1.018	0.00014	0.00004	0.001
15-Aug-07	10	0.0236						0.1497		1.0529	0.000266	0.00008	0.0006
22-Aug-07	11	0.032	0.0001	0.0003	0.001	0.00002	0.00002	0.141	0.000004	1.088	0.00039	0.00011	0.00026
29-Aug-07	12	0.0489						0.1371		1.1092	0.000432	0.00011	0.0004
5-Sep-07	13	0.065	0.0001	0.0003	0.001	0.00002	0.00002	0.133	0.000013	1.131	0.00047	0.00011	0.001
12-Sep-07	14	0.0447						0.1323		1.0416	0.000281	0.00009	0.0003
19-Sep-07	15	0.024	0.0001	0.0003	0.001	0.00002	0.00002	0.132	0.000004	0.952	0.00009	0.00007	0.000
26-Sep-07	16	0.0219						0.1068		0.9845	0.000114	0.00007	0.0002
3-Oct-07	17	0.020	0.0001	0.0002	0.001	0.00002	0.00002	0.082	0.000005	1.017	0.00014	0.00007	0.00032
10-Oct-07	18	0.0215						0.07		0.9469	0.000155	0.00006	0.0004
17-Oct-07	19	0.023	0.0000	0.0004	0.001	0.00000	0.00000	0.058	0.000007	0.877	0.00017	0.00005	0.00048
24-Oct-07	20	0.0159						0.0577		1.3622	0.00011	0.00004	0.0004
31-Oct-07	21	0.008	0.0003	0.0007	0.001	0.00000	0.00000	0.057	0.000002	1.847	0.00005	0.00003	0.00004
7-Nov-07	22	0.0076						0.0657		1.7217	4.65E-05	0.00004	0.0007
14-Nov-07	23	0.007	0.0001	0.0002	0.002	0.00000	0.00000	0.074	0.000002	1.596	0.00005	0.00006	0.00138
21-Nov-07	24	0.0126						0.058		1.3817	0.000116	0.00007	0.001
28-Nov-07	25	0.018	0.0000	0.0001	0.001	0.00000	0.00000	0.042	0.000002	1.167	0.00019	0.00008	0.001
5-Dec-07	26	0.0198						0.0386		1.348	0.000191	0.00007	0.0004
12-Dec-07	27	0.021	0.0000	0.0001	0.002	0.00000	0.00000	0.035	0.000002	1.529	0.00020	0.00006	0.000
19-Dec-07	28	0.0145						0.0348		1.5596	0.000145	0.00006	0.0003
26-Dec-07	29	0.008	0.0000	0.0001	0.002	0.00000	0.00000	0.034	0.000013	1.590	0.00009	0.00006	0.000
2-Jan-08	30	0.007						0.037		1.9152	0.00007	0.00006	0.0002
9-Jan-08	31	0.006	0.0000	0.0001	0.002	0.00001	0.00000	0.040	0.000003	2.240	0.00005	0.00007	0.000
16-Jan-08	32	0.007						0.0327		2.0728	0.000049	0.00006	0.0002
23-Jan-08	33	0.008	0.0000	0.0001	0.002	0.00000	0.00000	0.026	0.000002	1.906	0.00005	0.00006	0.000
30-Jan-08	34	0.0107						0.0264		1.9252	0.00009	0.00007	0.0006
6-Feb-08	35	0.014	0.0000	0.0001	0.002	0.00000	0.00000	0.027	0.000002	1.945	0.00013	0.00007	0.001
13-Feb-08	36	0.011						0.03		2.003	8.88E-05	0.00008	0.0005
20-Feb-08	37	0.008	0.0000	0.0001	0.002	0.00000	0.00000	0.033	0.000002	2.061	0.00005	0.00010	0.000
27-Feb-08	38	0.0083						0.0333		2.3176	6.78E-05	0.00008	0.0003
5-Mar-08	39	0.008	0.0000	0.0001	0.002	0.00000	0.00000	0.033	0.000002	2.574	0.00009	0.00006	0.000
12-Mar-08	40	0.0073						0.0413		2.8308	0.00007	0.00006	0.0003
19-Mar-08	41	0.006	0.0000	0.0002	0.003	0.00000	0.00000	0.049	0.000003	3.088	0.00005	0.00006	0.000
26-Mar-08	42	0.0103						0.0481		3.1748	0.00009	0.00006	0.0003
2-Apr-08	43	0.014	0.0000	0.0001	0.003	0.00000	0.00000	0.047	0.000002	3.262	0.00012	0.00006	0.000
9-Apr-08	44	0.0112						0.0502		3.1396	0.000103	0.00007	0.0003
16-Apr-08	45	0.008	0.0000	0.0001	0.003	0.00000	0.00000	0.053	0.000003	3.017	0.00008	0.00008	0.000
23-Apr-08	46	0.0075						0.0503		3.3346	0.00008	0.00007	0.0003
30-Apr-08	47	0.007	0.0001	0.0001	0.004	0.00000	0.00000	0.047	0.000002	3.652	0.00008	0.00006	0.000
7-May-08	48	0.007						0.0458		3.6603	0.00008	0.00006	0.0003
14-May-08	49	0.007	0.0000	0.0001	0.004	0.00000	0.00000	0.044	0.000002	3.669	0.00008	0.00006	0.000
21-May-08	50	0.0077						0.0392		3.4811	0.00006	0.00006	0.0006
28-May-08	51	0.008	0.0000	0.0001	0.003	0.00000	0.00000	0.034	0.000002	3.294	0.00005	0.00005	0.001
4-Jun-08	52	0.0083						0.0285		3.1303	0.000069	0.00006	0.0011
11-Jun-08	53	0.008	0.0001	0.0001	0.003	0.00000	0.00000	0.023	0.000009	2.967	0.00009	0.00007	0.001
18-Jun-08	54	0.0073						0.0234		2.9669	0.000116	0.00006	0.0008
25-Jun-08	55	0.006	0.0000	0.0001	0.003	0.00000	0.00000	0.024	0.000002	2.967	0.00014	0.00005	0.000
2-Jul-08	56	0.0091						0.026		3.4174	0.000117	0.00005	0.0006
9-Jul-08	57	0.012	0.0000	0.0001	0.003	0.00000	0.00000	0.028	0.000002	3.868	0.00009	0.00006	0.001
16-Jul-08	58	0.01						0.0257		3.5034	0.00009	0.00006	0.0006
23-Jul-08	59	0.008	0.0000	0.0001	0.003	0.00000	0.00000	0.023	0.000002	3.139	0.00009	0.00005	0.000
30-Jul-08	60	0.0067						0.0238		3.4633	0.00007	0.00005	0.0003
6-Aug-08	61	0.005	0.0000	0.0001	0.003	0.00000	0.00002	0.024	0.000007	3.788	0.00005	0.00006	0.000
13-Aug-08	62	0.0053						0.0239		3.5648	0.00005	0.00005	0.0002
20-Aug-08	63	0.006	0.0000	0.0001	0.003	0.00000	0.00000	0.024	0.000006	3.342	0.00005	0.00005	0.000

**HUMIDITY CELL HC-1
CALCULATED LOADING RATES**

2.8-70

(mg/kg/wk)

MINAGO PROJECT

Date	Cycle No.	Fe	Pb	Li	Mg	Mn	Hg	Mo	Ni	P	K	Se	Si	Ag
		mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk
12-Jun-07	1	0.037	0.00002	0.030	4.602	0.0016	0.026	0.011	0.120	0.052	6.968	0.005	0.775	0.000005
20-Jun-07	2	0.02233		0.0255	3.4804			0.01144	0.0658			0.0044		
27-Jun-07	3	0.007	0.00002	0.021	2.359	0.0008	0.021	0.012	0.012	0.043	3.587	0.004	0.455	0.000004
4-Jul-07	4	0.02187		0.018	1.6898			0.01041	0.0081			0.0034		
11-Jul-07	5	0.037	0.00007	0.015	1.021	0.0004	0.021	0.009	0.004	0.042	3.586	0.003	0.610	0.000004
18-Jul-07	6	0.02378		0.0151	0.8187			0.00755	0.0037			0.0025		
25-Jul-07	7	0.011	0.00001	0.015	0.616	0.0002	0.023	0.006	0.003	0.046	3.330	0.002	0.672	0.000005
1-Aug-07	8	0.00785		0.0136	0.4942			0.00517	0.0021			0.0017		
8-Aug-07	9	0.005	0.00002	0.012	0.372	0.0002	0.023	0.004	0.001	0.047	2.962	0.001	0.581	0.000005
15-Aug-07	10	0.01342		0.0109	0.3992			0.00337	0.0018			0.0013		
22-Aug-07	11	0.022	0.00006	0.009	0.426	0.0002	0.022	0.003	0.002	0.044	2.410	0.001	0.622	0.000009
29-Aug-07	12	0.02507		0.0109	0.4217			0.00272	0.0023			0.0011		
5-Sep-07	13	0.028	0.00006	0.012	0.417	0.0003	0.022	0.003	0.002	0.043	2.937	0.001	0.572	0.000004
12-Sep-07	14	0.01687		0.0123	0.3932			0.00231	0.002			0.0008		
19-Sep-07	15	0.006	0.00273	0.012	0.369	0.0002	0.022	0.002	0.002	0.045	3.271	0.001	0.565	0.000004
26-Sep-07	16	0.00933		0.0116	0.371			0.00164	0.0016			0.0006		
3-Oct-07	17	0.013	0.00001	0.011	0.373	0.0002	0.023	0.001	0.002	0.046	2.783	0.001	0.483	0.000005
10-Oct-07	18	0.00988		0.0095	0.3261			0.00107	0.0013			0.0004		
17-Oct-07	19	0.007	0.00013	0.008	0.280	0.0002	0.022	0.001	0.001	0.000	2.490	0.0003	0.396	0.000002
24-Oct-07	20	0.00462		0.0087	0.5087			0.00093	0.001			0.0003		
31-Oct-07	21	0.002	0.00000	0.009	0.738	0.0001	0.005	0.001	0.001	0.001	3.196	0.0003	0.470	0.000002
7-Nov-07	22	0.00233		0.0113	0.6266			0.001	0.0012			0.0003		
14-Nov-07	23	0.002	0.00001	0.013	0.515	0.0002	0.005	0.001	0.001	0.001	3.616	0.0003	0.445	0.000002
21-Nov-07	24	0.00603		0.0112	0.4645			0.00072	0.0016			0.0003		
28-Nov-07	25	0.010	0.00002	0.009	0.414	0.0002	0.005	0.001	0.002	0.001	2.837	0.0002	0.586	0.000002
5-Dec-07	26	0.00807		0.009	0.4372			0.0005	0.0017			0.0002		
12-Dec-07	27	0.006	0.00010	0.009	0.461	0.0002	0.005	0.000	0.002	0.001	3.009	0.0002	0.375	0.000002
19-Dec-07	28	0.00481		0.0086	0.4977			0.00046	0.0016			0.0002		
26-Dec-07	29	0.003	0.00674	0.008	0.535	0.0002	0.005	0.000	0.002	0.001	2.878	0.0002	0.339	0.000026
2-Jan-08	30	0.00263		0.0092	0.6199			0.00051	0.0018			0.0002		
9-Jan-08	31	0.002	0.00000	0.010	0.705	0.0002	0.005	0.001	0.002	0.001	3.315	0.0003	0.370	0.000003
16-Jan-08	32	0.00244		0.0094	0.6813			0.0005	0.0018			0.0002		
23-Jan-08	33	0.003	0.00072	0.009	0.658	0.0002	0.005	0.000	0.002	0.001	2.722	0.0001	0.332	0.000002
30-Jan-08	34	0.00452		0.0084	0.639			0.00041	0.0018			0.0001		
6-Feb-08	35	0.006	0.00374	0.008	0.620	0.0003	0.009	0.000	0.002	0.001	2.807	0.0001	0.337	0.000003
13-Feb-08	36	0.00422		0.0083	0.6765			0.0002	0.0036			0.0001		
20-Feb-08	37	0.002	0.00000	0.009	0.733	0.0004	0.005	0.000	0.005	0.001	2.839	0.0001	0.348	0.000002
27-Feb-08	38	0.00249		0.0092	0.7915			0.00027	0.0034			0.0001		
5-Mar-08	39	0.003	0.00015	0.010	0.851	0.0003	0.005	0.001	0.001	0.001	3.200	0.0001	0.364	0.000002
12-Mar-08	40	0.00205		0.0113	0.9972			0.00054	0.0015			0.0001		
19-Mar-08	41	0.001	0.00001	0.013	1.144	0.0003	0.005	0.001	0.002	0.001	3.887	0.0001	0.660	0.000002
26-Mar-08	42	0.00215		0.0134	1.1965			0.00052	0.0017			0.0001		
2-Apr-08	43	0.003	0.00001	0.014	1.249	0.0003	0.004	0.000	0.002	0.001	4.524	0.0001	0.564	0.000002
9-Apr-08	44	0.00267		0.0135	1.1713			0.00047	0.0017			0.0001		
16-Apr-08	45	0.002	0.00007	0.013	1.094	0.0002	0.004	0.000	0.001	0.001	4.536	0.0002	0.612	0.000002
23-Apr-08	46	0.00262		0.0138	1.2468			0.00047	0.0015			0.0001		
30-Apr-08	47	0.003	0.00000	0.015	1.400	0.0002	0.004	0.000	0.002	0.001	4.680	0.0001	0.620	0.000003
7-May-08	48	0.00223		0.0137	1.4802			0.00042	0.0017			0.0001		
14-May-08	49	0.002	0.00000	0.013	1.560	0.0002	0.004	0.000	0.002	0.001	4.482	0.0001	0.627	0.000002
21-May-08	50	0.00175		0.0122	1.4587			0.00034	0.0016			0.0002		
28-May-08	51	0.002	0.00001	0.011	1.357	0.0002	0.005	0.000	0.001	0.001	3.790	0.0002	0.534	0.000002
4-Jun-08	52	0.00276		0.0094	1.2167			0.00028	0.0017			0.0002		
11-Jun-08	53	0.004	0.00879	0.007	1.076	0.0003	0.005	0.000	0.002	0.001	2.870	0.0001	0.436	0.000002
18-Jun-08	54	0.00277		0.0078	1.1241			0.00024	0.0016			0.0002		
25-Jun-08	55	0.002	0.00001	0.008	1.172	0.0002	0.005	0.000	0.001	0.001	2.627	0.000	0.470	0.000006
2-Jul-08	56	0.00446		0.0087	1.2275			0.00028	0.0015			0.0002		
9-Jul-08	57	0.007	0.00004	0.009	1.283	0.0003	0.005	0.000	0.002	0.001	2.952	0.0002	0.498	0.000006
16-Jul-08	58	0.00492		0.0081	1.181			0.00027	0.0015			0.0002		
23-Jul-08	59	0.003	0.00001	0.007	1.079	0.0002	0.005	0.000	0.001	0.001	2.367	0.000	0.345	0.000002
30-Jul-08	60	0.00212		0.008	1.2427			0.00027	0.0015			0.0001		
6-Aug-08	61	0.001	0.00004	0.009	1.407	0.0002	0.005	0.000	0.001	0.001	2.832	0.0001	0.500	0.000002
13-Aug-08	62	0.0012		0.0084	1.3472			0.00028	0.0013			0.0001		
20-Aug-08	63	0.001	0.00002	0.008	1.288	0.0001	0.005	0.000	0.001	0.001	2.524	0.0001	0.421	0.000002

HUMIDITY CELL HC-1
CALCULATED LOADING RATES
(mg/kg/wk)
MINAGO PROJECT

2.8-71

Date	Cycle No.	Na mg/kg/wk	Sr mg/kg/wk	S mg/kg/wk	Tl mg/kg/wk	Sn mg/kg/wk	Ti mg/kg/wk	U mg/kg/wk	V mg/kg/wk	Zn mg/kg/wk	Zr mg/kg/wk
12-Jun-07	1	56.160	0.171	50.856	0.00004	0.00003	0.0033	0.0011	0.0010	0.0003	0.00260
20-Jun-07	2		0.1487								
27-Jun-07	3	41.948	0.126	35.403	0.00002	0.00002	0.0006	0.0006	0.0009	0.0008	0.00213
4-Jul-07	4		0.0893								
11-Jul-07	5	27.639	0.052	19.879	0.00002	0.00015	0.0012	0.0005	0.0015	0.0008	0.00208
18-Jul-07	6		0.0383								
25-Jul-07	7	26.404	0.024	13.938	0.00002	0.00002	0.0006	0.0007	0.0022	0.0003	0.00230
1-Aug-07	8		0.0201								
8-Aug-07	9	18.693	0.016	9.021	0.00002	0.00002	0.0002	0.0004	0.0020	0.0005	0.00233
15-Aug-07	10		0.0154								
22-Aug-07	11	17.618	0.015	8.744	0.00002	0.00002	0.0006	0.0004	0.0014	0.0002	0.00218
29-Aug-07	12		0.016								
5-Sep-07	13	16.254	0.017	8.815	0.00002	0.00003	0.0025	0.0003	0.0014	0.0006	0.00215
12-Sep-07	14		0.0161								
19-Sep-07	15	15.130	0.015	6.853	0.00002	0.00003	0.0002	0.0002	0.0009	0.0002	0.00223
26-Sep-07	16		0.0156								
3-Oct-07	17	10.258	0.016	5.382	0.00002	0.00002	0.0003	0.0003	0.0012	0.0002	0.00230
10-Oct-07	18		0.0138								
17-Oct-07	19	6.622	0.011	3.010	0.00001	0.00001	0.0002	0.0001	0.0009	0.0006	0.00004
24-Oct-07	20		0.0147								
31-Oct-07	21	7.050	0.018	4.230	0.00001	0.00001	0.0002	0.0001	0.0007	0.0003	0.00005
7-Nov-07	22		0.0204								
14-Nov-07	23	7.912	0.023	4.600	0.00001	0.00001	0.0002	0.0002	0.0009	0.0003	0.00005
21-Nov-07	24		0.0202								
28-Nov-07	25	4.315	0.018	1.860	0.00001	0.00001	0.0002	0.0001	0.0008	0.0002	0.00005
5-Dec-07	26		0.0195								
12-Dec-07	27	3.278	0.021	2.940	0.00001	0.00001	0.0003	0.0001	0.0006	0.0004	0.00005
19-Dec-07	28		0.0217								
26-Dec-07	29	3.320	0.022	2.325	0.00001	0.00000	0.0002	0.0001	0.0005	0.0004	0.00005
2-Jan-08	30		0.0253								
9-Jan-08	31	3.325	0.028	3.500	0.00001	0.00001	0.0003	0.0002	0.0004	0.0002	0.00005
16-Jan-08	32		0.0273								
23-Jan-08	33	2.275	0.026	2.400	0.00001	0.00000	0.0002	0.0001	0.0003	0.0003	0.00005
30-Jan-08	34		0.0262								
6-Feb-08	35	2.178	0.026	2.640	0.00001	0.00000	0.0002	0.0001	0.0004	0.0005	0.00004
13-Feb-08	36		0.0273								
20-Feb-08	37	2.298	0.028	3.185	0.00001	0.00000	0.0003	0.0001	0.0003	0.0003	0.00005
27-Feb-08	38		0.0315								
5-Mar-08	39	1.967	0.035	3.150	0.00001	0.00000	0.0002	0.0001	0.0003	0.0002	0.00005
12-Mar-08	40		0.0392								
19-Mar-08	41	2.255	0.044	2.790	0.00001	0.00000	0.0002	0.0003	0.0006	0.0002	0.00005
26-Mar-08	42		0.0439								
2-Apr-08	43	1.963	0.044	2.490	0.00001	0.00000	0.0005	0.0002	0.0006	0.0003	0.00004
9-Apr-08	44		0.0429								
16-Apr-08	45	1.567	0.042	2.430	0.00002	0.00000	0.0002	0.0002	0.0006	0.0007	0.00004
23-Apr-08	46		0.0477								
30-Apr-08	47	1.140	0.054	2.400	0.00002	0.00000	0.0002	0.0003	0.0007	0.0001	0.00004
7-May-08	48		0.0532								
14-May-08	49	0.768	0.053	2.075	0.00002	0.00000	0.0002	0.0002	0.0007	0.0002	0.00004
21-May-08	50		0.0505								
28-May-08	51	0.511	0.048	1.380	0.00001	0.00000	0.0002	0.0002	0.0005	0.0001	0.00005
4-Jun-08	52		0.0431								
11-Jun-08	53	0.331	0.038	1.380	0.00001	0.00000	0.0002	0.0001	0.0001	0.0010	0.00005
18-Jun-08	54		0.0386								
25-Jun-08	55	0.260	0.039	1.395	0.00001	0.00000	0.0002	0.0002	0.0004	0.0003	0.00005
2-Jul-08	56		0.0446								
9-Jul-08	57	0.249	0.050	1.880	0.00001	0.00000	0.0002	0.0002	0.0005	0.0013	0.00005
16-Jul-08	58		0.0446								
23-Jul-08	59	0.200	0.039	1.395	0.00001	0.00000	0.0002	0.0001	0.0004	0.0002	0.00005
30-Jul-08	60		0.0444								
6-Aug-08	61	0.209	0.049	1.455	0.00001	0.00000	0.0002	0.0002	0.0004	0.0003	0.00005
13-Aug-08	62		0.0465								
20-Aug-08	63	0.174	0.044	1.880	0.00001	0.00000	0.0002	0.0002	0.0003	0.0001	0.00005

HUMIDITY CELL HC-2
CALCULATED LOADING RATES
(mg/kg/wk)

2.8-72

MINAGO PROJECT

HC 2

Sample = ORE/AR Composite

Date	Cycle No.	Volume		pH	ORP mV	Cond. umhos/cm	Acidity (pH 4.5) mgCaCO3/L	Acidity (pH 8.3) mg/kg/wk	Alkalinity mg/kg/wk	Sulphate	Hardness	Al
		Input mL	Output L							mg/kg/wk	CaCO3 mg/L	mg/kg/wk
12-Jun-07	1	750	0.605	9.22	275	323	#N/A	0.0	43.2	48	5.7	0.174
20-Jun-07	2	500	0.395	8.91	296	536	#N/A	0.0	31.1	34		0.1806
27-Jun-07	3	500	0.415	8.72	330	462	#N/A	0.0	25.3	79	8.8	0.188
4-Jul-07	4	500	0.475	8.34	327	379	#N/A	0.0	21.8	61		0.2017
11-Jul-07	5	500	0.415	8.59	323	483	#N/A	0.0	22.3	78	13.3	0.216
18-Jul-07	6	500	0.435	8.54	333	501	#N/A	0.0	27.0	69		0.1561
25-Jul-07	7	500	0.45	8.49	349	264	#N/A	0.0	17.8	39	6.3	0.096
1-Aug-07	8	500	0.45	8.14	345	252	#N/A	0.8	17.1	22		0.1011
8-Aug-07	9	500	0.46	8.35	302	232	#N/A	0.0	16.9	32	5.6	0.106
15-Aug-07	10	500	0.435	8.42	355	24	#N/A	0.0	16.2	20		0.0735
22-Aug-07	11	500	0.43	8.43	354	176	#N/A	0.2	16.0	16	4.9	0.041
29-Aug-07	12	500	0.445	8.52	345	149	#N/A	0.0	15.4	17		0.0824
5-Sep-07	13	500	0.435	8.24	366	135	#N/A	0.4	13.7	18	3.9	0.124
12-Sep-07	14	500	0.495	8.15	377	108	#N/A	1.1	17.2	17		0.0807
19-Sep-07	15	500	0.45	8.26	352	103	#N/A	0.0	14.1	15	3.9	0.038
26-Sep-07	16	500	0.44	8.30	384	149	#N/A	0.0	12.9	12		0.0449
3-Oct-07	17	500	0.44	8.13	378	137	#N/A	1.0	12.8	12	4.5	0.052
10-Oct-07	18	500	0.465	8.22	396	123	#N/A	0.5	13.0	10		0.0704
17-Oct-07	19	500	0.415	7.57	403	118	#N/A	1.1	11.0	9	3.9	0.089
24-Oct-07	20	500	0.46	8.15	402	113	#N/A	0.7	14.4	11		0.0591
31-Oct-07	21	500	0.45	7.71	383	105	#N/A	1.4	10.5	8	3.1	0.029
7-Nov-07	22	500	0.46	7.90	399	99	#N/A	0.9	12.9	6		0.0287
14-Nov-07	23	500	0.45	7.81	410	99	#N/A	1.1	12.4	7	3.5	0.028
21-Nov-07	24	500	0.435	7.79	455	96	#N/A	1.1	10.3	9		0.0325
28-Nov-07	25	500	0.48	7.75	413	103	#N/A	1.4	14.2	8	3.6	0.037
5-Dec-07	26	500	0.46	7.72	436	84	#N/A	1.3	11.0	6		0.0296
12-Dec-07	27	500	0.515	7.76	404	84	#N/A	1.1	13.8	6	3.4	0.022
19-Dec-07	28	500	0.455	7.71	443	79	#N/A	0.8	10.9	5		0.0151
26-Dec-07	29	500	0.51	7.71	396	77	#N/A	0.9	12.3	10	3.4	0.008
2-Jan-08	30	500	0.465	7.72	440	71	#N/A	0.9	9.8	5		0.0085
9-Jan-08	31	500	0.51	7.61	410	76	#N/A	1.2	13.3	8	4.3	0.009
16-Jan-08	32	500	0.475	7.67	463	92	#N/A	1.5	12.8	7		0.0159
23-Jan-08	33	500	0.465	7.59	397	73	#N/A	1.5	10.2	4	3.8	0.023
30-Jan-08	34	500	0.445	7.72	417	71	#N/A	1.5	9.3	7		0.0382
6-Feb-08	35	500	0.435	7.69	444	70	#N/A	1.1	8.8	6	5.7	0.054
13-Feb-08	36	500	0.455	7.72	429	64	#N/A	1.5	9.2	6		0.0313
20-Feb-08	37	500	0.49	7.60	436	67	#N/A	1.5	10.2	6	5.6	0.009
27-Feb-08	38	500	0.45	7.70	407	59	#N/A	1.9	7.2	4		0.0114
5-Mar-08	39	500	0.45	7.63	411	55	#N/A	1.4	7.0	4	4.5	0.014
12-Mar-08	40	500	0.455	7.67	414	67	#N/A	1.2	8.3	6		0.0123
19-Mar-08	41	500	0.465	7.80	410	66	#N/A	1.2	9.9	5	5.6	0.011
26-Mar-08	42	500	0.455	7.64	406	61	#N/A	2.9	17.7	4		0.0226
2-Apr-08	43	500	0.425	7.67	419	56	#N/A	2.2	17.8	3	6.8	0.034
9-Apr-08	44	500	0.41	7.41	416	62	#N/A	2.6	18	5		0.033
16-Apr-08	45	500	0.42	7.43	417	72	#N/A	2.7	15	6	9.9	0.032
23-Apr-08	46	500	0.425	7.47	431	87	#N/A	2.7	15	9		0.0223
30-Apr-08	47	500	0.41	7.43	404	88	#N/A	2.3	13	9	15.2	0.013
7-May-08	48	500	0.42	7.62	387	97	#N/A	2.8	14	9		0.0169
14-May-08	49	500	0.41	7.52	374	91	#N/A	2.4	13	10	19.7	0.021
21-May-08	50	500	0.4	7.63	372	106	#N/A	2.7	18	8		0.0157
28-May-08	51	500	0.46	7.45	389	74	#N/A	3.0	11	9	18.8	0.010
4-Jun-08	52	500	0.45	7.64	399	61	#N/A	2.7	11	7		0.0081
11-Jun-08	53	500	0.475	7.51	415	54	#N/A	2.5	11	7	13.9	0.006
18-Jun-08	54	500	0.475	7.62	377	44	#N/A	3.4	11.4	6		0.0056
25-Jun-08	55	500	0.47	7.61	382	58	#N/A	3.5	12.3	5	13.8	0.005
2-Jul-08	56	500	0.465	7.49	386	50	#N/A	2.4	8.8	6		0.0091
9-Jul-08	57	500	0.47	7.46	378	55	#N/A	2.4	10.4	6	12.9	0.013
16-Jul-08	58	500	0.46	7.44	393	47	#N/A	2.8	9.9	5		0.0093
23-Jul-08	59	500	0.465	7.38	412	54	#N/A	2.7	11.4	5	13.8	0.006
30-Jul-08	60	500	0.49	7.41	398	52	#N/A	2.3	14.7	4		0.0057
6-Aug-08	61	500	0.465	7.42	386	47	#N/A	2.6	16.1	3	12	0.006
13-Aug-08	62	500	0.48	7.38	363	48	#N/A	2.3	11.1	4		0.0053
20-Aug-08	63	500	0.455	7.37	319	44	#N/A	2.6	11.7	3	12.8	0.005

HUMIDITY CELL HC-2
CALCULATED LOADING RATES
(mg/kg/wk)
MINAGO PROJECT

2.8-73

HC 2
Sample = ORE/AR C

Date	Cycle No.	Sb	As	Ba	Be	Bi	B	Cd	Ca	Cr	Co	Cu	Fe
		mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk
12-Jun-07	1	0.00010	0.0011	0.0009	0.000030	0.000030	1.204	0.000024	0.720	0.0002	0.0001	0.0011	0.1089
20-Jun-07	2						0.996225		0.750075	0.00024	0.00008	0.0009	0.1084
27-Jun-07	3	0.00004	0.0005	0.0007	0.000033	0.000021	0.789	0.000008	0.780	0.0003	0.0001	0.0007	0.1079
4-Jul-07	4						0.736625		0.92545	0.00054	0.0002	0.0006	0.125123
11-Jul-07	5	0.00004	0.0006	0.0012	0.000021	0.000021	0.685	0.000004	1.071	0.0008	0.0002	0.0005	0.1423
18-Jul-07	6						0.596625		0.8526	0.00051	0.0002	0.0009	0.093898
25-Jul-07	7	0.00003	0.0001	0.0006	0.000023	0.000023	0.509	0.000005	0.635	0.0002	0.0001	0.0013	0.0455
1-Aug-07	8						0.49345		0.57025	0.00037	0.0001	0.0007	0.051245
8-Aug-07	9	0.00003	0.0004	0.0007	0.000023	0.000023	0.478	0.000005	0.506	0.0005	0.0001	0.0001	0.0570
15-Aug-07	10						0.44259		0.468	0.0004	0.00009	0.0001	0.04572
22-Aug-07	11	0.00002	0.0003	0.0006	0.000022	0.000022	0.407	0.000004	0.430	0.0003	0.0001	0.0002	0.0344
29-Aug-07	12						0.376085		0.352025	0.00041	0.00009	0.0003	0.048085
5-Sep-07	13	0.00002	0.0003	0.0005	0.000039	0.000022	0.345	0.000004	0.274	0.0005	0.0001	0.0003	0.0618
12-Sep-07	14						0.331995		0.328275	0.00031	0.00009	0.0002	0.040785
19-Sep-07	15	0.00002	0.0001	0.0004	0.000023	0.000023	0.319	0.000005	0.383	0.0001	0.0001	0.0000	0.0198
26-Sep-07	16						0.29042		0.33645	0.00018	0.0001	0.0005	0.04972
3-Oct-07	17	0.00005	0.0037	0.0004	0.000022	0.000022	0.262	0.000004	0.290	0.0003	0.0002	0.0010	0.0796
10-Oct-07	18						0.24317		0.2614	0.00036	0.0002	0.0008	0.072398
17-Oct-07	19	0.00003	0.0008	0.0004	0.000004	0.000002	0.224	0.000002	0.232	0.0005	0.0002	0.0006	0.0652
24-Oct-07	20						0.224		0.262	0.0003	0.0001	0.0003	0.0447
31-Oct-07	21	0.00003	0.0004	0.0002	0.000005	0.000002	0.224	0.000002	0.293	0.0002	0.0001	0.0001	0.0243
7-Nov-07	22						0.204		0.313	0.0002	0.00007	0.0003	0.0243
14-Nov-07	23	0.00002	0.0003	0.0002	0.000005	0.000002	0.185	0.000002	0.333	0.0002	0.0001	0.0005	0.0243
21-Nov-07	24						0.185		0.303	0.0002	0.00009	0.0004	0.0278
28-Nov-07	25	0.00002	0.0001	0.0004	0.000005	0.000002	0.186	0.000002	0.274	0.0002	0.00010	0.0003	0.0312
5-Dec-07	26						0.166		0.312	0.0002	0.00007	0.0002	0.0233
12-Dec-07	27	0.00003	0.0001	0.0003	0.000005	0.000003	0.146	0.000003	0.350	0.0003	0.00004	0.0001	0.0155
19-Dec-07	28						0.141		0.349	0.0002	0.00003	0.0001	0.0105
26-Dec-07	29	0.00002	0.0001	0.0003	0.000005	0.000003	0.136	0.000003	0.347	0.0001	0.00002	0.0001	0.0056
2-Jan-08	30						0.147		0.411	0.0001	0.00002	0.0001	0.0069
9-Jan-08	31	0.00002	0.0001	0.0005	0.000005	0.000003	0.157	0.000003	0.474	0.0001	0.00002	0.0001	0.0082
16-Jan-08	32						0.141		0.398	0.0001	0.00004	0.0001	0.0138
23-Jan-08	33	0.00001	0.0001	0.0003	0.000005	0.000002	0.125	0.000006	0.321	0.0002	0.00006	0.0002	0.0195
30-Jan-08	34						0.125		0.354	0.0003	0.0001	0.0005	0.0441
6-Feb-08	35	0.00001	0.0001	0.0007	0.000004	0.000002	0.124	0.000006	0.387	0.0003	0.00023	0.0008	0.0687
13-Feb-08	36						0.128		0.453	0.0002	0.0001	0.0004	0.0376
20-Feb-08	37	0.00001	0.0000	0.0004	0.000005	0.000002	0.132	0.000002	0.519	0.0000	0.00004	0.0001	0.0064
27-Feb-08	38						0.115		0.449	0.0001	0.00004	0.0002	0.0088
5-Mar-08	39	0.00001	0.0000	0.0004	0.000005	0.000011	0.099	0.000002	0.378	0.0001	0.00005	0.0002	0.0113
12-Mar-08	40						0.109		0.433	0.0001	0.00004	0.0002	0.0091
19-Mar-08	41	0.00001	0.0001	0.0004	0.000005	0.000002	0.119	0.000002	0.488	0.0001	0.00003	0.0002	0.0070
26-Mar-08	42						0.107		0.508	0.0002	0.00006	0.0002	0.0173
2-Apr-08	43	0.00001	0.0001	0.0004	0.000004	0.000002	0.094	0.000002	0.527	0.0002	0.00010	0.0002	0.0276
9-Apr-08	44						0.090		0.654	0.0002	0.0001	0.0003	0.0306
16-Apr-08	45	0.00002	0.0012	0.0007	0.000004	0.000002	0.086	0.000002	0.781	0.0003	0.00015	0.0004	0.0336
23-Apr-08	46						0.080		0.973	0.0002	0.0001	0.0003	0.0232
30-Apr-08	47	0.00001	0.0001	0.0009	0.000004	0.000002	0.074	0.000002	1.164	0.0001	0.00008	0.0001	0.0127
7-May-08	48						0.080		1.287	0.0001	0.0001	0.0002	0.0148
14-May-08	49	0.00001	0.0000	0.0011	0.000004	0.000002	0.087	0.000006	1.410	0.0001	0.00013	0.0003	0.0168
21-May-08	50						0.077		1.439	0.0001	0.0001	0.0003	0.0132
28-May-08	51	0.00001	0.0000	0.0011	0.000005	0.000002	0.067	0.000002	1.467	0.0000	0.00007	0.0004	0.0097
4-Jun-08	52						0.072		1.325	0.0000	0.00006	0.0005	0.0070
11-Jun-08	53	0.00001	0.0000	0.0011	0.000005	0.000002	0.077	0.000019	1.183	0.0000	0.00004	0.0006	0.0043
18-Jun-08	54						0.075		1.144	0.0001	0.00004	0.0005	0.0092
25-Jun-08	55	0.00001	0.0000	0.0009	0.000005	0.000002	0.073	0.000002	1.105	0.0001	0.00003	0.0003	0.0141
2-Jul-08	56						0.072		1.107	0.0001	0.00004	0.0003	0.0134
9-Jul-08	57	0.00001	0.0000	0.0010	0.000005	0.000002	0.071	0.000002	1.109	0.0001	0.00005	0.0003	0.0127
16-Jul-08	58						0.071		1.150	0.0001	0.00004	0.0002	0.0082
23-Jul-08	59	0.00001	0.0000	0.0009	0.000005	0.000002	0.071	0.000002	1.190	0.0001	0.00003	0.0001	0.0037
30-Jul-08	60						0.068		1.090	0.0001	0.00003	0.0002	0.0040
6-Aug-08	61	0.00001	0.0000	0.0008	0.000005	0.000002	0.065	0.000009	0.990	0.0000	0.00003	0.0003	0.0042
13-Aug-08	62						0.061		1.014	0.0001	0.00003	0.0003	0.0039
20-Aug-08	63	0.00001	0.0000	0.0008	0.000005	0.000002	0.058	0.000012	1.037	0.0001	0.00004	0.0002	0.0036

HUMIDITY CELL HC-2
CALCULATED LOADING RATES
(mg/kg/wk)
MINAGO PROJECT

2.8-74

HC 2
Sample = ORE/AR C

Date	Cycle No.	Pb	Li	Mg	Mn	Hg	Mo	Ni	P	K	Se	Si	Ag	Na
		mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk
12-Jun-07	1	0.00004	0.0053	0.4054	0.0005	0.0303	0.0113	0.0019	0.061	2.69	0.0019	1.68	0.000006	46.04
20-Jun-07	2		0.0044	0.410175			0.0082	0.0024			0.0028			
27-Jun-07	3	0.00005	0.0035	0.4150	0.0007	0.0208	0.0050	0.0029	0.042	1.76	0.0037	1.23	0.000008	38.10
4-Jul-07	4		0.004	0.554025			0.0035	0.0046			0.0038			
11-Jul-07	5	0.00005	0.0044	0.6931	0.0010	0.0208	0.0020	0.0062	0.042	2.49	0.0040	1.48	0.000004	38.39
18-Jul-07	6		0.0036	0.497275			0.0014	0.0045			0.0036			
25-Jul-07	7	0.00076	0.0027	0.3015	0.0004	0.0225	0.0008	0.0027	0.045	1.60	0.0032	0.87	0.000005	23.22
1-Aug-07	8		0.0027	0.30715			0.0007	0.0031			0.0032			
8-Aug-07	9	0.00004	0.0027	0.3128	0.0005	0.0230	0.0006	0.0034	0.046	1.56	0.0031	0.94	0.000005	20.79
15-Aug-07	10		0.0024	0.2811			0.0005	0.0027			0.0028			
22-Aug-07	11	0.00002	0.0022	0.2494	0.0002	0.0215	0.0004	0.0020	0.043	1.17	0.0025	0.81	0.000004	18.02
29-Aug-07	12		0.0024	0.25085			0.0004	0.0028			0.0025			
5-Sep-07	13	0.00005	0.0026	0.2523	0.0004	0.0218	0.0004	0.0037	0.044	1.32	0.0024	0.91	0.000004	14.57
12-Sep-07	14		0.0024	0.22065			0.0004	0.0027			0.0022			
19-Sep-07	15	0.00002	0.0023	0.1890	0.0002	0.0225	0.0003	0.0018	0.045	1.26	0.0019	0.67	0.000005	13.46
26-Sep-07	16		0.0024	0.2485			0.0003	0.0042			0.0018			
3-Oct-07	17	0.00435	0.0026	0.3080	0.0005	0.0220	0.0003	0.0065	0.044	1.04	0.0016	0.89	0.000004	10.78
10-Oct-07	18		0.0024	0.2785			0.0002	0.0055			0.0014			
17-Oct-07	19	0.00008	0.0023	0.2490	0.0004	0.0042	0.0002	0.0044	0.000	1.04	0.0013	0.86	0.000002	9.30
24-Oct-07	20		0.0023	0.2078			0.0002	0.0031			0.0011			
31-Oct-07	21	0.00003	0.0023	0.1665	0.0002	0.0045	0.0002	0.0018	0.001	1.07	0.0010	0.68	0.000002	8.96
7-Nov-07	22		0.0024	0.1733			0.0002	0.0019			0.001			
14-Nov-07	23	0.00002	0.0025	0.1800	0.0002	0.0045	0.0002	0.0020	0.001	1.17	0.0009	0.63	0.000002	8.33
21-Nov-07	24		0.0029	0.2148			0.0002	0.0029			0.0009			
28-Nov-07	25	0.00002	0.0033	0.2496	0.0003	0.0048	0.0002	0.0038	0.001	1.32	0.0010	0.77	0.000002	9.12
5-Dec-07	26		0.0032	0.2304			0.0002	0.0027			0.0009			
12-Dec-07	27	0.00043	0.0031	0.2112	0.0002	0.0052	0.0001	0.0017	0.001	1.36	0.0008	0.64	0.000003	6.90
19-Dec-07	28		0.0029	0.2076			0.0001	0.0013			0.0007			
26-Dec-07	29	0.00004	0.0028	0.2040	0.0001	0.0051	0.0001	0.0009	0.001	1.34	0.0007	0.58	0.000003	6.73
2-Jan-08	30		0.0031	0.2219			0.0002	0.0012			0.0007			
9-Jan-08	31	0.00001	0.0033	0.2397	0.0002	0.0051	0.0002	0.0014	0.001	1.57	0.0007	0.58	0.000003	6.68
16-Jan-08	32		0.0031	0.2384			0.0002	0.0019			0.0007			
23-Jan-08	33	0.00003	0.0028	0.2372	0.0002	0.0047	0.0001	0.0023	0.001	1.39	0.0006	0.60	0.000002	5.53
30-Jan-08	34		0.0032	0.3035			0.0001	0.0045			0.0006			
6-Feb-08	35	0.00017	0.0035	0.3698	0.0005	0.0044	0.0001	0.0067	0.001	1.32	0.0006	0.80	0.000003	5.31
13-Feb-08	36		0.0037	0.3588			0.00006	0.0048			0.0006			
20-Feb-08	37	0.00001	0.0038	0.3479	0.0003	0.0049	0.0000	0.0029	0.001	1.62	0.0006	0.64	0.000002	5.88
27-Feb-08	38		0.0034	0.3067			0.00005	0.0027			0.0006			
5-Mar-08	39	0.00001	0.0029	0.2655	0.0002	0.0045	0.0001	0.0025	0.001	1.30	0.0005	0.44	0.000002	3.91
12-Mar-08	40		0.0033	0.3025			0.0001	0.0020			0.0005			
19-Mar-08	41	0.00028	0.0038	0.3395	0.0002	0.0047	0.0001	0.0016	0.001	1.60	0.0006	0.76	0.000002	4.57
26-Mar-08	42		0.0042	0.3589			0.0001	0.0033			0.0005			
2-Apr-08	43	0.00002	0.0045	0.3783	0.0003	0.0085	0.0001	0.0050	0.002	1.73	0.0005	0.56	0.000003	3.26
9-Apr-08	44		0.005	0.4600			0.00008	0.0070			0.0005			
16-Apr-08	45	0.00001	0.0056	0.5418	0.0003	0.0042	0.0001	0.0090	0.001	2.11	0.0005	0.65	0.000002	3.53
23-Apr-08	46		0.0064	0.6727			0.00008	0.0128			0.0005			
30-Apr-08	47	0.00000	0.0073	0.8036	0.0004	0.0082	0.0001	0.0167	0.001	2.29	0.0006	0.51	0.000002	3.08
7-May-08	48		0.0077	0.9533			0.00007	0.0208			0.0006			
14-May-08	49	0.00015	0.0081	1.1029	0.0004	0.0041	0.0001	0.0249	0.001	2.52	0.0006	0.55	0.000002	3.01
21-May-08	50		0.0075	1.1541			0.00007	0.0198			0.0006			
28-May-08	51	0.00001	0.0069	1.2052	0.0004	0.0046	0.0001	0.0147	0.001	2.34	0.0006	0.53	0.000002	2.41
4-Jun-08	52		0.0062	1.0491			0.00006	0.0120			0.0005			
11-Jun-08	53	0.00230	0.0055	0.8930	0.0003	0.0048	0.0001	0.0093	0.001	2.05	0.0004	0.49	0.000002	1.96
18-Jun-08	54		0.0055	0.9001			0.00005	0.0077			0.0005			
25-Jun-08	55	0.00000	0.0056	0.9071	0.0003	0.0047	0.0001	0.0062	0.001	1.78	0.0005	0.55	0.000006	1.52
2-Jul-08	56		0.0053	0.8507			0.00006	0.0057			0.0004			
9-Jul-08	57	0.00004	0.0051	0.7943	0.0004	0.0047	0.0001	0.0052	0.001	1.70	0.0004	0.52	0.000003	1.33
16-Jul-08	58		0.005	0.8157			0.00006	0.0049			0.0004			
23-Jul-08	59	0.00001	0.0050	0.8370	0.0002	0.0047	0.0001	0.0047	0.001	1.73	0.0004	0.45	0.000002	1.37
30-Jul-08	60		0.0049	0.7975			0.00005	0.0048			0.0004			
6-Aug-08	61	0.00925	0.0047	0.7580	0.0003	0.0047	0.0000	0.0049	0.001	1.56	0.0003	0.52	0.000002	1.12
13-Aug-08	62		0.0046	0.7703			0.00004	0.0049			0.0003			
20-Aug-08	63	0.00012	0.0046	0.7826	0.0003	0.0046	0.0000	0.0049	0.001	1.54	0.0003	0.46	0.000002	1.01

HUMIDITY CELL HC-2
CALCULATED LOADING RATES
(mg/kg/wk)
MINAGO PROJECT

2.8-75

HC 2

Sample = ORE/AR C

Date	Cycle No.	Sr	S	Tl	Sn	Ti	U	V	Zn	Zr
		mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk
12-Jun-07	1	0.0074	16.76	0.000030	0.000030	0.0011	0.0002	0.0079	0.0004	0.0030
20-Jun-07	2	0.0083								
27-Jun-07	3	0.0093	38.80	0.000021	0.000029	0.0022	0.0007	0.0049	0.0013	0.0021
4-Jul-07	4	0.0122								
11-Jul-07	5	0.0151	26.15	0.000021	0.000062	0.0022	0.0005	0.0037	0.0007	0.0021
18-Jul-07	6	0.0109								
25-Jul-07	7	0.0067	11.66	0.000023	0.000027	0.0009	0.0002	0.0032	0.0004	0.0023
1-Aug-07	8	0.0062								
8-Aug-07	9	0.0057	10.58	0.000023	0.000046	0.0010	0.0002	0.0031	0.0005	0.0023
15-Aug-07	10	0.0048								
22-Aug-07	11	0.0039	8.51	0.000022	0.000022	0.0006	0.0002	0.0022	0.0007	0.0022
29-Aug-07	12	0.0036								
5-Sep-07	13	0.0034	6.57	0.000022	0.000035	0.0012	0.0002	0.0028	0.0005	0.0022
12-Sep-07	14	0.0035								
19-Sep-07	15	0.0036	5.67	0.000023	0.000023	0.0005	0.0002	0.0024	0.0002	0.0023
26-Sep-07	16	0.0034								
3-Oct-07	17	0.0033	4.93	0.000022	0.000022	0.0005	0.0002	0.0021	0.0002	0.0022
10-Oct-07	18	0.0029								
17-Oct-07	19	0.0025	3.74	0.000004	0.000058	0.0009	0.0001	0.0020	0.0005	0.0002
24-Oct-07	20	0.0026								
31-Oct-07	21	0.0028	3.15	0.000004	0.000009	0.0002	0.0001	0.0017	0.0004	0.0000
7-Nov-07	22	0.0028								
14-Nov-07	23	0.0028	3.60	0.000003	0.000005	0.0003	0.0001	0.0015	0.0002	0.0001
21-Nov-07	24	0.0032								
28-Nov-07	25	0.0036	2.88	0.000006	0.000010	0.0002	0.0002	0.0017	0.0001	0.0001
5-Dec-07	26	0.0038								
12-Dec-07	27	0.0040	3.09	0.000004	0.000005	0.0003	0.0001	0.0012	0.0002	0.0001
19-Dec-07	28	0.004								
26-Dec-07	29	0.0039	2.55	0.000006	0.000005	0.0003	0.0001	0.0011	0.0002	0.0001
2-Jan-08	30	0.0043								
9-Jan-08	31	0.0047	2.55	0.000006	0.000005	0.0003	0.0001	0.0011	0.0004	0.0001
16-Jan-08	32	0.0042								
23-Jan-08	33	0.0038	2.33	0.000005	0.000005	0.0002	0.0001	0.0011	0.0007	0.0000
30-Jan-08	34	0.0042								
6-Feb-08	35	0.0047	2.61	0.000006	0.000004	0.0006	0.0001	0.0010	0.0009	0.0001
13-Feb-08	36	0.0053								
20-Feb-08	37	0.0059	2.45	0.000007	0.000005	0.0002	0.0001	0.0008	0.0008	0.0000
27-Feb-08	38	0.0052								
5-Mar-08	39	0.0046	1.80	0.000006	0.000005	0.0002	0.0001	0.0007	0.0003	0.0000
12-Mar-08	40	0.0053								
19-Mar-08	41	0.0061	1.86	0.000007	0.000005	0.0002	0.0001	0.0009	0.0001	0.0000
26-Mar-08	42	0.0062								
2-Apr-08	43	0.0062	2.13	0.000007	0.000004	0.0003	0.0001	0.0009	0.0002	0.0000
9-Apr-08	44	0.008								
16-Apr-08	45	0.0097	2.94	0.000009	0.000004	0.0004	0.0001	0.0007	0.0004	0.0000
23-Apr-08	46	0.0121								
30-Apr-08	47	0.0144	3.69	0.000013	0.000004	0.0002	0.0001	0.0005	0.0002	0.0000
7-May-08	48	0.0163								
14-May-08	49	0.0182	4.10	0.000014	0.000004	0.0002	0.0001	0.0006	0.0006	0.0000
21-May-08	50	0.019								
28-May-08	51	0.0198	4.14	0.000011	0.000005	0.0002	0.0001	0.0005	0.0003	0.0000
4-Jun-08	52	0.0178								
11-Jun-08	53	0.0158	2.85	0.000010	0.000005	0.0002	0.0001	0.0003	0.0026	0.0000
18-Jun-08	54	0.0148								
25-Jun-08	55	0.0139	2.35	0.000009	0.000005	0.0002	0.0001	0.0005	0.0001	0.0000
2-Jul-08	56	0.0142								
9-Jul-08	57	0.0145	2.35	0.000010	0.000005	0.0002	0.0001	0.0005	0.0008	0.0000
16-Jul-08	58	0.0142								
23-Jul-08	59	0.0140	2.33	0.000009	0.000005	0.0002	0.0001	0.0005	0.0001	0.0000
30-Jul-08	60	0.0134								
6-Aug-08	61	0.0128	1.86	0.000009	0.000005	0.0002	0.0001	0.0005	0.0003	0.0000
13-Aug-08	62	0.0124								
20-Aug-08	63	0.0121	1.82	0.000012	0.000005	0.0002	0.0001	0.0004	0.0006	0.0000

**HUMIDITY CELL HC-3
CALCULATED LOADING RATES
(mg/kg/wk)**

2.8-76

MINAGO PROJECT

Date	Cycle No.	Volume		pH	ORP mV	Cond. umhos/cm	Acidity (pH 4.5) mg/kg/wk	Acidity (pH 8.3) mg/kg/wk	Alkalinity mg/kg/wk	Sulphate mg/L
		Input mL	Output L							
12-Jun-07	1	750	0.625	9.13	271	344	#N/A	0.00	39	81
20-Jun-07	2	500	0.405	9.11	286	487	#N/A	0.00	34	37
27-Jun-07	3	500	0.41	9.08	307	308	#N/A	0.00	29	37
4-Jul-07	4	500	0.495	8.32	332	326	#N/A	0.00	28	46
11-Jul-07	5	500	0.42	8.43	327	311	#N/A	0.00	26	46
18-Jul-07	6	500	0.41	8.72	326	282	#N/A	0.00	33	27
25-Jul-07	7	500	0.44	8.66	342	172	#N/A	0.00	19	17
1-Aug-07	8	500	0.44	8.2	349	176	#N/A	0.62	17	13
8-Aug-07	9	500	0.445	8.42	305	161	#N/A	0.00	15	12
15-Aug-07	10	500	0.44	8.27	369	24	#N/A	0.29	15	13
22-Aug-07	11	500	0.415	8.42	361	134	#N/A	0.00	15	12
29-Aug-07	12	500	0.425	8.29	364	120	#N/A	0.73	15	11
5-Sep-07	13	500	0.43	8.31	371	110	#N/A	0.00	16	11
12-Sep-07	14	500	0.44	8.24	379	93	#N/A	0.85	16	9
19-Sep-07	15	500	0.435	8.17	368	76	#N/A	0.62	16	6
26-Sep-07	16	500	0.435	8.22	389	120	#N/A	0.83	14	6
3-Oct-07	17	500	0.445	7.91	386	106	#N/A	1.39	14	6
10-Oct-07	18	500	0.45	7.98	406	101	#N/A	0.74	12	6
17-Oct-07	19	500	0.42	7.50	407	96	#N/A	1.23	12	5
24-Oct-07	20	500	0.46	7.93	416	89	#N/A	0.74	13	5
31-Oct-07	21	500	0.445	7.63	396	84	#N/A	1.25	11	6
7-Nov-07	22	500	0.445	7.64	414	79	#N/A	0.95	12	4
14-Nov-07	23	500	0.455	7.54	423	71	#N/A	1.15	11	5
21-Nov-07	24	500	0.445	7.55	461	80	#N/A	1.16	10	6
28-Nov-07	25	500	0.455	7.64	413	85	#N/A	1.36	13	5
5-Dec-07	26	500	0.46	7.65	438	71	#N/A	1.24	12	4
12-Dec-07	27	500	0.46	7.66	411	68	#N/A	0.94	12	3
19-Dec-07	28	500	0.455	7.75	445	65	#N/A	0.85	12	3
26-Dec-07	29	500	0.455	7.36	405	52	#N/A	0.79	10	4
2-Jan-08	30	500	0.45	7.53	445	52	#N/A	0.90	9	4
9-Jan-08	31	500	0.515	7.53	405	66	#N/A	1.12	14	3
16-Jan-08	32	500	0.46	7.43	467	48	#N/A	1.46	8	2
23-Jan-08	33	500	0.47	7.38	408	60	#N/A	1.62	10	3
30-Jan-08	34	500	0.435	7.37	428	58	#N/A	1.49	9	4
6-Feb-08	35	500	0.44	7.53	447	57	#N/A	1.16	9	3
13-Feb-08	36	500	0.45	7.40	440	57	#N/A	1.52	10	5
20-Feb-08	37	500	0.45	7.44	442	58	#N/A	1.40	7	4
27-Feb-08	38	500	0.455	7.38	425	50	#N/A	1.46	7	3
5-Mar-08	39	500	0.45	7.41	422	49	#N/A	1.51	8	4
12-Mar-08	40	500	0.445	7.50	417	52	#N/A	1.12	8	2
19-Mar-08	41	500	0.46	7.62	414	53	#N/A	1.21	10	3
26-Mar-08	42	500	0.465	7.43	415	49	#N/A	2.91	18	2
2-Apr-08	43	500	0.45	7.46	428	45	#N/A	2.18	18	1
9-Apr-08	44	500	0.435	7.46	416	42	#N/A	2.28	25	3
16-Apr-08	45	500	0.44	7.46	413	50	#N/A	2.69	17	3
23-Apr-08	46	500	0.435	7.53	425	54	#N/A	2.41	17	3
30-Apr-08	47	500	0.445	7.52	400	58	#N/A	2.2	18	4
7-May-08	48	500	0.48	7.64	382	55	#N/A	2.4	16	5
14-May-08	49	500	0.48	7.56	375	51	#N/A	2.1	14	3
21-May-08	50	500	0.46	7.61	364	47	#N/A	2.6	15	3
28-May-08	51	500	0.455	7.50	385	38	#N/A	2.9	15	3
4-Jun-08	52	500	0.46	7.63	404	34	#N/A	2.8	14	3
11-Jun-08	53	500	0.465	7.61	406	34	#N/A	2.4	15	4
18-Jun-08	54	500	0.47	7.63	375	29	#N/A	3.0	14.0	2
25-Jun-08	55	500	0.47	7.58	381	37	#N/A	3.3	14.9	2
2-Jul-08	56	500	0.475	7.58	385	36	#N/A	2.1	13.1	2
9-Jul-08	57	500	0.465	7.50	382	41	#N/A	2.2	13.7	4
16-Jul-08	58	500	0.47	7.47	394	36	#N/A	2.5	14.2	3
23-Jul-08	59	500	0.465	7.48	409	41	#N/A	2.4	14.3	2
30-Jul-08	60	500	0.48	7.45	401	39	#N/A	1.9	17.7	2
6-Aug-08	61	500	0.465	7.52	388	41	#N/A	2.3	21.4	2
13-Aug-08	62	500	0.46	7.45	366	39	#N/A	2.1	13.7	1
20-Aug-08	63	500	0.465	7.51	326	37	#N/A	2.2	15.3	1

**HUMIDITY CELL HC-3
CALCULATED LOADING RATES
(mg/kg/wk)**

2.8-77

MINAGO PROJECT

Date	Cycle No.	Hardness CaCO3 mg/kg/wk	Al mg/kg/wk	Sb mg/kg/wk	As mg/kg/wk	Ba mg/kg/wk	Be mg/kg/wk	Bi mg/kg/wk	B mg/kg/wk	Cd mg/kg/wk	Ca mg/kg/wk
12-Jun-07	1	13.3	0.047	0.000138	0.00063	0.00284	0.000031	0.000031	0.608	0.000019	1.581
20-Jun-07	2		0.0587						0.495123		1.051
27-Jun-07	3	7.6	0.070	0.000103	0.00086	0.00076	0.000021	0.000021	0.382	0.000004	0.521
4-Jul-07	4		0.0831						0.3662		0.6636
11-Jul-07	5	13.9	0.096	0.000092	0.00059	0.00142	0.000021	0.000021	0.350	0.000004	0.806
18-Jul-07	6		0.0798						0.27678		0.8344
25-Jul-07	7	11.5	0.063	0.000040	0.00031	0.00105	0.000022	0.000022	0.203	0.000004	0.862
1-Aug-07	8		0.1047						0.18886		0.7983
8-Aug-07	9	10.5	0.146	0.000036	0.00045	0.00120	0.000022	0.000022	0.174	0.000004	0.734
15-Aug-07	10		0.085						0.167315		0.7386
22-Aug-07	11	10.5	0.024	0.000029	0.00033	0.00092	0.000021	0.000021	0.160	0.000004	0.743
29-Aug-07	12		0.0254						0.15255		0.709
5-Sep-07	13	9.3	0.027	0.000034	0.00030	0.00080	0.000022	0.000022	0.145	0.000004	0.675
12-Sep-07	14		0.0341						0.133573		0.7204
19-Sep-07	15	11.2	0.041	0.000035	0.00030	0.00088	0.000022	0.000022	0.122	0.000004	0.766
26-Sep-07	16		0.0408						0.11474		0.7855
3-Oct-07	17	11.1	0.040	0.000045	0.00036	0.00093	0.000022	0.000111	0.107	0.000004	0.805
10-Oct-07	18		0.0354						0.100873		0.7975
17-Oct-07	19	11.1	0.031	0.000029	0.00028	0.00082	0.000004	0.000002	0.095	0.000002	0.790
24-Oct-07	20		0.025						0.0933		0.882
31-Oct-07	21	12.4	0.018	0.000022	0.00027	0.00095	0.000004	0.000002	0.092	0.000002	0.975
7-Nov-07	22		0.018						0.0788		1.008
14-Nov-07	23	13	0.017	0.000018	0.00019	0.00102	0.000005	0.000002	0.066	0.000002	1.042
21-Nov-07	24		0.024						0.0733		1.058
28-Nov-07	25	15	0.031	0.000027	0.00014	0.00143	0.000005	0.000002	0.081	0.000002	1.074
5-Dec-07	26		0.033						0.0702		1.043
12-Dec-07	27	13	0.035	0.000028	0.00026	0.00112	0.000005	0.000002	0.059	0.000002	1.012
19-Dec-07	28		0.022						0.0508		0.975
26-Dec-07	29	12	0.010	0.000014	0.00009	0.00102	0.000009	0.000002	0.042	0.000005	0.937
2-Jan-08	30		0.008						0.0497		1.267
9-Jan-08	31	17	0.006	0.000021	0.00011	0.00164	0.000005	0.000003	0.057	0.000003	1.597
16-Jan-08	32		0.011						0.0528		1.400
23-Jan-08	33	15	0.016	0.000014	0.00009	0.00132	0.000005	0.000002	0.048	0.000002	1.203
30-Jan-08	34		0.015						0.0449		1.189
6-Feb-08	35	15.3	0.015	0.000013	0.00007	0.00132	0.000004	0.000002	0.041	0.000002	1.175
13-Feb-08	36		0.016						0.0418		1.222
20-Feb-08	37	16.6	0.017	0.000014	0.00007	0.00148	0.000005	0.000002	0.042	0.000002	1.269
27-Feb-08	38		0.015						0.0389		1.253
5-Mar-08	39	15.9	0.013	0.000009	0.00006	0.00133	0.000005	0.000002	0.036	0.000002	1.238
12-Mar-08	40		0.014						0.0376		1.247
19-Mar-08	41	16.3	0.014	0.000009	0.00006	0.00137	0.000005	0.000002	0.040	0.000002	1.256
26-Mar-08	42		0.021						0.0358		1.235
2-Apr-08	43	16.1	0.027	0.000018	0.00007	0.00135	0.000005	0.000002	0.032	0.000027	1.215
9-Apr-08	44		0.018						0.0320		1.254
16-Apr-08	45	17.1	0.009	0.000013	0.00007	0.00141	0.000004	0.000002	0.032	0.000002	1.294
23-Apr-08	46		0.009						0.0325		1.419
30-Apr-08	47	19.8	0.009	0.000013	0.00005	0.00173	0.000004	0.000002	0.033	0.000002	1.544
7-May-08	48		0.008						0.0318		1.550
14-May-08	49	19.3	0.008	0.000010	0.00011	0.00170	0.000005	0.000002	0.031	0.000002	1.555
21-May-08	50		0.008						0.0274		1.337
28-May-08	51	14.6	0.009	0.000009	0.00004	0.00126	0.000005	0.000002	0.024	0.000002	1.119
4-Jun-08	52		0.010						0.0237		1.148
11-Jun-08	53	14.4	0.011	0.000009	0.00004	0.00140	0.000005	0.000002	0.023	0.000002	1.176
18-Jun-08	54		0.009						0.0236		1.157
25-Jun-08	55	14.2	0.008	0.000009	0.00006	0.00126	0.000005	0.000002	0.024	0.000002	1.137
2-Jul-08	56		0.008						0.0264		1.166
9-Jul-08	57	14.1	0.009	0.000009	0.00004	0.00136	0.000005	0.000002	0.029	0.000002	1.195
16-Jul-08	58		0.008						0.0260		1.251
23-Jul-08	59	15.4	0.007	0.000009	0.00010	0.00127	0.000005	0.000002	0.023	0.000002	1.307
30-Jul-08	60		0.007						0.0235		1.295
6-Aug-08	61	15.6	0.007	0.000009	0.00004	0.00131	0.000005	0.000002	0.024	0.000007	1.283
13-Aug-08	62		0.007						0.0235		1.253
20-Aug-08	63	15.1	0.008	0.000009	0.00003	0.00122	0.000005	0.000002	0.023	0.000006	1.223

**HUMIDITY CELL HC-3
CALCULATED LOADING RATES
(mg/kg/wk)**

2.8-78

MINAGO PROJECT

Date	Cycle No.	Cr	Co	Cu	Fe	Pb	Li	Mg	Mn	Hg	Mo	Ni
		mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk
12-Jun-07	1	0.0001	0.00004	0.00069	0.036	0.00001	0.0056	1.06	0.0003	0.031	0.0071	0.0031
20-Jun-07	2	0.0001035	0.00006	0.00079	0.05134		0.004	0.7475			0.0053	0.0032
27-Jun-07	3	0.0001	0.00007	0.00090	0.066	0.00003	0.0024	0.44	0.0003	0.021	0.0035	0.0033
4-Jul-07	4	0.000251	0.0001	0.00104	0.09684		0.0033	0.6814			0.0026	0.006
11-Jul-07	5	0.0004	0.00022	0.00118	0.127	0.00006	0.0042	0.92	0.0009	0.021	0.0017	0.0088
18-Jul-07	6	0.000298	0.0002	0.0007	0.09201		0.0032	0.8118			0.0011	0.0068
25-Jul-07	7	0.0002	0.00012	0.00022	0.057	0.00003	0.0022	0.70	0.0008	0.022	0.0005	0.0048
1-Aug-07	8	0.0002883	0.0002	0.00047	0.06977		0.0026	0.6947			0.0004	0.006
8-Aug-07	9	0.0004	0.00020	0.00071	0.083	0.00005	0.0029	0.69	0.0006	0.022	0.0003	0.0073
15-Aug-07	10	0.0003248	0.0001	0.00046	0.05757		0.0025	0.6458			0.0003	0.0052
22-Aug-07	11	0.0002	0.00007	0.00021	0.032	0.00002	0.0020	0.60	0.0002	0.021	0.0003	0.0032
29-Aug-07	12	0.0001675	0.00007	0.00025	0.02715		0.0024	0.5804			0.0003	0.0028
5-Sep-07	13	0.0001	0.00006	0.00030	0.022	0.00003	0.0029	0.56	0.0002	0.022	0.0003	0.0023
12-Sep-07	14	0.00009	0.00010	0.0003	0.03467		0.0032	0.6406			0.0003	0.0039
19-Sep-07	15	0.0001	0.00013	0.00030	0.047	0.00003	0.0036	0.72	0.0004	0.022	0.0002	0.0056
26-Sep-07	16	0.00013	0.0002	0.0004	0.04574		0.0037	0.7148			0.0002	0.0059
3-Oct-07	17	0.0002	0.00021	0.00049	0.044	0.00008	0.0037	0.71	0.0005	0.022	0.0002	0.0063
10-Oct-07	18	0.00015	0.0001	0.00039	0.03421		0.0035	0.6793			0.0002	0.0046
17-Oct-07	19	0.0001	0.00008	0.00029	0.024	0.00055	0.0034	0.65	0.0002	0.004	0.0002	0.0028
24-Oct-07	20	0.00011	0.00007	0.0002	0.022		0.0033	0.70			0.0002	0.0025
31-Oct-07	21	0.0001	0.00006	0.00011	0.019	0.00002	0.0032	0.75	0.0002	0.004	0.0001	0.0023
7-Nov-07	22	0.00009	0.00007	0.00021	0.020		0.003	0.76			0.0001	0.0029
14-Nov-07	23	0.0001	0.00008	0.00031	0.021	0.00006	0.0028	0.77	0.0004	0.005	0.0001	0.0035
21-Nov-07	24	0.00014	0.00014	0.00026	0.029		0.0033	0.88			0.0001	0.0049
28-Nov-07	25	0.0002	0.00021	0.00021	0.036	0.00004	0.0039	1.00	0.0005	0.005	0.0002	0.0062
5-Dec-07	26	0.00023	0.00017	0.0002	0.035		0.0036	0.93			0.0001	0.0055
12-Dec-07	27	0.0003	0.00014	0.00019	0.034	0.00004	0.0033	0.86	0.0004	0.005	0.0001	0.0047
19-Dec-07	28	0.00016	0.00009	0.00021	0.021		0.0028	0.79			0.0001	0.0031
26-Dec-07	29	0.00005	0.00005	0.00022	0.009	0.00003	0.0023	0.71	0.0003	0.005	0.0001	0.0015
2-Jan-08	30	0.00005	0.00004	0.0002	0.007		0.003	0.95			0.0001	0.0015
9-Jan-08	31	0.0001	0.00004	0.00019	0.005	0.00003	0.0037	1.18	0.0004	0.005	0.0002	0.0015
16-Jan-08	32	0.00007	0.00006	0.00022	0.011		0.0032	1.10			0.0002	0.002
23-Jan-08	33	0.0001	0.00008	0.00025	0.016	0.00002	0.0027	1.02	0.0004	0.005	0.0001	0.0025
30-Jan-08	34	0.00009	0.00006	0.00042	0.015		0.0031	0.97			0.0001	0.0025
6-Feb-08	35	0.0001	0.00005	0.00058	0.014	0.00002	0.0034	0.92	0.0003	0.004	0.0001	0.0026
13-Feb-08	36	0.00007	0.00006	0.00045	0.014		0.0032	0.99			0.0001	0.0028
20-Feb-08	37	0.00005	0.00007	0.00032	0.015	0.00002	0.0031	1.05	0.0004	0.005	0.0001	0.0029
27-Feb-08	38	0.00005	0.00007	0.00028	0.014		0.0029	1.01			0.0001	0.0028
5-Mar-08	39	0.00005	0.00007	0.00025	0.014	0.00002	0.0027	0.98	0.0004	0.005	0.0001	0.0027
12-Mar-08	40	0.00007	0.00006	0.0002	0.012		0.0028	1.02			0.0001	0.0025
19-Mar-08	41	0.0001	0.00005	0.00016	0.010	0.00002	0.0029	1.06	0.0004	0.005	0.0001	0.0023
26-Mar-08	42	0.00023	0.00005	0.00031	0.011		0.0031	1.04			0.0001	0.0023
2-Apr-08	43	0.0004	0.00005	0.00047	0.012	-	0.0032	1.02	0.0003	0.005	0.0001	0.0024
9-Apr-08	44	0.00020	0.00005	0.00033	0.010		0.0033	1.03			0.0001	0.0024
16-Apr-08	45	0.00004	0.00004	0.00019	0.009	0.00001	0.0034	1.04	0.0003	0.004	0.0001	0.0024
23-Apr-08	46	0.00004	0.00005	0.0002	0.008		0.0036	1.12			0.0001	0.0026
30-Apr-08	47	0.00004	0.00005	0.00020	0.008	0.00001	0.0038	1.21	0.0003	0.004	0.0001	0.0027
7-May-08	48	0.00005	0.00004	0.00011	0.007		0.0034	1.26			0.0001	0.0025
14-May-08	49	0.00005	0.00004	0.00002	0.005	0.00001	0.0029	1.31	0.0004	0.005	0.0001	0.0023
21-May-08	50	0.00005	0.00004	0.00026	0.006		0.0025	1.12			0.0001	0.0022
28-May-08	51	0.00005	0.00004	0.00051	0.006	0.00002	0.0022	0.93	0.0003	0.005	0.0001	0.0020
4-Jun-08	52	0.00005	0.00004	0.00076	0.007		0.0021	0.92			0.0001	0.0019
11-Jun-08	53	0.00005	0.00003	0.00101	0.007	0.00003	0.0020	0.91	0.0004	0.005	0.0001	0.0018
18-Jun-08	54	0.00014	0.00003	0.00062	0.007		0.0022	0.92			0.0001	0.0017
25-Jun-08	55	0.00024	0.00003	0.00024	0.006	0.00002	0.0023	0.93	0.0003	0.005	0.0001	0.0015
2-Jul-08	56	0.00016	0.00004	0.00036	0.007		0.0023	0.90			0.0001	0.0018
9-Jul-08	57	0.00009	0.00004	0.00048	0.009	0.00004	0.0024	0.87	0.0004	0.005	0.0001	0.0020
16-Jul-08	58	0.00007	0.00004	0.00034	0.007		0.0023	0.91			0.0001	0.0017
23-Jul-08	59	0.00005	0.00003	0.00020	0.004	0.00107	0.0022	0.95	0.0003	0.005	0.0001	0.0014
30-Jul-08	60	0.00005	0.00003	0.0002	0.004		0.0023	0.97			0.0001	0.0015
6-Aug-08	61	0.00005	0.00003	0.00019	0.004	0.00323	0.0024	0.99	0.0003	0.005	0.0001	0.0016
13-Aug-08	62	0.00005	0.00003	0.00017	0.004		0.0023	0.98			0.0001	0.0015
20-Aug-08	63	0.00005	0.00003	0.00014	0.004	0.00003	0.0021	0.97	0.0003	0.005	0.0001	0.0013

**HUMIDITY CELL HC-3
CALCULATED LOADING RATES
(mg/kg/wk)**

2.8-79

MINAGO PROJECT

Date	Cycle No.	P mg/kg/wk	K mg/kg/wk	Se mg/kg/wk	Si mg/kg/wk	Ag mg/kg/wk	Na mg/kg/wk	Sr mg/kg/wk	S mg/kg/wk	Tl mg/kg/wk	Sn mg/kg/wk	Ti mg/kg/wk
12-Jun-07	1	0.063	2.81	0.0017	0.92	0.000006	48.4	0.0134	27.2	0.00003	0.000031	0.00069
20-Jun-07	2			0.0014				0.0092				
27-Jun-07	3	0.041	1.04	0.0011	0.95	0.000008	26.6	0.0050	19.8	0.00002	0.000021	0.00111
4-Jul-07	4			0.0014				0.0065				
11-Jul-07	5	0.042	1.58	0.0016	1.29	0.000004	26.1	0.0080	12.0	0.00002	0.000059	0.00139
18-Jul-07	6			0.0013				0.0064				
25-Jul-07	7	0.044	0.99	0.0011	0.59	0.000004	14.2	0.0048	5.1	0.00002	0.000022	0.00136
1-Aug-07	8			0.001				0.0053				
8-Aug-07	9	0.045	1.12	0.0010	0.85	0.000004	13.0	0.0057	5.7	0.00002	0.000022	0.00245
15-Aug-07	10			0.0008				0.0055				
22-Aug-07	11	0.042	0.91	0.0007	0.55	0.000004	12.4	0.0053	5.6	0.00002	0.000021	0.00046
29-Aug-07	12			0.0006				0.0058				
5-Sep-07	13	0.043	1.17	0.0005	0.53	0.000004	10.3	0.0062	4.2	0.00002	0.000026	0.00047
12-Sep-07	14			0.0005				0.0063				
19-Sep-07	15	0.044	1.17	0.0005	0.54	0.000004	9.0	0.0063	2.8	0.00002	0.000022	0.00035
26-Sep-07	16			0.0004				0.0064				
3-Oct-07	17	0.045	1.03	0.0004	0.52	0.000004	7.3	0.0066	2.6	0.00002	0.000085	0.00058
10-Oct-07	18			0.0004				0.0069				
17-Oct-07	19	0.000	1.16	0.0004	0.48	0.000002	6.3	0.0072	2.1	0.00001	0.000029	0.00038
24-Oct-07	20			0.0003				0.0078				
31-Oct-07	21	0.001	1.15	0.0003	0.44	0.000002	5.2	0.0085	1.8	0.00001	0.000022	0.00022
7-Nov-07	22			0.0003				0.0081				
14-Nov-07	23	0.001	1.10	0.0003	0.38	0.000002	4.1	0.0076	2.7	0.00000	0.000027	0.00027
21-Nov-07	24			0.0003				0.0088				
28-Nov-07	25	0.001	1.24	0.0004	0.53	0.000005	4.9	0.0100	1.8	0.00001	0.000014	0.00032
5-Dec-07	26			0.0003				0.0093				
12-Dec-07	27	0.001	1.19	0.0003	0.48	0.000002	3.1	0.0086	1.8	0.00001	0.000005	0.00069
19-Dec-07	28			0.0003				0.0081				
26-Dec-07	29	0.001	0.92	0.0002	0.29	0.000002	2.3	0.0076	1.4	0.00001	0.000005	0.00023
2-Jan-08	30			0.0003				0.0096				
9-Jan-08	31	0.001	1.38	0.0004	0.38	0.000003	3.0	0.0116	2.1	0.00001	0.000005	0.00026
16-Jan-08	32			0.0004				0.0104				
23-Jan-08	33	0.001	1.06	0.0004	0.36	0.000002	2.4	0.0093	1.4	0.00001	0.000005	0.00033
30-Jan-08	34			0.0003				0.0094				
6-Feb-08	35	0.001	1.06	0.0002	0.36	0.000002	2.1	0.0095	1.3	0.00001	0.000004	0.00022
13-Feb-08	36			0.0002				0.0095				
20-Feb-08	37	0.001	1.08	0.0002	0.36	0.000002	2.0	0.0096	1.8	0.00001	0.000005	0.00045
27-Feb-08	38			0.0002				0.0093				
5-Mar-08	39	0.001	0.99	0.0002	0.28	0.000002	1.5	0.0090	1.4	0.00001	0.000005	0.00023
12-Mar-08	40			0.0002				0.0091				
19-Mar-08	41	0.001	0.95	0.0002	0.39	0.000002	1.4	0.0091	1.4	0.00001	0.000005	0.00028
26-Mar-08	42			0.0002				0.0092				
2-Apr-08	43	0.002	1.08	0.0002	0.31	0.000002	1.2	0.0093	1.4	0.00001	0.000005	0.00032
9-Apr-08	44			0.0002				0.0093				
16-Apr-08	45	0.001	1.03	0.0002	0.32	0.000002	1.2	0.0093	1.3	0.00001	0.000004	0.00022
23-Apr-08	46			0.0002				0.0105				
30-Apr-08	47	0.001	1.06	0.0002	0.34	0.000002	1.1	0.0117	1.3	0.00001	0.000004	0.00022
7-May-08	48			0.0002				0.0114				
14-May-08	49	0.001	0.94	0.0002	0.32	0.000002	1.1	0.0111	1.9	0.00001	0.000005	0.00024
21-May-08	50			0.0002				0.0095				
28-May-08	51	0.001	0.70	0.0001	0.25	0.000002	0.8	0.0079	1.4	0.00000	0.000005	0.00023
4-Jun-08	52			0.0002				0.008				
11-Jun-08	53	0.001	0.74	0.0002	0.26	0.000002	1.0	0.0081	1.4	0.00001	0.000005	0.00023
18-Jun-08	54			0.0002				0.0078				
25-Jun-08	55	0.001	0.71	0.0002	0.25	0.000003	0.7	0.0075	1.4	0.00001	0.000005	0.00024
2-Jul-08	56			0.0002				0.0079				
9-Jul-08	57	0.001	0.79	0.0002	0.28	0.000002	0.7	0.0084	1.4	0.00001	0.000005	0.00023
16-Jul-08	58			0.0002				0.0083				
23-Jul-08	59	0.001	0.80	0.0002	0.23	0.000002	0.7	0.0083	1.4	0.00001	0.000005	0.00023
30-Jul-08	60			0.0002				0.0083				
6-Aug-08	61	0.001	0.80	0.0002	0.27	0.000002	0.7	0.0082	1.4	0.00001	0.000005	0.00023
13-Aug-08	62			0.0002				0.008				
20-Aug-08	63	0.001	0.70	0.0002	0.24	0.000003	0.6	0.0079	1.4	0.00001	0.000005	0.00023

**HUMIDITY CELL HC-3
CALCULATED LOADING RATES
(mg/kg/wk)**

2.8-80

MINAGO PROJECT

Date	Cycle No.	U	V	Zn	Zr
		mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/L
12-Jun-07	1	0.0003	0.0033	0.0003	0.00313
20-Jun-07	2				
27-Jun-07	3	0.0009	0.0023	0.0003	0.00205
4-Jul-07	4				
11-Jul-07	5	0.0015	0.0018	0.0007	0.00210
18-Jul-07	6				
25-Jul-07	7	0.0006	0.0013	0.0002	0.00220
1-Aug-07	8				
8-Aug-07	9	0.0004	0.0012	0.0003	0.00223
15-Aug-07	10				
22-Aug-07	11	0.0004	0.0008	0.0002	0.00208
29-Aug-07	12				
5-Sep-07	13	0.0004	0.0009	0.0002	0.00215
12-Sep-07	14				
19-Sep-07	15	0.0004	0.0008	0.0002	0.00218
26-Sep-07	16				
3-Oct-07	17	0.0005	0.0007	0.0004	0.00223
10-Oct-07	18				
17-Oct-07	19	0.0004	0.0007	0.0002	0.00004
24-Oct-07	20				
31-Oct-07	21	0.0003	0.0005	0.0002	0.00004
7-Nov-07	22				
14-Nov-07	23	0.0003	0.0005	0.0002	0.00005
21-Nov-07	24				
28-Nov-07	25	0.0004	0.0007	0.0001	0.00005
5-Dec-07	26				
12-Dec-07	27	0.0003	0.0006	0.0001	0.00005
19-Dec-07	28				
26-Dec-07	29	0.0002	0.0004	0.0004	0.00005
2-Jan-08	30				
9-Jan-08	31	0.0004	0.0004	0.0003	0.00005
16-Jan-08	32				
23-Jan-08	33	0.0002	0.0004	0.0003	0.00005
30-Jan-08	34				
6-Feb-08	35	0.0003	0.0003	0.0007	0.00004
13-Feb-08	36				
20-Feb-08	37	0.0002	0.0004	0.0002	0.00005
27-Feb-08	38				
5-Mar-08	39	0.0002	0.0003	0.0001	0.00005
12-Mar-08	40				
19-Mar-08	41	0.0002	0.0004	0.0002	0.00005
26-Mar-08	42				
2-Apr-08	43	0.0002	0.0004	0.0027	0.00005
9-Apr-08	44				
16-Apr-08	45	0.0002	0.0003	0.0002	0.00004
23-Apr-08	46				
30-Apr-08	47	0.0003	0.0003	0.0001	0.00004
7-May-08	48				
14-May-08	49	0.0004	0.0003	0.0001	0.00005
21-May-08	50				
28-May-08	51	0.0002	0.0003	0.0001	0.00005
4-Jun-08	52				
11-Jun-08	53	0.0003	0.0002	0.0007	0.00005
18-Jun-08	54				
25-Jun-08	55	0.0003	0.0003	0.0004	0.00005
2-Jul-08	56				
9-Jul-08	57	0.0002	0.0003	0.0007	0.00005
16-Jul-08	58				
23-Jul-08	59	0.0002	0.0003	0.0002	0.00005
30-Jul-08	60				
6-Aug-08	61	0.0003	0.0003	0.0002	0.00005
13-Aug-08	62				
20-Aug-08	63	0.0002	0.0002	0.0001	0.00005

HUMIDITY CELL HC-4
CALCULATED LOADING RATES
(mg/kg/wk)
MINAGO PROJECT

2.8-81

HC 4

Sample = OB/LS/FS/AR/ORE Composite

Date	Cycle No.	Volume Input mL	Volume Output L	pH	ORP mV	Cond. umhos/cm	Acidity (pH 4.5) mg/kg/wk	Acidity (pH 8.3) mg/kg/wk	Alkalinity mg/kg/wk	Sulphate mg/L
12-Jun-07	1	750	0.600	8.96	272	319	#N/A	0	36.7	54
20-Jun-07	2	500	0.405	8.38	313	662	#N/A	0	21.6	71
27-Jun-07	3	500	0.435	8.49	337	590	#N/A	0	21.0	96
4-Jul-07	4	500	0.495	8.60	326	422	#N/A	0	24.2	71
11-Jul-07	5	500	0.425	8.04	351	485	#N/A	0.812	18.0	74
18-Jul-07	6	500	0.435	8.50	344	398	#N/A	0	19.6	64
25-Jul-07	7	500	0.465	8.63	351	267	#N/A	0	19.8	40
1-Aug-07	8	500	0.470	8.41	343	276	#N/A	0	20.1	29
8-Aug-07	9	500	0.470	8.61	299	260	#N/A	0	20.6	33
15-Aug-07	10	500	0.46	8.35	366	24	#N/A	0	18.4	26
22-Aug-07	11	500	0.44	8.51	356	179	#N/A	0	17.4	22
29-Aug-07	12	500	0.44	8.38	364	157	#N/A	0	15.5	17
5-Sep-07	13	500	0.435	8.52	362	150	#N/A	0	15.7	20
12-Sep-07	14	500	0.435	8.40	369	129	#N/A	0	15.8	16
19-Sep-07	15	500	0.455	8.53	361	118	#N/A	0	17.8	18
26-Sep-07	16	500	0.445	8.52	375	174	#N/A	0.000	15.4	13
3-Oct-07	17	500	0.455	8.26	377	161	#N/A	0.8645	16.2	15
10-Oct-07	18	500	0.48	8.45	388	150	#N/A	0	17.3	12
17-Oct-07	19	500	0.435	7.57	412	147	#N/A	1.3398	15.1	10
24-Oct-07	20	500	0.465	8.26	405	120	#N/A	0.5208	16.7	11
31-Oct-07	21	500	0.445	7.71	401	121	#N/A	1.32165	12.7	9
7-Nov-07	22	500	0.46	7.89	411	113	#N/A	1.0442	13.7	10
14-Nov-07	23	500	0.465	7.76	431	115	#N/A	1.0974	13.2	10
21-Nov-07	24	500	0.455	7.78	458	106	#N/A	1.20575	11.1	9
28-Nov-07	25	500	0.475	7.81	417	113	#N/A	1.311	14.3	11
5-Dec-07	26	500	0.475	7.73	436	105	#N/A	1.368	13.3	10
12-Dec-07	27	500	0.485	7.66	417	92	#N/A	1.08155	12.2	8
19-Dec-07	28	500	0.46	7.69	452	94	#N/A	0.8648	11.3	7
26-Dec-07	29	500	0.47	7.42	417	96	#N/A	0.9353	11.5	9
2-Jan-08	30	500	0.47	7.63	448	87	#N/A	1.0857	11.2	7
9-Jan-08	31	500	0.495	7.70	408	104	#N/A	1.17315	15.1	10
16-Jan-08	32	500	0.47	7.50	471	78	#N/A	1.4946	9.6	7
23-Jan-08	33	500	0.46	7.48	413	85	#N/A	1.817	10.4	7
30-Jan-08	34	500	0.45	7.57	427	92	#N/A	1.6605	11.1	9
6-Feb-08	35	500	0.445	7.70	445	90	#N/A	1.246	10.8	8
13-Feb-08	36	500	0.435	7.62	438	78	#N/A	1.6878	9.9	5
20-Feb-08	37	500	0.465	7.48	442	71	#N/A	1.488	8.5	7
27-Feb-08	38	500	0.455	7.54	421	71	#N/A	1.5561	9.2	5
5-Mar-08	39	500	0.445	7.47	421	69	#N/A	1.78	7.9	5
12-Mar-08	40	500	0.435	7.56	419	78	#N/A	1.1049	9.1	6
19-Mar-08	41	500	0.46	7.66	416	75	#N/A	1.2926	10.2	6
26-Mar-08	42	500	0.48	7.46	419	69	#N/A	3.13	20.2	6
2-Apr-08	43	500	0.47	7.47	429	60	#N/A	2.59	18.3	6
9-Apr-08	44	500	0.475	7.48	413.08	72.1	#N/A	2.5	17	5
16-Apr-08	45	500	0.47	7.50	417.96	81.2	#N/A	3.1	21	8
23-Apr-08	46	500	0.465	7.53	429.68	80.7	#N/A	2.8	22	7
30-Apr-08	47	500	0.47	7.53	404.78	79.6	#N/A	2.4	20	7
7-May-08	48	500	0.47	7.66	390.62	81.7	#N/A	2.8	23	7
14-May-08	49	500	0.475	7.57	379.88	68.1	#N/A	2.4	18	5
21-May-08	50	500	0.455	7.66	373.53	95.1	#N/A	3.0	27	7
28-May-08	51	500	0.47	7.58	392.57	63.8	#N/A	3.1	22	5
4-Jun-08	52	500	0.465	7.62	415.03	60.0	#N/A	3.3	21	5
11-Jun-08	53	500	0.48	7.67	413.08	62.2	#N/A	2.8	26	5
18-Jun-08	54	500	0.47	7.64	383	62	#N/A	3.6	27.4	6
25-Jun-08	55	500	0.475	7.61	390	76	#N/A	3.8	26.0	5
2-Jul-08	56	500	0.465	7.60	393	64	#N/A	2.3	16.1	5
9-Jul-08	57	500	0.48	7.57	389	81	#N/A	2.6	22.2	8
16-Jul-08	58	500	0.47	7.52	399	64	#N/A	2.7	20.3	6
23-Jul-08	59	500	0.475	7.49	414	73	#N/A	2.9	17.9	6
30-Jul-08	60	500	0.49	7.43	409	59	#N/A	2.3	16.2	4
6-Aug-08	61	500	0.485	7.52	395	66	#N/A	2.4	22.0	5
13-Aug-08	62	500	0.48	7.45	375	68	#N/A	2.4	15.6	4
20-Aug-08	63	500	0.485	7.36	338	62	#N/A	2.6	15.9	4

HUMIDITY CELL HC-4
CALCULATED LOADING RATES
(mg/kg/wk)
MINAGO PROJECT

2.8-82

Hardness CaCO3 mg/kg/wk	Al mg/kg/wk	Sb mg/kg/wk	As mg/kg/wk	Ba mg/kg/wk	Be mg/kg/wk	Bi mg/kg/wk	B mg/kg/wk	Cd mg/kg/wk	Ca mg/kg/wk	Cr mg/kg/wk	Co mg/kg/wk	Cu mg/kg/wk
12.8	0.298	0.00010	0.0005	0.003	0.000042	0.000030	0.630	0.000012	1.470	0.001	0.000	0.002
	0.2022						0.5499		1.8051	0.00034	0.0002	0.0018
20.5	0.106	0.00005	0.0005	0.002	0.000022	0.000022	0.470	0.000009	2.140	0.000	0.000	0.002
	0.1493						0.444425		2.0455	0.00019	0.0002	0.0011
20.5	0.193	0.00004	0.0003	0.002	0.000055	0.000021	0.419	0.000004	1.951	0.000	0.000	0.001
	0.1755						0.379018		1.6241	0.00033	0.0002	0.0006
12.8	0.159	0.00003	0.0002	0.002	0.000023	0.000023	0.339	0.000005	1.297	0.000	0.000	0.001
	0.123						0.343393		1.1892	0.00028	0.0001	0.0005
9.4	0.087	0.00004	0.0003	0.001	0.000024	0.000024	0.348	0.000005	1.081	0.000	0.000	0.000
	0.0579						0.31294		1.0443	0.0002	0.00006	0.0003
9.3	0.028	0.00002	0.0002	0.001	0.000022	0.000022	0.278	0.000004	1.008	0.000	0.000	0.000
	0.061						0.263233		1.0106	0.00018	0.00007	0.0004
9.7	0.094	0.00003	0.0003	0.001	0.000022	0.000022	0.248	0.000004	1.014	0.000	0.000	0.001
	0.0763						0.24181		0.9732	0.00011	0.00009	0.0005
8.5	0.059	0.00003	0.0004	0.001	0.000023	0.000023	0.235	0.000005	0.933	0.000	0.000	0.001
	0.0439						0.223405		0.91	0.00009	0.00008	0.0008
8	0.029	0.00010	0.0008	0.001	0.000023	0.000023	0.212	0.000005	0.887	0.000	0.000	0.001
	0.037						0.199313		0.8286	0.00011	0.00007	0.0008
7.6	0.045	0.00002	0.0004	0.001	0.000004	0.000002	0.187	0.000002	0.770	0.000	0.000	0.000
	0.036						0.180		0.85	0.00011	0.0001	0.0005
8.6	0.028	0.00003	0.0003	0.001	0.000004	0.000002	0.173	0.000002	0.930	0.00009	0.00006	0.00046
	0.025						0.161		0.9556	0.0001	0.0001	0.0005
8.7	0.022	0.00002	0.0001	0.001	0.000005	0.000002	0.149	0.000002	0.981	0.00009	0.00005	0.001
	0.042						0.138		1.0606	0.00019	0.0001	0.0005
11	0.061	0.00002	0.0001	0.001	0.000005	0.000002	0.126	0.000002	1.140	0.00029	0.00016	0.00032
	0.050						0.112		1.1884	0.00022	0.0001	0.0004
10.9	0.038	0.00003	0.0001	0.001	0.000005	0.000002	0.097	0.000002	1.237	0.00015	0.00008	0.00044
	0.028						0.103		1.2764	0.0001	0.0001	0.0004
12.4	0.017	0.00003	0.0001	0.001	0.000005	0.000002	0.108	0.000021	1.316	0.00005	0.00004	0.00040
	0.016						0.120		1.7	0.00005	0.0000	0.0004
18.1	0.014	0.00002	0.0001	0.002	0.000005	0.000002	0.132	0.000002	2.084	0.00005	0.00004	0.00033
	0.014						0.109		1.8424	0.00007	0.0000	0.0004
16.3	0.014	0.00002	0.0001	0.001	0.000005	0.000002	0.086	0.000002	1.601	0.00009	0.00004	0.00046
	0.022						0.094		1.7282	0.00009	0.0001	0.0005
18.7	0.031	0.00002	0.0001	0.002	0.000004	0.000003	0.101	0.000002	1.856	0.00009	0.00009	0.001
	0.023						0.095		1.7811	0.00007	0.0001	0.0004
16.9	0.015	0.00001	0.0001	0.001	0.000005	0.000002	0.089	0.000002	1.707	0.00005	0.00004	0.00028
	0.014						0.082		1.77	0.00005	0.00004	0.0002
18.5	0.012	0.00001	0.0001	0.001	0.000004	0.000002	0.075	0.000002	1.833	0.00004	0.00003	0.00020
	0.011						0.087		1.9471	0.00011	0.00003	0.0002
21.5	0.010	0.00002	0.0001	0.002	0.000005	0.000002	0.099	0.000002	2.061	0.00018	0.00003	0.00027
	0.016						0.083		2.0433	0.00016	0.00004	0.0003
20.3	0.022	0.00002	0.0001	0.002	0.000005	0.000002	0.067	0.000013	2.026	0.00014	0.00005	0.00038
	0.017						0.075		2.3547	9.4E-05	0.00005	0.0004
25.9	0.013	0.00001	0.0001	0.002	0.000005	0.000002	0.082	0.000002	2.684	0.00005	0.00005	0.00048
	0.011						0.077		2.6273	4.7E-05	0.00004	0.0004
25.6	0.009	0.00002	0.0001	0.002	0.000005	0.000002	0.072	0.000002	2.571	0.00005	0.00004	0.00041
	0.009						0.072		2.5086	4.7E-05	0.00003	0.0003
24.6	0.010	0.00002	0.0000	0.002	0.000005	0.000002	0.071	0.000002	2.446	0.00005	0.00003	0.00015
	0.011						0.065		2.3629	4.7E-05	0.00004	0.0004
23.6	0.012	0.00002	0.0001	0.002	0.000005	0.000002	0.059	0.000002	2.280	0.00005	0.00004	0.00061
	0.013						0.063		2.5534	4.8E-05	0.00005	0.0007
27.7	0.015	0.00002	0.0001	0.002	0.000005	0.000002	0.068	0.000002	2.827	0.00005	0.00005	0.00084
	0.015						0.069		2.7602	9.5E-05	0.00005	0.0007
27.1	0.015	0.00001	0.0001	0.002	0.000005	0.000002	0.070	0.000002	2.693	0.00014	0.00004	0.00057
	0.023						0.063		2.8034	0.00012	0.00005	0.0009
27.3	0.030	0.00001	0.0001	0.003	0.000005	0.000002	0.055	0.000002	2.914	0.00010	0.00006	0.00130
	0.020						0.051		2.8343	7.2E-05	0.00004	0.0007
26.1	0.009	0.00001	0.0001	0.002	0.000005	0.000002	0.046	0.000002	2.755	0.00005	0.00003	0.00018
	0.008						0.043		2.6312	4.8E-05	0.00003	0.0002
23.8	0.008	0.00001	0.0000	0.002	0.000005	0.000002	0.039	0.000008	2.507	0.00005	0.00003	0.00031
	0.008						0.038		2.4565	4.9E-05	0.00003	0.0004
23.3	0.009	0.00001	0.0000	0.002	0.000005	0.000002	0.036	0.000007	2.406	0.00005	0.00003	0.00047

HUMIDITY CELL HC-4
CALCULATED LOADING RATES
(mg/kg/wk)
MINAGO PROJECT


2.8-83


Fe	Pb	Li	Mg	Mn	Hg	Mo	Ni	P	K	Se	Si	Ag	Na
mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk
0.202	0.00007	0.007	0.978	0.0020	0.0300	0.006	0.005	0.060	3.306	0.001	1.554	0.000006	43.500
0.14213		0.0054	0.924			0.0059	0.008			0.0007			
0.083	0.00004	0.004	0.870	0.0015	0.0218	0.006	0.011	0.044	2.466	0.001	0.774	0.000004	45.240
0.12165		0.0043	0.9004			0.0041	0.0089			0.0012			
0.161	0.00009	0.004	0.931	0.0014	0.0213	0.003	0.007	0.043	2.784	0.001	1.216	0.000009	37.060
0.13659		0.0038	0.7955			0.0019	0.0073			0.0012			
0.113	0.00010	0.003	0.660	0.0014	0.0233	0.001	0.008	0.047	1.986	0.00098	0.828	0.000005	23.715
0.08047		0.0033	0.5393			0.0012	0.0056			0.001			
0.048	0.00003	0.003	0.418	0.0005	0.0235	0.001	0.003	0.047	2.195	0.00108	0.776	0.000005	22.795
0.04203		0.0028	0.4006			0.0009	0.003			0.001			
0.036	0.00003	0.002	0.383	0.0004	0.0220	0.001	0.003	0.044	1.505	0.00084	0.620	0.000004	18.040
0.05045		0.0027	0.4002			0.0008	0.0034			0.0009			
0.065	0.00004	0.003	0.418	0.0006	0.0218	0.001	0.004	0.044	1.927	0.00087	0.748	0.000004	15.182
0.05128		0.003	0.3954			0.0007	0.004			0.0007			
0.037	0.00004	0.003	0.373	0.0005	0.0228	0.001	0.004	0.046	1.961	0.00050	0.610	0.000005	14.151
0.03526		0.0029	0.3617			0.0006	0.0034			0.0006			
0.033	0.00007	0.003	0.350	0.0004	0.0228	0.001	0.003	0.046	1.638	0.00077	0.596	0.000005	12.149
0.03792		0.003	0.3427			0.0005	0.0032			0.0006			
0.043	0.00003	0.003	0.335	0.0004	0.0044	0.000	0.003	0.000	1.853	0.00037	0.626	0.000002	11.006
0.034		0.0032	0.350			0.0004	0.003			0.0003			
0.024	0.00002	0.003	0.365	0.0004	0.0045	0.000	0.003	0.001	1.887	0.00018	0.579	0.000002	8.900
0.022		0.0035	0.378			0.0004	0.0026			0.0002			
0.020	0.00016	0.004	0.391	0.0004	0.0047	0.000	0.002	0.001	2.246	0.00013	0.535	0.000005	8.370
0.041		0.004	0.487			0.0004	0.0047			0.0001			
0.063	0.00029	0.004	0.584	0.0007	0.0048	0.000	0.007	0.001	2.185	0.00014	0.708	0.000002	7.410
0.049		0.0041	0.559			0.0003	0.0056			0.0001			
0.034	0.00005	0.004	0.534	0.0006	0.0049	0.000	0.004	0.001	2.323	0.00010	0.538	0.000002	4.899
0.025		0.0041	0.572			0.0003	0.0032			0.0001			
0.015	0.00054	0.004	0.611	0.0004	0.0047	0.000	0.002	0.001	2.458	0.00006	0.531	0.000002	5.452
0.013		0.0048	0.763			0.0004	0.0025			0.0001			
0.011	0.00001	0.005	0.916	0.0004	0.0050	0.000	0.003	0.001	3.188	0.00015	0.559	0.000002	5.297
0.012		0.0047	0.886			0.0003	0.0027			0.0001			
0.012	0.00002	0.004	0.856	0.0005	0.0046	0.000	0.003	0.001	2.374	0.00006	0.469	0.000002	3.202
0.029		0.0045	0.875			0.0003	0.0036			0.0001			
0.045	0.00002	0.005	0.894	0.0006	0.0134	0.000	0.004	0.001	2.915	0.00006	0.587	0.000003	3.329
0.029		0.0047	0.884			0.0003	0.0035			0.0001			
0.012	0.00012	0.004	0.874	0.0005	0.0047	0.000	0.002	0.001	2.367	0.00007	0.474	0.000002	2.511
0.010		0.0041	0.880			0.0002	0.0023			0.0001			
0.009	0.00001	0.004	0.886	0.0004	0.0045	0.000	0.002	0.001	2.132	0.00004	0.390	0.000002	1.651
0.008		0.0043	1.015			0.0002	0.0022			0.0001			
0.006	0.00018	0.005	1.145	0.0004	0.0046	0.000	0.002	0.001	3.068	0.00007	0.492	0.000002	1.523
0.011		0.0046	1.116			0.0002	0.0025			0.0001			
0.015	0.00000	0.005	1.086	0.0004	0.0047	0.000	0.003	0.002	2.425	0.00006	0.443	0.000002	1.067
0.012		0.005	1.208			0.0002	0.003			0.0001			
0.010	0.00002	0.005	1.330	0.0006	0.0047	0.000	0.003	0.001	2.956	0.00006	0.559	0.000002	1.175
0.009		0.0054	1.347			0.0002	0.0029			0.0001			
0.008	0.00019	0.006	1.363	0.0004	0.0047	0.000	0.003	0.001	2.703	0.00007	0.531	0.000002	0.888
0.007		0.0053	1.358			0.0002	0.0026			0.0001			
0.006	0.00225	0.005	1.354	0.0005	0.0048	0.000	0.003	0.001	2.617	0.00006	0.532	0.000002	0.831
0.007		0.005	1.330			0.0002	0.0027			0.0001			
0.008	0.00001	0.005	1.307	0.0004	0.0047	0.000	0.003	0.001	2.468	0.00005	0.564	0.000002	0.597
0.010		0.0052	1.407			0.0002	0.0031			0.0001			
0.013	0.00001	0.005	1.507	0.0006	0.0048	0.000	0.003	0.001	2.942	0.00006	0.730	0.000002	0.662
0.017		0.0058	1.499			0.0002	0.0033			0.0001			
0.021	0.00001	0.006	1.492	0.0005	0.0048	0.000	0.003	0.001	2.617	0.00012	0.689	0.000005	0.475
0.022		0.0057	1.454			0.0002	0.0033			0.0001			
0.023	0.00006	0.005	1.416	0.0005	0.0048	0.000	0.004	0.001	2.482	0.00007	0.662	0.000002	0.480
0.014		0.005	1.380			0.0002	0.003			0.0001			
0.005	0.00001	0.005	1.344	0.0004	0.0048	0.000	0.002	0.001	2.309	0.00009	0.459	0.000002	0.333
0.006		0.0044	1.315			0.0002	0.0026			0.0001			
0.006	0.00041	0.004	1.285	0.0004	0.0049	0.000	0.003	0.001	2.056	0.00002	0.472	0.000002	0.291
0.006		0.0041	1.285			0.0002	0.0025			0.0000			
0.006	0.00003	0.004	1.285	0.0004	0.0049	0.000	0.002	0.001	1.969	0.00005	0.428	0.000002	0.291


HUMIDITY CELL HC-4
CALCULATED LOADING RATES
(mg/kg/wk)
MINAGO PROJECT

2.8-84

Sr	S	Tl	Sn	Ti	U	V	Zn	Zr
mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/L
0.011	18.480	0.000030	0.00003	0.00522	0.00052	0.00696	0.00054	0.00300
0.0168								
0.022	28.667	0.000022	0.00003	0.00278	0.00080	0.00314	0.00170	0.00218
0.0219								
0.022	23.588	0.000021	0.00004	0.00557	0.00054	0.00291	0.00068	0.00213
0.0155								
0.009	12.044	0.000023	0.00002	0.00428	0.00063	0.00278	0.00084	0.00233
0.0091								
0.009	11.186	0.000024	0.00008	0.00183	0.00060	0.00288	0.00061	0.00235
0.0076								
0.006	8.316	0.000022	0.00002	0.00097	0.00041	0.00189	0.00035	0.00220
0.0069								
0.007	7.656	0.000022	0.00003	0.00239	0.00037	0.00203	0.00039	0.00218
0.007								
0.007	5.915	0.000023	0.00002	0.00146	0.00044	0.00206	0.00023	0.00228
0.0068								
0.007	5.551	0.000023	0.00002	0.00086	0.00047	0.00192	0.00091	0.00228
0.0062								
0.006	4.350	0.000003	0.00005	0.00109	0.00040	0.00178	0.00048	0.00009
0.0061								
0.007	3.115	0.000004	0.00001	0.00067	0.00041	0.00125	0.00062	0.00004
0.0071								
0.007	4.650	0.000002	0.00003	0.00074	0.00043	0.00116	0.00028	0.00009
0.0086								
0.010	3.325	0.000005	0.00001	0.00176	0.00046	0.00119	0.00010	0.00010
0.0101								
0.010	3.395	0.000004	0.00001	0.00146	0.00040	0.00092	0.00019	0.00005
0.011								
0.012	3.760	0.000006	0.00000	0.00033	0.00034	0.00085	0.00188	0.00005
0.0139								
0.016	4.455	0.000006	0.00000	0.00025	0.00048	0.00074	0.00015	0.00005
0.0149								
0.014	2.760	0.000005	0.00000	0.00041	0.00026	0.00060	0.00060	0.00005
0.0147								
0.016	3.115	0.000007	0.00000	0.00085	0.00025	0.00067	0.00040	0.00004
0.0148								
0.014	2.790	0.000005	0.00000	0.00042	0.00021	0.00060	0.00047	0.00005
0.0138								
0.014	2.670	0.000005	0.00000	0.00031	0.00016	0.00049	0.00022	0.00004
0.0155								
0.017	2.760	0.000006	0.00000	0.00060	0.00021	0.00037	0.00032	0.00005
0.0172								
0.017	2.350	0.000007	0.00000	0.00089	0.00023	0.00052	0.00127	0.00005
0.0192								
0.021	2.820	0.000008	0.00000	0.00033	0.00022	0.00052	0.00042	0.00005
0.0213								
0.021	2.350	0.000008	0.00000	0.00028	0.00025	0.00056	0.00028	0.00005
0.0208								
0.020	2.850	0.000008	0.00000	0.00029	0.00028	0.00057	0.00019	0.00005
0.02								
0.020	1.880	0.000007	0.00000	0.00024	0.00035	0.00052	0.00019	0.00005
0.0218								
0.024	1.920	0.000009	0.00000	0.00048	0.00038	0.00048	0.00034	0.00024
0.0228								
0.022	1.900	0.000008	0.00000	0.00038	0.00037	0.00062	0.00052	0.00024
0.0235								
0.025	2.400	0.000008	0.00000	0.00067	0.00031	0.00048	0.00139	0.00024
0.0235								
0.022	2.375	0.000008	0.00000	0.00029	0.00027	0.00043	0.00029	0.00024
0.0207								
0.020	1.940	0.000008	0.00000	0.00024	0.00023	0.00039	0.00015	0.00024
0.0195								
0.019	2.425	0.000009	0.00000	0.00024	0.00022	0.00034	0.00019	0.00024

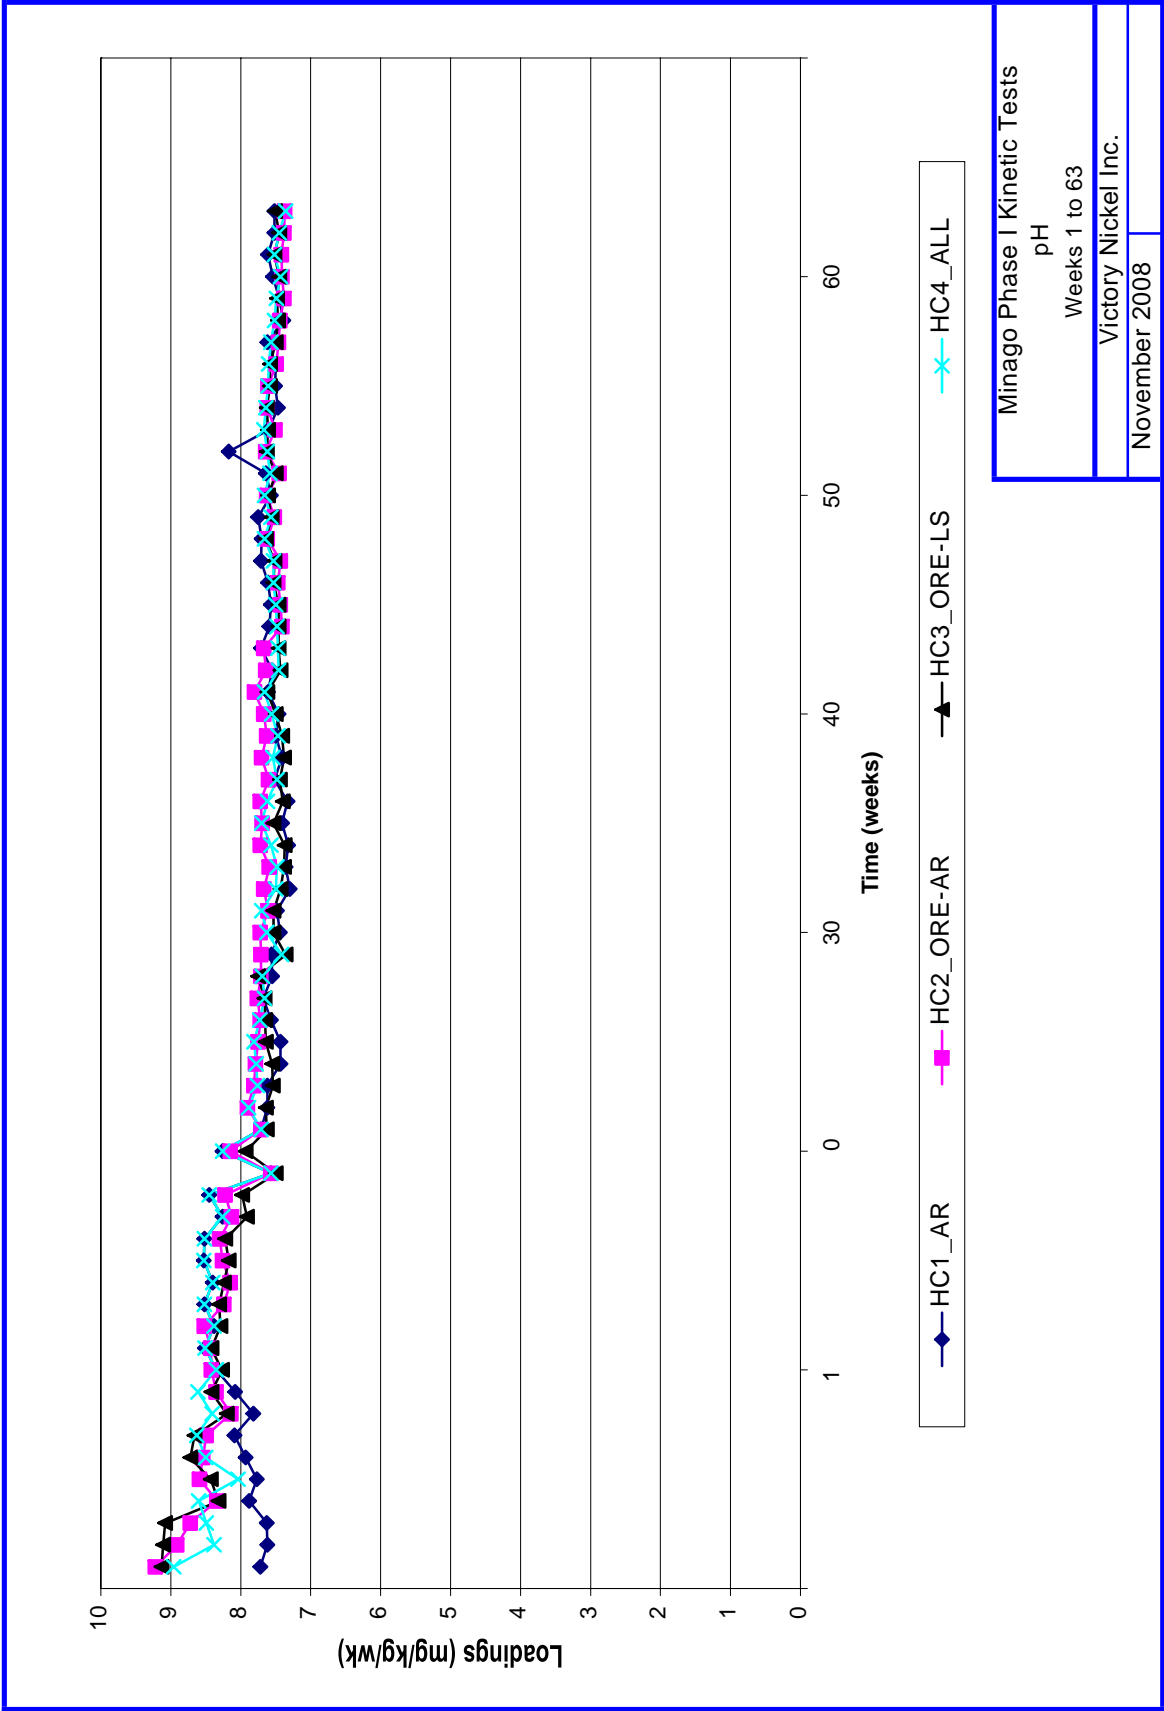


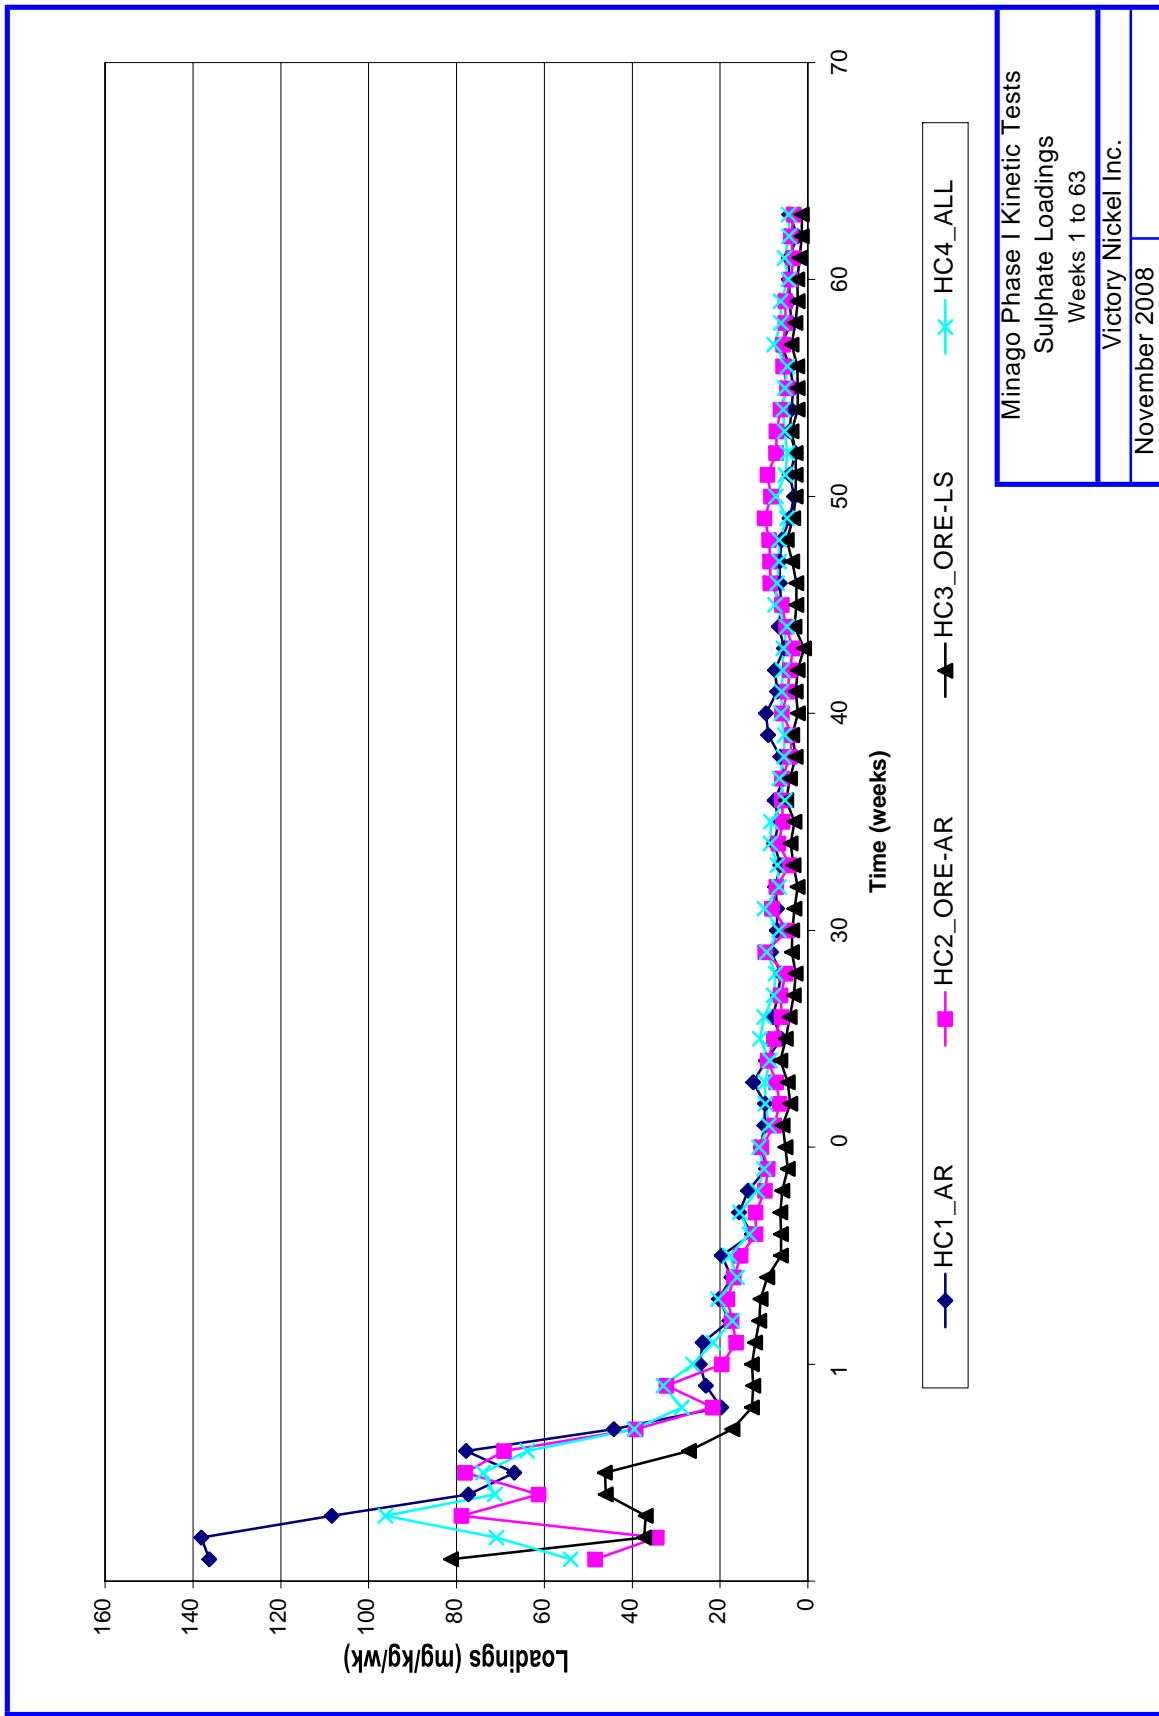


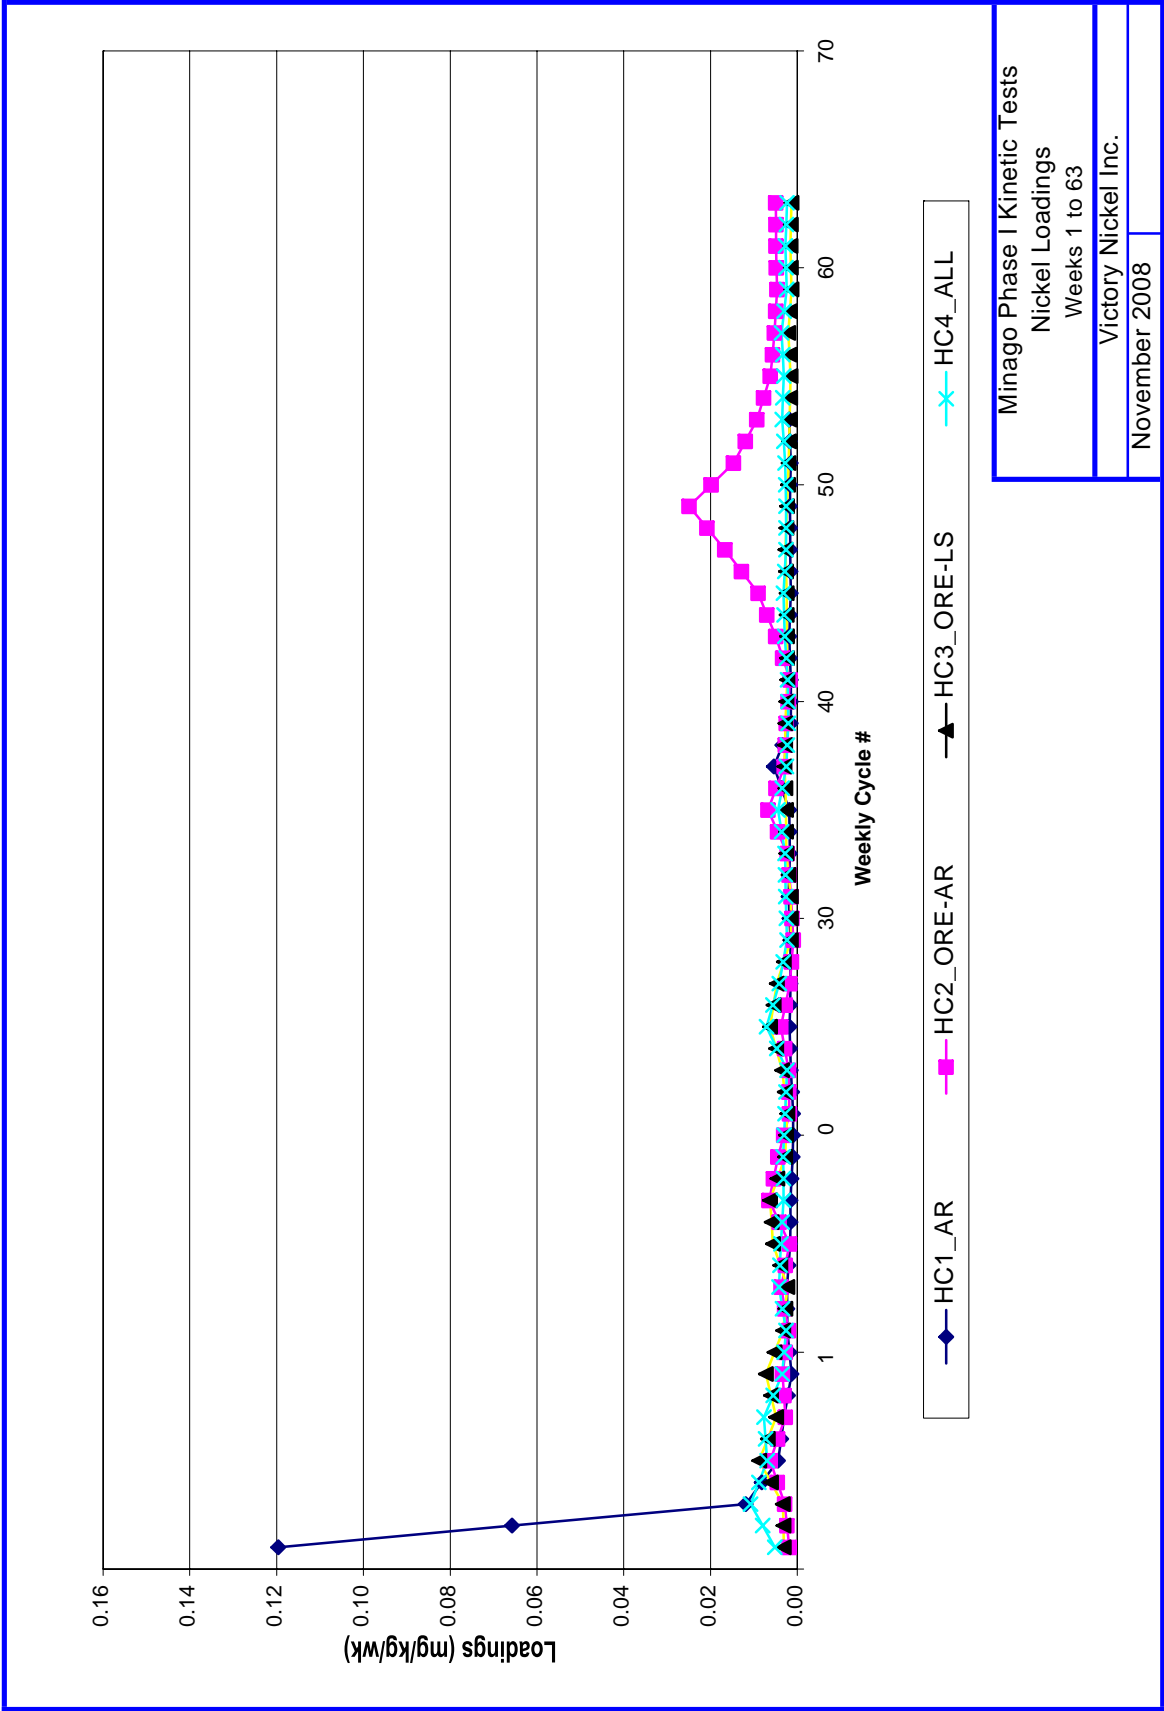

Minago Phase I Kinetic Tests
Nickel Loadings
Weeks 1 to 63
Victory Nickel Inc.
November 2008




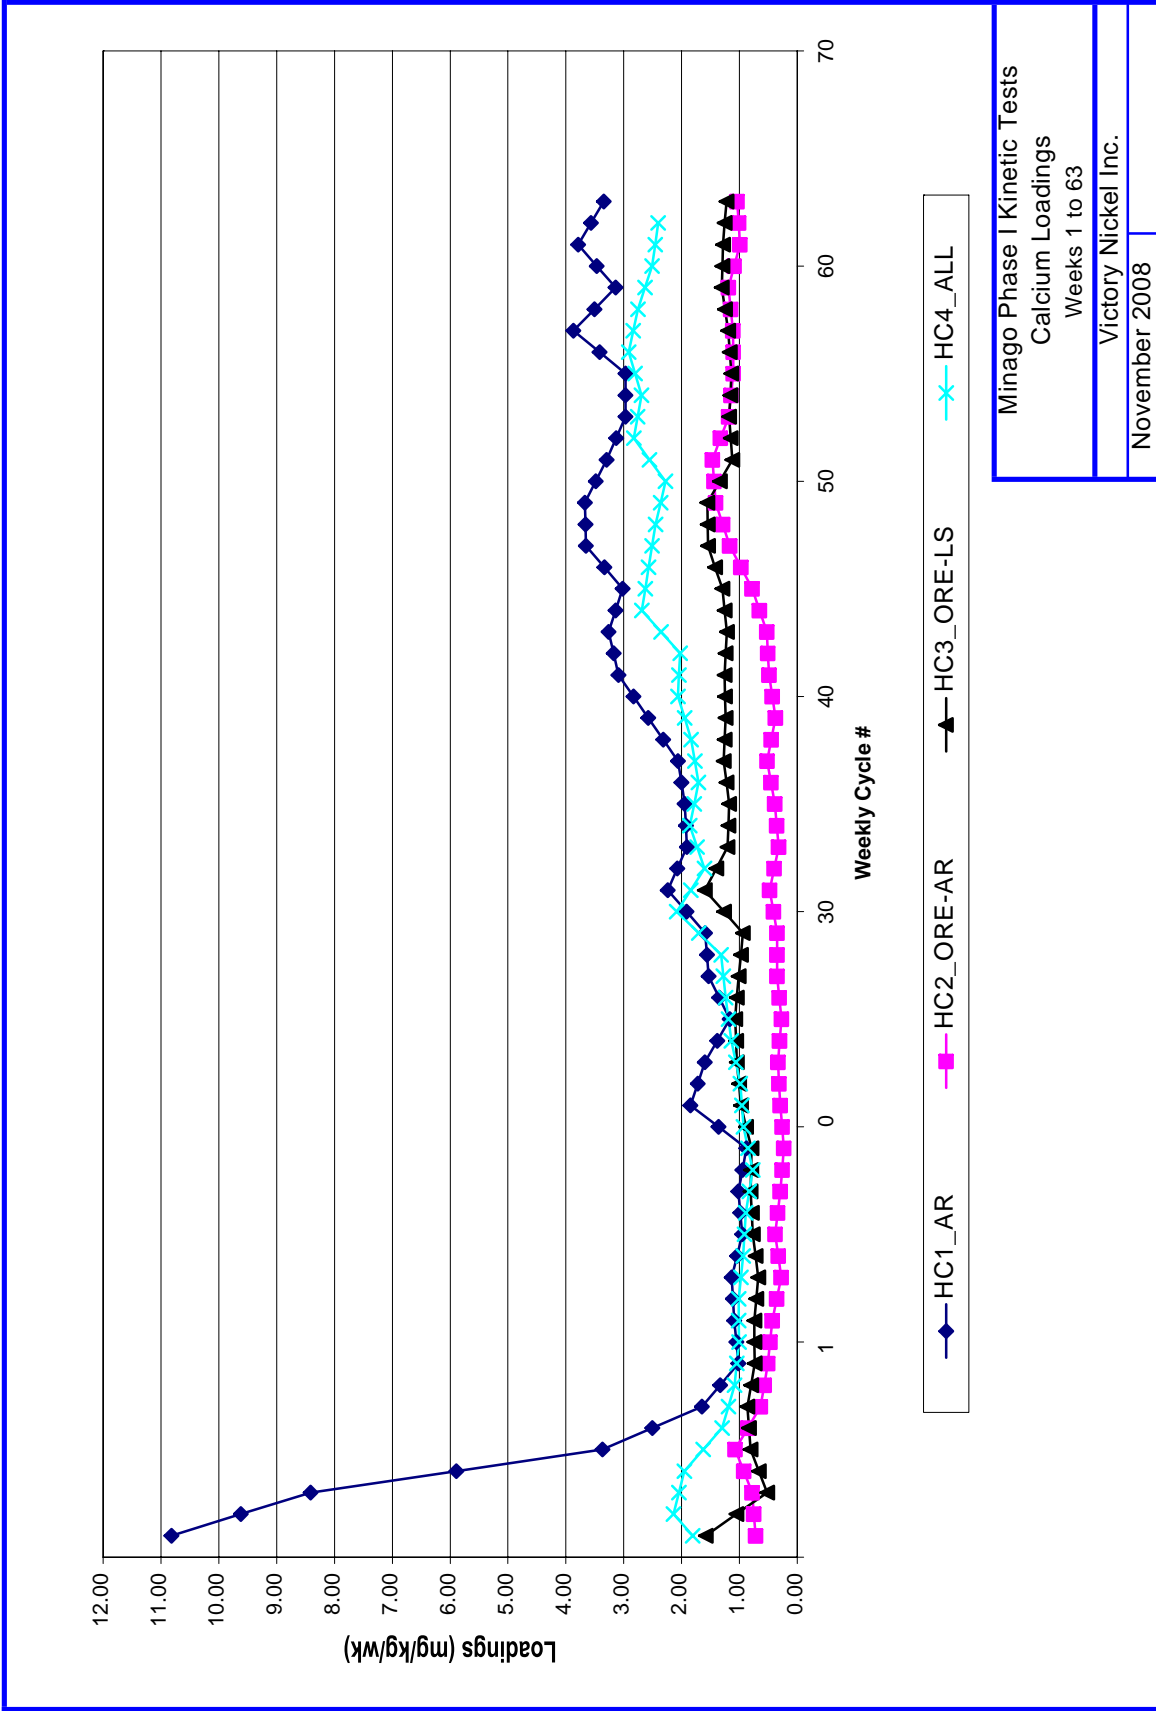

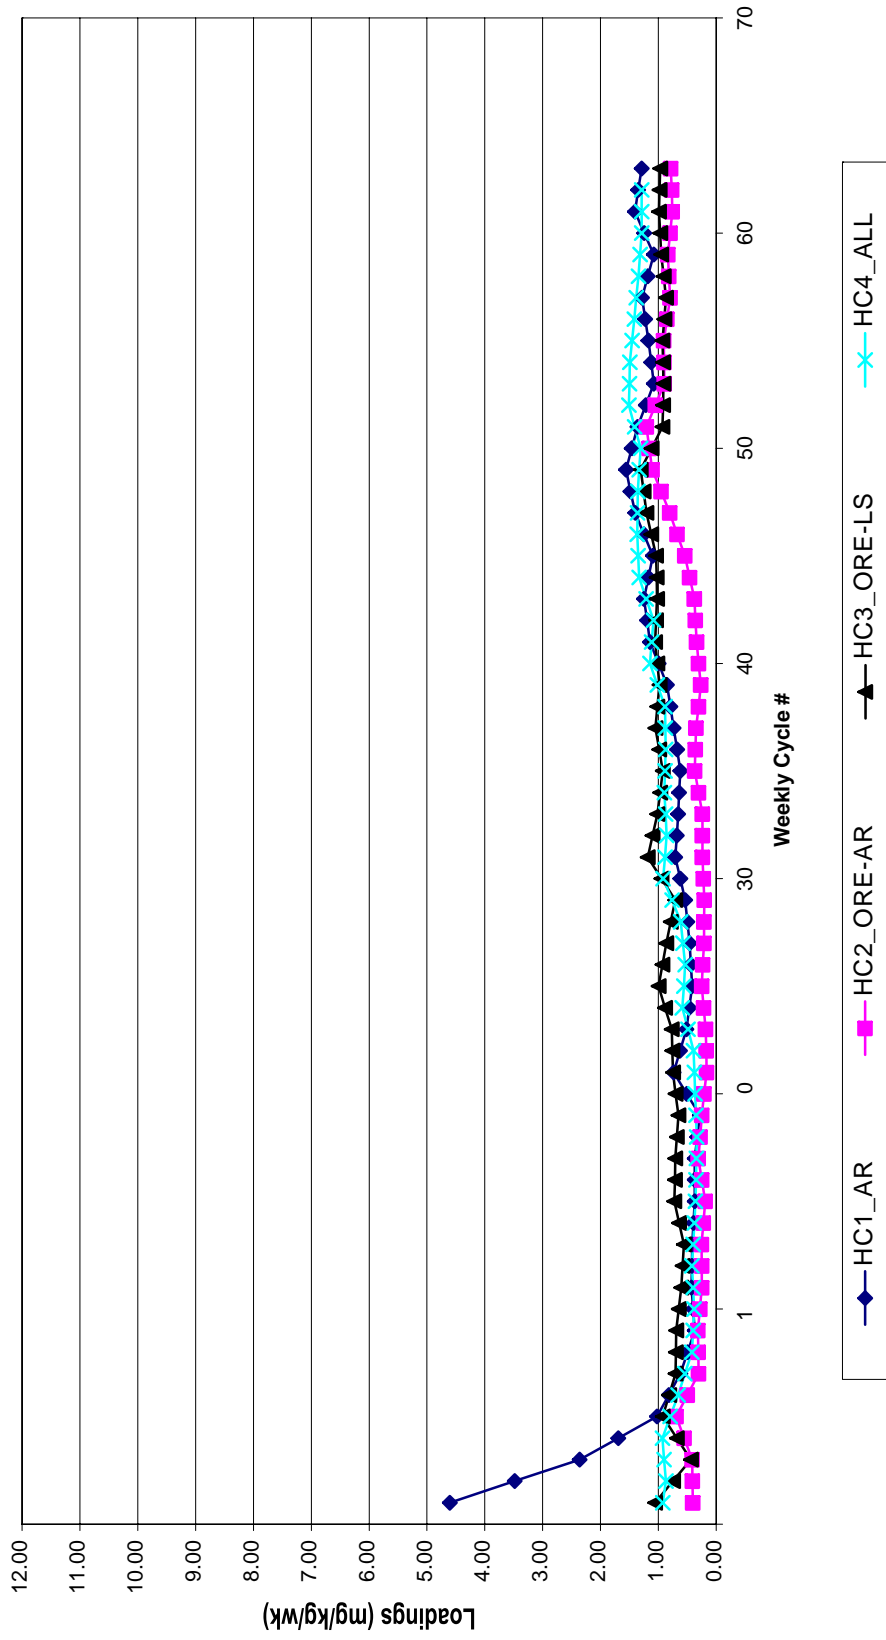


Minago Phase I Kinetic Tests
Magnesium Loadings
Weeks 1 to 63
Victory Nickel Inc.
November 2008



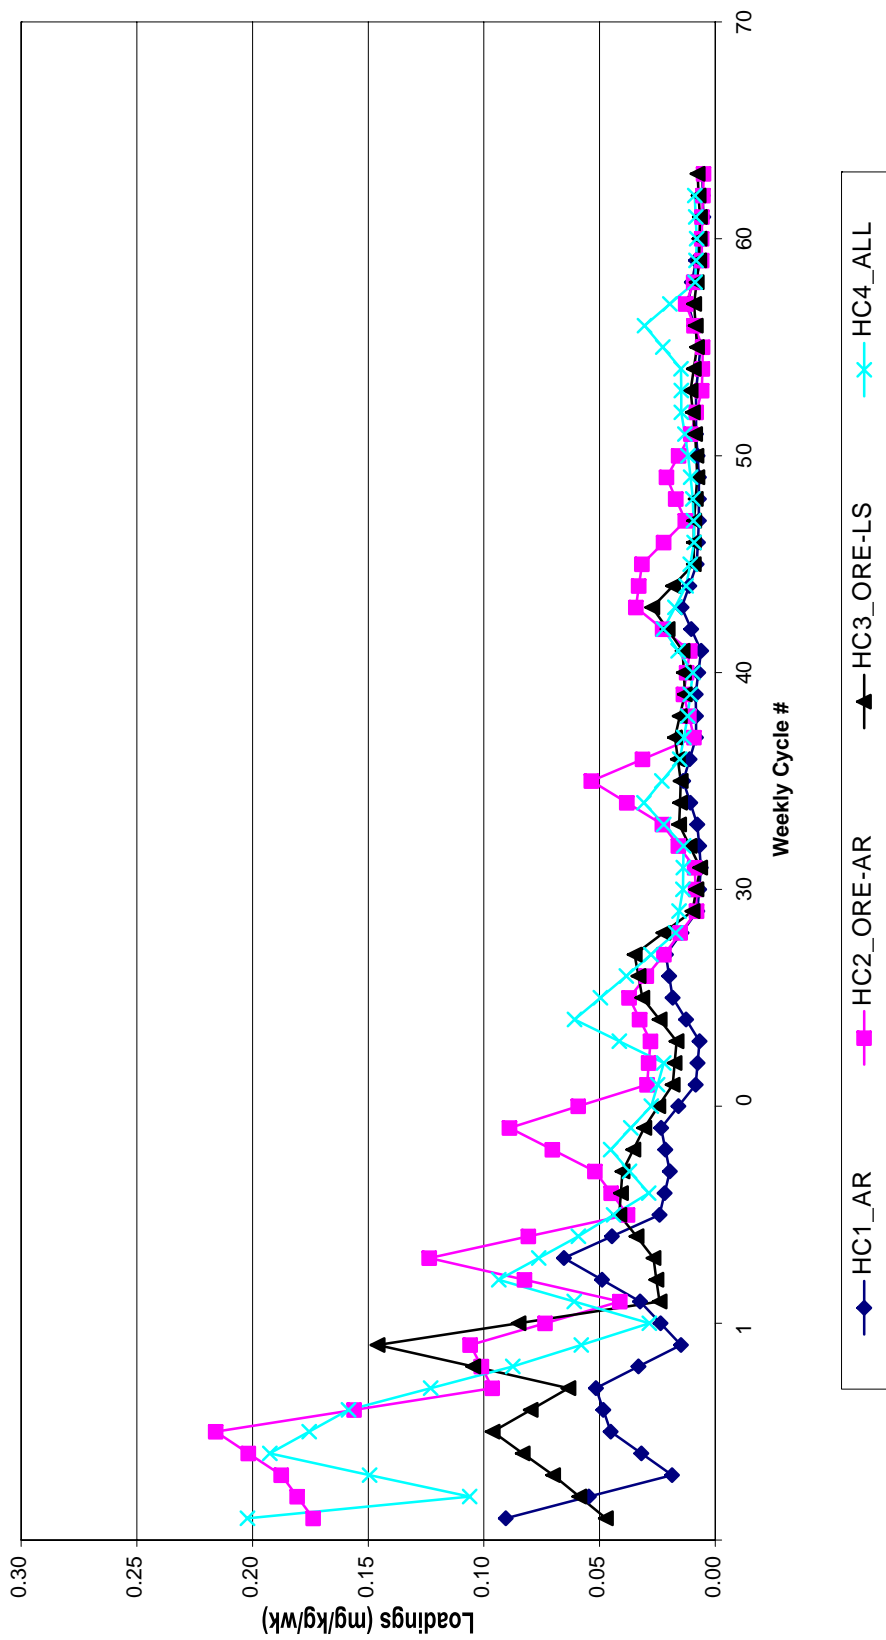

Minago Phase I Kinetic Tests
 Aluminum Loadings
 Weeks 1 to 63
 Victory Nickel Inc.
 November 2008



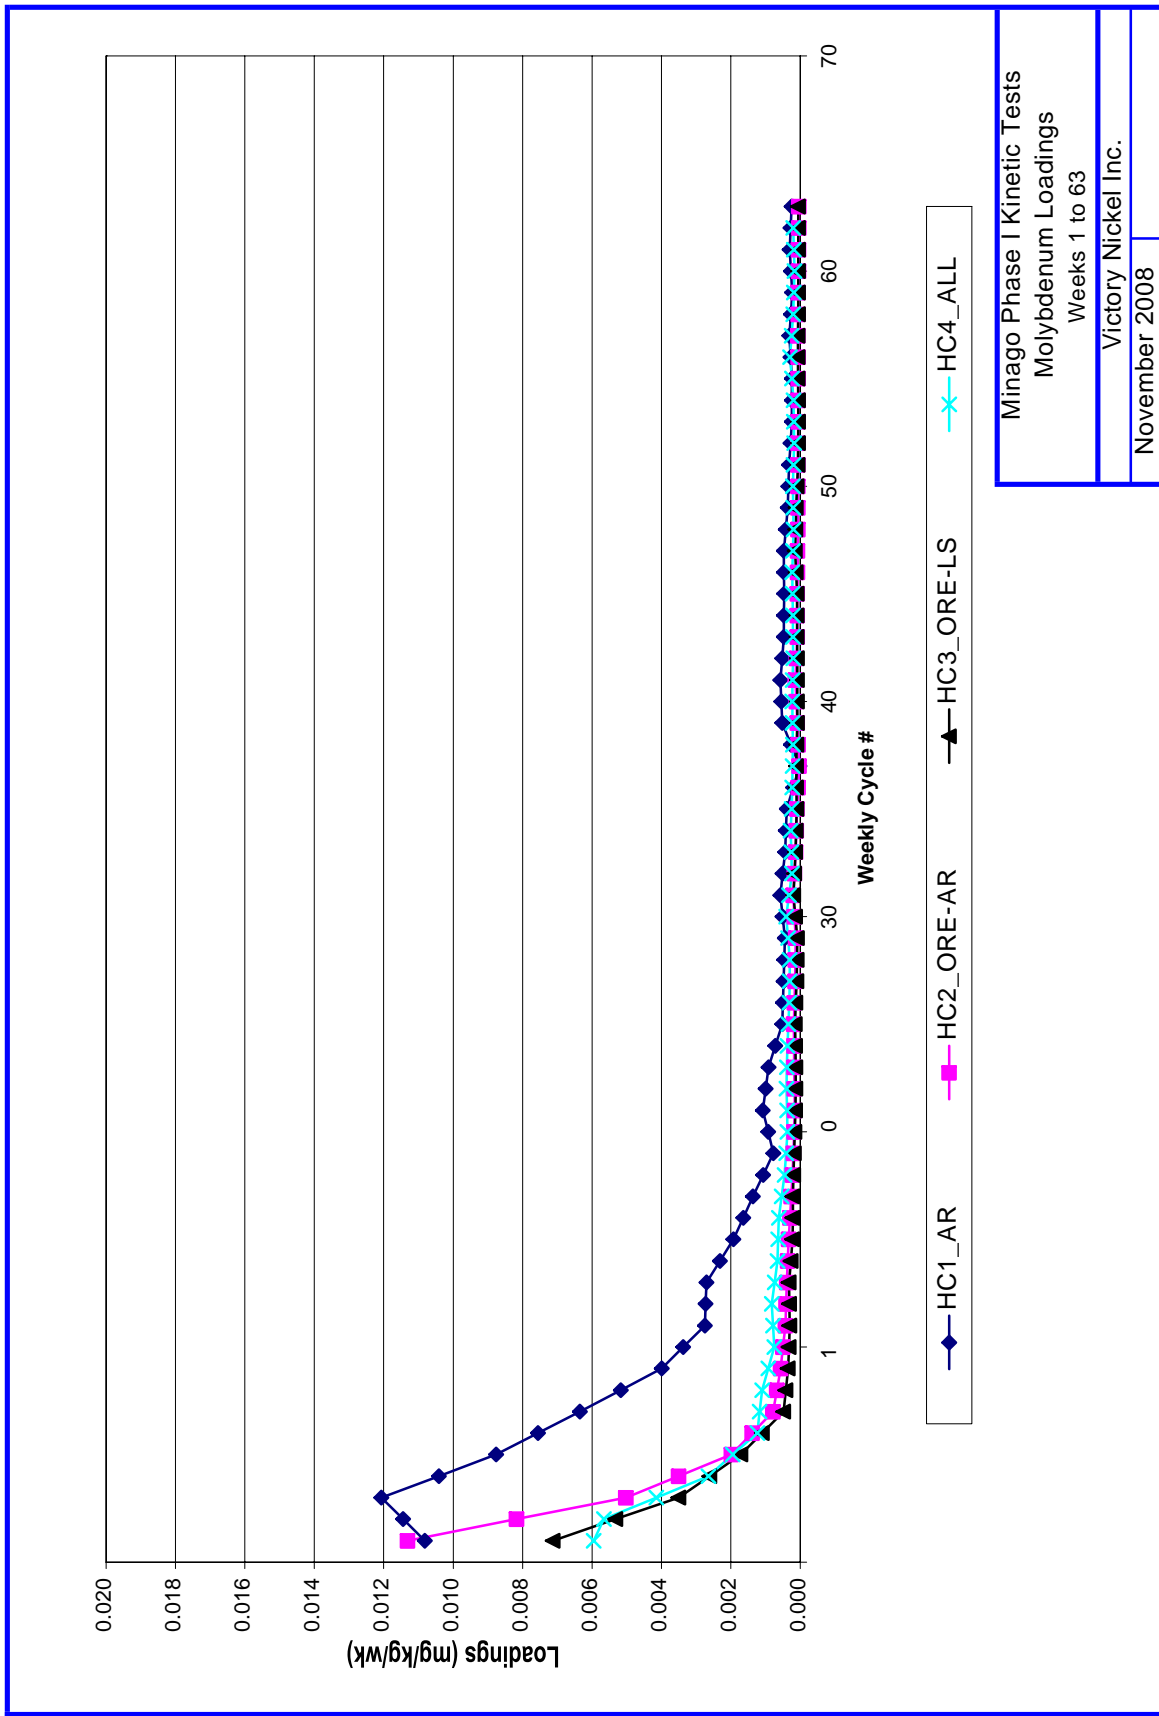


Minago Phase I Kinetic Tests
 Molybdenum Loadings
 Weeks 1 to 63
 Victory Nickel Inc.
 November 2008





Minago Phase I Kinetic Tests
 Selenium Loadings
 Weeks 1 to 63
 Victory Nickel Inc.
 November 2008

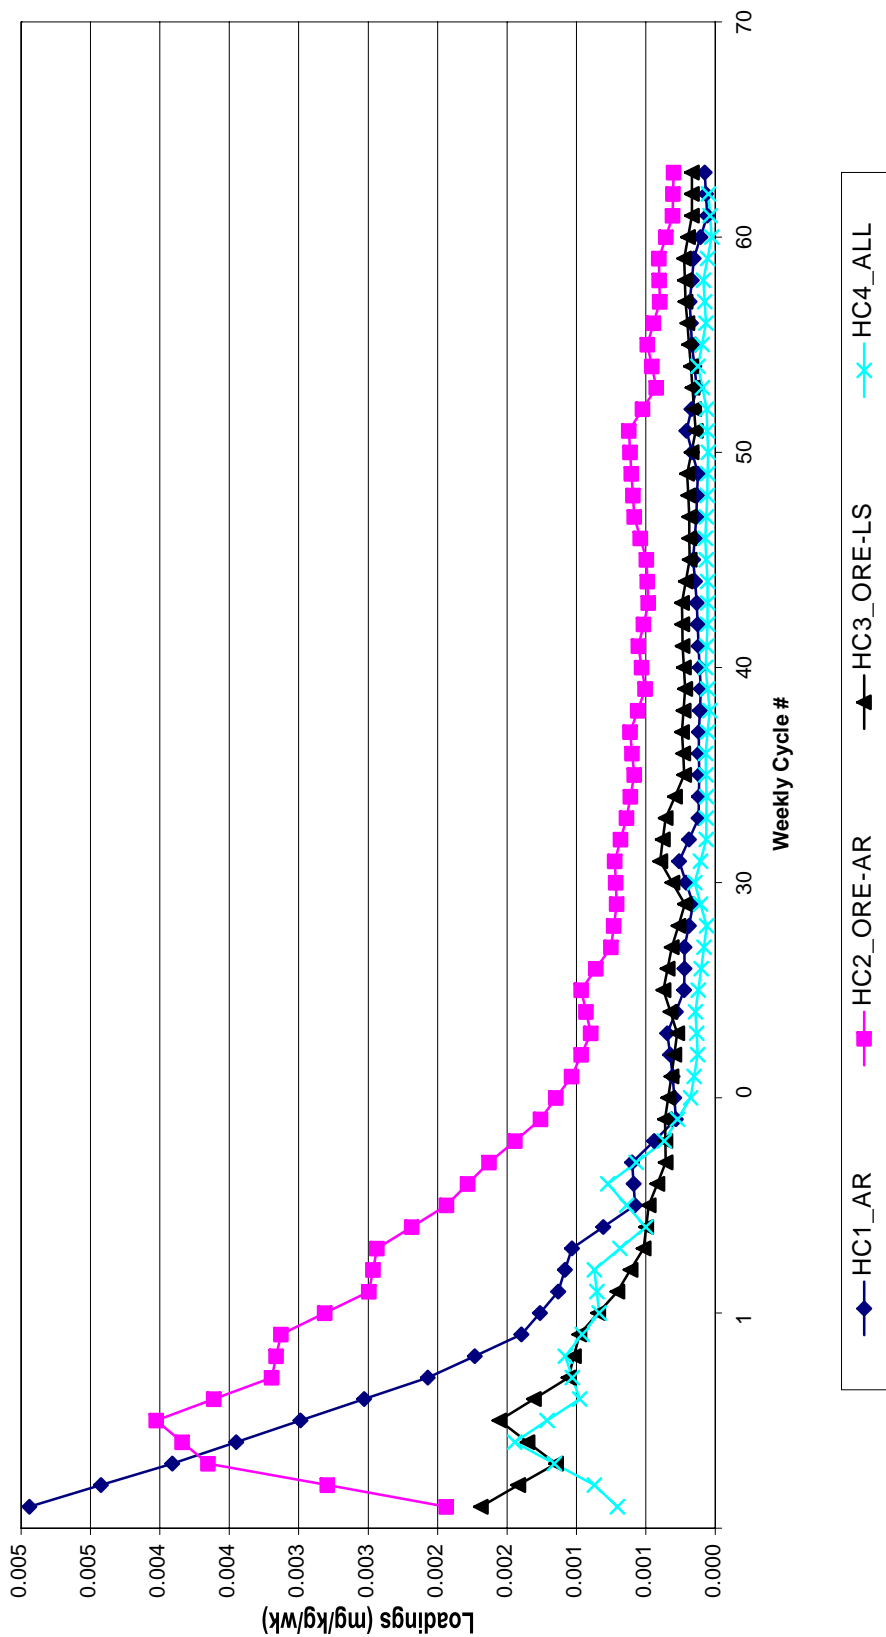

APPENDIX 2.8-B

Tailings

	Page
Appendix 2.8-B1: Static, Grainsize and Metal Results	2.8-94
Appendix 2.8-B2: 2006 SGS Lakefield Research Limited ABA Report	2.8-107
Appendix 2.8-B3: Kinetic Test Results	2.8-110

APPENDIX 2.8-B1

Static, Grainsize and Metal Results

**2006 Metallurgical Tailings Samples
Tailings Geochemical Characterization
Minago Project**

Sample #	Sample ID				Sample Weight (g)	
1	11241-1	1st cl	Tail A	CCT3	485.0	
2	11241-1	1st cl	Tail B	CCT3	707.0	
3	11241-1	1st cl	Tail C	CCT3	737.0	
4	11241-1	1st cl	Tail D	CCT3	694.0	
5	11241-1	1st cl	Tail E	CCT3	745.0	
6	11241-1	1st cl	Tail F	CCT3	765.0	4133.0
7	11241-1	Ru	Tail A	CCT3	1330.0	
8	11241-1	Ru	Tail B	CCT3	1214.0	
9	11241-1	Ru	Tail C	CCT3	1199.0	
10	11241-1	Ru	Tail D	CCT3	1180.0	
11	11241-1	Ru	Tail E	CCT3	1199.0	
12	11241-1	Ru	Tail F	CCT3	1150.0	7272.0

CLIENT : Keith Mountjoy
PROJECT : Minago (Nuinsco Resources Ltd.)
CEMI Project # : 0714
Test : Modified and Sobek Acid-Base Accounting
Date : October 22, 2007

Sample ID	Paste pH	TIC %	CaCO3 P	S(T) N	S(SO4) %	S(S-2) %	Insoluble S %	AP %	Modified NP	Sobek P	Net (Modified)		Net (Sobek) NP	Fizz Test
											N	NP		
1st Cleaner + Rougher Tails Composite	8.70	0.41	34.2	0.12	0.03	0.07	0.02	2.2	74.6	433.4	72.4	431.2	Slight	
Duplicate														
1st Cleaner + Rougher Tails Composite		0.4		0.12	0.03	0.07								

Note:

AP = Acid potential in tonnes CaCO3 equivalent per 1000 tonnes of material. AP is determined from sulphide sulphur content
 NP = Neutralization potential in tonnes CaCO3 equivalent per 1000 tonnes of material.
 NET NP = NP - AP
 Carbonate NP is calculated from TIC originating from carbonates and is expressed in kg CaCO3/tonne
 Sulphate sulphur determined by 25% HCL with gravimetric finish
 Sulphide sulphur determined by Sobek 1:7 nitric acid with gravimetric finish
 Insoluble S is acid insoluble S (Total S - (Sulphate S + Sulphide S)).

CLIENT : Keith Mounjojoy
PROJECT : Minago (Nuinsco Resources Ltd.)
CEMI Project # : 0714
Test : Metals by Aqua Regia Digestion with ICP Finish
Date : November 7, 2007

Sample ID	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm
1st Cleaner + Rougher Tails Composite	<0.2	0.89	7	166	<0.5	<5	0.92	2	48	319	46	4.51	<1	0.35	40	>15.00	435

CLIENT : Keith Mounjjoy
PROJECT : Minago (Nuinsco Resources Ltd.)
CEMI Project # : 0714
Test : Metals by Aqua Regia Digestion with ICP Finish
Date : November 7, 2007

Sample ID	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
1st Cleaner + Rougher Tailis Composite	<2	0.05	2292	111	6	0.13	9	5	11	8	0.03	<10	20	30	<10	22	6

CLIENT : Nuinsco Resources Ltd.
PROJECT : Minago
CEMI Project # : 0714
Test : Screen Assay
Date : November 22, 2007

1st Cleaner Scavenger & Rougher Tails

Sieve Designation	Aperture (mm)	Weight Retained		
		(g)	(%)	Cumulative (%)
+60	0.250	13.85	13.9%	13.9%
-60 + 100	0.150	6.48	6.5%	20.4%
-100 + 140	0.106	8.82	8.8%	29.2%
- 140 + 270	0.053	24.85	24.9%	54.1%
-270 + 325	0.045	10.38	10.4%	64.5%
-325	-0.045	35.40	35.5%	100.0%
TOTAL		99.78	100.0%	

CLIENT : Nuinsco Resources Ltd.
PROJECT : Minago
CEMI Project # : 0714
Test : Modified and Sobek Acid-Base Accounting
Date : November 30, 2007

Sample ID	Paste pH	TIC %	CaCO3 NP	S(T) %	S(SO4) %	S(S-2) %	Insoluble S %	AP	Modified NP	Sobek NP	Net (Modified) NP	Net (Sobek) NP	Fizz Test
1st Cleaner Scavenger + Rougher Tails Duplicate	8.41	0.46	38.3	0.12	0.05	0.07	<0.01	2.2	76.5	397.2	74.3	395.0	None
1st Cleaner Scavenger + Rougher Tails		0.46		0.13	0.05	0.07							

Note:

AP = Acid potential in tonnes CaCO3 equivalent per 1000 tonnes of material. AP is determined from sulphide sulphur content.
 NP = Neutralization potential in tonnes CaCO3 equivalent per 1000 tonnes of material.

NET NP = NP - AP

Carbonate NP is calculated from TIC originating from carbonates and is expressed in kg CaCO3/tonne.

Sulphate sulphur determined by 25% HCL with gravimetric finish

Sulphide sulphur determined by Sobek 1:7 nitric acid with gravimetric finish

Insoluble S is acid insoluble S (Total S - (Sulphate S + Sulphide S)).

CLIENT : Nuin sco Resources Ltd.
 PROJECT : MInago
 CEMI Project # : 0714
 Test : Metals by Aqua Regia Digestion with ICP Finish
 Date : December 4, 2007

Sample ID	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm
1st Cleaner Scavenger + Rougher Tails	<0.2	0.85	<5	19.2	0.6	<5	0.92	2	83	259	8	5.44	<1	0.5	59	>15.00	524

CLIENT
PROJECT
CEMI Project #
Test
Date

Sample ID	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Ti ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
1st Cleaner Scavenger + Rougher Tails	<2	0.03	2456	66	8	0.15	6	4	29	<5	0.02	<10	26	16	<10	60	6

CLIENT : Nuinsco Resources Ltd.
PROJECT : Minago (Nuinsco Resources Ltd.)
CEMI Project # : 0714
Test : Modified and Sobek Acid-Base Accounting
Date : May 6, 2008

Sample ID	Paste pH	TIC %	CaCO3 %	S(T) N	S(SO4) %	S(S-2) %	Insoluble S %	AP %	Modified NP	Sobek P	Net (Modified)		Net (Sobek)		Fizz Test
											N	NP	N	NP	
1st Cleaner Scavenger + Rougher Tails (1-6)	8.32	0.38	31.7	0.12	0.02	0.04	0.06	1.3	74.7	455.9	73.5	454.7		None	
Duplicate															
1st Cleaner Scavenger + Rougher Tails (1-6)	8.38	0.38		0.12	0.02	0.04			74.2	-				None	

Note:

AP = Acid potential in tonnes CaCO3 equivalent per 1000 tonnes of material. AP is determined from sulphide sulphur content

NP = Neutralization potential in tonnes CaCO3 equivalent per 1000 tonnes of material

NET NP = NP - AP

Carbonate NP is calculated from TIC originating from carbonates and is expressed in kg CaCO3/tonne.

Sulphate sulphur determined by 25% HCL with gravimetric finish

Sulphide sulphur determined by Sobek 1:7 nitric acid with gravimetric finish

Insoluble S is acid insoluble S (Total S - (Sulphate S + Sulphide S)).

CLIENT : Nuiusco Resources Ltd.
 PROJECT : Mingo (Nuiusco Resources Ltd.)
 CEMI Project # : 0714
 Test : Metals by Aqua Regia Digestion with ICP-MS Finish
 Date : May 26, 2008

Sample ID	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn
141 Cement Storage + Rougher Tank (1-6)	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm
	0.1	1.74	0.3	0.1	1	0.71	0.74	0.1	0.1	0.79	0.77	2.5	0.97	5.27	1	0.2	0.1	0.1	0.01	0.57	0.7	0.93	>1000	0.11

CLIENT
PROJECT
CEMI Project #
Test
Date

Sample ID	Mo	Na	Nb	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti	Tl	U	V	W	Y	Zn	Zr
141 Cement Storage + Roughout Table (1-6)	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm
	1.2	0.05	0.01	0.0003	0.025	1.9	25.5	0.2	0.14	0.01	0.4	0.01	0.04	0.01	0.01	0.01	0.07	0.024	0.01	0.59	2.0	0.1	0.5	1.2	0.1

CLIENT : Nuinsco Resources Ltd.
PROJECT : Minago (Nuinsco Resources Ltd.)
CEMI Project # : 0714
Test : Ra-226 Assay
Date : May 23, 2008

Sample ID	Ra-226 Bq/L
1st Cleaner Scavenger + Rougher Tails (1-6)	0.04

APPENDIX 2.8-B2

2006 SGS Lakefield Research Limited ABA Report

Environmental Met

Attn : Rob Thorpe Project Manager

Copy brianr@tbaytel.net

Wednesday, October 25, 2006

Date Rec. : 23 October 2006

LR Report: CA10415-OCT06

Copy: #1

CERTIFICATE OF ANALYSIS

Final Report

Analysis	3: Analysis Approval Date	4: Analysis Approval Time	5: Ro Tail F
Sample Date & Time			Date:NA
Paste pH [units]	25-Oct-06	14:50	9.78
Fizz Rate [---]	25-Oct-06	14:50	1
Sample [weight(g)]	25-Oct-06	14:50	1.97
HCl added [mL]	25-Oct-06	14:50	50.10
HCl [Normality]	25-Oct-06	14:50	0.10
NaOH [Normality]	25-Oct-06	14:50	0.10
NaOH to [pH=8.3 mL]	25-Oct-06	14:50	15.10
Final pH [units]	25-Oct-06	14:50	1.65
NP [t CaCO3/1000t]	25-Oct-06	14:50	88.8
AP [t CaCO3/1000 t]	25-Oct-06	09:41	0.31
Net NP [t CaCO3/1000 t]	25-Oct-06	14:51	88.5
NP/AP [ratio]	25-Oct-06	14:51	286
Total Sulphur [%]	25-Oct-06	09:23	0.066
Sulphide [%]	25-Oct-06	09:23	< 0.01
Sulphate [%]	25-Oct-06	14:34	< 0.4
Total Carbon [%]	25-Oct-06	09:23	0.36
Carbonate [%]	25-Oct-06	09:23	1.319

SGS Lakefield Research Limited

P.O. Box 4300 - 185 Concession St.

Lakefield - Ontario - K0L 2H0

Phone: 705-652-2038 FAX: 705-652-6441

Project : CALR-11241-001

LR Report : CA10415-OCT06

*NP (Neutralization Potential)

$$= 50 \times \frac{(N \text{ of HCL} \times \text{Total HCL added} - N \text{ NaOH} \times \text{NaOH added})}{\text{weight of Sample}}$$

*AP (Acid Potential) = % Sulphide Sulphur x 31.25

*Net NP (Net Neutralization Potential) = NP-AP

NP/AP Ratio = NP/AP

*Results expressed as tonnes CaCO₃ equivalent/1000 tonnes of material

Samples with a % sulphide value of <0.01 will be calculated using a 0.01 value.

Brian Graham B.Sc.

Project Coordinator

Environmental Services, Analytical

APPENDIX 2.8-B3

Kinetic Test Results for Tailings

insoluble S is acid insoluble S (Total S - (Sulphate S + Sulphide S))
 Sulphide sulphur determined by Zorex 1:1 with acid with gravimetric finish
 Sulphate sulphur determined by 22% HCl with gravimetric finish
 Carbonate IB is calculated from TIC subtracting from carbonate and is expressed in kg CaCO₃/tonne.

net-AIB = AIB - ACP

AIB = Neutralization potential in tonnes CaCO₃ equivalent per 1000 tonnes of material.

ACP = Acid potential in tonnes CaCO₃ equivalent per 1000 tonnes of material. AP is determined from sulphide sulphur content.

Note:

SAC-1 (1st Cleaner Scavenger + Rougher Tails)		0.48		0.13	0.02	0.01							
ᄀᄀᄀᄀᄀᄀ													
SAC-1 (1st Cleaner Scavenger + Rougher Tails)	8.44	0.48	38.3	0.15	0.02	0.01	<0.01	5.5	18.2	38.5	14.3	382.0	
ᄀᄀᄀᄀᄀᄀ ID	ᄀᄀᄀᄀ	ᄀᄀᄀ	IB	ᄀᄀᄀ	ᄀᄀᄀᄀ	ᄀᄀᄀᄀ	ᄀᄀᄀᄀᄀᄀ	ᄀᄀᄀ	ᄀᄀᄀᄀᄀᄀ	ᄀᄀᄀᄀᄀᄀ	(ᄀᄀᄀᄀᄀᄀ)	(ᄀᄀᄀᄀᄀᄀ)	ᄀᄀᄀᄀᄀᄀ

Date : November 30, 2007
 Test : Modified and Zorex Acid-Base Accounting
 CEMI Project # : 0714
 PROJECT : Minago
 CLIENT : NuinSCO Resources Ltd.

CLIENT : NuinSCO Resources Ltd.
 PROJECT : Minago
 CEMI Project # : 0714
 Test : Metals by Aqua Regia Digestion with ICP Finish
 Date : December 4, 2007

Sample ID	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %
SAC-1 (1st Cleaner Scavenger + Rougher Tails)	<0.2	0.85	<5	192	0.6	<5	0.92	2	93	259	8	5.44	<1	0.5

Sample ID	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm
SAC-1 (1st Cleaner Scavenger + Rougher Tails)	<2	0.03	2456	65	8	0.15	6	4	29	<5	0.02	<10	26	16

Cell No.	Sample ID	Sample Type	Method Reference	Column Dimensions			Column Packing			Pore Volume	Total Volume of Initial Flushings	Flushing Rate/Weekly Input*	Temp	Sampling Frequency	Start-up date	Sampling Day	Operation Procedure	Sample prep for flushings
				Inner Diameter (cm)	Length (cm)	Distance from Top of column to Sample (cm)	Dry Wt. of Sample (kg)	Other Materials Used	Column Material	(mL)	(mL)	(mL)	(°C)					
Subaqueous	1st Cleaner + Rougher Tails	Tailings	MEND	17.00	60.00		5.00	Plexiglas perforated disk & nylon mesh	Plexiglas	2700			20-22 °C	Weekly	31-Oct	Wednesday	Recirculation	none

Subaqueous Column - Surface Water

Sample = 1st Cleaner + Rougher Tails

Date	Cycle No.	Volume		pH	ORP mV	Cond. umhos/cm	Acidity (pH 4.5) mgCaCO3/L	Acidity (pH 8.3) mgCaCO3/L	Alkalinity mgCaCO3/L	Sulphate mg/L	Dissolved Oxygen mg/L	Hardness CaCO3 mg/L	Al mg/L	Sb mg/L	As mg/L	Ba mg/L	Be mg/L	Bi mg/L	B mg/L	Cd mg/L	Ca mg/L	Cr mg/L	Co mg/L	Cu mg/L
		Input mL	Output L																					
31-Oct-07	1	160	0.16	6.90	258	754	#N/A	4.2	24.3	125	8.50	109	0.0054	0.0011	0.0021	0.0143	<0.00001	<0.000005	0.378	0.000486	23.3	0.0004	0.0001	0.0049
07-Nov-07	2	100	0.10	6.58	500	1351	#N/A			123	#NA	120	0.019	0.0019	0.0308	0.021	<0.0001	<0.001	0.51	0.00011	26.9	<0.001	<0.0005	0.0153
14-Nov-07	3	160	0.16	7.19	149	875	#N/A	3.5	47.6	133	#NA	123	0.0027	0.0004	0.0002	0.0258	<0.00001	<0.000005	0.676	0.00004	28.1	0.0002	0.0002	0.0019
21-Nov-07	4	100	0.10	7.44	397	572	#N/A			118	#NA	129	0.004	0.0006	0.0031	0.029	<0.0001	<0.001	0.671	0.00002	30.6	<0.001	<0.0005	0.0014
28-Nov-07	5	160	0.16	7.53	413	557	#N/A	4.7	54.8	129	8.90	121	0.0035	0.0007	0.0088	0.0332	<0.00001	<0.000005	0.73	0.000027	27.8	0.0001	0.0002	0.0018
05-Dec-07	6	100	0.10	7.36	323	613	#N/A			124		136	0.007	0.0006	0.001	0.032	<0.0001	<0.001	0.725	0.00003	32.5	<0.001	<0.0005	0.0012
12-Dec-07	7	160	0.16	7.35	378	605	#N/A	3.5	56.3	140	8.80	134	0.0053	0.0004	0.0007	0.0339	<0.00001	<0.000005	0.767	0.000029	32.1	0.0005	0.0002	0.0029
19-Dec-07	8	100	0.10	7.33	265	604	#N/A			114		132	0.004	<0.0005	0.0005	0.028	<0.0001	<0.001	0.684	0.00002	30.7	<0.001	<0.0005	0.0029
26-Dec-07	9	160	0.16	7.59	343	669	#N/A	2.6	59.3	140	6.50	137	0.0093	0.0003	0.0003	0.0375	<0.00001	<0.000005	0.807	0.000016	31.7	0.0003	0.0002	0.003
02-Jan-08	10	100	0.10	7.61	315	606	#N/A			110		151	0.004	0.0005	0.0036	0.035	<0.0001	<0.001	0.919	0.00003	34.8	<0.001	<0.0005	0.0023
09-Jan-08	11	160	0.16	7.59	280	575	#N/A	3.3	59.2	150	8.60	138	0.0032	0.0004	0.0007	0.0379	<0.00001	<0.000005	0.894	0.0000116	32.6	<0.0001	0.0001	0.0023
16-Jan-08	12	100	0.10	7.65	245	570	#N/A			119		136	0.003	<0.0005	0.0002	0.036	<0.0001	<0.001	0.799	<0.00001	31.7	<0.001	<0.0005	0.0009
23-Jan-08	13	160	0.16	7.37	335	555	#N/A	5.6	60.0	140	11.10	136	0.0019	0.0003	0.0002	0.0384	<0.00001	<0.000005	0.892	0.000008	30.9	<0.0001	0.0001	0.0014
30-Jan-08	14	100	0.10	7.83	269	515	#N/A			104		127	0.003	<0.0005	0.0008	0.041	<0.0001	<0.001	0.924	<0.00001	28.5	<0.001	<0.0005	0.0018
06-Feb-08	15	160	0.16	7.30	370	514	#N/A	4.2	60.0	130	6.80	130	0.0031	0.0003	0.0006	0.0389	<0.00001	<0.000005	0.916	0.000026	30.1	<0.0001	0.0001	0.0028
13-Feb-08	16	100	0.10	6.45	487	374	#N/A			106		124	0.037	<0.0005	0.0028	0.038	<0.0001	<0.001	0.844	0.00002	29.3	<0.001	<0.0005	0.0046
20-Feb-08	17	160	0.16	7.79	382	492	#N/A	4.4	59.0	132	6.60	130	0.0043	0.0003	0.0012	0.0377	<0.00001	<0.000005	0.987	0.000013	29.5	<0.0001	0.00008	0.0032
27-Feb-08	18	100	0.10	7.36	265	511	#N/A			87		125	0.004	<0.0005	0.0032	0.036	<0.0001	<0.001	0.872	<0.00001	29	<0.001	<0.0005	0.003
05-Mar-08	19	160	0.16	7.35	383	535	#N/A	6.0	58.6	110	10.10	124	0.0053	0.0004	0.0006	0.0374	<0.00001	<0.000005	0.933	0.000011	28.7	<0.0001	0.00005	0.003
12-Mar-08	20	100	0.10	7.37	221	524	#N/A			93		121	0.003	<0.0005	0.0027	0.037	<0.0001	<0.001	0.869	<0.00001	27.7	<0.001	<0.0005	0.0009
19-Mar-08	21	160	0.16	7.54	419	519	#N/A	4.0	56.2	110	9.50	119	0.004	0.0003	0.0005	0.0365	<0.00001	<0.000005	0.928	0.000079	27.2	0.0002	0.0004	0.0037
26-Mar-08	22	100	0.10	7.59	252	523	#N/A			92		123	0.013	<0.0005	0.0009	0.034	<0.0001	<0.001	0.814	0.00003	28.1	<0.001	<0.0005	0.0027
02-Apr-08	23	160	0.16	7.08	412	470	#N/A	3.8	55.5	97	8.25	112	0.0036	0.0004	0.001	0.0335	0.00003	<0.000005	0.826	0.000013	26.3	0.0002	0.00003	0.0022
09-Apr-08	24	100	0.10	7.43	270	427	#N/A			81		113	0.004	<0.0005	0.0008	0.035	<0.0001	<0.001	0.851	0.00003	26.9	<0.001	<0.0005	0.002
16-Apr-08	25	160	0.16	7.63	364	432	#N/A	4.1	56.0	86	7.00	111	0.0049	0.0003	0.0002	0.0359	0.00003	<0.000005	0.798	0.000012	25.6	<0.0001	0.00004	0.0019
23-Apr-08	26	100	0.10	8.15	390	448	#N/A			86		115	0.005	<0.0005	0.0002	0.04	<0.0001	<0.001	0.928	<0.00001	26.8	<0.001	<0.0005	0.0013
30-Apr-08	27	160	0.16	7.65	391	445	#N/A	3.1	55.2	84	8.20	102	0.0117	0.0003	0.0001	0.0354	0.00001	<0.000005	0.745	0.00002	24.2	0.0001	0.00004	0.0038
07-May-08	28	100	0.10	7.54	384	451	#N/A			81		101	0.007	<0.0005	0.0004	0.038	<0.0001	<0.001	0.762	0.00002	23.2	<0.001	<0.0005	0.0044
14-May-08	29	160	0.16	7.32	387	437	#N/A	3.9	53.6	100	8.20	113	0.0039	0.0003	0.0002	0.04	<0.00001	<0.000005	0.891	0.00001	25.5	0.0002	0.00006	0.0024
21-May-08	30	100	0.10	7.55	418	370	#N/A			61		105	0.001	<0.0005	0.0002	0.037	<0.0001	<0.001	0.716	<0.00001	24.1	<0.001	<0.0005	0.0012
28-May-08	31	160	0.16	7.16	410	361	#N/A	4.1	53.1	75	9.50	100	0.0024	0.0003	0.0001	0.0369	0.00001	<0.000005	0.653	0.000008	22.7	<0.0001	0.00002	0.0046
04-Jun-08	32	100	0.10	7.32	419	371	#N/A			79		94.9	0.007	<0.0005	0.0005	0.037	<0.0001	<0.001	0.719	0.00001	21.9	<0.001	<0.0005	0.0084
11-Jun-08	33	160	0.16	7.45	416	345	#N/A	3.6	52.2	62	8.00	93.5	0.0036	0.0002	0.0001	0.0354	0.00001	<0.000005	0.79	<0.000005	21.9	0.0001	0.00002	0.007
18-Jun-08	34	100	0.10	7.71	312	355	#N/A			55		94.7	0.004	<0.0005	0.0003	0.032	0.00001	<0.001	0.8	<0.00001	22.1	<0.001	<0.0005	0.0046
25-Jun-08	35	160	0.16	7.34	445	331	#N/A	5.5	59.6	66	9.40	97.6	0.0023	0.0002	0.0001	0.0367	0.00002	<0.000005	0.692	0.000015	22.8	0.0002	0.00003	0.0047
02-Jul-08	36	100	0.10	7.59	374	326	#N/A			59		96.7	0.006	<0.0005	0.0001	0.037	0.00001	<0.001	0.681	0.00001	22.7	<0.001	<0.0005	0.0039
09-Jul-08	37	160	0.16	7.59	388	321	#N/A	3.3	51.7	52	9.40	92.6	0.0035	0.0003	0.0001	0.0398	0.00001	<0.000005	0.68	0.000015	22.3	0.0002	0.00003	0.0015
16-Jul-08	38	100	0.10	7.94	311	327	#N/A			57		93	0.006	<0.0005	0.0003	0.036	0.00001	<0.001	0.695	<0.00001	21.6	<0.001	<0.0005	0.0015
23-Jul-08	39	160	0.16	7.99	389	263	#N/A	4.1	56.0	56	8.60	90.7	0.0046	0.0002	0.0009	0.0358	0.00001	0.000032	0.689	0.000023	21.5	<0.0001	0.00002	0.0023
30-Jul-08	40	100	0.10	7.27	375	311	#N/A			56		91.2	0.006	<0.0005	0.0001	0.038	0.00001	<0.001	0.671	<0.00001	21.4	<0.001	<0.0005	0.0011
06-Aug-08	41	160	0.16	7.86	412	308	#N/A	3.1	52.1	49	7.50	89.2	0.0039	0.0003	0.0001	0.0387	0.00001	<0.000005	0.639	0.000024	21.0	<0.0001	0.00002	0.0016
13-Aug-08	42	100	0.10	7.75	363	316	#N/A			48		92.7	0.067	<0.0005	0.0001	0.04	<0.0001	<0.001	0.75	<0.00001	21.5	<0.001	<0.0005	0.0018
20-Aug-08	43	160	0.16	8.08	333	313	#N/A	3.0	53.3	46	8.50	87.4	0.0031	0.0002	0.0009	0.0373	0.00001	<0.000005	0.598	0.000028	20.2	0.0003	0.00002	0.0025
27-Aug-08	44	100	0.10	7.91	353	305	#N/A			50		86.1	0.004	<0.0005	0.0001	0.036	0.00001	<0.001	0.546	0.0001	20.2	<0.001	<0.0005	0.0032
03-Sep-08	45	160	0.16	7.65	252	319	#N/A	5.2	55.9	50	9.90	84.9	0.0125	0.0002	0.0004	0.039	0.00002	0.000006	0.648	0.000018	19.9	0.0001	0.00003	0.0061
10-Sep-08	46	100	0.10	7.50	213	351	#N/A			51		89.1	0.004	<0.0005	0.0002	0.037	0.00001	<0.001	0.587	0.00001	20.7	<0.001	<0.0005	0.0017
17-Sep-08	47	160	0.16	7.73	147	324	#N/A	3.5	51.3	48	9.10	84	0.005	0.0002	0.0001	0.0376	0.00002	<0.000005	0.595	0.000014	19.8	<0.0001	0.00003	0.004
24-Sep-08	48	100	0.10	7.66	313	310	#N/A			53		84.4	0.002	<0.0005	0.0001	0.04	<0.0001	<0.001	0.688	0.00002	19.7	<0.001	<0.0005	0.0029
01-Oct-08	49	160	0.16	7.71	260	306	#N/A	3.7	50.1	45	9.00	79.6	0.045	0.0002	0.0002	0.0399	0.00001	<0.000005	0.61	0.000014	18.7			

Subaqueous Column - Surface Water

Sample = 1st Cleaner + Rougher Tails

Date	Cycle No.	Fe	Pb	Li	Mg	Mn	Hg	Mo	Ni	P	K	Se	Si	Ag	Na	Sr	S	Tl	Sn	Ti	U	V	Zn	Zr
		mg/L	mg/L	mg/L	mg/L	mg/L	ug/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L
31-Oct-07	1	0.003	0.00026	0.0095	12.3	0.0058	<0.01	0.0033	0.0139	<0.002	11.2	0.0012	0.454	0.000011	52.8	0.116	41	0.000152	0.0062	<0.0005	0.000032	<0.0002	0.0157	<0.0001
07-Nov-07	2	0.201	0.0034		12.9	0.003		0.004	0.023	<0.01	10.9	0.0019	0.834	0.00006	58	0.155	45	0.00022	0.016	<0.005	<0.0001	<0.005	0.007	<0.0005
14-Nov-07	3	0.002	0.00006	0.0134	12.9	0.0036	<0.01	0.005	0.023	0.003	11.1	0.0014	0.975	0.000005	58.1	0.161	44	0.000218	0.022	<0.0005	0.000057	<0.0002	0.0027	<0.0001
21-Nov-07	4	<0.005	<0.0002		12.8	0.003		0.005	0.024	<0.01	12.2	0.0014	1.16	0.00002	52.9	0.171	47	0.00024	0.024	<0.005	<0.0001	<0.005	<0.005	<0.0005
28-Nov-07	5	0.003	0.00017	0.0163	12.5	0.0032	<0.01	0.0059	0.0236	0.151	12.1	0.0013	1.33	0.000009	54.8	0.188	41	0.000302	0.0281	<0.0005	0.000083	<0.0002	0.0037	<0.0001
05-Dec-07	6	0.007	0.0005		13.2	0.002		0.006	0.026	0.05	14.2	0.0013	1.27	<0.00002	51.7	0.176	51	0.00031	0.026	<0.005	<0.0001	<0.005	<0.005	<0.0005
12-Dec-07	7	0.004	0.00005	0.0175	13	0.0044	<0.01	0.006	0.0259	0.004	12.9	0.0009	1.49	<0.000005	48.7	0.188	51	0.000307	0.0269	<0.0005	0.000132	0.0003	0.0267	0.0001
19-Dec-07	8	<0.005	<0.0002		13.4	0.003		0.005	0.027	<0.01	13.2	0.0008	1.38	<0.00002	50.8	0.172	48	0.00029	0.023	<0.005	0.0001	<0.005	<0.005	<0.0005
26-Dec-07	9	0.023	0.00018	0.0181	14.2	0.0029	<0.01	0.0063	0.0267	0.003	13.9	0.0007	1.57	<0.000005	50.8	0.207	49	0.000346	0.0251	<0.0005	0.000102	<0.0002	0.0014	<0.0001
02-Jan-08	10	<0.005	0.0005		15.6	0.004		0.006	0.026	<0.01	14.3	0.0007	2.02	<0.00002	52.2	0.204	56	0.00035	0.022	<0.005	0.0001	<0.005	<0.005	<0.0005
09-Jan-08	11	0.001	0.00006	0.0174	13.7	0.0029	<0.01	0.0061	0.0236	0.002	13.9	0.0007	1.55	<0.000005	45.8	0.194	51	0.000345	0.0216	<0.0005	0.000094	<0.0002	0.0022	<0.0001
16-Jan-08	12	0.007	<0.0002		13.9	0.003		0.006	0.024	<0.01	12.7	0.0006	1.53	<0.00002	45.5	0.182	47	0.00033	0.022	<0.005	<0.0001	<0.005	<0.005	<0.0005
23-Jan-08	13	0.001	0.00116	0.0197	14.3	0.0029	<0.01	0.006	0.0263	<0.002	13.6	0.0006	1.81	<0.000005	45.9	0.195	47	0.000355	0.022	<0.0005	0.000091	<0.0002	0.0022	<0.0001
30-Jan-08	14	0.013	<0.0002		13.5	0.003		0.006	0.026	<0.01	12.9	0.0006	2.02	<0.00002	43.9	0.203	44	0.00038	0.023	<0.005	0.0001	<0.005	<0.005	<0.0005
06-Feb-08	15	0.002	0.00107	0.0182	13.4	0.0028	0.02	0.006	0.0235	<0.002	13.5	0.0005	1.67	<0.000005	44	0.192	44	0.000344	0.0199	<0.0005	0.000095	<0.0002	0.0029	<0.0001
13-Feb-08	16	0.031	0.002		12.5	0.003		0.006	0.023	<0.01	13.5	0.0005	1.59	<0.00002	38.9	0.187	42	0.00033	0.016	<0.005	0.0001	<0.005	<0.005	<0.0005
20-Feb-08	17	0.003	0.00007	0.0181	13.7	0.0026	<0.01	0.0058	0.0232	0.002	13.7	0.0005	1.93	<0.000005	45	0.185	45	0.000342	0.0191	<0.0005	0.000091	<0.0002	0.0079	<0.0001
27-Feb-08	18	<0.005	<0.0002		12.7	0.002		0.006	0.022	<0.01	13.6	0.0005	1.62	<0.00002	36.7	0.182	43	0.00033	0.018	<0.005	<0.0001	<0.005	<0.005	<0.0005
05-Mar-08	19	0.013	0.00003	0.0175	12.6	0.0012	<0.01	0.0056	0.0202	0.002	12.8	0.0005	1.8	<0.000005	36.8	0.179	41	0.000335	0.0165	<0.0005	0.000104	<0.0002	0.0013	<0.0001
12-Mar-08	20	<0.005	<0.0002		12.6	0.002		0.006	0.019	<0.01	12.6	0.0004	2.15	<0.00002	34.9	0.186	39	0.00024	0.017	<0.005	<0.0001	<0.005	<0.005	<0.0005
19-Mar-08	21	0.004	0.00039	0.0201	12.4	0.0016	<0.01	0.0053	0.0193	0.004	16.9	0.0004	1.82	0.000005	34.2	0.173	40	0.000313	0.0152	0.0025	0.000077	<0.0002	0.0172	<0.0001
26-Mar-08	22	<0.005	0.0016		12.9	0.002		0.005	0.017	<0.01	13.3	0.0004	3.15	<0.00002	35.7	0.177	40	0.00022	0.014	<0.005	<0.0001	<0.005	<0.005	<0.0005
02-Apr-08	23	<0.001	0.00003	0.0171	11.4	0.0006	<0.01	0.0054	0.0172	0.008	12.5	0.0004	1.69	<0.000005	30.8	0.175	37	0.000314	0.0148	0.0014	0.000072	<0.0002	0.0048	<0.0001
09-Apr-08	24	<0.005	0.0017		11.2	0.002		0.005	0.015	<0.01	48.6	0.0004	1.84	0.00003	30.1	0.165	36	0.00015	0.012	<0.005	<0.0001	<0.005	<0.005	<0.0005
16-Apr-08	25	0.007	7.8E-05	0.0159	11.5	0.0008	<0.01	0.0048	0.0197	0.005	12.9	0.0003	1.95	<0.000005	31.4	0.156	34	0.000314	0.0136	<0.0005	0.000084	<0.0002	0.0021	<0.0001
23-Apr-08	26	<0.005	<0.0002		11.8	<0.001		0.005	0.018	<0.01	12.5	0.0003	1.86	<0.00002	27.3	0.163	33	0.00033	0.013	<0.005	<0.0001	<0.005	<0.005	<0.0005
30-Apr-08	27	0.01	0.00009	0.0173	10.2	0.0013	<0.01	0.0052	0.0158	0.069	11.6	0.0004	1.82	0.000007	25	0.16	30	0.000311	0.0126	<0.0005	0.000087	<0.0002	0.0021	<0.0001
07-May-08	28	0.006	<0.0002		10.4	0.003		0.005	0.015	0.105	11.4	0.0004	1.78	<0.00002	24.8	0.153	29	0.00031	0.013	<0.005	<0.0001	<0.005	<0.005	<0.0005
14-May-08	29	0.002	0.000219	0.0168	11.9	0.0073	<0.01	0.0048	0.0158	0.191	12.2	0.0003	2.05	<0.000005	28.2	0.156	34	0.000323	0.0129	<0.0005	0.000065	<0.0002	0.0038	<0.0001
21-May-08	30	<0.005	<0.0002		10.8	0.002		0.005	0.014	<0.01	11.1	0.0004	1.56	<0.00002	24.8	0.154	30	0.00029	0.012	<0.005	<0.0001	<0.005	<0.005	<0.0005
28-May-08	31	0.003	0.00319	0.0163	10.6	0.0008	<0.01	0.0045	0.0144	0.369	11.3	0.0003	1.89	<0.000005	24	0.144	29	0.000307	0.0112	<0.0005	0.000066	<0.0002	0.0022	<0.0001
04-Jun-08	32	<0.005	0.0003		9.77	<0.001		0.004	0.014	<0.01	9.75	0.0003	1.71	<0.00002	22.8	0.136	27	0.00029	0.009	<0.005	<0.0001	<0.005	<0.005	<0.0005
11-Jun-08	33	0.002	0.00004	0.0146	9.45	0.0003	<0.01	0.0042	0.0128	0.337	10.9	0.0002	1.89	<0.000005	22.1	0.13	27	0.000277	0.0089	<0.0005	0.000051	<0.0002	0.0038	<0.0001
18-Jun-08	34	0.006	<0.0002		9.59	0.001		0.004	0.011	0.066	9.91	0.0003	1.81	<0.00002	20.5	0.153	27	0.00015	0.009	<0.005	<0.0001	<0.005	<0.005	<0.0005
25-Jun-08	35	0.005	0.00015	0.0168	9.9	0.0007	<0.01	0.0041	0.0138	0.183	10.2	0.0003	1.89	0.000006	20.2	0.134	27	0.000293	0.009	<0.0005	0.000071	<0.0002	0.0041	<0.0001
02-Jul-08	36	<0.005	<0.0002		9.73	0.002		0.004	0.013	0.115	10.7	0.0003	1.83	<0.00002	20.2	0.142	27	0.00032	0.01	<0.005	<0.0001	<0.005	<0.005	<0.0005
09-Jul-08	37	0.005	0.00011	0.0157	8.97	0.0018	<0.01	0.0042	0.0119	0.084	10.2	0.0003	1.85	<0.000005	18	0.139	26	0.000317	0.0087	<0.0005	0.000058	<0.0002	0.0047	<0.0001
16-Jul-08	38	0.006	<0.0002		9.51	0.001		0.004	0.012	0.02	10.4	0.0002	1.75	<0.00002	19.1	0.144	25	0.00023	0.007	<0.005	<0.0001	<0.005	<0.005	<0.0005
23-Jul-08	39	0.003	0.00029	0.0149	8.99	0.0003	<0.01	0.0041	0.0115	0.109	10.5	0.0004	1.5	<0.000005	18.4	0.131	23	0.000266	0.0074	0.001	0.000052	0.0002	0.0027	<0.0001
30-Jul-08	40	0.018	<0.0002		9.15	<0.001		0.004	0.015	0.101	9.81	0.0002	1.83	<0.00002	17	0.13	24	0.00027	0.007	<0.005	<0.0001	<0.005	<0.005	<0.0005
06-Aug-08	41	0.008	0.00087	0.0153	8.93	0.0006	<0.01	0.0039	0.011	0.003	9.63	0.0002	1.77	<0.000005	16.7	0.127	23	0.000295	0.0068	<0.0005	0.000041	<0.0002	0.024	<0.0001
13-Aug-08	42	0.01	0.0004		9.45	<0.001		0.004	0.012	0.067	10.1	0.0002	1.87	<0.00002	17.6	0.128	24	0.00028	0.006	<0.005	<0.0001	<0.005	<0.005	<0.0005
20-Aug-08	43	0.003	0.00013	0.0146	9	0.0004	<0.01	0.0038	0.0107	0.006	9.38	0.0002	1.61	<0.000005	16.3	0.126	22	0.000293	0.0075	<0.0005	0.000038	<0.0002	0.0015	<0.0001
27-Aug-08	44	0.007	0.0006		8.65	0.001		0.003	0.011	0.284	10.1	0.0002	1.67	<0.00002	15.5	0.121	20	0.00032	0.006	<0.005	<0.0001	<0.005	<0.005	<0.0005
03-Sep-08	45	0.012	0.00508	0.0143	8.55	0.0004	<0.01	0.0037	0.0117	0.022	9.62	0.0003	1.57	<0.000005	15.1	0.121	21	0.000264	0.0068	<0.0				

Subaqueous Column - Surface Water
 Sample = 1st Cleaner + Rougher Tails

Date	Cycle No.	Volume Input mL	Volume Output L	pH	ORP mV	Cond. umhos/cm	Acidity (pH 4.5) mgCaCO3/L	Acidity (pH 8.3) mg/kg/wk	Alkalinity mg/kg/wk	Sulphate mg/kg/wk	Dissolved Oxygen mg/L	Hardness CaCO3 mg/L	Al mg/kg/wk	Sb mg/kg/wk	As mg/kg/wk	Ba mg/kg/wk	Be mg/kg/wk	Bi mg/kg/wk	B mg/kg/wk	Cd mg/kg/wk	Ca mg/kg/wk	Cr mg/kg/wk	Co mg/kg/wk	Cu mg/kg/wk	Fe mg/kg/wk	Pb mg/kg/wk
31-Oct-07	1	160	0.16	6.90	258	754	#N/A	0.1	0.8	4.00	8.50	109	0.00017	0.00003	0.00007	0.00046	0.00000	0.0000020	0.0121	0.00016	0.75	0.00001	0.00000	0.00016	0.0001	0.00008
07-Nov-07	2	100	0.10	6.58	500	1351	#N/A			2.46		120	0.00038	0.00004	0.00062	0.00042	0.00000	0.0000200	0.0102	0.00002	0.54	0.00002	0.00001	0.00031	0.0040	0.00068
14-Nov-07	3	160	0.16	7.19	149	875	#N/A	0.1	1.5	4.26		123	0.00009	0.00001	0.00006	0.00083	0.00000	0.0000002	0.0216	0.00001	0.90	0.00001	0.00000	0.00006	0.001	0.00002
21-Nov-07	4	100	0.10	7.44	397	572	#N/A			2.36		129	0.00008	0.00001	0.00006	0.00058	0.00000	0.0000200	0.0134	0.00000	0.61	0.00002	0.00001	0.00003	0.001	0.00004
28-Nov-07	5	160	0.16	7.53	413	557	#N/A	0.2	1.8	4.13	8.90	121	0.00011	0.00002	0.00028	0.00106	0.00000	0.0000002	0.0234	0.00001	0.89	0.00000	0.00001	0.00006	0.001	0.00005
05-Dec-07	6	100	0.10	7.36	323	613	#N/A			2.48		136	0.00014	0.00001	0.00002	0.00064	0.00000	0.0000200	0.0145	0.00001	0.65	0.00002	0.00001	0.00002	0.001	0.00010
12-Dec-07	7	160	0.16	7.35	378	605	#N/A	0.1	1.8	4.48	8.80	134	0.00017	0.00001	0.00002	0.00108	0.00000	0.0000002	0.0245	0.00001	1.03	0.00002	0.00001	0.00009	0.001	0.00002
19-Dec-07	8	100	0.10	7.33	265	604	#N/A			2.28		132	0.00008	0.00001	0.00001	0.00056	0.00000	0.0000200	0.0137	0.00000	0.61	0.00002	0.00001	0.00006	0.001	0.00004
26-Dec-07	9	160	0.16	7.59	343	669	#N/A	0.1	1.9	4.48	6.50	137	0.00030	0.00001	0.00001	0.00120	0.00000	0.0000002	0.0258	0.00001	1.01	0.00001	0.00000	0.00010	0.001	0.00006
02-Jan-08	10	100	0.10	7.61	315	606	#N/A			2.20		151	0.00008	0.00001	0.00007	0.00070	0.00000	0.0000200	0.0184	0.00001	0.70	0.00002	0.00001	0.00005	0.001	0.00010
09-Jan-08	11	160	0.16	7.59	280	575	#N/A	0.1	1.9	4.80	8.60	138	0.00010	0.00001	0.00002	0.00121	0.00000	0.0000002	0.0286	0.00004	1.04	0.00000	0.00000	0.00007	0.001	0.00002
16-Jan-08	12	100	0.10	7.65	245	570	#N/A			2.38		136	0.00006	0.00001	0.00000	0.00072	0.00000	0.0000200	0.0160	0.00000	0.63	0.00002	0.00001	0.00002	0.001	0.00004
23-Jan-08	13	160	0.16	7.37	335	555	#N/A	0.2	1.9	4.48	11.10	136	0.00006	0.00001	0.00001	0.00123	0.00000	0.0000002	0.0285	0.00000	0.99	0.00000	0.00000	0.00004	0.001	0.00003
30-Jan-08	14	100	0.10	7.83	269	515	#N/A			2.08		127	0.00006	0.00001	0.00002	0.00082	0.00000	0.0000200	0.0185	0.00000	0.57	0.00002	0.00001	0.00004	0.001	0.00004
06-Feb-08	15	160	0.16	7.30	370	514	#N/A	0.1	1.9	4.16	6.80	130	0.00010	0.00001	0.00002	0.00124	0.00000	0.0000002	0.0293	0.00001	0.96	0.00000	0.00000	0.00009	0.001	0.00004
13-Feb-08	16	100	0.10	6.45	487	374	#N/A			2.12		124	0.00074	0.00001	0.00006	0.00076	0.00000	0.0000200	0.0169	0.00000	0.59	0.00002	0.00001	0.00009	0.001	0.00004
20-Feb-08	17	160	0.16	7.79	382	492	#N/A	0.1	1.9	4.22	6.60	130	0.00014	0.00001	0.00004	0.00121	0.00000	0.0000002	0.0316	0.00000	0.94	0.00000	0.00000	0.00010	0.001	0.00002
27-Feb-08	18	100	0.10	7.36	265	511	#N/A			1.74		125	0.00008	0.00001	0.00006	0.00072	0.00000	0.0000200	0.0174	0.00000	0.58	0.00002	0.00001	0.00006	0.001	0.00004
05-Mar-08	19	160	0.16	7.35	383	535	#N/A	0.2	1.9	3.52	10.10	124	0.00017	0.00001	0.00002	0.00120	0.00000	0.0000002	0.0299	0.00000	0.92	0.00000	0.00000	0.00010	0.001	0.00001
12-Mar-08	20	100	0.10	7.37	221	524	#N/A			1.86		121	0.00006	0.00001	0.00005	0.00074	0.00000	0.0000200	0.0174	0.00000	0.55	0.00002	0.00001	0.00002	0.001	0.00004
19-Mar-08	21	160	0.16	7.54	419	519	#N/A	0.1	1.8	3.52	9.50	119	0.00013	0.00001	0.00001	0.00117	0.00000	0.0000002	0.0297	0.00003	0.87	0.00001	0.00001	0.00012	0.001	0.00012
26-Mar-08	22	100	0.10	7.59	252	523	#N/A			1.84		123	0.00026	0.00001	0.00002	0.00068	0.00000	0.0000200	0.0163	0.00001	0.56	0.00002	0.00001	0.00004	0.001	0.00003
02-Apr-08	23	160	0.16	7.08	412	470	#N/A	0.1	1.8	3.10	8.25	112	0.00012	0.00001	0.00003	0.00107	0.00000	0.0000002	0.0264	0.00000	0.84	0.00001	0.00000	0.00007	0.001	0.00001
09-Apr-08	24	100	0.10	7.43	270	427	#N/A			1.62		113	0.00008	0.00001	0.00002	0.00070	0.00000	0.0000200	0.0170	0.00001	0.54	0.00002	0.00001	0.00004	0.001	0.00004
16-Apr-08	25	160	0.16	7.63	364	432	#N/A	0.1	1.8	2.75	7.00	111	0.00016	0.00001	0.00001	0.00115	0.00000	0.0000002	0.0255	0.00000	0.82	0.00000	0.00000	0.00006	0.001	0.00002
23-Apr-08	26	100	0.10	8.15	390	448	#N/A			1.72		115	0.00010	0.00001	0.00000	0.00080	0.00000	0.0000200	0.0186	0.00000	0.54	0.00002	0.00001	0.00003	0.001	0.00004
30-Apr-08	27	160	0.16	7.65	391	445	#N/A	0.1	1.8	2.69	8.20	102	0.00037	0.00001	0.00000	0.00113	0.00000	0.0000002	0.0238	0.00001	0.77	0.00000	0.00000	0.00012	0.001	0.00003
07-May-08	28	100	0.10	7.54	384	451	#N/A			1.62		101	0.00014	0.00001	0.00001	0.00076	0.00000	0.0000200	0.0152	0.00000	0.46	0.00002	0.00001	0.00009	0.001	0.00004
14-May-08	29	160	0.16	7.32	387	437	#N/A	0.1	1.7	3.20	8.20	113	0.00012	0.00001	0.00001	0.00128	0.00000	0.0000002	0.0285	0.00000	0.82	0.00001	0.00000	0.00008	0.001	0.00007
21-May-08	30	100	0.10	7.55	418	370	#N/A			1.22		105	0.00002	0.00001	0.00000	0.00074	0.00000	0.0000200	0.0143	0.00000	0.48	0.00002	0.00001	0.00002	0.001	0.00004
28-May-08	31	160	0.16	7.16	410	361	#N/A	0.1	1.7	2.40	9.50	100	0.00008	0.00001	0.00000	0.00118	0.00000	0.0000002	0.0209	0.00000	0.73	0.00000	0.00000	0.00015	0.001	0.00102
04-Jun-08	32	100	0.10	7.32	419	371	#N/A			1.58		94.9	0.00014	0.00001	0.00001	0.00074	0.00000	0.0000200	0.0144	0.00000	0.44	0.00002	0.00001	0.00017	0.001	0.00006
11-Jun-08	33	160	0.16	7.45	416	345	#N/A	0.1	1.7	1.98	8.00	93.5	0.00012	0.00001	0.00000	0.00113	0.00000	0.0000002	0.0253	0.00000	0.70	0.00000	0.00000	0.00022	0.001	0.00001
18-Jun-08	34	100	0.10	7.71	312	355	#N/A			1.10		94.7	0.00008	0.00001	0.00001	0.00064	0.00000	0.0000200	0.0160	0.00000	0.44	0.00002	0.00001	0.00009	0.001	0.00004
25-Jun-08	35	160	0.16	7.34	445	331	#N/A	0.2	1.9	2.11	9.40	97.6	0.00007	0.00001	0.00000	0.00117	0.00000	0.0000002	0.0221	0.00000	0.73	0.00001	0.00000	0.00015	0.001	0.00005
02-Jul-08	36	100	0.10	7.59	374	326	#N/A			1.18		96.7	0.00012	0.00001	0.00000	0.00074	0.00000	0.0000200	0.0136	0.00000	0.45	0.00002	0.00001	0.00008	0.001	0.00004
09-Jul-08	37	160	0.16	7.59	388	321	#N/A	0.1	1.7	1.66	9.40	92.6	0.00011	0.00001	0.00000	0.00127	0.00000	0.0000002	0.0218	0.00000	0.71	0.00001	0.00000	0.00005	0.001	0.00003
16-Jul-08	38	100	0.10	7.94	311	327	#N/A			1.14		93	0.00012	0.00001	0.00001	0.00072	0.00000	0.0000200	0.0139	0.00000	0.43	0.00002	0.00001	0.00003	0.001	0.00004
23-Jul-08	39	160	0.16	7.99	389	263	#N/A	0.1	1.8	1.79	8.60	90.7	0.00015	0.00001	0.00003	0.00115	0.00000	0.0000010	0.0220	0.00001	0.69	0.00000	0.00000	0.00007	0.001	0.00009
30-Jul-08	40	100	0.10	7.27	375	311	#N/A			1.12		91.2	0.00012	0.00001	0.00000	0.00076	0.00000	0.0000200	0.0134	0.00000	0.43	0.00002	0.00001	0.00002	0.001	0.00004
06-Aug-08	41	160	0.16	7.86	412	308	#N/A	0.1	1.7	1.57	7.50	89.2	0.00012	0.00001	0.00000	0.00124	0.00000	0.0000002	0.0204	0.00008	0.67	0.00000	0.00000	0.00005	0.001	0.00028
13-Aug-08	42	100	0.10	7.75	363	313	#N/A			0.96		92.7	0.00134	0.00001	0.00000	0.00080	0.00000	0.0000200	0.0150	0.00000	0.43	0.00002	0.00001	0.00004	0.001	0.00008
20-Aug-08	43	160	0.16	8.08	333	316	#N/A	0.1	1.7	1.47	8.50	87.4	0.00010	0.00001	0.00000	0.00119	0.00000	0.0000002	0.0191	0.00001	0.65	0.00001	0.00000	0.00008	0.001	0.00004
27-Aug-08	44	100	0.10	7.91	353	305	#N/A			1.00		86.1	0.00008	0.00001	0.00000	0.00072	0.00000	0.0000200	0.0109	0.00002	0.40	0.00002	0.00001	0.00006	0.001	0.00012
03-Sep-08	45																									

Subaqueous Column - Surface Water
 Sample = 1st Cleaner + Rougher Tails

Date	Cycle No.	Li	Mg	Mn	Hg	Mo	Ni	P	K	Se	Si	Ag	Na	Sr	S	Tl	Sn	Ti	U	V	Zn	Zr
		mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk
31-Oct-07	1	0.000304	0.39	0.000186	0.000032	0.00010	0.00044	0.000064	0.36	0.0000371	0.015	0.000004	1.69	0.003712	1.31	0.000005	0.000198	0.000016	0.000001	0.000006	0.000502	0.000032
07-Nov-07	2	0.000304	0.26	0.000060	0.000008	0.00008	0.00046	0.000200	0.22	0.0000380	0.02	0.0000012	1.16	0.003100	0.90	0.000004	0.000320	0.000100	0.000002	0.000100	0.000140	0.0000100
14-Nov-07	3	0.000429	0.41	0.000114	0.000032	0.00016	0.00074	0.000096	0.36	0.0000451	0.031	0.0000002	1.86	0.005152	1.41	0.000007	0.000704	0.000016	0.000002	0.000006	0.000086	0.0000032
21-Nov-07	4	0.000429	0.26	0.000060	0.000008	0.00010	0.00048	0.000200	0.24	0.0000280	0.02	0.0000004	1.06	0.003420	0.94	0.000005	0.000480	0.000100	0.000002	0.000100	0.000100	0.0000100
28-Nov-07	5	0.000522	0.40	0.000103	0.000032	0.00019	0.00076	0.000432	0.39	0.0000403	0.043	0.0000003	1.75	0.006016	1.31	0.000010	0.000899	0.000016	0.000003	0.000006	0.000118	0.0000032
05-Dec-07	6	0.000522	0.26	0.000040	0.000012	0.00012	0.00052	0.000100	0.28	0.0000260	0.03	0.0000004	1.03	0.003520	1.02	0.000006	0.000520	0.000100	0.000002	0.000100	0.000100	0.0000100
12-Dec-07	7	0.000560	0.42	0.000139	0.000032	0.00019	0.00083	0.000128	0.41	0.0000301	0.048	0.0000002	1.56	0.006016	1.63	0.000010	0.000861	0.000016	0.000004	0.000010	0.000854	0.0000032
19-Dec-07	8	0.000560	0.27	0.000060	0.000010	0.00010	0.00054	0.000200	0.26	0.0000160	0.03	0.0000004	1.02	0.003440	0.96	0.000006	0.000460	0.000100	0.000002	0.000100	0.000100	0.0000100
26-Dec-07	9	0.000579	0.45	0.000094	0.000032	0.00020	0.00085	0.000096	0.44	0.0000230	0.050	0.0000002	1.63	0.006624	1.57	0.000011	0.000803	0.000016	0.000003	0.000006	0.000045	0.0000032
02-Jan-08	10	0.000579	0.31	0.000080	0.000012	0.00012	0.00052	0.000200	0.29	0.0000140	0.04	0.0000004	1.04	0.004080	1.12	0.000007	0.000440	0.000100	0.000002	0.000100	0.000100	0.0000100
09-Jan-08	11	0.000557	0.44	0.000093	0.000032	0.00020	0.00076	0.000064	0.44	0.0000218	0.050	0.0000002	1.47	0.006208	1.63	0.000011	0.000691	0.000016	0.000003	0.000006	0.000070	0.0000032
16-Jan-08	12	0.000557	0.28	0.000060	0.000012	0.00012	0.00048	0.000200	0.25	0.0000120	0.03	0.0000004	0.91	0.003640	0.94	0.000007	0.000440	0.000100	0.000002	0.000100	0.000100	0.0000100
23-Jan-08	13	0.000630	0.46	0.000091	0.000032	0.00019	0.00084	0.000064	0.44	0.0000189	0.058	0.0000002	1.47	0.006240	1.50	0.000011	0.000704	0.000016	0.000003	0.000006	0.000070	0.0000032
30-Jan-08	14	0.000630	0.27	0.000060	0.000012	0.00012	0.00052	0.000200	0.26	0.0000120	0.04	0.0000004	0.88	0.004060	0.88	0.000008	0.000460	0.000100	0.000002	0.000100	0.000100	0.0000100
06-Feb-08	15	0.000582	0.43	0.000091	0.000064	0.00019	0.00075	0.000064	0.43	0.0000157	0.053	0.0000002	1.41	0.006144	1.41	0.000011	0.000637	0.000016	0.000003	0.000006	0.000093	0.0000032
13-Feb-08	16	0.000582	0.25	0.000060	0.000012	0.00012	0.00046	0.000200	0.27	0.0000100	0.03	0.0000004	0.78	0.003740	0.84	0.000007	0.000320	0.000100	0.000002	0.000100	0.000100	0.0000100
20-Feb-08	17	0.000579	0.44	0.000084	0.000032	0.00019	0.00074	0.000064	0.44	0.0000150	0.062	0.0000002	1.44	0.005920	1.44	0.000011	0.000611	0.000016	0.000003	0.000006	0.000253	0.0000032
27-Feb-08	18	0.000579	0.25	0.000040	0.000012	0.00012	0.00044	0.000200	0.27	0.0000100	0.03	0.0000004	0.73	0.003640	0.86	0.000007	0.000360	0.000100	0.000002	0.000100	0.000100	0.0000100
05-Mar-08	19	0.000560	0.40	0.000038	0.000032	0.00018	0.00065	0.000064	0.41	0.0000154	0.058	0.0000002	1.18	0.005728	1.31	0.000011	0.000528	0.000016	0.000003	0.000006	0.000042	0.0000032
12-Mar-08	20	0.000560	0.25	0.000040	0.000012	0.00012	0.00038	0.000200	0.25	0.0000080	0.04	0.0000004	0.70	0.003720	0.78	0.000005	0.000340	0.000100	0.000002	0.000100	0.000100	0.0000100
19-Mar-08	21	0.000643	0.40	0.000050	0.000032	0.00017	0.00062	0.000128	0.54	0.0000141	0.058	0.0000002	1.09	0.005536	1.28	0.000010	0.000486	0.000080	0.000002	0.000006	0.000550	0.0000032
26-Mar-08	22	0.000643	0.26	0.000040	0.000010	0.00010	0.00034	0.000200	0.27	0.0000080	0.06	0.0000004	0.71	0.003540	0.80	0.000004	0.000280	0.000100	0.000002	0.000100	0.000100	0.0000100
02-Apr-08	23	0.000547	0.36	0.000020	0.000032	0.00017	0.00055	0.000256	0.40	0.0000122	0.054	0.0000002	0.99	0.005600	1.18	0.000010	0.000474	0.000045	0.000002	0.000006	0.000154	0.0000032
09-Apr-08	24	0.000547	0.22	0.000040	0.000010	0.00010	0.00030	0.000200	0.27	0.0000080	0.04	0.0000006	0.60	0.003300	0.72	0.000003	0.000240	0.000100	0.000002	0.000100	0.000100	0.0000100
16-Apr-08	25	0.000509	0.37	0.000026	0.000032	0.00015	0.00063	0.000160	0.41	0.0000106	0.062	0.0000002	1.00	0.004992	1.09	0.000010	0.000435	0.000016	0.000003	0.000006	0.000067	0.0000032
23-Apr-08	26	0.000509	0.24	0.000020	0.000010	0.00010	0.00036	0.000200	0.25	0.0000060	0.04	0.0000004	0.55	0.003260	0.66	0.000007	0.000260	0.000100	0.000002	0.000100	0.000100	0.0000100
30-Apr-08	27	0.000554	0.33	0.000042	0.000032	0.00017	0.00051	0.000208	0.37	0.0000115	0.058	0.0000002	0.80	0.005120	0.96	0.000010	0.000403	0.000016	0.000003	0.000006	0.000067	0.0000032
07-May-08	28	0.000554	0.21	0.000060	0.000010	0.00010	0.00030	0.000200	0.23	0.0000080	0.04	0.0000004	0.50	0.003060	0.58	0.000006	0.000260	0.000100	0.000002	0.000100	0.000100	0.0000100
14-May-08	29	0.000538	0.38	0.000234	0.000032	0.00015	0.00051	0.000612	0.39	0.0000093	0.066	0.0000002	0.90	0.004992	1.09	0.000010	0.000413	0.000016	0.000002	0.000006	0.000122	0.0000032
21-May-08	30	0.000538	0.22	0.000040	0.000010	0.00010	0.00028	0.000200	0.22	0.0000080	0.03	0.0000004	0.50	0.003080	0.60	0.000006	0.000240	0.000100	0.000002	0.000100	0.000100	0.0000100
28-May-08	31	0.000522	0.34	0.000026	0.000032	0.00014	0.00046	0.011808	0.36	0.0000083	0.060	0.0000002	0.77	0.004608	0.93	0.000010	0.000358	0.000016	0.000002	0.000006	0.000070	0.0000032
04-Jun-08	32	0.000522	0.20	0.000020	0.000008	0.00008	0.00028	0.000200	0.20	0.0000060	0.03	0.0000004	0.46	0.002720	0.54	0.000006	0.000180	0.000100	0.000002	0.000100	0.000100	0.0000100
11-Jun-08	33	0.000467	0.30	0.000010	0.000032	0.00013	0.00041	0.010784	0.35	0.0000074	0.060	0.0000002	0.71	0.004160	0.86	0.000009	0.000285	0.000016	0.000002	0.000006	0.000122	0.0000032
18-Jun-08	34	0.000467	0.19	0.000020	0.000008	0.00008	0.00022	0.001320	0.20	0.0000060	0.04	0.0000004	0.41	0.003060	0.54	0.000003	0.000180	0.000100	0.000002	0.000100	0.000100	0.0000100
25-Jun-08	35	0.000538	0.32	0.000022	0.000032	0.00013	0.00044	0.005856	0.33	0.0000093	0.060	0.0000002	0.65	0.004288	0.86	0.000009	0.000288	0.000016	0.000002	0.000006	0.000131	0.0000032
02-Jul-08	36	0.000538	0.19	0.000040	0.000008	0.00008	0.00026	0.002300	0.21	0.0000060	0.04	0.0000004	0.40	0.002940	0.54	0.000006	0.000200	0.000100	0.000002	0.000100	0.000100	0.0000100
09-Jul-08	37	0.000502	0.29	0.000056	0.000032	0.00013	0.00038	0.002688	0.33	0.0000096	0.059	0.0000002	0.58	0.004448	0.83	0.000010	0.000279	0.000016	0.000002	0.000006	0.000150	0.0000032
16-Jul-08	38	0.000502	0.19	0.000020	0.000008	0.00008	0.00024	0.004040	0.21	0.0000040	0.04	0.0000004	0.38	0.002880	0.50	0.000005	0.000140	0.000100	0.000002	0.000100	0.000100	0.0000100
23-Jul-08	39	0.000477	0.29	0.000009	0.000032	0.00013	0.00037	0.003488	0.34	0.0000112	0.048	0.0000002	0.59	0.004192	0.74	0.000009	0.000236	0.000032	0.000002	0.000006	0.000086	0.0000032
30-Jul-08	40	0.000477	0.18	0.000020	0.000008	0.00008	0.00030	0.002020	0.20	0.0000040	0.04	0.0000004	0.34	0.002600	0.48	0.000005	0.000140	0.000100	0.000002	0.000100	0.000100	0.0000100
06-Aug-08	41	0.000490	0.29	0.000019	0.000032	0.00013	0.00035	0.000096	0.31	0.0000067	0.057	0.0000002	0.53	0.004064	0.74	0.000009	0.000218	0.000016	0.000001	0.000006	0.000078	0.0000032
13-Aug-08	42	0.000490	0.19	0.000020	0.000008	0.00008	0.00024	0.001340	0.20	0.0000040	0.04	0.0000004	0.35	0.002560	0.48	0.000006	0.000120	0.000100	0.000002	0.000100	0.000100	0.0000100
20-Aug-08	43	0.000467	0.29	0.000011	0.000032	0.00012	0.00034	0.001192	0.30	0.0000064	0.052	0.0000002	0.52	0.004032	0.70	0.000009	0.000240	0.000016	0.000001	0.0000		

Subaqueous Column - Pore Water

Sample = 1st Cleaner + Rougher Tails

Date	Cycle No.	Volume mL		pH	ORP mV	Cond. umhos/cm	Acidity (pH 4.5) mgCaCO3/L	Acidity (pH 8.3) mgCaCO3/L	Alkalinity mgCaCO3/L	Sulphate mg/L	Dissolved Oxygen mg/L	Hardness CaCO3 mg/L	Al mg/L	Sb mg/L	As mg/L	Ba mg/L	Be mg/L	Bi mg/L	B mg/L	Cd mg/L	Ca mg/L	Cr mg/L	Co mg/L	Cu mg/L
		Input	Output																					
31-Oct-07	1	160	160	7.56	259	408	#N/A	4.2	23.9	63	1.45	92.4	0.0097	0.0009	0.0013	0.0505	<0.00001	<0.000005	0.792	0.000067	29	0.0009	0.000045	0.00337
07-Nov-07	2	100	100	6.77	303	641	#N/A			103		119	0.012	0.0014	0.0037	0.069	<0.0001	<0.001	1.01	0.00026	36.3	<0.001	<0.0005	0.0059
14-Nov-07	3	160	160	7.10	145	719	#N/A	3.8	25.1	144	2.25	148	0.0029	0.00097	0.0022	0.0791	<0.00001	<0.000005	1.49	0.000021	43.4	0.0001	0.000058	0.00096
21-Nov-07	4	100	100	7.15	180	488	#N/A			159		170	0.016	0.0013	0.0054	0.085	<0.0001	<0.001	1.38	0.00003	49.6	<0.001	<0.0005	0.0016
28-Nov-07	5	160	160	6.77	275	564	#N/A	5.1	27.7	196	0.95	191	0.0046	0.327	0.027	0.0947	<0.00001	<0.000005	1.53	0.000141	53.3	0.0001	0.000056	0.00257
05-Dec-07	6	100	100	6.87	285	687	#N/A			223		238	0.004	0.0013	0.0016	0.105	<0.0001	<0.001	1.55	0.00005	66.9	<0.001	<0.0005	0.0039
12-Dec-07	7	160	160	7.54	299	773	#N/A	4.0	28.0	261	2.15	243	0.0052	0.00475	0.002	0.113	<0.00001	<0.000005	1.7	0.000037	67	0.0001	0.000063	0.00308
19-Dec-07	8	100	100	7.47	285	861	#N/A			281		264	0.008	0.006	0.0028	0.097	<0.0001	<0.001	1.65	0.00005	69.7	<0.001	<0.0005	0.0062
26-Dec-07	9	160	160	7.58	322	1023	#N/A	3.5	29.7	370	0.75	290	0.0042	0.00603	0.0023	0.119	<0.00001	<0.000005	1.98	0.000051	74.5	0.0001	0.00006	0.00416
02-Jan-08	10	100	100	8.02	134	1002	#N/A			358		340	0.004	0.0051	0.0033	0.123	<0.0001	<0.001	2.51	0.00003	87.4	<0.001	<0.0005	0.0018
09-Jan-08	11	160	160	7.85	265	1152	#N/A	4.2	35.8	470	2.45	330	0.0055	0.0051	0.0032	0.128	<0.00001	<0.000005	2.67	0.000144	84.2	<0.001	0.000063	0.001
16-Jan-08	12	100	100	8.06	115	1280	#N/A			423		358	0.004	0.0053	0.0024	0.125	<0.0001	<0.001	2.58	0.00007	89	<0.001	<0.0005	0.0027
23-Jan-08	13	160	160	7.46	195	1225	#N/A	6.9	40.3	475	2.25	355	0.0025	0.00153	0.0011	0.118	<0.00001	<0.000005	2.81	0.000041	85.7	0.0004	0.000077	0.00295
30-Jan-08	14	100	100	7.66	180	1240	#N/A			507		340	0.005	0.0053	0.0029	0.122	<0.0001	<0.001	3.08	0.00003	77.8	<0.001	<0.0005	0.0038
06-Feb-08	15	160	160	7.82	260	1187	#N/A	5.2	43.4	452	1.90	345	0.004	0.0013	0.0014	0.11	<0.00001	<0.000005	3.17	0.000026	79.5	<0.0001	0.000064	0.00338
13-Feb-08	16	100	100	7.50	187	1199	#N/A			476		332	0.007	<0.0005	0.0012	0.102	<0.0001	<0.001	3.04	0.00002	77	<0.001	<0.0005	0.0035
20-Feb-08	17	160	160	7.86	285	1219	#N/A	5.4	45.6	444	1.75	336	0.0045	0.00186	0.0037	0.094	0.00002	<0.000005	3.53	0.000021	73.2	<0.0001	0.00006	0.00203
27-Feb-08	18	100	100	7.36	202	1220	#N/A			513		326	0.006	0.0006	0.0056	0.085	<0.0001	<0.001	3.28	0.00002	72.2	<0.001	<0.0005	0.0094
05-Mar-08	19	160	160	7.62	302	1286	#N/A	6.9	51.6	420	2.30	314	0.0045	0.0007	0.0011	0.083	0.00001	<0.000005	3.52	0.000013	67.9	<0.0001	0.000049	0.00201
12-Mar-08	20	100	100	7.49	160	1280	#N/A			392		313	0.004	0.0015	0.0012	0.079	<0.0001	<0.001	3.36	0.00001	65	<0.001	<0.0005	0.0025
19-Mar-08	21	160	160	7.79	202	11265	#N/A	5.1	55.4	440	1.75	347	0.0071	0.00202	0.0011	0.0764	0.00002	<0.000005	3.77	0.000053	79.4	0.0002	0.000053	0.00348
26-Mar-08	22	100	100	7.82	146	1402	#N/A			369		304	0.018	0.0012	0.0014	0.069	<0.0001	<0.001	3.53	0.00003	61.9	<0.001	<0.0005	0.0013
02-Apr-08	23	160	160	7.84	335	1127	#N/A	4.8	57.9	324	1.75	269	0.0069	0.00214	0.0008	0.0572	0.00013	<0.000005	3.66	0.000038	56	0.0002	0.000062	0.00513
09-Apr-08	24	100	100	7.96	240	1002	#N/A			348		268	0.005	0.0009	0.0009	0.061	0.0001	<0.001	3.94	0.00001	55.6	<0.001	<0.0005	0.0012
16-Apr-08	25	160	160	7.87	301	998	#N/A	5.04	60.3	317	1.8	260	0.0078	0.00197	0.0007	0.0568	0.00012	<0.000005	3.96	0.000031	51.8	0.0001	0.000065	0.00327
23-Apr-08	26	100	100	8.39	337	1009	#N/A			312		265	0.006	<0.0005	0.0004	0.059	0.0002	<0.001	4.56	0.00002	53.2	<0.001	<0.0005	0.0013
30-Apr-08	27	160	160	8.23	365	1000	#N/A	3.84	61.8	278	2.0	223	0.009	0.0008	0.0004	0.0541	0.00005	<0.00003	4.17	<0.00003	43.9	<0.0005	0.00003	0.0044
07-May-08	28	100	100	7.88	337	1018	#N/A			238		219	0.011	0.0014	0.0006	0.051	<0.0001	<0.001	3.83	0.00004	42.5	<0.001	<0.0005	0.0044
14-May-08	29	160	160	6.97	315	956	#N/A	4.01	63.2	203	2.0	234	0.006	0.001	0.0005	0.049	0.00003	<0.000005	4.45	0.000012	42.7	0.0001	0.000046	0.00611
21-May-08	30	100	100	7.44	384	814	#N/A			237		219	<0.001	0.0009	0.0004	0.049	<0.0001	<0.001	3.89	0.00001	39.9	<0.001	<0.0005	0.001
28-May-08	31	160	160	7.37	374	771	#N/A	3.97	64.0	234	2.5	214	0.0359	0.00054	0.0004	0.0444	0.00005	<0.000005	3.36	0.000021	38.7	0.0001	0.00131	0.00699
04-Jun-08	32	100	100	7.41	369	802	#N/A			226		208	0.014	0.0008	0.0004	0.043	<0.0001	<0.001	3.68	<0.00002	38.9	<0.001	<0.0005	0.003
11-Jun-08	33	160	160	7.81	381	752	#N/A	2.49	65.1	219	2.6	194	0.0033	0.00054	0.0003	0.0419	0.00003	<0.000005	4.1	0.000006	35.9	0.0001	0.000029	0.00299
18-Jun-08	34	100	100	8.36	276	737	#N/A			212		195	0.004	<0.0005	0.0004	0.04	<0.0001	<0.001	4.24	0.00001	36.5	<0.001	<0.0005	0.0015
25-Jun-08	35	160	160	7.82	406	691	#N/A	4.7	74.7	225	3.20	208	0.0043	0.00057	0.0004	0.0395	0.00013	<0.000005	3.91	0.000019	38.1	0.0001	0.000025	0.00422
02-Jul-08	36	100	100	7.84	326	687	#N/A			193		236	0.007	0.0012	0.0004	0.048	<0.0001	<0.001	4.66	0.00001	43.1	<0.001	<0.0005	0.0032
09-Jul-08	37	160	160	8.25	325	676	#N/A	3.1	68.5	194	2.00	177	0.0076	0.00076	0.001	0.0397	0.00006	<0.000005	3.8	0.000014	33.9	<0.001	0.000077	0.00177
16-Jul-08	38	100	100	8.17	282	664	#N/A			202		187	0.012	0.0009	0.0003	0.038	<0.0001	<0.001	3.74	<0.00001	33.8	<0.001	<0.0005	0.0036
23-Jul-08	39	160	160	7.80	369	528	#N/A	3.7	67.3	188	2.25	182	0.0055	0.00105	0.001	0.0354	0.00005	<0.000005	3.81	0.000022	33.6	<0.0001	0.00002	0.00228
30-Jul-08	40	100	100	7.50	208	639	#N/A			189		179	0.004	0.0009	0.0003	0.037	<0.0001	<0.001	3.75	0.00001	31.7	<0.001	<0.0005	0.0025
06-Aug-08	41	160	160	8.14	256	623	#N/A	3.5	71.9	158	1.50	170	0.007	0.00098	0.0005	0.036	0.00003	<0.000005	3.62	0.000014	31.3	<0.0001	0.000017	0.00205
13-Aug-08	42	100	100	8.08	291	639	#N/A			156		175	0.006	0.0009	0.0003	0.033	<0.0001	<0.001	3.42	0.00005	31.5	<0.001	<0.0005	0.0062
20-Aug-08	43	160	160	7.91	229	613	#N/A	3.2	74.9	136	1.90	169	0.0053	0.00098	0.0004	0.0322	0.00007	<0.000005	3.44	0.000041	29.4	<0.0001	0.000029	0.00543
27-Aug-08	44	100	100	7.54	292	602	#N/A			160		164	0.006	<0.0005	0.0004	0.032	<0.0001	<0.001	3.31	0.00009	28.5	<0.001	<0.0005	0.0049
03-Sep-08	45	160	160	7.50	191	629	#N/A	4.9	76.3	149	2.75	160	0.0139	0.00107	0.0006	0.0315	0.00009	<0.000005	3.5	0.000056	28.6	0.0001	0.00003	0.0136
10-Sep-08	46	100	100	7.50	160	657	#N/A			153		175	0.005	0.0007	0.0003	0.031	<0.0001	<0.001	3.39	0.00001	30.6	<0.001	<0.0005	0.0014
17-Sep-08	47	160	160	7.97	150	632	#N/A	3.8	71.9	151	3.10	158	0.0065	0.00086	0.0004	0.0323	0.00007	<0.000005	3.66	0.000019	28	<0.0001	0.000044	0.00474
24-Sep-08	48	100	100	7.60	101	642	#N/A			146		163	0.004	<0.0005	0.0003	0.034	<0.0001	<0.001	4.14	0.00002	28.9	<0.001	<0.0005	0.0037
01-Oct-08	49	160	160	7.55	158	620	#N/A	3.3	72.1	149	3.50	154	0.036	0.00053	0.0004	0.0338	0.00007	<0.000005	3.94	0.000012	26.7	0.0001	0.000025	0.00216
08-Oct-08	50	100																						

Subaqueous Column - Pore Water

Sample = 1st Cleaner + Rougher Tails

Date	Cycle No.	Fe	Pb	Li	Mg	Mn	Hg	Mo	Ni	P	K	Se	Si	Ag	Na	Sr	S	Tl	Sn	Ti	U	V	Zn	Zr
		mg/L	mg/L	mg/L	mg/L	mg/L	ug/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L
31-Oct-07	1	0.004	0.00036	0.015	4.88	0.00179	<0.01	0.00888	0.00474	0.002	11	0.0009	1.78	0.000144	5.11	0.219	27	0.000213	0.00027	<0.0005	0.000024	<0.0002	0.0051	<0.0001
07-Nov-07	2	0.062	0.00260		6.75	0.002		0.012	0.011	<0.01	14.9	0.0012	1.94	0.00004	7.91	0.314	38	0.00025	<0.005	<0.005	<0.0001	<0.005	0.014	<0.0005
14-Nov-07	3	0.004	0.00008	0.0264	9.54	0.00443	<0.01	0.0154	0.00743	0.003	17.8	0.00063	2	0.000008	11.4	0.395	48	0.000193	<0.0002	<0.0005	0.000034	<0.0002	0.0028	<0.0001
21-Nov-07	4	0.019	0.00020		11.3	0.004		0.016	0.008	<0.01	19.2	0.0003	2.15	<0.00002	13.1	0.438	58	0.00021	<0.005	<0.005	<0.0001	<0.005	<0.005	<0.0005
28-Nov-07	5	0.005	0.00005	0.0329	14.2	0.00284	<0.01	0.0198	0.00769	0.004	21.3	0.00019	2.16	0.000191	20.2	0.55	65	0.000182	0.00716	<0.0005	0.000063	0.0003	0.0052	<0.0001
05-Dec-07	6	0.015	0.00030		17.1	0.002		0.021	0.009	<0.01	27.8	0.0002	1.92	0.00008	27	0.568	90	0.00015	<0.005	<0.005	<0.0001	<0.005	<0.005	<0.0005
12-Dec-07	7	0.006	0.00006	0.036	18.4	0.00369	0.01	0.0245	0.00857	0.003	28	0.00012	2.21	0.000096	34.3	0.647	101	0.000106	0.00252	<0.0005	0.000075	0.0003	0.0052	0.0001
19-Dec-07	8	0.008	0.00020		21.8	0.007		0.024	0.009	<0.01	31.4	0.0001	1.98	<0.00005	49.5	0.639	118	<0.00005	<0.005	<0.005	<0.0001	<0.005	0.006	<0.0005
26-Dec-07	9	0.003	0.00024	0.0398	25.3	0.00518		0.0282	0.00822	0.004	42.4	0.00012	2.3	0.000143	65	0.756	140	0.00003	0.00594	<0.0005	0.000112	<0.0002	0.0021	<0.0001
02-Jan-08	10	0.02	0.00020		29.7	0.005		0.03	0.009	<0.01	38.7	0.0001	2.87	<0.00002	76.7	0.821	170	<0.00005	0.005	<0.005	0.0002	<0.005	<0.005	<0.0005
09-Jan-08	11	0.006	0.00030	0.0451	29.1	0.00644	0.03	0.0321	0.00719	0.006	41.1	0.00013	2.31	0.000017	83.1	0.833	169	0.00001	0.00811	<0.0005	0.000146	<0.0002	0.0097	<0.0001
16-Jan-08	12	0.013	0.00050		32.8	0.007		0.033	0.007	<0.01	43.8	0.0002	2.27	<0.00002	96.5	0.832	183	<0.00005	<0.005	<0.005	0.0002	<0.005	<0.005	<0.0005
23-Jan-08	13	0.005	0.00002	0.0459	34.2	0.00727	0.02	0.0334	0.00717	0.003	41.2	0.00016	2.54	0.00006	98.5	0.846	176	0.000011	0.00617	<0.0005	0.000195	<0.0002	0.0043	<0.0001
30-Jan-08	14	0.009	0.00020		35.5	0.008		0.037	0.009	<0.01	40.7	0.0001	2.81	<0.00002	105	0.915	181	<0.00005	0.011	<0.005	0.0002	<0.005	<0.005	<0.0005
06-Feb-08	15	0.006	0.00001	0.0467	35.7	0.00796	0.02	0.0353	0.00681	0.005	43	0.00012	2.46	0.000105	109	0.868	185	0.000012	0.00159	<0.0005	0.000238	<0.0002	0.0015	<0.0001
13-Feb-08	16	0.018	0.00020		33.9	0.01		0.034	0.006	<0.01	43	0.0001	2.25	<0.00002	100	0.83	177	<0.00005	<0.005	<0.005	0.0002	<0.005	<0.005	<0.0005
20-Feb-08	17	0.007	0.00006	0.0449	37.2	0.00939	0.01	0.0348	0.0057	0.005	41.5	0.00013	2.7	0.00001	117	0.803	183	0.000013	0.00112	<0.0005	0.000242	<0.0002	0.0079	<0.0001
27-Feb-08	18	0.023	0.00030		35.3	0.009		0.033	0.005	<0.01	60.7	0.0002	2.34	<0.00002	97.1	0.798	176	<0.00005	<0.005	<0.005	0.0002	<0.005	<0.005	<0.0005
05-Mar-08	19	0.005	0.00001	0.0421	35.1	0.00839	0.02	0.0336	0.00497	0.005	38.4	0.00016	2.34	0.000065	96.4	0.75	164	0.000013	0.00337	<0.0005	0.000259	<0.0002	0.0011	<0.0001
12-Mar-08	20	0.015	0.00020		36.6	0.009		0.035	0.005	<0.01	38.7	0.0001	2.89	<0.00002	96	0.766	158	<0.00005	<0.005	<0.005	0.0003	<0.005	<0.005	<0.0005
19-Mar-08	21	0.021	0.00026	0.0479	36	0.00937	0.02	0.035	0.00463	0.008	46.7	0.00015	2.64	0.000076	94.3	0.758	165	0.000005	0.00466	0.0014	0.000236	<0.0002	0.012	<0.0001
26-Mar-08	22	0.015	0.00030		36.2	0.009		0.034	0.004	<0.01	83.2	<0.0001	4.66	<0.00002	97.4	0.702	152	<0.00005	<0.005	<0.005	0.0002	<0.005	<0.005	<0.0005
02-Apr-08	23	0.012	0.00007	0.0436	31.4	0.00854	0.02	0.0338	0.00371	0.011	38.3	0.00029	2.33	0.000164	81	0.684	138	0.000007	0.00391	0.0016	0.000231	<0.0002	0.0041	<0.0001
09-Apr-08	24	0.01	0.0003		31.4	0.008		0.031	0.004	<0.01	38.9	0.0001	2.54	<0.00002	81.8	0.619	132	<0.00005	<0.005	<0.005	0.0002	<0.005	<0.005	<0.0005
16-Apr-08	25	0.016	0.00031	0.0427	31.7	0.00878	0.02	0.0323	0.00666	0.01	37.2	0.0001	2.89	0.000064	84.4	0.605	121	0.000013	0.00218	<0.0005	0.000222	<0.0002	0.0039	<0.0001
23-Apr-08	26	0.007	<0.0002		32.2	0.008		0.032	0.005	<0.01	36.4	<0.0001	2.66	<0.00002	71.9	0.586	120	<0.00005	<0.005	<0.005	0.0002	<0.005	<0.005	<0.0005
30-Apr-08	27	0.024	0.00007	0.042	27.5	0.0083	<0.05	0.0289	0.0043	<0.01	34.3	<0.0002	2.41	0.00005	60.3	0.546	102	0.00001	0.00349	<0.003	0.0002	<0.001	0.002	<0.0005
07-May-08	28	0.023	<0.0002		27.3	0.011		0.027	0.003	0.013	29.4	0.0002	2.44	<0.00002	61.3	0.507	94	0.00005	<0.005	<0.005	0.0002	<0.005	<0.005	<0.0005
14-May-08	29	0.014	0.000116	0.0417	30.9	0.00969	0.01	0.0303	0.00281	0.159	30.7	0.00012	2.57	0.000054	67.7	0.515	104	0.000011	0.00429	<0.0005	0.000208	<0.0002	0.0039	<0.0001
21-May-08	30	0.02	<0.0002		29.1	0.009		0.028	0.002	0.012	29.8	0.0003	2.01	<0.00002	60	0.492	94	<0.00005	<0.005	<0.005	0.0002	<0.005	<0.005	<0.0005
28-May-08	31	0.018	0.000285	0.0404	28.4	0.00858	0.01	0.0307	0.00259	0.078	30.3	0.00008	2.41	0.000141	59.4	0.488	92	0.000016	0.00605	0.001	0.000191	<0.0002	0.0041	0.0002
04-Jun-08	32	0.021	0.0003		26.9	0.007		0.025	0.004	0.01	27	0.0004	2.2	0.00003	58.6	0.448	84	<0.00005	<0.005	<0.005	0.0002	<0.005	0.005	<0.0005
11-Jun-08	33	0.012	0.000032	0.0363	25.4	0.00662	0.03	0.0273	0.00198	0.267	27.9	0.00008	2.33	0.000018	55	0.416	78	0.000005	0.00398	<0.0005	0.000164	<0.0002	0.0022	<0.0001
18-Jun-08	34	0.016	<0.0002		25.2	0.007		0.027	0.002	0.017	26.2	0.0004	2.35	<0.00002	50.6	0.461	81	<0.00005	0.005	<0.005	0.0002	<0.005	0.005	<0.0005
25-Jun-08	35	0.041	0.00125	0.0413	27.5	0.00764	0.01	0.029	0.00202	0.084	27.9	0.00011	2.6	0.000017	53.2	0.438	86	0.000009	0.00352	<0.0005	0.000172	<0.0002	0.0025	<0.0001
02-Jul-08	36	0.057	<0.0002		31.1	0.011		0.029	0.003	0.013	33.5	<0.0001	3.02	<0.00002	58.2	0.505	90	<0.00005	<0.005	<0.005	0.0001	<0.005	0.005	<0.0005
09-Jul-08	37	0.019	0.000121	0.0393	22.5	0.00784	<0.01	0.0275	0.00197	0.007	26.9	0.00007	2.52	<0.000005	43.9	0.428	74	0.000022	0.00315	<0.0005	0.000166	<0.0002	0.0032	<0.0001
16-Jul-08	38	0.021	<0.0002		24.9	0.007		0.027	0.002	<0.01	26.9	<0.0001	2.52	<0.00002	48.5	0.434	73	<0.00005	<0.005	<0.005	0.0001	<0.005	0.005	<0.0005
23-Jul-08	39	0.03	0.00009	0.0366	23.8	0.00674	<0.01	0.0265	0.00182	0.161	26.6	0.00016	2.11	<0.000005	45.4	0.395	69	0.000007	0.00347	<0.0005	0.000119	<0.0002	0.0014	<0.0001
30-Jul-08	40	0.098	<0.0002		24.2	0.008		0.024	0.002	0.341	25.6	<0.0001	2.5	<0.00002	41.9	0.372	70	<0.00005	<0.005	<0.005	0.0001	<0.005	0.005	<0.0005
06-Aug-08	41	0.06	0.000234	0.0398	22.4	0.00699	<0.01	0.0261	0.00148	0.025	24.3	<0.00004	2.1	<0.000005	40.2	0.398	63	0.000005	0.00402	<0.0005	0.000111	<0.0002	0.0028	<0.0001
13-Aug-08	42	0.023	<0.0002		23.5	0.007		0.025	0.002	0.115	25.4	0.0001	2.46	<0.00002	40.8	0.381	63	<0.00005	<0.005	<0.005	0.0001	<0.005	0.005	<0.0005
20-Aug-08	43	0.018	0.000242	0.0358	23.2	0.00683	<0.01	0.0245	0.00153	0.051	23.7	0.00007	2.17	0.000023	40.6	0.356	60	0.000004	0.00407	0.0009	0.000106	0.0002	0.0032	<0.0001
27-Aug-08	44	0.027	0.0004		22.5	0.006		0.021	0.004	<0.01	23.7	0.0001	2.24	<0.00002	36.7	0.34	57	<0.00005	<0.005	<0.005	<0.0001	<0.005	0.005	<0.0005
03-Sep-08	45	0.014	0.000511	0.0354	21.6	0.00657	<0.01	0.024	0.0018	1.14	25.4	0.00013	2.13	0.000009	37.2	0.348	59							


Subaqueous Column - Pore Water

Sample = 1st Cleaner + Rougher Tails

Date	Cycle No.	Input L	Output L	pH	Volume mV	ORP mV	Cond. umhos/cm	Acidity (pH 4.5) mgCaCO3/L	Acidity (pH 8.3) mg/kg/wk	Alkalinity mg/kg/wk	Sulphate mg/kg/wk	Dissolved Oxygen mg/L	Hardness CaCO3 mg/L	Al mg/kg/wk	Sb mg/kg/wk	As mg/kg/wk	Ba mg/kg/wk	Be mg/kg/wk	Bi mg/kg/wk	B mg/kg/wk	Cd mg/kg/wk	Ca mg/kg/wk	Cr mg/kg/wk	Co mg/kg/wk	Cu mg/kg/wk	Fe mg/kg/wk
31-Oct-07	1	0.16	0.16	7.56	259	408	#N/A	0.1347	0.7645	2.016	1.45	92.4	0.0003104	0.0000288	0.0000422	0.0016160	0.0000003	0.0000002	0.0000023	0.0000021	0.93	0.0000288	0.0000014	0.0001078	0.0001280	
07-Nov-07	2	0.10	0.10	6.77	303	641	#N/A			2.06		119	0.0002400	0.0000280	0.0000740	0.0013800	0.0000020	0.0000020	0.00200	0.0000052	0.73	0.0000200	0.0000010	0.0001180	0.0001240	
14-Nov-07	3	0.16	0.16	7.1	145	719	#N/A	0.1210	0.8016	4.608	2.25	148	0.0000928	0.0000310	0.0000688	0.0025312	0.0000003	0.0000002	0.04768	0.0000007	1.39	0.0000032	0.0000019	0.0000307	0.0001280	
21-Nov-07	4	0.10	0.10	7.15	180	488	#N/A			3.18		170	0.0003200	0.0000260	0.0001080	0.0017000	0.0000020	0.0000020	0.02760	0.0000006	0.99	0.0000200	0.0000100	0.0000320	0.0003800	
28-Nov-07	5	0.16	0.16	6.77	275	564	#N/A	0.1645	0.8870	6.272	0.95	191	0.0001472	0.0104640	0.00008640	0.0030304	0.0000003	0.0000002	0.04896	0.0000045	1.71	0.0000032	0.0000018	0.0000822	0.0001600	
05-Dec-07	6	0.10	0.10	6.87	285	687	#N/A			4.46		238	0.0000800	0.0000260	0.0000320	0.0021000	0.0000020	0.0000020	0.03100	0.0000010	1.34	0.0000200	0.0000100	0.0000780	0.0003000	
12-Dec-07	7	0.16	0.16	7.54	299	773	#N/A	0.1267	0.8957	8.352	2.15	243	0.0001664	0.0001520	0.0000627	0.0036160	0.0000003	0.0000002	0.05440	0.0000012	2.14	0.0000032	0.0000020	0.0000986	0.0001920	
19-Dec-07	8	0.10	0.10	7.47	285	861	#N/A			5.62		264	0.0001600	0.0001200	0.0000560	0.0019400	0.0000020	0.0000020	0.03300	0.0000010	1.39	0.0000200	0.0000100	0.0001240	0.0001600	
26-Dec-07	9	0.16	0.16	7.58	322	1023	#N/A	0.1120	0.9507	11.84	0.75	290	0.0001344	0.0001930	0.0000720	0.0039800	0.0000003	0.0000002	0.06336	0.0000016	2.38	0.0000032	0.0000019	0.0001331	0.0000960	
02-Jan-08	10	0.10	0.10	8.02	134	1002	#N/A			7.16		340	0.0000800	0.0001020	0.0000660	0.0024600	0.0000020	0.0000020	0.05920	0.0000006	1.75	0.0000200	0.0000100	0.0000360	0.0004000	
09-Jan-08	11	0.16	0.16	7.85	265	1152	#N/A	0.1334	1.1462	15.04	2.45	330	0.0001760	0.0001632	0.0001008	0.0040960	0.0000003	0.0000002	0.08544	0.0000046	2.69	0.0000032	0.0000020	0.0000320	0.0001920	
16-Jan-08	12	0.10	0.10	8.06	115	1280	#N/A			8.46		358	0.0000800	0.0001060	0.0000480	0.0025900	0.0000020	0.0000020	0.05160	0.0000014	1.78	0.0000200	0.0000100	0.0000540	0.0002800	
23-Jan-08	13	0.16	0.16	7.46	195	1225	#N/A	0.2205	1.2890	15.2	2.25	355	0.0000800	0.0000490	0.0000339	0.0025900	0.0000003	0.0000002	0.08992	0.0000013	2.74	0.0000128	0.0000025	0.0000944	0.0001600	
30-Jan-08	14	0.10	0.10	7.66	180	1240	#N/A			10.14		340	0.0001000	0.0001060	0.0000580	0.0024400	0.0000020	0.0000020	0.06160	0.0000006	1.56	0.0000200	0.0000100	0.0000780	0.0001800	
06-Feb-08	15	0.16	0.16	7.82	260	1187	#N/A	0.1664	1.3901	14.464	1.90	345	0.0001280	0.0000416	0.0000432	0.0035200	0.0000003	0.0000002	0.10144	0.0000008	2.54	0.0000032	0.0000020	0.0001082	0.0001920	
13-Feb-08	16	0.10	0.10	7.50	187	1199	#N/A			9.52		332	0.0001400	0.0000100	0.0000240	0.0020400	0.0000020	0.0000020	0.06080	0.0000004	1.54	0.0000200	0.0000100	0.0000700	0.0003600	
20-Feb-08	17	0.16	0.16	7.86	285	1219	#N/A	0.1738	1.4579	14.208	1.75	336	0.0001440	0.0000595	0.0001197	0.0030800	0.0000006	0.0000002	0.11296	0.0000007	2.34	0.0000032	0.0000019	0.0000650	0.0002240	
27-Feb-08	18	0.10	0.10	7.96	202	1220	#N/A			10.26		326	0.0001200	0.0000120	0.0001120	0.0017000	0.0000020	0.0000020	0.06560	0.0000004	1.44	0.0000200	0.0000100	0.0001880	0.0004600	
05-Mar-08	19	0.16	0.16	7.62	302	1286	#N/A	0.2218	1.6518	13.44	2.30	314	0.0001440	0.0000224	0.0000362	0.0026560	0.0000003	0.0000002	0.11264	0.0000004	2.17	0.0000032	0.0000016	0.0000643	0.0001600	
12-Mar-08	20	0.10	0.10	7.49	160	1280	#N/A			7.84		313	0.0000800	0.0000300	0.0000240	0.0015800	0.0000020	0.0000020	0.06720	0.0000002	1.30	0.0000200	0.0000100	0.0000500	0.0003000	
19-Mar-08	21	0.16	0.16	7.79	202	11265	#N/A	0.1622	1.7722	14.08	1.75	347	0.0002272	0.0000646	0.0000342	0.0024448	0.0000006	0.0000002	0.12064	0.0000017	2.54	0.0000064	0.0000017	0.0001114	0.0006720	
26-Mar-08	22	0.10	0.10	7.82	146	1402	#N/A			7.38		304	0.0003600	0.0000240	0.0000280	0.0013800	0.0000020	0.0000020	0.07060	0.0000006	1.24	0.0000020	0.0000004	0.0000260	0.0003000	
02-Apr-08	23	0.16	0.16	7.84	335	1127	#N/A	0.1523	1.8515	10.368	1.75	269	0.0002208	0.0000685	0.0000259	0.0018200	0.0000042	0.0000002	0.11712	0.0000012	1.79	0.0000064	0.0000020	0.0001642	0.0003840	
09-Apr-08	24	0.10	0.10	7.96	240	1002	#N/A			6.96		268	0.0001000	0.0000180	0.0000180	0.0012300	0.0000020	0.0000020	0.07880	0.0000002	1.11	0.0000020	0.0000004	0.0000240	0.0002000	
16-Apr-08	25	0.16	0.16	7.87	301	998	#N/A	0.1613	1.9296	10.144	1.75	260	0.0002496	0.0000630	0.0000224	0.0018176	0.0000038	0.0000002	0.12672	0.0000010	1.66	0.0000032	0.0000021	0.0001046	0.0005120	
23-Apr-08	26	0.10	0.10	8.39	337	1009	#N/A			6.24		265	0.0001200	0.0000100	0.0000080	0.0011800	0.0000040	0.0000020	0.09120	0.0000004	1.06	0.0000020	0.0000004	0.0000260	0.0001400	
30-Apr-08	27	0.16	0.16	8.23	365	1000	#N/A	0.1229	1.9760	8.896	2	223	0.0002880	0.0000256	0.0000128	0.0017312	0.0000016	0.0000016	0.13344	0.0000010	1.40	0.0000160	0.0000010	0.0001408	0.0007680	
07-May-08	28	0.10	0.10	7.88	337	1018	#N/A			4.76		219	0.0002200	0.0000280	0.0000120	0.0010200	0.0000020	0.0000020	0.07660	0.0000008	0.85	0.0000020	0.0000010	0.0000880	0.0004600	
14-May-08	29	0.16	0.16	6.97	315	956	#N/A	0.1283	2.0208	6.496	1.95	234	0.0001920	0.0000320	0.0000144	0.0015680	0.0000010	0.0000002	0.14240	0.0000004	1.37	0.0000032	0.0000015	0.0001955	0.0004480	
21-May-08	30	0.10	0.10	7.44	384	814	#N/A			4.74		219	0.0000200	0.0000180	0.0000080	0.0009800	0.0000020	0.0000020	0.07780	0.0000002	0.80	0.0000200	0.0000010	0.0000200	0.0004000	
28-May-08	31	0.16	0.16	7.37	374	771	#N/A	0.1270	2.0493	7.488	2.5	214	0.0011488	0.0000173	0.0000118	0.0014208	0.0000016	0.0000002	0.10752	0.0000007	1.24	0.0000032	0.0000019	0.0002237	0.0005760	
04-Jun-08	32	0.10	0.10	7.41	369	802	#N/A			4.52		208	0.0002800	0.0000160	0.0000080	0.0008600	0.0000020	0.0000020	0.07360	0.0000004	0.78	0.0000200	0.0000010	0.0000260	0.0004200	
11-Jun-08	33	0.16	0.16	7.81	381	752	#N/A	0.0797	2.0829	7.008	2.6	194	0.0001056	0.0000173	0.0000086	0.0013408	0.0000010	0.0000002	0.13120	0.0000002	1.15	0.0000032	0.0000009	0.0000957	0.0003840	
18-Jun-08	34	0.10	0.10	8.36	276	737	#N/A			4.24		195	0.0000800	0.0000100	0.0000080	0.0008000	0.0000020	0.0000020	0.08480	0.0000002	0.73	0.0000020	0.0000004	0.0000300	0.0003200	
25-Jun-08	35	0.16	0.16	7.82	406	691	#N/A	0.1510	2.3894	7.2	3.2	208	0.0001376	0.0000182	0.0000115	0.0012640	0.0000042	0.0000002	0.12512	0.0000006	1.22	0.0000032	0.0000008	0.0001350	0.0013120	
02-Jul-08	36	0.10	0.10	7.84	326	687	#N/A			3.86		236	0.0001400	0.0000240	0.0000080	0.0009600	0.0000020	0.0000020	0.09320	0.0000002	0.86	0.0000200	0.0000010	0.0000640	0.0011400	
09-Jul-08	37	0.16	0.16	8.25	325	676	#N/A	0.0998	2.1930	6.208	2	177	0.0002432	0.0000243	0.0000304	0.0012704	0.0000019	0.0000002	0.12160	0.0000004	1.08	0.0000032	0.0000025	0.0000566	0.0006080	
16-Jul-08	38	0.10	0.10	8.17	282	664	#N/A			4.04		187	0.0002400	0.0000180	0.0000060	0.0007600	0.0000020	0.0000020	0.07480	0.0000002	0.68	0.0000200	0.0000010	0.0000720	0.0004200	
23-Jul-08	39	0.16	0.16	7.8	369	528	#N/A	0.1184	2.1533	6.016	2.25	182	0.0001760	0.0000336	0.0000320	0.0011328	0.0000016	0.0000002	0.12192	0.0000007	1.08	0.0000032	0.0000006	0.0000730	0.0009600	
30-Jul-08	40	0.10	0.10	7.5	208	639	#N/A			3.78		179	0.0000800	0.0000180	0.0000060	0.0007400	0.0000020	0.0000020	0.07500	0.0000002	0.63	0.0000200	0.0000010	0.0000500	0.0019600	
06-Aug-08	41	0.16	0.16	8.14	256	623	#N/A	0.1133	2.3005	5.056	1.5	170	0.0002240	0.0000314	0.0000144	0.0011520	0.0000010	0.0000002	0.11584	0.0000004	1.00	0.0000032	0.0000005	0.0000656	0.0001920	
13-Aug-08	42	0.10	0.10	8.08	291	639	#N/A			3.12		175	0.0001200	0.0000180	0.0000060	0.0006600										

Subaqueous Column - Pore Water
 Sample = 1st Cleaner + Rougher Tails


Date	Cycle No.	Pb	Li	Mg	Mn	Hg	Mo	Ni	P	K	Se	Si	Ag	Na	Sr	S	Ti	Sn	Tl	U	V	Zn	Zr	
		mg/kg/wk	mg/ka/wk	mg/ka/wk	mg/kg/wk	mg/kg/wk	mg/ka/wk	mg/kg/wk	mg/kg/wk	mg/ka/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	mg/kg/wk	
31-Oct-07	1	0.000115	0.000480		0.16	0.000573	0.0003200	0.0002842	0.0001517	0.0000640	0.35	0.000029	0.056960	0.0000046	0.16	0.007008	0.86	0.0000068	0.000009	0.000016	0.000001	0.0000064	0.000163	0.0000032
07-Nov-07	2	0.0000520		0.14	0.000400		0.0002400	0.0002200	0.0002000	0.30	0.000024	0.038800	0.0000008	0.16	0.01	0.76	0.0000050	0.000100	0.000002	0.0001000	0.000280	0.000280	0.000100	0.0000100
14-Nov-07	3	0.0000024	0.0008448	0.31	0.0001418	0.0003200	0.0004928	0.0002378	0.0000960	0.57	0.000020	0.064000	0.0000003	0.36	0.01264	1.54	0.0000062	0.000006	0.000016	0.000001	0.0000064	0.000090	0.0000032	0.0000032
21-Nov-07	4	0.0000040		0.23	0.0000800		0.0003200	0.0001600	0.0002000	0.38	0.000006	0.043000	0.0000004	0.26	0.000876	1.16	0.0000042	0.000100	0.000002	0.0001000	0.000100	0.000100	0.000100	0.0000100
28-Nov-07	5	0.0000016	0.0010528	0.45	0.0000909	0.0003200	0.0006336	0.0002461	0.0001280	0.68	0.000006	0.069120	0.0000061	0.65	0.01760	2.08	0.0000058	0.000229	0.000016	0.000002	0.0000096	0.000166	0.0000032	0.0000100
05-Dec-07	6	0.0000060		0.34	0.0000400		0.0004200	0.0001800	0.0002000	0.56	0.000004	0.038400	0.0000016	0.54	0.01136	1.80	0.0000030	0.000100	0.000002	0.0001000	0.000100	0.000100	0.000100	0.0000100
12-Dec-07	7	0.0000018	0.0011520	0.59	0.0001181	0.0003200	0.0007840	0.0002742	0.0000960	0.90	0.000004	0.070720	0.0000031	1.10	0.02070	3.23	0.0000034	0.000081	0.000016	0.000002	0.0000096	0.000166	0.0000032	0.0000100
19-Dec-07	8	0.0000040		0.44	0.0001400		0.0004800	0.0001800	0.0002000	0.63	0.000002	0.039600	0.0000004	0.99	0.01278	2.36	0.0000010	0.000100	0.000002	0.0001000	0.000100	0.000100	0.000100	0.0000100
26-Dec-07	9	0.0000078	0.0012736	0.81	0.0001658	0.0000000	0.0009024	0.0002630	0.0001280	1.36	0.000004	0.073600	0.0000046	2.08	0.02419	4.48	0.0000010	0.000190	0.000016	0.000004	0.0000064	0.000067	0.0000032	0.0000100
02-Jan-08	10	0.0000040		0.59	0.0001000		0.0006000	0.0001800	0.0002000	0.77	0.000002	0.057400	0.0000004	1.53	0.01642	3.40	0.0000010	0.000100	0.000004	0.0001000	0.000100	0.000100	0.000100	0.0000100
09-Jan-08	11	0.0001056	0.0014432	0.93	0.0002061	0.0009600	0.0010272	0.0002301	0.0001920	1.32	0.000004	0.073920	0.0000005	2.66	0.02666	5.41	0.0000003	0.000260	0.000016	0.000005	0.0000064	0.000310	0.0000032	0.0000100
16-Jan-08	12	0.0000100		0.66	0.0001400		0.0006800	0.0001400	0.0002000	0.88	0.000004	0.045400	0.0000004	1.98	0.01664	3.66	0.0000010	0.000100	0.000004	0.0001000	0.000100	0.000100	0.000100	0.0000100
23-Jan-08	13	0.0000077	0.0014688	1.09	0.0002326	0.0006400	0.0010688	0.0002294	0.0001920	1.32	0.000005	0.051280	0.0000019	3.15	0.02707	5.63	0.0000004	0.000197	0.000016	0.000006	0.0000064	0.000138	0.0000032	0.0000100
30-Jan-08	14	0.0000040		0.71	0.0001600		0.0007400	0.0001800	0.0002000	0.81	0.000002	0.056200	0.0000004	2.10	0.01830	3.62	0.0000010	0.000220	0.000004	0.0001000	0.000100	0.000100	0.000100	0.0000100
06-Feb-08	15	0.0000004	0.0014944	1.14	0.0002547	0.0006400	0.0011296	0.0002179	0.0001600	1.38	0.000004	0.078720	0.0000034	3.49	0.02778	5.92	0.0000004	0.000051	0.000016	0.000008	0.0000064	0.000048	0.0000032	0.0000100
13-Feb-08	16	0.0000040		0.68	0.0002000		0.0006800	0.0001200	0.0002000	0.86	0.000002	0.045000	0.0000004	2.00	0.01660	3.54	0.0000010	0.000100	0.000004	0.0001000	0.000100	0.000100	0.000100	0.0000100
20-Feb-08	17	0.0000019	0.0014368	1.19	0.0003005	0.0003200	0.0011136	0.0001824	0.0001600	1.33	0.000004	0.086400	0.0000003	3.74	0.02570	5.86	0.0000004	0.000036	0.000016	0.000008	0.0000064	0.000253	0.0000032	0.0000100
27-Feb-08	18	0.0000060		0.71	0.0001800		0.0006800	0.0001200	0.0002000	1.21	0.000004	0.046800	0.0000004	1.94	0.01596	3.52	0.0000010	0.000100	0.000004	0.0001000	0.000100	0.000100	0.000100	0.0000100
05-Mar-08	19	0.0000004	0.0013472	1.12	0.0002685	0.0006400	0.0010752	0.0001590	0.0001600	1.23	0.000005	0.074880	0.0000021	3.08	0.02400	5.25	0.0000004	0.000108	0.000016	0.000008	0.0000064	0.000035	0.0000032	0.0000100
12-Mar-08	20	0.0000040		0.73	0.0001800		0.0007000	0.0001000	0.0002000	0.77	0.000002	0.057800	0.0000004	1.92	0.01532	3.16	0.0000010	0.000100	0.000004	0.000006	0.0001000	0.000100	0.000100	0.0000100
19-Mar-08	21	0.0000083	0.0015328	1.15	0.0002998	0.0006400	0.0011200	0.0001482	0.0002560	1.49	0.000005	0.084480	0.0000024	3.02	0.02426	5.28	0.0000002	0.000149	0.000045	0.000008	0.0000064	0.000384	0.0000032	0.0000100
26-Mar-08	22	0.0000070		0.72	0.0001800		0.0006800	0.0001000	0.0002000	1.66	0.000002	0.093200	0.0000004	1.95	0.01404	3.04	0.0000010	0.000100	0.000004	0.0001000	0.000100	0.000100	0.000100	0.0000100
02-Apr-08	23	0.0000022	0.0013952	1.00	0.0002733	0.0006400	0.0010816	0.0001187	0.0003520	1.23	0.000009	0.074560	0.0000052	2.59	0.02189	4.42	0.0000002	0.000125	0.000051	0.000007	0.0000064	0.000131	0.0000032	0.0000100
09-Apr-08	24	0.0000060		0.63	0.0001600		0.0006200	0.0000800	0.0002000	0.78	0.000002	0.050800	0.0000004	1.64	0.01238	2.64	0.0000010	0.000100	0.000004	0.0001000	0.000100	0.000100	0.000100	0.0000100
16-Apr-08	25	0.0000010	0.0013664	1.01	0.0002810	0.0006400	0.0010336	0.0002131	0.0003200	1.19	0.000003	0.092480	0.0000020	2.70	0.01936	3.87	0.0000004	0.000070	0.000016	0.000007	0.0000064	0.000125	0.0000032	0.0000100
23-Apr-08	26	0.0000040		0.64	0.0001600		0.0006400	0.0001000	0.0002000	0.73	0.000002	0.053200	0.0000004	1.44	0.01172	2.40	0.0000010	0.000100	0.000004	0.0001000	0.000100	0.000100	0.000100	0.0000100
30-Apr-08	27	0.0000022	0.0013440	0.88	0.0002656	0.0016000	0.0009248	0.0001376	0.0003200	1.10	0.000006	0.077120	0.0000016	1.93	0.01747	3.26	0.0000003	0.000112	0.000096	0.000006	0.00000320	0.000064	0.0000160	0.0000100
07-May-08	28	0.0000040		0.55	0.0002200		0.0005400	0.0000600	0.0002600	0.59	0.000004	0.048800	0.0000004	1.23	0.01014	1.88	0.0000010	0.000100	0.000004	0.0001000	0.000100	0.000100	0.000100	0.0000100
14-May-08	29	0.0000037	0.0013344	0.99	0.0003101	0.0003200	0.000696	0.0000899	0.0005080	0.98	0.000004	0.082240	0.0000017	2.17	0.01648	3.33	0.0000004	0.000137	0.000016	0.000007	0.0000064	0.000125	0.0000032	0.0000100
21-May-08	30	0.0000040		0.58	0.0001800		0.0005600	0.0000400	0.0002400	0.60	0.000006	0.042000	0.0000004	1.20	0.00984	1.88	0.0000010	0.000100	0.000004	0.0001000	0.000100	0.000100	0.000100	0.0000100
28-May-08	31	0.0000091	0.0012928	0.91	0.0002746	0.0003200	0.0009824	0.0000829	0.0002460	0.97	0.000003	0.071720	0.0000045	1.90	0.01562	2.94	0.0000005	0.000194	0.000032	0.000006	0.0000064	0.000131	0.0000064	0.0000100
04-Jun-08	32	0.0000060		0.54	0.0001400		0.0005000	0.0000800	0.0002000	0.54	0.000008	0.044000	0.0000006	1.17	0.00896	1.68	0.0000010	0.000100	0.000004	0.0001000	0.000100	0.000100	0.000100	0.0000100
11-Jun-08	33	0.0000010	0.0011616	0.81	0.0002118	0.0009600	0.0008736	0.0000634	0.0008540	0.89	0.000003	0.074560	0.0000006	1.76	0.01331	2.50	0.0000002	0.000127	0.000016	0.000005	0.0000064	0.000070	0.0000032	0.0000100
18-Jun-08	34	0.0000040		0.50	0.0001400		0.0005400	0.0000400	0.0003400	0.52	0.000008	0.047000	0.0000004	1.01	0.00922	1.62	0.0000010	0.000100	0.000004	0.0001000	0.000100	0.000100	0.000100	0.0000100
25-Jun-08	35	0.0000040	0.0013216	0.88	0.0002445	0.0003200	0.0009280	0.0000646	0.0002680	0.89	0.000004	0.083200	0.0000005	1.70	0.01402	2.75	0.0000003	0.000113	0.000016	0.000006	0.0000064	0.000080	0.0000032	0.0000100
02-Jul-08	36	0.0000040		0.62	0.0002200		0.0005800	0.0000600	0.0002600	0.67	0.000002	0.060400	0.0000004	1.16	0.01010	1.80	0.0000010	0.000100	0.000004	0.0001000	0.000100	0.000100	0.000100	0.0000100
09-Jul-08	37	0.0000039	0.0012576	0.72	0.0002509	0.0003200	0.0008800	0.0000630	0.0002240	0.86	0.000002	0.080400	0.0000002	1.40	0.01370	2.37	0.0000007	0.000101	0.000016	0.000005	0.0000064	0.000102	0.0000032	0.0000100
16-Jul-08	38	0.0000040		0.50	0.0001400		0.0005400	0.0000400	0.0002000	0.54	0.000002	0.050400	0.0000004	0.97	0.00868	1.46	0.0000010	0.000100	0.000004	0.0001000	0.000100	0.000100	0.000100	0.0000100
23-Jul-08	39	0.0000028	0.0011712	0.76	0.0002157	0.0003200	0.0008480	0.0000582	0.0051520	0.85	0.000005	0.067520	0.0000002	1.45	0.01264	2.21	0.0000002	0.000111	0.00001					

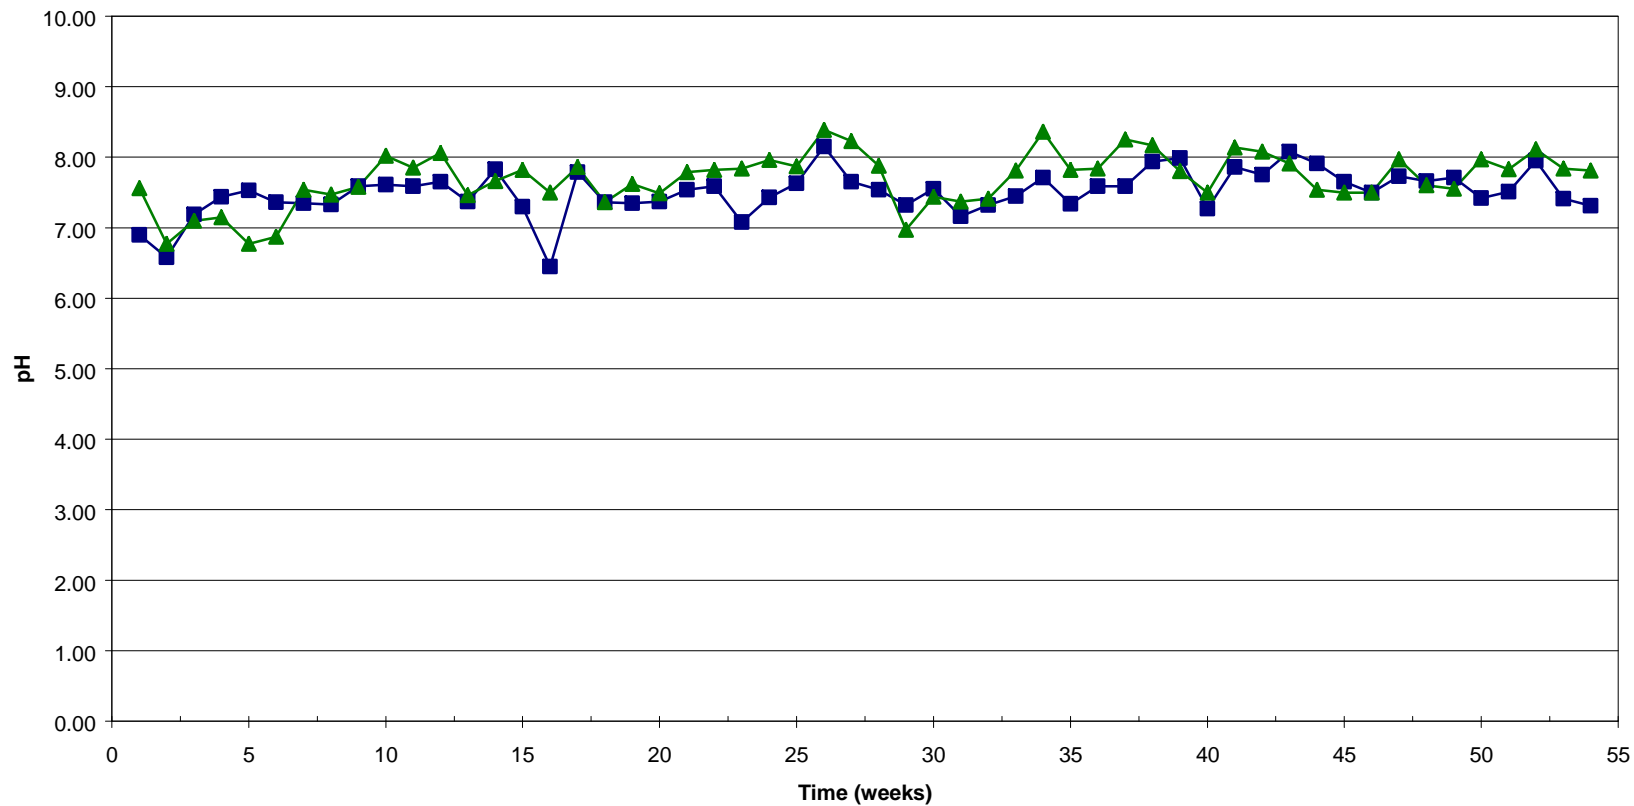

Minago Tails Column Tests
pH
Weeks 1 to 54
Victory Nickel Inc.

Source: adapted from URS (2009i)



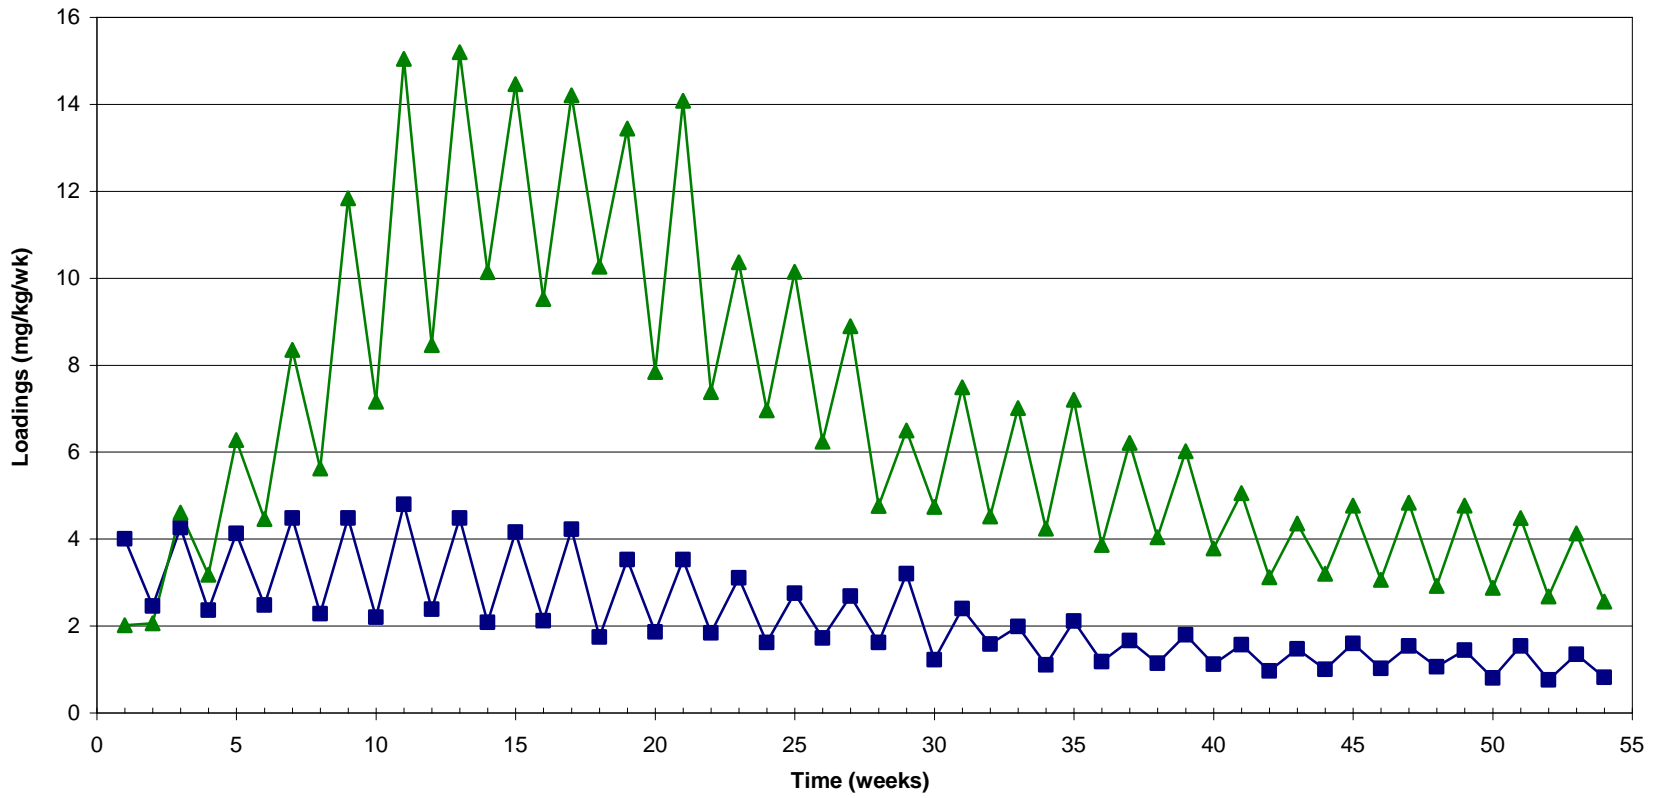


■ Sub-Surface Water ▲ Sub-Pore Water

Minago Tails Column Tests
 Sulphate Loadings
 Weeks 1 to 54
 Victory Nickel Inc.

Source: adapted from URS (2009i)



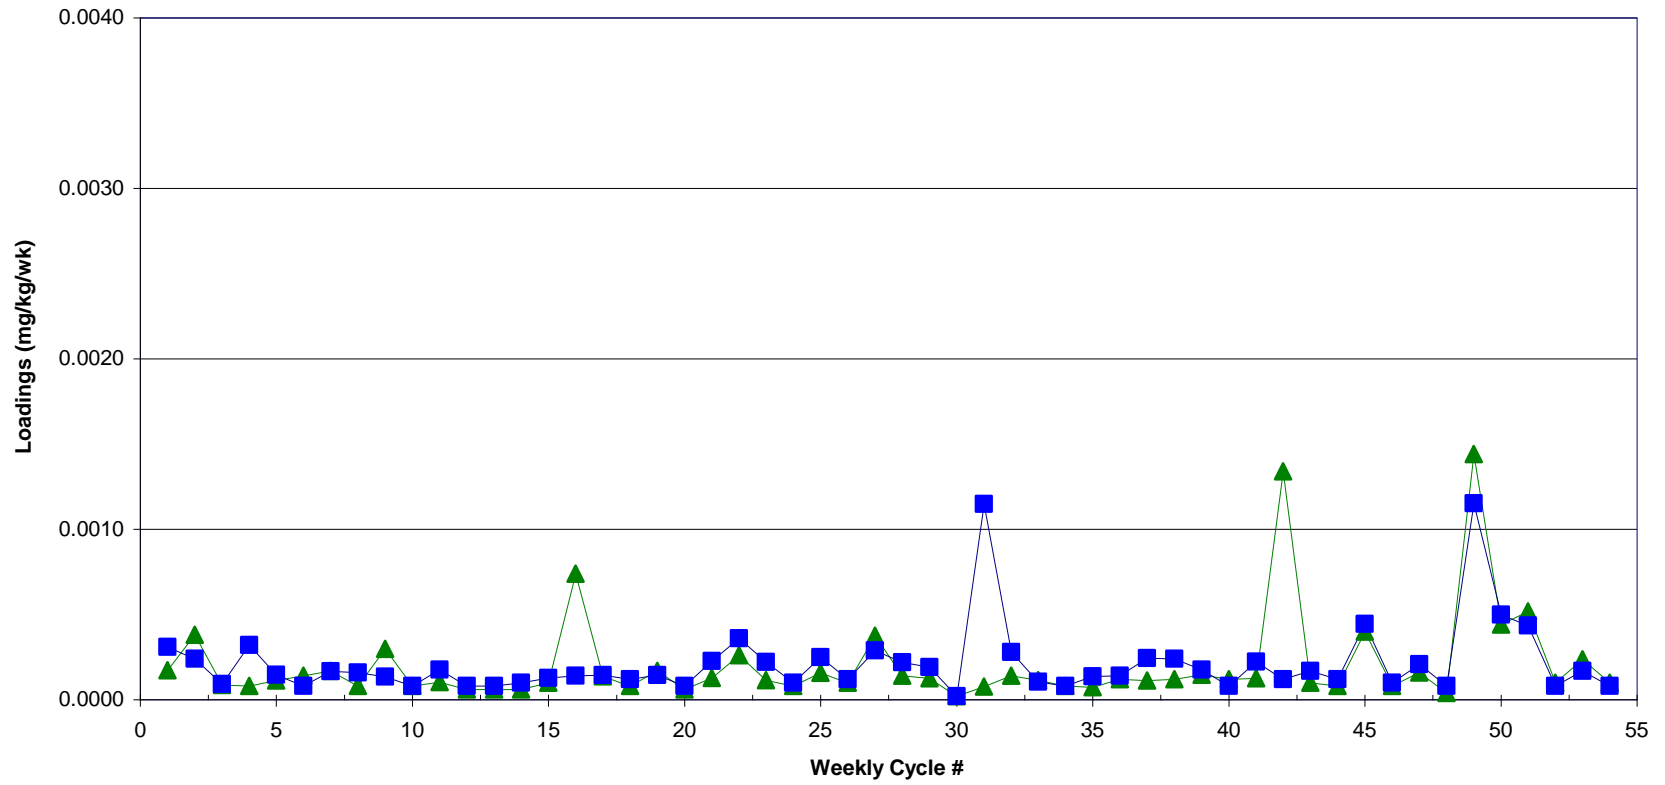


Sub-Surface Water
 Sub-Pore Water

Minago Tails Column Tests
 Aluminum Loadings
 Weeks 1 to 54
 Victory Nickel Inc.

Source: adapted from URS (2009i)



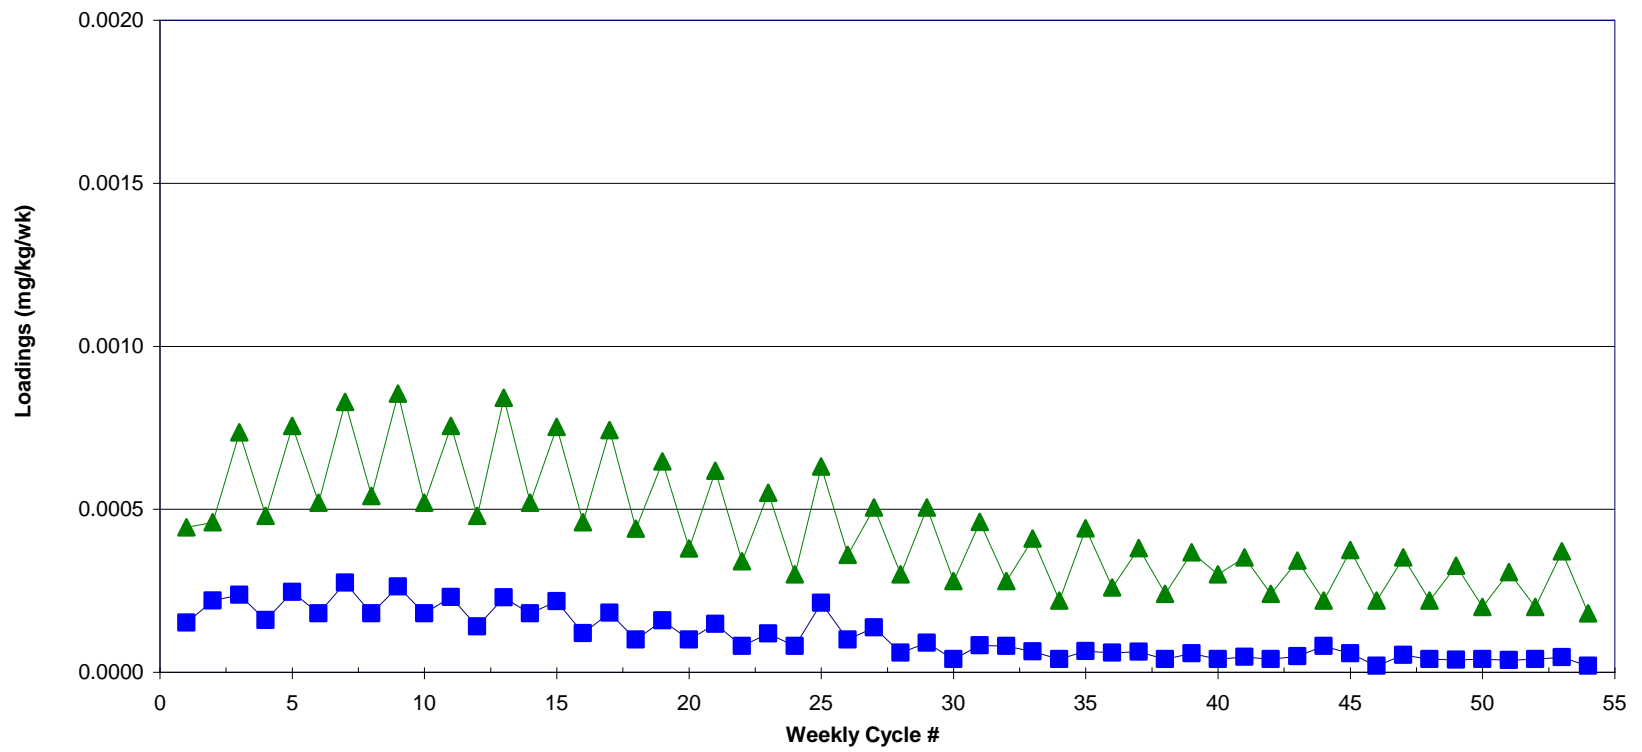


Sub-Surface Water
 Sub-Pore Water

Minago Tails Column Tests Nickel Loadings Weeks 1 to 54
Victory Nickel Inc.

Source: adapted from URS (2009i)



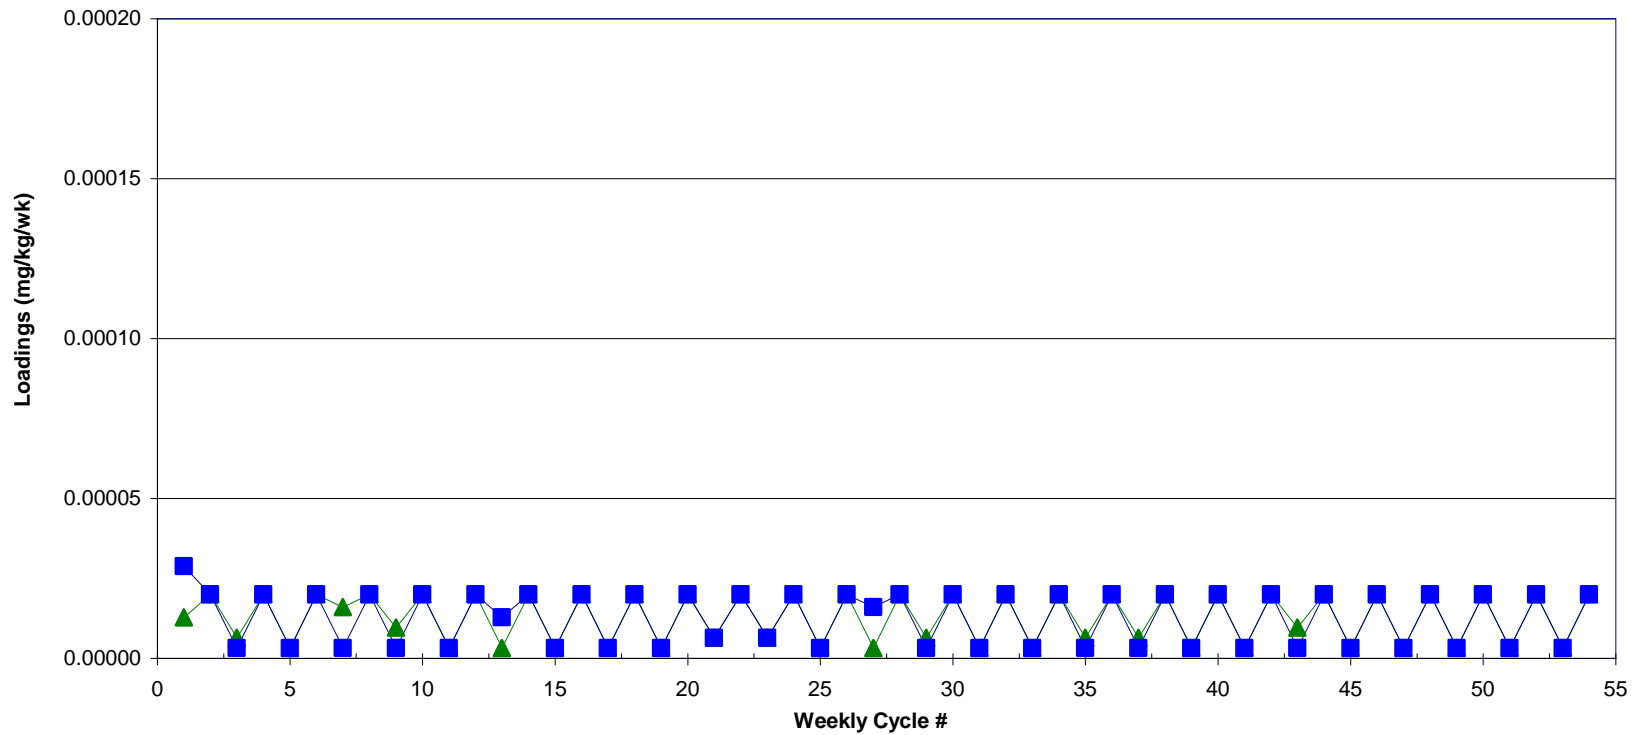


Sub-Surface Water
 Sub-Pore Water

Minago Tails Column Tests	
Chromium Loadings	
Weeks 1 to 54	
Victory Nickel Inc.	

Source: adapted from URS (2009i)




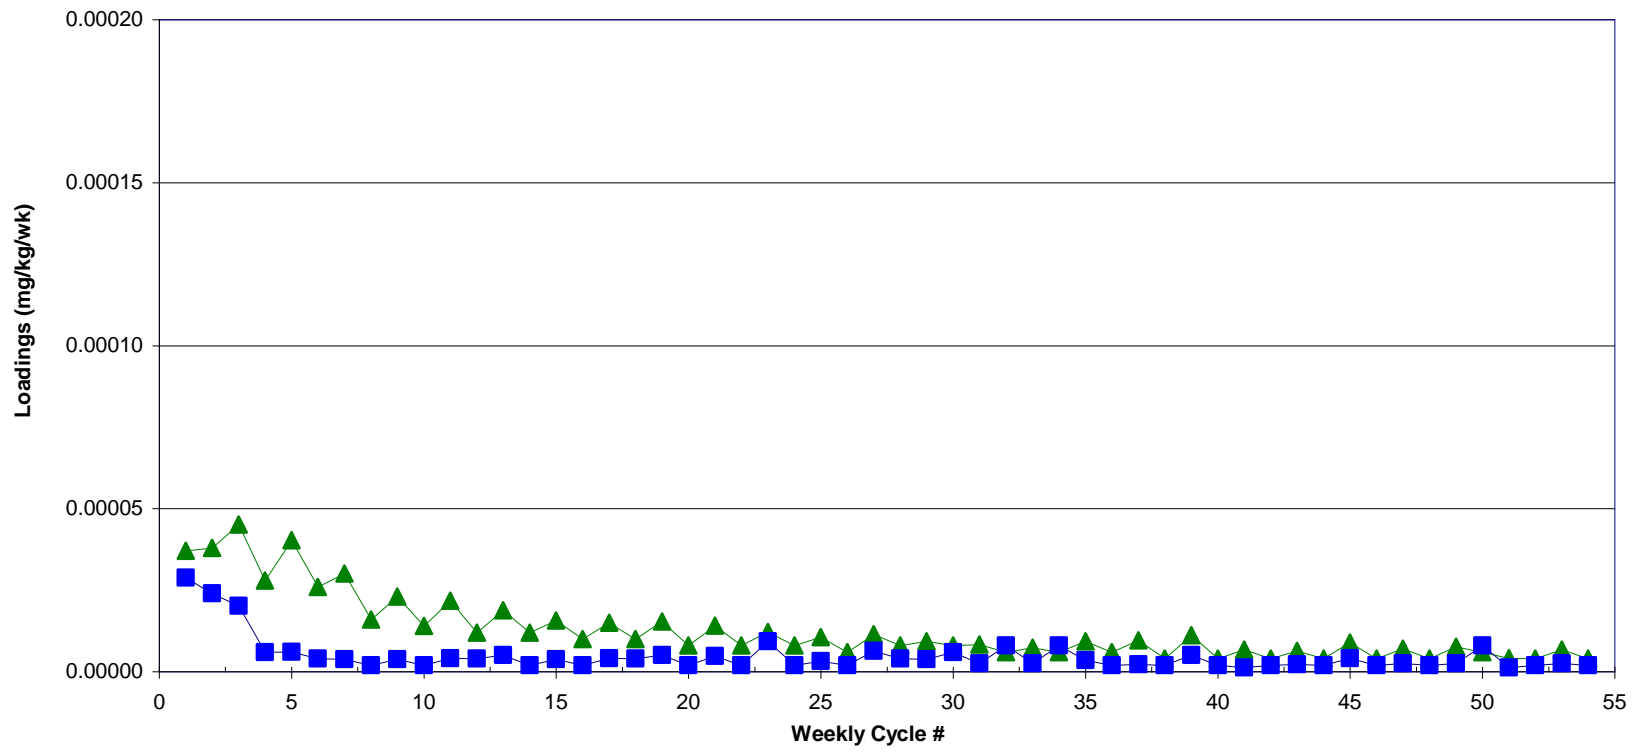

Minago Tails Column Tests
 Selenium Loadings
 Weeks 1 to 54
 Victory Nickel Inc.

Source: adapted from URS (2009i)




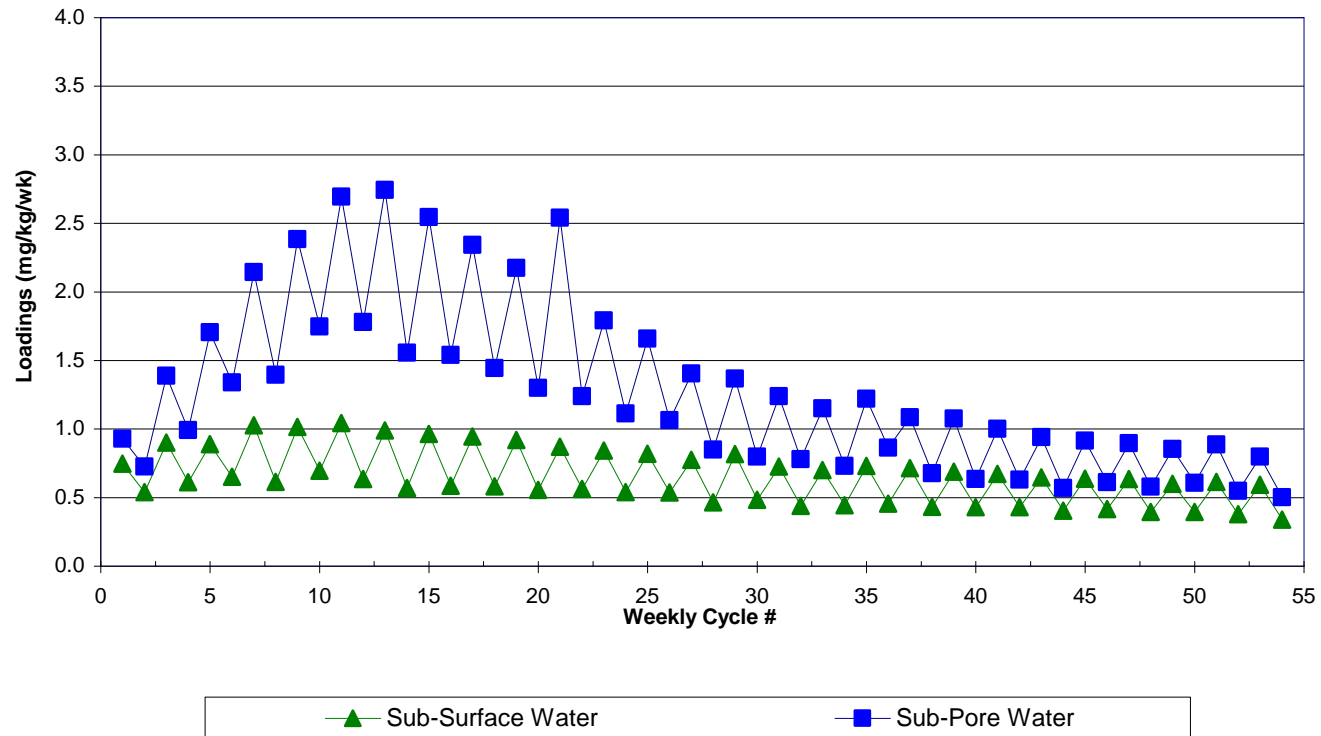

Minago Tails Column Tests
 Calcium Loadings
 Weeks 1 to 54
 Victory Nickel Inc.

Source: adapted from URS (2009i)



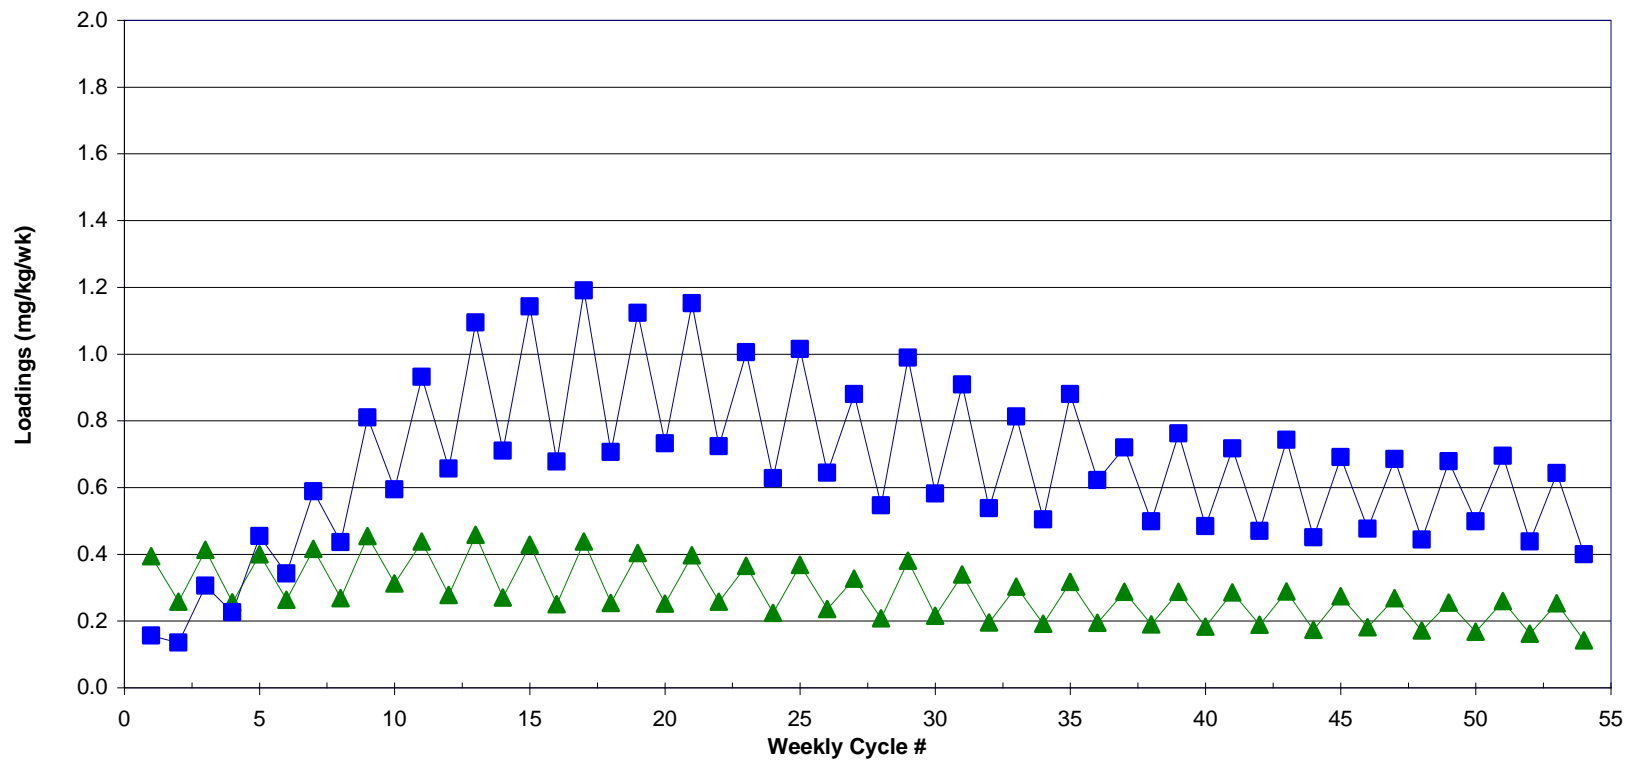

Minago Tails Column Tests Magnesium Loadings Weeks 1 to 54
Victory Nickel Inc.

Source: adapted from URS (2009i)



**TAILINGS SUBAQUEOUS COLUMNS
SULPHIDE DEPLETION CALCULATIONS
MINAGO PROJECT**

WEEK	DATE	SAC-1 Surface Water					SAC-1 Pore Water				
		Loading Rates					Loading Rates				
		Sulphate		Sulphur			Sulphate		Sulphur		
mg/wk	g/wk	mg/wk	g/wk	mol/wk	mmol/wk	mg/wk	g/wk	mg/wk	g/wk	mol/wk	mmol/wk
1	31-Oct-07	20.00	6.67	0.007	0.00021	0.21	10.08	3.36	0.003	0.00010	0.10
2	07-Nov-07	12.30	4.11	0.004	0.00013	0.13	10.30	3.44	0.003	0.00011	0.11
3	14-Nov-07	21.28	7.10	0.007	0.00022	0.22	23.04	7.69	0.008	0.00024	0.24
4	21-Nov-07	11.80	3.94	0.004	0.00012	0.12	15.90	5.31	0.005	0.00017	0.17
5	28-Nov-07	20.64	6.89	0.007	0.00021	0.21	31.36	10.47	0.010	0.00033	0.33
6	05-Dec-07	12.40	4.14	0.004	0.00013	0.13	22.30	7.44	0.007	0.00023	0.23
7	12-Dec-07	22.40	7.48	0.007	0.00023	0.23	41.76	13.94	0.014	0.00043	0.43
8	19-Dec-07	11.40	3.80	0.004	0.00012	0.12	28.10	9.38	0.009	0.00029	0.29
9	26-Dec-07	22.40	7.48	0.007	0.00023	0.23	59.20	19.76	0.020	0.00062	0.62
10	02-Jan-08	11.00	3.67	0.004	0.00011	0.11	35.80	11.95	0.012	0.00037	0.37
11	09-Jan-08	24.00	8.01	0.008	0.00025	0.25	75.20	25.10	0.025	0.00078	0.78
12	16-Jan-08	11.90	3.97	0.004	0.00012	0.12	42.30	14.12	0.014	0.00044	0.44
13	23-Jan-08	22.40	7.48	0.007	0.00023	0.23	76.00	25.36	0.025	0.00079	0.79
14	30-Jan-08	10.40	3.47	0.003	0.00011	0.11	50.70	16.92	0.017	0.00053	0.53
15	06-Feb-08	20.80	6.94	0.007	0.00022	0.22	72.32	24.14	0.024	0.00075	0.75
16	13-Feb-08	10.60	3.54	0.004	0.00011	0.11	47.60	15.89	0.016	0.00050	0.50
17	20-Feb-08	21.12	7.05	0.007	0.00022	0.22	71.04	23.71	0.024	0.00074	0.74
18	27-Feb-08	8.70	2.90	0.003	0.00009	0.09	51.30	17.12	0.017	0.00053	0.53
19	05-Mar-08	17.60	5.87	0.006	0.00018	0.18	67.20	22.43	0.022	0.00070	0.70
20	12-Mar-08	9.30	3.10	0.003	0.00010	0.10	39.20	13.08	0.013	0.00041	0.41
21	19-Mar-08	17.60	5.87	0.006	0.00018	0.18	70.40	23.50	0.023	0.00073	0.73
22	26-Mar-08	9.20	3.07	0.003	0.00010	0.10	36.90	12.32	0.012	0.00038	0.38
23	02-Apr-08	15.52	5.18	0.005	0.00016	0.16	51.84	17.30	0.017	0.00054	0.54
24	09-Apr-08	8.10	2.70	0.003	0.00008	0.08	34.80	11.61	0.012	0.00036	0.36
25	16-Apr-08	13.76	4.59	0.005	0.00014	0.14	50.72	16.93	0.017	0.00053	0.53
26	23-Apr-08	8.60	2.87	0.003	0.00009	0.09	31.20	10.41	0.010	0.00032	0.32
27	30-Apr-08	13.44	4.49	0.004	0.00014	0.14	44.48	14.85	0.015	0.00046	0.46
28	07-May-08	8.10	2.70	0.003	0.00008	0.08	23.80	7.94	0.008	0.00025	0.25
29	14-May-08	16.00	5.34	0.005	0.00017	0.17	32.48	10.84	0.011	0.00034	0.34
30	21-May-08	6.10	2.04	0.002	0.00006	0.06	23.70	7.91	0.008	0.00025	0.25
31	28-May-08	12.00	4.00	0.004	0.00012	0.12	37.44	12.50	0.012	0.00039	0.39
32	04-Jun-08	7.90	2.64	0.003	0.00008	0.08	22.60	7.54	0.008	0.00024	0.24
33	11-Jun-08	9.92	3.31	0.003	0.00010	0.10	35.04	11.69	0.012	0.00036	0.36
34	18-Jun-08	5.50	1.84	0.002	0.00006	0.06	21.20	7.08	0.007	0.00022	0.22
35	25-Jun-08	10.56	3.52	0.004	0.00011	0.11	36.00	12.01	0.012	0.00037	0.37
36	02-Jul-08	5.90	1.97	0.002	0.00006	0.06	19.30	6.44	0.006	0.00020	0.20
37	09-Jul-08	8.32	2.78	0.003	0.00009	0.09	31.04	10.36	0.010	0.00032	0.32
38	16-Jul-08	5.70	1.90	0.002	0.00006	0.06	20.20	6.74	0.007	0.00021	0.21
39	23-Jul-08	8.96	2.99	0.003	0.00009	0.09	30.08	10.04	0.010	0.00031	0.31
40	30-Jul-08	5.60	1.87	0.002	0.00006	0.06	18.90	6.31	0.006	0.00020	0.20
41	06-Aug-08	7.84	2.62	0.003	0.00008	0.08	25.28	8.44	0.008	0.00026	0.26
42	13-Aug-08	4.80	1.60	0.002	0.00005	0.05	15.60	5.21	0.005	0.00016	0.16
43	20-Aug-08	7.36	2.46	0.002	0.00008	0.08	21.76	7.26	0.007	0.00023	0.23
44	27-Aug-08	5.00	1.67	0.002	0.00005	0.05	16.00	5.34	0.005	0.00017	0.17
45	03-Sep-08	8.00	2.67	0.003	0.00008	0.08	23.84	7.96	0.008	0.00025	0.25
46	10-Sep-08	5.10	1.70	0.002	0.00005	0.05	15.30	5.11	0.005	0.00016	0.16
47	17-Sep-08	7.68	2.56	0.003	0.00008	0.08	24.16	8.06	0.008	0.00025	0.25
48	24-Sep-08	5.30	1.77	0.002	0.00006	0.06	14.60	4.87	0.005	0.00015	0.15
49	01-Oct-08	7.20	2.40	0.002	0.00007	0.07	23.84	7.96	0.008	0.00025	0.25
50	08-Oct-08	4.00	1.33	0.001	0.00004	0.04	14.40	4.81	0.005	0.00015	0.15
51	15-Oct-08	7.68	2.56	0.003	0.00008	0.08	22.40	7.48	0.007	0.00023	0.23
52	22-Oct-08	3.80	1.27	0.001	0.00004	0.04	13.40	4.47	0.004	0.00014	0.14
53	29-Oct-08	6.72	2.24	0.002	0.00007	0.07	20.64	6.89	0.007	0.00021	0.21
54	05-Nov-08	4.10	1.37	0.001	0.00004	0.04	12.80	4.27	0.004	0.00013	0.13
Weekly depletion rates, steady state period - weeks 11 to 54		9.96	3.32	0.0033	0.0001	0.10	34.75	11.60	0.0116	0.0004	0.36

COLUMN	Column mass (kg)	Initial Sulphide-S					Sulphur remaining (mmol)	Avg. Sulphur depletion rate (mmol/kg/wk)	Weeks to Sulphur depletion	Years to Sulphur depletion
		(%)	(mg/kg)	(g/kg)	(mol)	(mmol)				
SAC-1 SURFACE WATER	5	0.07	700	0.7	0.11	109.17	102.88	0.021	992.4	19.08
SAC-1 PORE WATER	5	0.07	700	0.7	0.11	109.17	90.36	0.072	249.8	4.80

**TAILINGS SUBAQUEOUS COLUMNS
ACID NEUTRALIZATION DEPLETION CALCULATIONS
MINAGO PROJECT**

WEEK	DATE	SAC-1 Surface Water				SAC-1 Pore Water			
		Calcium Loading				Calcium Loading			
		mg/lwk	g/wk	mmol/wk	mmol/wk	mg/lwk	g/wk	mmol/wk	mmol/wk
2	31-Oct-07	3.73	0.00373	0.00009	0.08301	4.64	0.0046	0.0001	0.1158
3	07-Nov-07	2.69	0.00269	0.00007	0.06712	3.63	0.0036	0.0001	0.0906
4	14-Nov-07	4.50	0.00450	0.00011	0.11218	6.94	0.0069	0.0002	0.1733
5	21-Nov-07	3.06	0.00306	0.00008	0.07635	4.96	0.0050	0.0001	0.1238
6	28-Nov-07	4.45	0.00445	0.00011	0.11098	8.53	0.0085	0.0002	0.2128
7	05-Dec-07	3.25	0.00325	0.00008	0.08109	6.69	0.0067	0.0002	0.1669
8	12-Dec-07	5.14	0.00514	0.00013	0.13014	10.72	0.0107	0.0003	0.2675
9	19-Dec-07	3.07	0.00307	0.00008	0.07660	6.97	0.0070	0.0002	0.1739
10	26-Dec-07	5.07	0.00507	0.00013	0.12655	11.92	0.0119	0.0003	0.2974
11	02-Jan-08	3.48	0.00348	0.00009	0.08683	8.74	0.0087	0.0002	0.2181
12	09-Jan-08	5.22	0.00522	0.00013	0.13014	13.47	0.0135	0.0003	0.3361
13	16-Jan-08	3.17	0.00317	0.00008	0.07909	8.90	0.0089	0.0002	0.2221
14	23-Jan-08	4.94	0.00494	0.00012	0.12335	13.71	0.0137	0.0003	0.3421
15	30-Jan-08	2.85	0.00285	0.00007	0.07111	7.78	0.0078	0.0002	0.1941
16	06-Feb-08	4.82	0.00482	0.00012	0.12016	12.72	0.0127	0.0003	0.3174
17	13-Feb-08	2.93	0.00293	0.00007	0.07410	7.70	0.0077	0.0002	0.1921
18	20-Feb-08	4.72	0.00472	0.00012	0.11776	11.71	0.0117	0.0003	0.2922
19	27-Feb-08	2.90	0.00290	0.00007	0.07236	7.22	0.0072	0.0002	0.1801
20	05-Mar-08	4.59	0.00459	0.00011	0.11457	10.86	0.0109	0.0003	0.2711
21	12-Mar-08	2.77	0.00277	0.00007	0.06911	6.50	0.0065	0.0002	0.1622
22	19-Mar-08	4.35	0.00435	0.00011	0.10858	12.70	0.0127	0.0003	0.3170
23	26-Mar-08	2.27	0.00227	0.00006	0.05604	4.21	0.0042	0.0001	0.1075
24	02-Apr-08	4.21	0.00421	0.00010	0.10499	8.96	0.0090	0.0002	0.2236
25	09-Apr-08	2.69	0.00269	0.00007	0.06712	5.56	0.0056	0.0001	0.1387
26	16-Apr-08	4.10	0.00410	0.00010	0.10220	8.29	0.0083	0.0002	0.2068
27	23-Apr-08	2.68	0.00268	0.00007	0.06687	5.32	0.0053	0.0001	0.1327
28	30-Apr-08	3.87	0.00387	0.00010	0.09661	7.02	0.0070	0.0002	0.1752
29	07-May-08	2.32	0.00232	0.00006	0.05788	4.25	0.0043	0.0001	0.1060
30	14-May-08	4.98	0.00498	0.00012	0.10160	10.83	0.0108	0.0003	0.2705
31	21-May-08	2.41	0.00241	0.00006	0.06013	3.99	0.0040	0.0001	0.0996
32	28-May-08	3.63	0.00363	0.00009	0.09062	6.19	0.0062	0.0002	0.1545
33	04-Jun-08	2.19	0.00219	0.00005	0.05464	3.89	0.0039	0.0001	0.0971
34	11-Jun-08	3.50	0.00350	0.00009	0.08743	5.74	0.0057	0.0001	0.1433
35	18-Jun-08	2.21	0.00221	0.00006	0.05514	3.65	0.0037	0.0001	0.0911
36	25-Jun-08	3.65	0.00365	0.00009	0.09102	6.10	0.0061	0.0002	0.1521
37	02-Jul-08	2.27	0.00227	0.00006	0.05664	4.21	0.0042	0.0001	0.1075
38	09-Jul-08	3.57	0.00357	0.00009	0.08902	5.42	0.0054	0.0001	0.1353
39	16-Jul-08	2.16	0.00216	0.00005	0.05389	3.38	0.0034	0.0001	0.0843
40	23-Jul-08	3.44	0.00344	0.00009	0.08583	5.38	0.0054	0.0001	0.1341
41	30-Jul-08	2.14	0.00214	0.00005	0.05339	3.17	0.0032	0.0001	0.0791
42	06-Aug-08	3.36	0.00336	0.00008	0.08383	5.01	0.0050	0.0001	0.1250
43	13-Aug-08	2.15	0.00215	0.00005	0.05364	3.15	0.0032	0.0001	0.0786
44	20-Aug-08	3.23	0.00323	0.00008	0.08064	4.70	0.0047	0.0001	0.1174
45	27-Aug-08	2.02	0.00202	0.00005	0.05040	2.85	0.0029	0.0001	0.0711
46	03-Sep-08	3.18	0.00318	0.00008	0.07944	4.58	0.0046	0.0001	0.1142
47	10-Sep-08	2.07	0.00207	0.00005	0.05165	3.06	0.0031	0.0001	0.0763
48	17-Sep-08	3.17	0.00317	0.00008	0.07904	4.48	0.0045	0.0001	0.1118
49	24-Sep-08	1.97	0.00197	0.00005	0.04915	2.89	0.0029	0.0001	0.0721
50	01-Oct-08	2.99	0.00299	0.00007	0.07465	4.27	0.0043	0.0001	0.1066
51	08-Oct-08	1.97	0.00197	0.00005	0.04915	3.03	0.0030	0.0001	0.0756
52	15-Oct-08	3.07	0.00307	0.00008	0.07665	4.43	0.0044	0.0001	0.1106
53	22-Oct-08	1.89	0.00189	0.00005	0.04716	2.74	0.0027	0.0001	0.0684
54	29-Oct-08	2.96	0.00296	0.00007	0.07385	3.98	0.0040	0.0001	0.0994
54	05-Nov-08	1.69	0.00169	0.00004	0.04217	2.51	0.0025	0.0001	0.0626
		SAC-1 Surface Water				SAC-1 Pore Water			
		Magnesium Loading				Magnesium Loading			
WEEK	DATE	mg/lwk	g/wk	mmol/wk	mmol/wk	mg/lwk	g/wk	mmol/wk	mmol/wk
1	31-Oct-07	1.97	0.002	0.00008	0.081	0.78	0.001	0.00003	0.032
2	07-Nov-07	1.29	0.001	0.00005	0.053	0.68	0.001	0.00003	0.028
3	14-Nov-07	2.06	0.002	0.00008	0.085	1.53	0.002	0.00006	0.063
4	21-Nov-07	1.28	0.001	0.00005	0.053	1.13	0.001	0.00005	0.046
5	28-Nov-07	2.00	0.002	0.00008	0.082	2.27	0.002	0.00009	0.093
6	05-Dec-07	2.08	0.002	0.00008	0.086	2.94	0.003	0.00012	0.121
7	12-Dec-07	1.34	0.001	0.00006	0.055	2.18	0.002	0.00009	0.090
8	19-Dec-07	2.27	0.002	0.00009	0.093	4.05	0.004	0.00017	0.167
9	26-Dec-07	1.56	0.002	0.00006	0.064	2.97	0.003	0.00012	0.122
10	02-Jan-08	2.19	0.002	0.00009	0.090	4.66	0.005	0.00019	0.192
11	09-Jan-08	1.39	0.001	0.00006	0.057	3.28	0.003	0.00013	0.135
12	16-Jan-08	2.29	0.002	0.00009	0.094	4.47	0.004	0.00016	0.157
13	23-Jan-08	1.35	0.001	0.00006	0.056	3.55	0.004	0.00015	0.146
14	30-Jan-08	2.14	0.002	0.00009	0.088	5.71	0.006	0.00023	0.235
15	06-Feb-08	1.25	0.001	0.00005	0.051	3.39	0.003	0.00014	0.139
16	13-Feb-08	2.19	0.002	0.00009	0.090	5.95	0.006	0.00024	0.245
17	20-Feb-08	1.27	0.001	0.00005	0.052	3.53	0.004	0.00015	0.145
18	27-Feb-08	2.02	0.002	0.00008	0.083	5.62	0.006	0.00023	0.231
19	05-Mar-08	1.26	0.001	0.00005	0.052	3.66	0.004	0.00015	0.151
20	12-Mar-08	1.98	0.002	0.00008	0.082	5.76	0.006	0.00024	0.237
21	19-Mar-08	1.29	0.001	0.00005	0.053	3.62	0.004	0.00015	0.149
22	26-Mar-08	1.82	0.002	0.00008	0.075	5.02	0.005	0.00021	0.207
23	02-Apr-08	1.12	0.001	0.00005	0.046	3.14	0.003	0.00013	0.129
24	09-Apr-08	1.84	0.002	0.00008	0.076	5.07	0.005	0.00021	0.209
25	16-Apr-08	1.18	0.001	0.00005	0.049	3.22	0.003	0.00013	0.132
26	23-Apr-08	1.63	0.002	0.00007	0.067	4.40	0.004	0.00016	0.161
27	30-Apr-08	1.04	0.001	0.00004	0.043	2.73	0.003	0.00011	0.112
28	07-May-08	1.90	0.002	0.00008	0.078	4.94	0.005	0.00020	0.203
29	14-May-08	1.08	0.001	0.00004	0.044	2.91	0.003	0.00012	0.120
30	21-May-08	1.70	0.002	0.00007	0.070	4.54	0.005	0.00019	0.187
31	28-May-08	0.98	0.001	0.00004	0.040	2.69	0.003	0.00011	0.111
32	04-Jun-08	1.51	0.002	0.00006	0.062	4.06	0.004	0.00017	0.167
33	11-Jun-08	0.96	0.001	0.00004	0.039	2.52	0.003	0.00010	0.104
34	18-Jun-08	1.58	0.002	0.00007	0.065	4.40	0.004	0.00018	0.181
35	25-Jun-08	0.97	0.001	0.00004	0.040	3.11	0.003	0.00013	0.128
36	02-Jul-08	1.44	0.001	0.00006	0.059	3.60	0.004	0.00015	0.148
37	09-Jul-08	0.95	0.001	0.00004	0.039	2.49	0.002	0.00010	0.102
38	16-Jul-08	1.44	0.001	0.00006	0.059	3.81	0.004	0.00016	0.157
39	23-Jul-08	0.92	0.001	0.00004	0.038	2.42	0.002	0.00010	0.100
40	30-Jul-08	1.43	0.001	0.00006	0.059	3.58	0.004	0.00015	0.147
41	06-Aug-08	0.95	0.001	0.00004	0.039	2.35	0.002	0.00010	0.097
42	13-Aug-08	1.44	0.001	0.00006	0.059	3.71	0.004	0.00015	0.153
43	20-Aug-08	0.87	0.001	0.00004	0.036	2.25	0.002	0.00009	0.093
44	27-Aug-08	1.37	0.001	0.00006	0.056	3.46	0.003	0.00014	0.142
45	03-Sep-08	0.91	0.001	0.00004	0.037	2.38	0.002	0.00010	0.098
46	10-Sep-08	1.34	0.001	0.00006	0.055	3.42	0.003	0.00014	0.141
47	17-Sep-08	0.86	0.001	0.00004	0.035	2.22	0.002	0.00009	0.091
48	24-Sep-08	1.28	0.001	0.00005	0.052	3.39	0.003	0.00014	0.140
49	01-Oct-08	0.84	0.001	0.00003	0.035	2.49	0.002	0.00010	0.102
50	08-Oct-08	1.30	0.001	0.00005	0.053	3.47	0.003	0.00014	0.143
51	15-Oct-08	0.81	0.001	0.00003	0.033	2.19	0.002	0.00009	0.090
52	22-Oct-08	1.27	0.001	0.00005	0.052	3.22	0.003	0.00013	0.132
53	29-Oct-08	0.71	0.001	0.00003	0.029	2.00	0.002	0.00008	0.082
54	05-Nov-08	4.48	0.0045	0.00013	0.134	9.73	0.010	0.00030	0.301
Combined weekly depletion rates, steady state period - weeks 11 to 54									

COLUMN	Sample mass (kg)	Initial Total Carbonate ¹					Remaining Carbonate (mmol) ²	Avg. Carbonate Depletion Rate (mmol/kg/wk) ³	Weeks to Carbonate Depletion
--------	------------------	--------------------------------------	--	--	--	--	---	---	------------------------------

APPENDIX 2.9

Supplemental Material for Mining Processes

Table A2.9.1 Anticipated Penetration Rate and Drilling Rate

	Units	Rock Type		
		Dolomite	Basement Waste	Ore
Hole Depth	m	13.7	13.7	13.6
Penetration Rate	cm/min	100	65	65
Grade control sampling time	min	2.0	2.0	2.0
Move and Align Time	min	3.0	3.0	3.0
Total Time Per Hole	min	18.18	25.55	25.42
Holes Per Hour	holes	3.30	2.35	2.36
Average Drilling Rate	m/h	45	32	32

Source: Wardrop, 2009b

Table A2.9.2 Yearly Drill Net Operating Hours Available per Unit

Drills		2011	2012	2013	2014	2015	2016	2017	2018	2019	2020	2021
Total Time	hrs/unit		8,640	8,640	8,640	8,640	8,640	8,640	8,640	8,640	8,640	8,640
Availability	%		85.00%	82.00%	79.00%	76.00%	73.00%	70.00%	70.00%	70.00%	70.00%	70.00%
Down Time	hrs/unit		1,296	1,555	1,814	2,074	2,333	2,592	2,592	2,592	2,592	2,592
Available Time	hrs/unit		7,344	7,085	6,826	6,566	6,307	6,048	6,048	6,048	6,048	6,048
Standby Time	hrs/unit		0	0	0	0	0	0	0	0	0	0
Gross Operating Hours	hrs/unit		7,344	7,085	6,826	6,566	6,307	6,048	6,048	6,048	6,048	6,048
Operating Delays	hrs/unit		1,104	1,104	1,104	1,104	1,104	1,104	1,104	1,104	1,104	1,104
Net Operating Hours	hrs/unit		6,240	5,981	5,722	5,462	5,203	4,944	4,944	4,944	4,944	4,944

Source: Wardrop, 2009b

Table A2.9.3 Yearly Shovel Net Operating Hours Available per Unit

Shovel PC4000		2012	2013	2014	2015	2016	2017	2018	2019	2020	2021
Total Time	hrs/unit	8,640	8,640	8,640	8,640	8,640	8,640	8,640	8,640	8,640	8,640
Physical Availability	%	92%	92%	89%	86%	83%	80%	77%	74%	74%	74%
Down Time	hrs/unit	691	691	950	1,210	1,469	1,728	1,987	2,246	2,246	2,246
Available Time	hrs/unit	7,949	7,949	7,690	7,430	7,171	6,912	6,653	6,394	6,394	6,394
Standby Time	hrs/unit	238	238	231	223	215	207	200	192	192	192
Gross Operating Hours	hrs/unit	7,710	7,710	7,459	7,207	6,956	6,705	6,453	6,202	6,202	6,202
Operating Delays	hrs/unit	1,524	1,524	1,524	1,524	1,524	1,524	1,524	1,524	1,524	1,524
Net Operating Hours (NOH)	hrs/unit	6,186	6,186	5,935	5,683	5,432	5,181	4,929	4,678	4,678	4,678

Source: Wardrop, 2009b

Table A2.9.4 Sample Shovel Productivity Calculations

		PC 400E Shovel	L1350 Loader
Bucket Capacity (heaped)	m ³	21.0	20.0
Material Weight	dmt /bcm	2.57	2.57
Bulk Factor		1.3	1.3
Material Weight	dmt /lcm	1.98	1.98
Moisture	%	3%	3%
Material Weight	wmt /lcm	2.04	2.04
Fill Factor	%	95%	95%
Effective Bucket Capacity	m ³	20.0	19.0
Tonnes/Pass	wmt	40.7	38.7
Truck Size Capacity	wmt	223.4	223.4
Ave # Passes	Passes	5.5	5.8
Truck Spot Time	Sec	30	30
First Bucket Cycle Time	Sec	37	47
Subsequent Bucket Cycle Time	Sec	37	47
Load Time per Truck	Min	3.9	5.0
Maximum Productivity	trks /hr	15.4	12.0
	wmt /hr	3,447	2,671
Truck Availability to Shovel	%	80%	80%
Producing Hours	hrs/year	4,133	4,133
Annual wet Tonnes	wmt /year	14,246,575	11,036,558
Base Productivity	wmt /NOH	2,758	2,136

Source: Wardrop, 2009b

Note:

- * dmt - dry metric tonne
- wmt - wet metric tonne
- bcm - bank cubic metre
- lcm - loose cubic metre
- NOH - Net Operating Hour

Table A2.9.5 Yearly Truck Net Operation Hours Available per Unit

Trucks		2011	2012	2013	2014	2015	2016	2017	2018	2019	2020	2021
Total Time	hrs/unit		8,640	8,640	8,640	8,640	8,640	8,640	8,640	8,640	8,640	8,640
Availability	%		95.00%	92.78%	89.90%	87.12%	84.45%	81.87%	79.38%	76.98%	75.00%	75.00%
Down Time	hrs/unit		432	688	934	1,172	1,401	1,622	1,835	2,040	2,160	2,160
Available Time	hrs/unit		8,208	7,952	7,706	7,468	7,239	7,018	6,805	6,600	6,480	6,480
Gross Operating Hours	hrs/unit		8,208	7,952	7,706	7,468	7,239	7,018	6,805	6,600	6,480	6,480
Operating Delays	hrs/unit		1,104	1,104	1,104	1,104	1,104	1,104	1,104	1,104	1,104	1,104
Net Operating	hrs/unit		7,104	6,848	6,602	6,364	6,135	5,914	5,701	5,496	5,376	5,376

Source: Wardrop, 2009b

APPENDIX 2.10

Supplemental Material for Milling Processes

	Page
Appendix 2.10-A: Material Safety Data Sheets for the Mill Reagents and Flocculants	2.10-1
Appendix 2.10-B: Process Flow Diagrams for the Frac Sand Plant	2.10-68

Drawing No.	Title	Description
WP-PFD-001 revP2	Area 01/Wet Plant	Screening and scrubbing
WP-PFD-002 revP2	Area 02/Wet Plant	Density separator circuit - Friable
WP-PFD-003 revP2	Area 03/Wet Plant	Crushing - Non Friable
WP-PFD-004 revP2	Area 04/Wet Plant	Density separator circuit - Non Friable
WP-PFD-005 revP2	Area 05/Wet Plant	Plant Thickener
DP-PFD-001 revP3	Area 06/Dry Plant	Drying and screening - Friable
DP-PFD-002 revP3	Area 07/Dry Plant	Screening and magnetic separation - Friable
DP-PFD-003 revP2	Area 08/Dry Plant	Drying and Screening - Non Friable
DP-PFD-004 revP3	Area 09/Dry Plant	Storage silos - Friable and Non Friable
DP-PFD-005 revP2	Area 09/Dry Plant	Plant Product load out

Source: Outotec, 2008

APPENDIX 2.10-A

Material Safety Data Sheets for the Mill Reagents and Flocculants

CMC	Carboxmethyl Cellulose
PAX	Potassium Amyl Xanthate
SHMP	Sodium hexametaphosphate
MIBC	Methyl isobutyl carbinol
Flocculant	Anionic polyacrylamide, Hyperfloc

MATERIAL SAFETY DATA SHEET

2.10-2

Avicel® RC/CL Microcrystalline Cellulose and Sodium Carboxymethylcellulose

FMC BioPolymer

MSDS Ref. No.: 51395-75-6
Date Approved: 01/31/2008
Revision No.: 9

This document has been prepared to meet the requirements of the U.S. OSHA Hazard Communication Standard, 29 CFR 1910.1200 and Canada's Workplace Hazardous Materials Information System (WHMIS) requirements.

1. PRODUCT AND COMPANY IDENTIFICATION

PRODUCT NAME: Avicel® RC/CL Microcrystalline Cellulose and Sodium Carboxymethylcellulose

CHEMICAL FAMILY: Carbohydrate, Cellulose Derivative

SYNONYMS: Microcrystalline cellulose (INCI name): MCC, cellulose gel; Sodium Carboxymethylcellulose: NaCMC, CMC, SCMC, Carboxymethylcellulose, Carboxymethyl ether, Sodium CMC, Sodium salt, Cellulose gum

ALTERNATE PRODUCT NAME(S): Avicel® RC 501, 581, 591, CL 611

MANUFACTURER

FMC BioPolymer
1735 Market Street
Philadelphia, PA 19103
(800) 526-3649 (General Information)
msdsinfo@fmc.com (Email - General Information)

FMC Europe NV
Avenue Mounier 83
1200 Brussels, Belgium
353 21 435 4133 (General Information - Cork, Ireland)

EMERGENCY TELEPHONE NUMBERS

(302) 451-0100 (FMC Plant - Newark, Delaware)

(303) 595-9048 (Medical - U.S. - Call Collect)

For leak, fire, spill, or accident emergencies, call:
(800) 424-9300 (CHEMTREC - U.S.A. & Canada)
(703) 527-3887 (CHEMTREC - Collect - All Other Countries)

2. HAZARDS IDENTIFICATION

EMERGENCY OVERVIEW:

- Off-white, free-flowing, odorless powder.
- Accumulation of overhead settled dust may form explosive concentrations in air when disturbed and dispersed.
- Powder becomes slippery when wet.

POTENTIAL HEALTH EFFECTS: No significant health hazard expected.

3. COMPOSITION / INFORMATION ON INGREDIENTS

Chemical Name	CAS#	Wt.%	EC No.	EC Class
Microcrystalline cellulose	9004-34-6		232-674-9	Not Classified
Sodium Carboxymethylcellulose	9004-32-4		None	Not classified

4. FIRST AID MEASURES

EYES: Flush with water for at least 15 minutes. If irritation occurs and persists, obtain medical attention.

SKIN: Wash with plenty of soap and water.

INGESTION: Drink plenty of water. Never give anything by mouth to an unconscious person. If any discomfort persists, obtain medical attention.

INHALATION: Remove to fresh air. If breathing difficulty or discomfort occurs and persists, obtain medical attention.

NOTES TO MEDICAL DOCTOR: This product has low oral, dermal and inhalation toxicity. It is non-irritating to the eyes and skin, and non-sensitizing to the skin. Treatment is symptomatic and supportive.

5. FIRE FIGHTING MEASURES

EXTINGUISHING MEDIA: Water

FIRE / EXPLOSION HAZARDS: The accumulation of excessive dust on overhead structures may produce explosive concentrations when disturbed and dispersed. According to NFPA 68, (Explosion Venting Guide), the Hazard Class of Dust Deflagrations for microcrystalline cellulose is St-1, the lowest hazard class.

FIRE FIGHTING PROCEDURES: For fires involving this material, do not enter any enclosed or confined fire space without wearing full protective clothing and self-contained breathing apparatus (SCBA) approved for firefighting. This is necessary to protect against the hazards of heat, products of combustion and oxygen deficiency. Do not breathe smoke, gases or vapors generated.

FLAMMABLE LIMITS: Not applicable

6. ACCIDENTAL RELEASE MEASURES

RELEASE NOTES: Powder becomes slippery when wet. Maintain good housekeeping practices to minimize accumulation of settled dust, especially on overhead surfaces. Sweep up the spilled material and dispose of in accordance with the waste disposal method outlined in Section 13, "Disposal Considerations".

7. HANDLING AND STORAGE

HANDLING AND STORAGE: Use local exhaust or general dilution ventilation to control exposure to dust. Always use safe lifting techniques when manually moving containers, especially when handling containers weighing more than 50 pounds (22.7 kg). To protect quality, store in a tight container in a dry place. Avoid exposure to excessive heat.

8. EXPOSURE CONTROLS / PERSONAL PROTECTION

EXPOSURE LIMITS

Chemical Name	ACGIH	OSHA	Supplier
Microcrystalline cellulose	10 mg/m ³ (TWA)	15 mg/m ³ (PEL) (total dust) 5 mg/m ³ (PEL) (respirable fraction of dust)	

PERSONAL PROTECTIVE EQUIPMENT

EYES AND FACE: Whenever airborne dust concentrations are high, appropriate protective eyewear, such as mono-goggles, should be worn to prevent eye contact.

RESPIRATORY: Whenever dust in the worker's breathing zone cannot be controlled with ventilation or other engineering means, workers should wear respirators or dust masks approved by NIOSH/MSHA, EU CEN or comparable certification organization to protect them against airborne dust.

PROTECTIVE CLOTHING: No special clothing is required.

GLOVES: No special gloves are required.

COMMENTS:

ADDITIONAL EXPOSURE LIMITS:

MCC:

Australia (TWA) 10 mg/m³

Belgium (TWA) 10 mg/m³ (inhalable dust)

China (STEL): 25 mg/m³

China (TWA): 10 mg/m³

Hong Kong (TWA): 10 mg/m³

Ireland (TWA): 10 mg/m³ (inhalable dust)

Korea (TWA): 10 mg/m³

New Zealand (TWA): 10 mg/m³ (respirable dust with no asbestos and less than 1% free silica)

Singapore (PEL): 10 mg/m³

Switzerland (TWA): 3 mg/m³ (respirable dust)

United Kingdom (STEL): 10 mg/m³ (total inhalable dust)

United Kingdom (TWA): 10 mg/m³ (total inhalable dust); 4 mg/m³ (respirable dust)

9. PHYSICAL AND CHEMICAL PROPERTIES

ODOR:	Odorless
APPEARANCE:	Off-white, free-flowing powder
AUTOIGNITION TEMPERATURE:	Not applicable
BOILING POINT:	Not applicable
COEFFICIENT OF OIL / WATER:	(Octanol/Water) Not available
EVAPORATION RATE:	(Butyl acetate = 1) Not applicable
FLASH POINT:	Not applicable
MELTING POINT:	Not applicable
OXIDIZING PROPERTIES:	Not applicable
PERCENT VOLATILE:	Approximately 4% water, by weight
pH:	(In solution) 6.0 - 8.0 (2% solids dispersion)
SOLUBILITY IN WATER:	Dispersible
SPECIFIC GRAVITY:	(H ₂ O = 1) Bulk density, 0.6 g/cc
VAPOR DENSITY:	(Air = 1) Not applicable
VAPOR PRESSURE:	Not applicable

COMMENTS:

EXPLOSIVE PROPERTIES: Microcrystalline cellulose: St-1

MINIMUM IGNITION TEMPERATURE: Microcrystalline cellulose: 420°C

10. STABILITY AND REACTIVITY

CONDITIONS TO AVOID:	None known
STABILITY:	Stable
HAZARDOUS DECOMPOSITION PRODUCTS:	None known.

11. TOXICOLOGICAL INFORMATION

EYE EFFECTS: Non-irritating (rabbit)

SKIN EFFECTS: Non-irritating (rabbit) (PII = 0/8.0)

DERMAL LD₅₀: > 2,000 mg/kg (rabbit)

ORAL LD₅₀: > 5,000 mg/kg (rat)

INHALATION LC₅₀: > 5.82 mg/l (4 h) (rat) Maximum attainable concentration - zero mortality

SENSITIZATION: (Skin) Non-sensitizing (guinea pig)

ACUTE EFFECTS FROM OVEREXPOSURE: This product has low oral, dermal and inhalation toxicity. It is non-irritating to the eyes and skin, and non-sensitizing to the skin. No significant acute toxicological effects are expected.

CHRONIC EFFECTS FROM OVEREXPOSURE: Ninety-day feeding studies with microcrystalline cellulose/sodium carboxymethylcellulose blend, in laboratory animals, at levels up to and including 50,000 ppm showed no significant toxicological effects as well as no adverse fetal effects. The maternal/fetal NOELs were > 50,000 ppm. Microcrystalline cellulose/sodium carboxymethylcellulose blend was negative in a battery of standard genotoxic tests. Microcrystalline cellulose is considered an inert dust, which is not toxic to the lungs when exposures are properly controlled.

CARCINOGENICITY:

NTP:	Not listed
IARC:	Not listed
OSHA:	Not listed
OTHER:	Not Listed (ACGIH)

12. ECOLOGICAL INFORMATION

ENVIRONMENTAL DATA: Microcrystalline cellulose is inherently biodegradable in soil. It biodegrades in soil at a rate comparable to corn starch.

ECOTOXICOLOGICAL INFORMATION: No data available for the formulation.

MCC:

48-hour LC₅₀ > 100%, saturated solution, NOEC = 100% (daphnia)

96-hour LC₅₀ > 100%, saturated solution, NOEC = 100% (rainbow trout)

96-hour EC₅₀ > 100%, saturated solution, NOEC = 12.5% (algae)

13. DISPOSAL CONSIDERATIONS

DISPOSAL METHOD: No special disposal methods are suggested. It is the user's responsibility to comply with all applicable local, state, and federal laws, rules, regulations and standards.

14. TRANSPORT INFORMATION

U.S. DEPARTMENT OF TRANSPORTATION (DOT)

MARINE POLLUTANT:

None

ADDITIONAL INFORMATION:

Not listed in Title 49 of the U.S. Code of Federal Regulations as a hazardous material.

ADDITIONAL INFORMATION:

National Motor Freight Classification Item 71390, Flour Cellulose, Edible

INTERNATIONAL MARITIME DANGEROUS GOODS (IMDG)

ADDITIONAL INFORMATION:

Not applicable

ADR - EUROPEAN AGREEMENT CONCERNING THE INTERNATIONAL CARRIAGE OF DANGEROUS GOODS BY ROAD

ADDITIONAL INFORMATION: Not applicable

**INTERNATIONAL CIVIL AVIATION ORGANIZATION (ICAO) /
INTERNATIONAL AIR TRANSPORT ASSOCIATION (IATA)**

ADDITIONAL INFORMATION: Not applicable

OTHER INFORMATION:

Canada (TDG) : Not applicable

15. REGULATORY INFORMATION

UNITED STATES

SARA TITLE III (SUPERFUND AMENDMENTS AND REAUTHORIZATION ACT)

SECTION 302 EXTREMELY HAZARDOUS SUBSTANCES (40 CFR 355, APPENDIX A):

Not applicable

SECTION 311 HAZARD CATEGORIES (40 CFR 370):

None

SECTION 312 THRESHOLD PLANNING QUANTITY (40 CFR 370):

The Threshold Planning Quantity (TPQ) for this product, if treated as a mixture, is 10,000 lbs; however, this product contains the following ingredients with a TPQ of less than 10,000 lbs.:

None

SECTION 313 REPORTABLE INGREDIENTS (40 CFR 372):

This product does not contain any toxic chemicals subject to the reporting requirements of Section 313, Title III of the SARA (Superfund Amendments and Reauthorization Act) of 1986.

CERCLA (COMPREHENSIVE ENVIRONMENTAL RESPONSE COMPENSATION AND LIABILITY ACT)

CERCLA DESIGNATION & REPORTABLE QUANTITIES (RQ) (40 CFR 302.4):

Not applicable

TSCA (TOXIC SUBSTANCE CONTROL ACT)

TSCA INVENTORY STATUS (40 CFR 710):

Listed (components)

CANADA

WHMIS (WORKPLACE HAZARDOUS MATERIALS INFORMATION SYSTEM):

This product has been classified in accordance with the hazard criteria of the Controlled Products Regulations and the MSDS contains all the information required by the Controlled Products Regulations.

Not a controlled product under the Canadian Workplace Hazardous Materials Information System (WHMIS).

Domestic Substance List: Listed (components)

E NUMBERS:

E 460(i) (microcrystalline cellulose)

E 466 (sodium carboxymethylcellulose)

INTERNATIONAL LISTINGS

MCC

Australia (AICS): Listed

China: Listed

Japan (ENCS): (8)-568

Korea: KE-05339

Philippines (PICCS): Listed

CMC

Australia (AICS): Listed

China: Listed

Japan (ENCS): (8)-203

Korea: KE-05354

Philippines (PICCS): Listed

HAZARD, RISK AND SAFETY PHRASE DESCRIPTIONS:

EC Symbols: (Not classified as hazardous)

EC Risk Phrases: (Not classified as hazardous)

EC Safety Phrases: (Not classified as hazardous)

16. OTHER INFORMATION

NFPA

Health	0
Flammability	1
Reactivity	0
Special	None

No special requirements

NFPA (National Fire Protection Association)

Degree of Hazard Code:

4 = Extreme

3 = High

2 = Moderate

1 = Slight

0 = Insignificant

REVISION SUMMARY:

This MSDS replaces Revision #8, dated November 7, 2005.

Changes in information are as follows:

Section 1 (Product and Company Identification)

Section 15 (Regulatory Information)

Section 16 (Other Information)

Avicel and FMC BioPolymer - Trademarks of FMC Corporation

© 2008 FMC Corporation. All Rights Reserved.

MATERIAL SAFETY DATA SHEET

1. IDENTIFICATION

Revision Date	November 2007			
Product Name	XANTHATES			
Other Names	POTASSIUM AMYL XANTHATE ; CARBONODITHIOIC ACID, O-PENTYL ESTER, POTASSIUM SALT ;			
Uses	As a collector in the flotation of sulphide minerals. Especially for gold telluride, antimony and bismuth ores.			
Contact Information	Organisation	Location	Telephone	Ask For
	Redox Pty Ltd	2 Swettenham Road Minto NSW 2566 Australia	+61 2 97333000	Technical Officer
		11 Mayo Road Wiri Auckland 2104 New Zealand	+64 9 2506222	
	Poison Information Centre	Westmead NSW Australia	131126 1800-251525	
	Chemcall	Australia New Zealand	1800-127406 0800-243622	
	National Poisons Centre	New Zealand	0800-764766	

2. HAZARD IDENTIFICATION

Hazardous according to criteria of NOHSC/ASCC.

Dangerous According to the Australian Code for the Transport of Dangerous Goods.

Classified as Dangerous Goods According to NZS 5433:1999.

HARMFUL

Risk Phrases

R15 Contact with water liberates extremely flammable gases.

R20/22 Harmful by inhalation and if swallowed.

R36/37/38 Irritating to eyes, respiratory system and skin.

Safety Phrases

S2 Keep out of reach of children.

S16 Keep away from sources of ignition - No smoking.

S17 Keep away from combustible material.

S26 In case of contact with eyes, rinse immediately with plenty of water and seek medical

advice.

2.10-12

**ERMA New Zealand
Approval Code** HSR007608

**HSNO Hazard
Classification** 4.2C 6.1E 6.3A 6.4A

This Material Safety Data Sheet may not provide exhaustive guidance for all HSNO Controls assigned to this substance. The ERMA Web Site should be consulted for a full list of triggered controls and cited regulations.

3. COMPOSITION/INFORMATION ON INGREDIENTS

Ingredients	Chemical Entity	CAS Number	Proportions (%)
	POTASSIUM AMYL XANTHATE	[2720-73-2]	> 90

4. FIRST AID MEASURES

Description of necessary measures according to routes of exposure.

Swallowed	Rinse mouth with water. Give water to drink provided person is conscious. Do NOT induce vomiting. Seek medical attention.
Eye	Immediately flush eyes with plenty of water holding eyelids open. Seek medical attention.
Skin	Remove contaminated clothing. Wash affected area with soap and plenty of water. If irritation persists, seek medical attention.
Inhaled	Remove victim from exposure to fresh air. If not breathing, give artificial respiration. If breathing is difficult, give oxygen. Seek medical attention.
Advice to Doctor	Treat symptomatically based on individual reactions of patient and judgement of doctor. NOTE: For advice in an emergency, contact a Poisons Information Centre (Australia 13-11-26 or New Zealand 0800-764-766).
Aggravated medical conditions caused by exposure	Long-term exposure to carbon disulphide (CS ₂) may cause serious damage to the central nervous system (degeneration of the peripheral nerves), vision problems, liver and kidney damage, anaemia, fatigue and debility. Other symptoms of chronic exposure include insomnia, nightmares, memory deficits and impotence. Exposure to CS ₂ has also been linked to coronary heart disease. Exposure for 4 hours daily at a concentration of 150ppm will cause chronic intoxication within months; at 100-150ppm, within a year or more, while 50-100ppm occasionally causes chronic intoxication. People with pre-existing nervous system, gastrointestinal tract, liver, kidney, skin or blood disorders are more susceptible to symptoms of exposure. Concentrations as low as 20ppm may damage the nervous system. This is characterized by headache, apprehension, lethargy, hearing loss and disorientation, muscle pain, tremors, weakness, loss of lower extremity reflexes and paralysis.

5. FIRE FIGHTING MEASURES

Extinguishing Media	In case of fire, appropriate extinguishing media is dry chemical powder. Beware of re-ignition.
Hazards from Combustion Products	Spontaneous combustible solid. Incompatible with oxidizing agents, acids, combustible materials and sources of ignition. Reacts with water to produce toxic and flammable carbon disulphide vapour and hydrogen sulphide gas. Carbon disulphide vapours which may evolve due to decomposition can readily be ignited by static discharge. Risk of dust explosion. Carbon oxides and various hydrocarbons formed when burned.
Special Protective	Fire fighters should wear a self contained breathing apparatus and full protective clothing along

Precautions and Equipment for Fire Fighters	with protective equipment.
Flammability Conditions	Spontaneous combustible solid.
Additional Information	
Hazchem Code	1[Y]

6. ACCIDENTAL RELEASE MEASURES

Emergency Procedures	Personnel involved in the clean up should wear full protective clothing. Eliminate all sources of ignition. Increase ventilation. Avoid generating dust. Ensure that walking surfaces are not slippery before walking on them. Do not allow product to reach drains, sewers or waterways. If the product does enter a waterway, advise the Environmental Protection Authority or your local Waste Management. Use clean, non-sparking tools and equipment.
Methods and Materials for Containment and Clean Up	Contain and sweep/shovel up spills with dust binding material or use an industrial vacuum cleaner. Transfer to a suitable, labelled container and hold for disposal.

7. HANDLING AND STORAGE

Precautions for Safe Handling	Ensure an eye bath and safety shower are available and ready for use. Observe good personal hygiene practices and recommended procedures. Wash thoroughly after handling. Take precautionary measures against static discharges by bonding and grounding equipment.
Conditions for Safe Storage (Including Any Incompatibles)	Store in a cool, dry, well-ventilated area. Keep containers tightly closed when not in use. Inspect regularly for deficiencies such as damage or leaks. Protect against physical damage. Store away from incompatible materials including oxidizing agents, acids, combustible materials and ignition sources. Protect from direct sunlight, moisture and static charges. Store away from food, drink and animal feed stuffs. Storage life 6 months. This product has a UN classification of 3342 and a Dangerous Goods Class 4.2 (spontaneous combustible solid) according to The Australian Code for the Transport of Dangerous Goods by Road and Rail.
Container Type	Packaging must comply with requirements of Hazardous Substances (Packaging) Regulations 2001. Store in original packaging as approved by manufacturer.

8. EXPOSURE CONTROLS / PERSONAL PROTECTION

National Exposure Standards	No exposure standard has been established for this product by the Australian Safety and Compensation Council (ASCC) formerly known as NOHSC. However, the following exposure standard applies for decomposition products; Carbon Disulphide cas no: 75-15-0 TWA = 10ppm (31mg/m ³) (Sk) Hydrogen Sulphide cas no: 7783-06-4 TWA= 10ppm (14mg/m ³) STEL = 15ppm (21mg/m ³)
Biological Limit Values	Carbon disulphide intoxication results in severe debilitating CNS symptoms (irritability, mania, hallucinations, tremors, memory loss). Chronic exposure may cause neuropsychiatric changes, peripheral neuropathies and accelerated atherogenic changes. Peak blood concentrations appear 2 hours after inhaled. Plasma elimination half-life is about 1 hour. Metabolic products seen in urine include thiourea, 2-mercapto-2-thiazolin-5-one and 2-thiothiazolidine-4-carboxylic acid (TTCA). The iodine-azide test identifies these. These represent the determinants observed in specimens collected from a healthy worker exposed at the Exposure Standard; DETERMINANT INDEX SAMPLING TIME 2-Thiothiazolidine-4-carboxylic acid 5mg/gm creatinine End of Shift (TTCA) in urine
Engineering Controls	

A system of local and/or general exhaust is recommended to keep employee exposures as low as possible. Local exhaust ventilation is generally preferred because it can control the emissions of the contaminant at its source, preventing dispersion of it into the general work area. Use a flame proof exhaust ventilation system.

Personal Protection RESPIRATOR: Wear an approved full-face piece airline respirator in the positive pressure mode with emergency escape provisions (AS1715/1716) EYES: Safety glasses with side shields (AS1336/1337) HANDS: Wear PVC gloves (AS2161) CLOTHING: Impervious coveralls and antistatic footwear (AS3765/2210)

9. PHYSICAL AND CHEMICAL PROPERTIES

Appearance	yellow to grey pellets, powder
Formula	C ₆ H ₁₂ OS ₂ .K
Odour	strong carbon disulphide like odour
Vapour Pressure	Not applicable.
Vapour Density	Not applicable.
Boiling Point	Not applicable.
Melting Point	Not applicable.
Solubility in Water	Soluble
Specific Gravity	0.94 (Water = 1)
Flash Point	Closed Cup 12-13°C
pH	Not applicable.
Lower Explosion Limit	1.3% (as percentage volume in air)
Upper Explosion Limit	50% (as percentage volume in air)
Ignition Temperature	Not applicable.
Specific Heat Value	Not applicable.
Particle Size	Not applicable.
Flame Propagation/Burning Rate of Solid Materials	Not applicable.
Properties of Materials That May Initiate or Contribute to Fire Intensity	Not applicable.
Potential for Dust Explosion	Potential dust explosion hazard
Reactions that Release Flammable Gases	Decomposition yields carbon disulphide and hydrogen sulphide
Fast of Intensely Burning Characteristics	Not applicable.
Non-flammables	water

That Could Contribute Unusual Hazards to a Fire	Not applicable.
Release of Invisible Flammable Vapours and Gases	
Decomposition Temperature	Not applicable.
Additional Information	Solubility: Readily soluble in water and alcohol. Insoluble in hydrocarbons and ether.

10. STABILITY AND REACTIVITY

Chemical Stability	Product is stable under directed conditions of use, storage and temperature. Self-heating solid.
Conditions to Avoid	Avoid excessive heat, direct sunlight, generating dust, moisture, static discharges and high temperatures.
Incompatible Materials	Incompatible with oxidizing agents, acids, combustible materials and sources of ignition.
Hazardous Decomposition Products	Reacts with water to product toxic, flammable carbon disulphide vapour and hydrogen sulphide gas. Burning produces carbon oxides, sulfur oxides and carbon disulphide.
Hazardous Reactions	

11. TOXICOLOGICAL INFORMATION

Toxicity Data	Effects from Carbon Disulphide; Severe acute effects on the central nervous system and the mind. Anaesthesia/respiratory paralysis. Local effects are skin or mucosal membrane irritation and burning, peripheral nerve degeneration. Chronic over-exposure leads to cardio-vascular disease. Effects from Hydrogen Sulphide; Deep rapid breathing. Loss of consciousness. Respiratory paralysis. Irritating to the respiratory tract. Conjunctivitis and keratitis.
----------------------	--

Health Effects - Acute

Swallowed	Harmful if swallowed. If swallowed, carbon disulphide is released into the stomach due to the acid present.
Eye	Irritating to eyes. Possible infection and injury.
Skin	Mildly irritates skin. Toxic components can be absorbed through the skin.
Inhaled	Inhalation of dust may cause irritation of the nose, throat and respiratory tract. Causes deep and rapid breathing, drowsiness and loss of feeling. Inhalation of decomposition products may cause loss of consciousness and respiratory paralysis. Affects the central nervous system. May cause irritability, mania, hallucinations, tremors and memory loss.

12. ECOLOGICAL INFORMATION

Ecotoxicity	No data available.
Persistence and Degradability	No information available on persistence/degradability for this product.
Mobility	

No information available on mobility for this product.

**Environmental Fate
(Exposure)**

Do not allow product to enter drains, waterways or sewers.

**Bioaccumulative
Potential**

No information available on bioaccumulation for this product.

13. DISPOSAL CONSIDERATIONS

Disposal

Dispose of in accordance with all local, state and federal regulations.

**Special Precautions
for Land Fill or
Incineration**

The waste code classification is to be carried out according to the European Waste Catalogue (EWC) specifically for each branch of industry and each type of process.

14. TRANSPORT INFORMATION

Land Transport

UN Number	3342
Shipping Name	XANTHATES
Dangerous Goods Class	4.2
Subsidiary Risk	Not applicable.
Pack Group	II
Precaution for User	HARMFUL
Hazchem Code	1[Y]



Sea Transport

UN Number	3342
Shipping Name	XANTHATES
Dangerous Goods Class	4.2
Subsidiary Risk	Not applicable.
Pack Group	II
Precaution for User	HARMFUL
Hazchem Code	1[Y]



15. REGULATORY INFORMATION

National Inventories; Australia AICS - Listed Canada DSL - Listed USA TSCA - Listed

Poisons Schedule	N/A
EPG	25
AICS Name	CARBONODITHIOIC ACID, O-PENTYL ESTER, POTASSIUM SALT
NZ Toxic Substance	N

16. OTHER INFORMATION

Literature References No data available.

Sources for Data No data available.

Legend to Abbreviations and Acronyms

<	less than
>	greater than
AICS	Australian Inventory of Chemical Substances
CAS	Chemical Abstracts Service (Registry Number)
cm²	square centimetres
CO₂	Carbon Dioxide
COD	Chemical Oxygen Demand
deg C (°C)	degrees Celsius
ERMA	Environmental Risk Management Authority
g	gram
g/cm³	grams per cubic centimetre
g/l	grams per litre
HSNO	Hazardous Substance and New Organism
IDLH	Immediately Dangerous to Life and Health
immiscible	liquids are insoluble in each other
kg	kilogram
kg/m³	kilograms per cubic metre
LC₅₀	LC stands for lethal concentration. LC ₅₀ is the concentration of a material in air which causes

the death of 50% (one half) of a group of test animals. The material is inhaled over a set period of time, usually 1 or 4 hours.

LD50	LD stands for Lethal Dose. LD50 is the amount of a material, given all at once, which causes the death of 50% (one half) of a group of test animals
ltr	Litre
m3	cubic metre
mbar	millibar
mg	milligram
mg/24H	milligrams per 24 hours
mg/kg	milligrams per kilogram
mg/m3	milligrams per cubic metre
Misc	miscible
miscible	liquids form one homogeneous liquid phase regardless of the amount of either component present
mm	millimetre
mPa.s	milli Pascal per second
N/A	Not Applicable
NIOSH	National Institute for Occupational Safety and Health
NOHSC	National Occupational Health and Safety Commission
OECD	Organization for Economic Co-operation and Development
PEL	Permissible Exposure Limit
ppb	parts per billion
ppm	parts per million
ppm/2h	parts per million per 2 hours
ppm/6h	parts per million per 6 hours
RCP	Reciprocal Calculation Procedure
STEL	Short Term Exposure Limit
TLV	Threshold Limit Value
tne	tonne
TWA	Time Weighted Average
ug/24H	micrograms per 24 hours
UN	United Nations (number)
wt	weight



Australia New Zealand
 Adelaide Auckland
 Brisbane Christchurch
 Melbourne Hawke's Bay
 Perth
 Sydney

Sydney Office
 2 Swettenham Road
 Minto NSW 2566
 Australia

telephone +61 2 97333000
facsimile +61 2 97333111
web www.redox.com
email info@redox.com

This MSDS summarises Redox Pty Ltd best knowledge of the health and safety hazard information of the selected substance and how to safely handle the selected substance in the workplace however Redox Pty Ltd expressly disclaims that the MSDS is a representation or guarantee of the chemical specifications for the substance.

Each user should read the MSDS and consider the information in the context of how the selected substance will be handled and used in the workplace including its use in conjunction with other substances.

MSDS: 0000290
 Print Date: 04/23/2007
 Revision Date: 04/23/2007

MATERIAL SAFETY DATA SHEET

1. CHEMICAL PRODUCT AND COMPANY IDENTIFICATION

Product Name: AERO[®]50 Xanthate
Synonyms: Potassium Amyl Xanthate, Potassium Isoamyl Xanthate
Chemical Family: Alkyl xanthate salt
Molecular Formula: C₆H₁₂OS₂K
Molecular Weight: 203.4

CYTEC INDUSTRIES INC., FIVE GARRET MOUNTAIN PLAZA, WEST PATERSON, NEW JERSEY 07424, USA
 For Product Information call 1-800/652-6013. Outside the USA and Canada call 1-973/357-3193.

EMERGENCY PHONE: For emergency involving spill, leak, fire, exposure or accident call CHEMTREC: 1-800/424-9300. Outside the USA and Canada call 1-703/527-3887.

® indicates trademark registered in the U.S. Outside the U.S., mark may be registered, pending or a trademark. Mark is or may be used under license.

2. COMPOSITION/INFORMATION ON INGREDIENTS

OSHA REGULATED COMPONENTS

Component / CAS No.	%	(w/w)	OSHA (PEL):	ACGIH (TLV)	Carcinogen
Potassium sulfide 1312-73-8	~ 1		Not established	Not established	-
Carbonodithioic acid, O-(3-methylbutyl) ester, potassium salt 928-70-1	> 90		Not established	Not established	-
Potassium hydroxide 1310-58-3	0 - 1		2 mg/m ³ (ceiling)	2 mg/m ³ (Ceiling)	-

3. HAZARDS IDENTIFICATION

EMERGENCY OVERVIEW

APPEARANCE AND ODOR:

Color: yellow
 Appearance: pellets or powder
 Odor: slight disagreeable

STATEMENTS OF HAZARD:

WARNING!

Environmental Precautions:

Use appropriate containment to avoid environmental contamination.

**7. HANDLING AND STORAGE****HANDLING**

Precautionary Measures: Avoid excessive heat or moisture. Avoid contact with eyes, skin and clothing. Avoid breathing dust. Keep container closed. Wash thoroughly after handling. Use non-sparking tools and do not smoke when opening drum. Use with adequate ventilation. Contains finely divided material. Dust suspended in air may ignite with static discharge, sparks or flame. Equipment, including venting systems, should be grounded. Provide adequate ventilation in areas of use to remove dust. Wash contaminated clothing before reuse.

Special Handling Statements: Minimize dust. Special precautions against fire and explosion must be observed in (1) pumping xanthate solutions, (2) draining mobile tanks, (3) cleaning mobile tanks, and (4) performing maintenance work on storage tanks and pipelines leading to and from tanks. Use nonsparking tools and do not smoke when opening drums of xanthate.

STORAGE

Heating or overexposure to moisture of solid xanthates or heating or aging of xanthate solutions causes some decomposition to poisonous and flammable carbon disulfide. Storage tanks should have certain design features for maximum safety, and the vapor space should be free of sources of ignition.

Storage Temperature: Store at <32.2 - 10 °C 90 - 50 °F

Reason: Safety.

8. EXPOSURE CONTROLS/PERSONAL PROTECTION**Engineering Measures:**

Where this material is not used in a closed system, good enclosure and local exhaust ventilation should be provided to control exposure.

Respiratory Protection:

Where exposures are below the established exposure limit, no respiratory protection is required. Where exposures exceed the established exposure limit, use respiratory protection recommended for the material and level of exposure.

Eye Protection:

Wear eye/face protection such as chemical splash proof goggles or face shield. Eyewash equipment and safety shower should be provided in areas of potential exposure.

Skin Protection:

Avoid skin contact. Wear impermeable gloves and suitable protective clothing.

Additional Advice:

Food, beverages, and tobacco products should not be carried, stored, or consumed where this material is in use. Before eating, drinking, or smoking, wash face and hands thoroughly with soap and water.

9. PHYSICAL AND CHEMICAL PROPERTIES


Color:	yellow
Appearance:	pellets or powder
Odor:	slight disagreeable
Boiling Point:	Not applicable
Melting Point:	255 - 280 °C 491 - 536 °F
Vapor Pressure:	Not applicable
Specific Gravity/Density:	Not available

9. PHYSICAL AND CHEMICAL PROPERTIES

Vapor Density:	Not applicable
Percent Volatile (% by wt.):	~1.5
pH:	Not applicable
Saturation In Air (% By Vol.):	Not applicable
Evaporation Rate:	Not applicable
Solubility In Water:	35 g/100 g @ 20°C-
Volatile Organic Content:	Not available
Flash Point:	Not applicable
Flammable Limits (% By Vol):	Not applicable
Autoignition Temperature:	120 °C 248 °F (value for carbon disulfide)
Decomposition Temperature:	>131 - 280 °C 267.8 - 536 °F -
Partition coefficient (n-octanol/water):	Not available
Odor Threshold:	Not available

10. STABILITY AND REACTIVITY

Stability:	Stable
Conditions To Avoid:	Keep water and moist air out of container. Exposure of the solid xanthate to heat or moisture and heating or aging of xanthate solutions. Keep container in a cool, well-ventilated area. Containers filled with this product should be kept closed when not in use. Avoid prolonged exposure to heat; avoid strong acids, alkalies and oxidizing agents.
Polymerization:	Will not occur
Conditions To Avoid:	None known
Materials To Avoid:	Strong acids, oxidizing agents, moisture.
Hazardous Decomposition Products:	Carbon monoxide (CO) Carbon dioxide oxides of sulfur (includes sulfur di and tri oxides) carbon disulfide hydrogen sulfide (H ₂ S)



11. TOXICOLOGICAL INFORMATION

Toxicological information for the product is found under Section 3. HAZARDS IDENTIFICATION.

Toxicological information on the regulated components of this product is as follows:

Potassium hydroxide has an acute oral (rat) LD50 value of 273 mg/kg. Acute overexposure to potassium hydroxide or dusts causes severe respiratory irritation. Potassium hydroxide is severely irritating to the eyes and skin.

Potassium sulfide may cause eye and skin irritation. Under acidic conditions, potassium sulfide can decompose to produce flammable poisonous hydrogen sulfide gas.

Potassium 3 methylbutyl xanthate has an estimated acute oral (rat) LD50 and acute dermal (rabbit) LD50 values of > 1,000 mg/kg and > 500 mg/kg, respectively, based on similar materials. Direct contact with this material may cause moderate eye and skin irritation. Airborne dust may cause significant eye, skin or respiratory tract irritation.

California Proposition 65 Warning (applicable in California only) - This product contains (a) chemical(s) known to the State of California to cause birth defects or other reproductive harm.

12. ECOLOGICAL INFORMATION

Toxic to aquatic organisms, may cause long-term adverse effects in the aquatic environment.
This material is not readily biodegradable.
All ecological information provided was conducted on a structurally similar product.

FISH TEST RESULTS

Test: Acute toxicity, freshwater (OECD 203)

Duration: 96 hr.

Species: Rainbow Trout (*Oncorhynchus mykiss*)

>10 - 100 mg/l LC50

INVERTEBRATE TEST RESULTS

Test: Acute Immobilization (OECD 202)

Duration: 48 hr

Species: Water Flea (*Daphnia magna*)


>1 - 10 mg/l EC50

DEGRADATION

Test: Biodegradability

<70 %

Information based on a
structurally similar
material



13. DISPOSAL CONSIDERATIONS

13. DISPOSAL CONSIDERATIONS

The information on RCRA waste classification and disposal methodology provided below applies only to the product, as supplied. If the material has been altered or contaminated, or it has exceeded its recommended shelf life, the guidance may be inapplicable. Hazardous waste classification under federal regulations (40 CFR Part 261 et seq) is dependent upon whether a material is a RCRA `listed hazardous waste` or has any of the four RCRA `hazardous waste characteristics.` Refer to 40 CFR Part 261.33 to determine if a given material to be disposed of is a RCRA `listed hazardous waste`; information contained in Section 15 of this MSDS is not intended to indicate if the product is a `listed hazardous waste.` RCRA Hazardous Waste Characteristics: There are four characteristics defined in 40 CFR Section 261.21-61.24: Ignitability, Corrosivity, Reactivity, and Toxicity. To determine Ignitability, see Section 9 of this MSDS (flash point). For Corrosivity, see Sections 9 and 14 (pH and DOT corrosivity). For Reactivity, see Section 10 (incompatible materials). For Toxicity, see Section 2 (composition). Federal regulations are subject to change. State and local requirements, which may differ from or be more stringent than the federal regulations, may also apply to the classification of the material if it is to be disposed. The Company encourages the recycle, recovery and reuse of materials, where permitted, as an alternate to disposal as a waste. The Company recommends that organic materials classified as RCRA hazardous wastes be disposed of by thermal treatment or incineration at EPA approved facilities. The Company has provided the foregoing for information only; the person generating the waste is responsible for determining the waste classification and disposal method.

14. TRANSPORT INFORMATION

This section provides basic shipping classification information. Refer to appropriate transportation regulations for specific requirements.

US DOT

Proper Shipping Name: Xanthates

Hazard Class: 4.2

Packing Group: II

UN/ID Number: UN3342

Transport Label Required: Spontaneously Combustible
Marine Pollutant

Technical Name (N.O.S.): Contains potassium amyl xanthate

Hazardous Substances:

Not applicable

Comments: Marine Pollutants - DOT requirements specific to Marine Pollutants do not apply to non-bulk packagings transported by motor vehicles, rail cars or aircraft.

TRANSPORT CANADA

Proper Shipping Name: Xanthates

Hazard Class: 4.2

Packing Group: II

UN Number: 3342

Transport Label Required: Spontaneously Combustible
Marine Pollutant

Technical Name (N.O.S.): Contains potassium amyl xanthate

ICAO / IATA

Proper Shipping Name: Xanthates

Hazard Class: 4.2

Packing Group: II

UN Number: 3342

Transport Label Required: Spontaneously Combustible

Packing Instructions/Maximum Net Quantity Per Package:

Passenger Aircraft: 415; 15 KG

Cargo Aircraft: 417; 50 KG

Technical Name (N.O.S.): Contains potassium amyl xanthate

IMO

Proper Shipping Name: Xanthates
 Hazard Class: 4.2
 UN Number: 3342
 Packing Group: II
 Transport Label Required: Spontaneously Combustible
 Marine Pollutant
 Technical Name (N.O.S.): Contains potassium amyl xanthate

15. REGULATORY INFORMATION**INVENTORY INFORMATION**

United States (USA): All components of this product are included on the TSCA Chemical Inventory or are not required to be listed on the TSCA Chemical Inventory.

Canada: This product contains components not on the Domestic Substances List. These components are on the Non-Domestic Substances List.

European Union (EU): All components of this product are included in the European Inventory of Existing Chemical Substances (EINECS) in compliance with Council Directive 67/548/EEC and its amendments.

Australia: All components of this product are included in the Australian Inventory of Chemical Substances (AICS) or are not required to be listed on AICS.

China: All components of this product are included on the Chinese inventory or are not required to be listed on the Chinese inventory.

Japan: All components of this product are included on the Japanese (ENCS) inventory or are not required to be listed on the Japanese inventory.

Korea: All components of this product are NOT included on the Korean (ECL) inventory.

Philippines: All components of this product are NOT included on the Philippine (PICCS) inventory.

OTHER ENVIRONMENTAL INFORMATION

The following components of this product may be subject to reporting requirements pursuant to Section 313 of CERCLA (40 CFR 372), Section 12(b) of TSCA, or may be subject to release reporting requirements (40 CFR 307, 40 CFR 311, etc.) See Section 13 for information on waste classification and waste disposal of this product.

Component / CAS No.	%	TPQ (lbs)	RQ(lbs)	S313	TSCA 12B
Carbon disulfide 75-15-0	~ 0.001	10000	100	Yes	Yes

PRODUCT HAZARD CLASSIFICATION UNDER SECTION 311 OF SARA

- Acute
 - Fire
 - Reactivity
-

16. OTHER INFORMATION**NFPA Hazard Rating (National Fire Protection Association)**

Health: 2 - Materials that, under emergency conditions, can cause temporary incapacitation or residual injury.

Fire: 1 - Materials that must be preheated before ignition can occur.

Reactivity: 1 - Materials that in themselves are normally stable, but that can become unstable at elevated temperatures and pressures.

Reasons For Issue:

Revised Section 15

Randy Deskin, Ph.D., DABT +1-973-357-3100

This information is given without any warranty or representation. We do not assume any legal responsibility for same, nor do we give permission, inducement, or recommendation to practice any patented invention without a license. It is offered solely for your consideration, investigation, and verification. Before using any product, read its label.



Material Safety Data Sheet

From: Mallinckrodt Baker, Inc.
222 Red School Lane
Phillipsburg, NJ 08865



Mallinckrodt
CHEMICALS



24 Hour Emergency Telephone: 908-859-2151
CHEMTREC: 1-800-424-9300

National Response in Canada
CANUTEC: 613-996-6666

Outside U.S. and Canada
Chemtrec: 703-527-3887

NOTE: CHEMTREC, CANUTEC and National Response Center emergency numbers to be used only in the event of chemical emergencies involving a spill, leak, fire, exposure or accident involving chemicals.

All non-emergency questions should be directed to Customer Service (1-800-582-2537) for assistance.

1. SODIUM HEXAMETAPHOSPHATE

1. Product Identification

Synonyms: Hexametaphosphate, sodium salt; SHMP; Metaphosphoric acid, hexadecium salt; Sodium polyphosphates, glassy

CAS No.: 68915-31-1

Molecular Weight: Not applicable to mixtures.

Chemical Formula: Na(x+2) Px O(3x+1) x = 6 to 21

Product Codes:

J.T. Baker: V030

Mallinckrodt: E024

2. Composition/Information on Ingredients

Ingredient	CAS No	Percent	Hazardous
Polyphosphoric Acids, Sodium Salts	68915-31-1	90 - 100%	Yes

3. Hazards Identification

Emergency Overview

CAUTION! MAY CAUSE IRRITATION TO SKIN, EYES, AND RESPIRATORY TRACT. MAY BE HARMFUL IF SWALLOWED OR INHALED.

SAF-T-DATA^(tm) Ratings (Provided here for your convenience)

Health Rating: 2 - Moderate (Life)

Flammability Rating: 0 - None

Reactivity Rating: 0 - None

Contact Rating: 2 - Moderate

Lab Protective Equip: GOGGLES; LAB COAT; VENT HOOD; PROPER GLOVES

Storage Color Code: Green (General Storage)

Potential Health Effects

Many of the systemic effects given below were taken from toxicity information for other phosphates.

Inhalation:

May cause irritation to the respiratory tract. Symptoms may include coughing and shortness of breath.

Ingestion:

Phosphates are slowly and incompletely absorbed when ingested, and seldom result in systemic effects. Such effects, however, have occurred. Symptoms may include vomiting, lethargy, diarrhea, blood chemistry effects, heart disturbances and central nervous system effects. The toxicity of phosphates is because of their ability to sequester calcium. Systemic acidosis may result as this material is believed to hydrolyze into phosphoric acid when ingested.

Skin Contact:

May cause irritation with redness and pain.

Eye Contact:

May cause irritation, redness and pain.

Chronic Exposure:

May sequester calcium and cause calcium phosphate deposits in the kidneys. Chronic ingestion or inhalation may induce systemic phosphorous poisoning. Liver damage, kidney damage, jaw/tooth abnormalities, blood disorders and cardiovascular effects can result.

Aggravation of Pre-existing Conditions:

Persons with pre-existing skin disorders or eye problems, jaw/tooth abnormalities, or impaired liver, kidney or respiratory function may be more susceptible to the effects of the substance.

4. First Aid Measures

Inhalation:

Remove to fresh air. Get medical attention for any breathing difficulty.

Ingestion:

Give large amounts of water to drink. Never give anything by mouth to an unconscious person. Get medical attention.

Skin Contact:

Immediately flush skin with plenty of water for at least 15 minutes. Remove contaminated clothing and shoes. Wash clothing before reuse. Thoroughly clean shoes before reuse. Get medical attention if irritation develops.

Eye Contact:

Immediately flush eyes with plenty of water for at least 15 minutes, lifting upper and lower eyelids occasionally. Get medical attention if irritation persists.

5. Fire Fighting Measures

Fire:

Not considered to be a fire hazard.

Explosion:

Not considered to be an explosion hazard.

Fire Extinguishing Media:

Use any means suitable for extinguishing surrounding fire.

Special Information:

In the event of a fire, wear full protective clothing and NIOSH-approved self-contained breathing apparatus with full facepiece operated in the pressure demand or other positive pressure mode.

6. Accidental Release Measures

Ventilate area of leak or spill. Wear appropriate personal protective equipment as specified in Section 8. Spills: Sweep up and containerize for reclamation or disposal. Vacuuming or wet sweeping may be used to avoid dust dispersal. Small amounts of residue may be flushed to sewer with plenty of water.



7. Handling and Storage

Keep in a tightly closed container, stored in a cool, dry, ventilated area. Protect against physical damage. Isolate from incompatible substances. Containers of this material may be hazardous when empty since they retain product residues (dust, solids); observe all warnings and precautions listed for the product.

8. Exposure Controls/Personal Protection

Airborne Exposure Limits:

None established.

Ventilation System:

In general, dilution ventilation is a satisfactory health hazard control for this substance. However, if conditions of use create discomfort to the worker, a local exhaust system should be considered.

Personal Respirators (NIOSH Approved):

For conditions of use where exposure to dust or mist is apparent and engineering controls are not feasible, a particulate respirator (NIOSH type N95 or better filters) may be worn. If oil particles (e.g. lubricants, cutting fluids, glycerine, etc.) are present, use a NIOSH type R or P filter. For emergencies or instances where the exposure levels are not known, use a full-face positive-pressure, air-supplied respirator. **WARNING:** Air-purifying respirators do not protect workers in oxygen-deficient atmospheres.

Skin Protection:

Wear protective gloves and clean body-covering clothing.

Eye Protection:

Use chemical safety goggles. Maintain eye wash fountain and quick-drench facilities in work area.

9. Physical and Chemical Properties

Appearance:

White powder or plates.

Odor:

No information found.

Solubility:

Soluble in water.

Density:

1.25

pH:

No information found.

% Volatiles by volume @ 21C (70F):

0

Boiling Point:

1500C (2732F)

Melting Point:

550C (1022F)

Vapor Density (Air=1):

No information found.

Vapor Pressure (mm Hg):

No information found.

Evaporation Rate (BuAc=1):

No information found.

10. Stability and Reactivity

Stability:

Stable under ordinary conditions of use and storage.

Hazardous Decomposition Products:

Sodium and phosphorus oxides may form when heated to decomposition.

Hazardous Polymerization:

Will not occur.

Incompatibilities:

No information found.

Conditions to Avoid:

No information found.

11. Toxicological Information**2.10-30**

Oral rat LD50: 3053 mg/kg

-----\Cancer Lists\-----

---NTP Carcinogen---

Ingredient	Known	Anticipated	IARC Category
Polyphosphoric Acids, Sodium Salts (68915-31-1)	No	No	None

12. Ecological Information**Environmental Fate:**

No information found.

Environmental Toxicity:

No information found.

13. Disposal Considerations

Whatever cannot be saved for recovery or recycling should be managed in an appropriate and approved waste disposal facility. Processing, use or contamination of this product may change the waste management options. State and local disposal regulations may differ from federal disposal regulations. Dispose of container and unused contents in accordance with federal, state and local requirements.

14. Transport Information

Not regulated.

15. Regulatory Information

-----\Chemical Inventory Status - Part 1\-----

Ingredient	TSCA	EC	Japan	Australia
Polyphosphoric Acids, Sodium Salts (68915-31-1)	Yes	Yes	Yes	Yes

-----\Chemical Inventory Status - Part 2\-----

--Canada--

Ingredient	Korea	DSL	NDSL	Phil.
Polyphosphoric Acids, Sodium Salts (68915-31-1)	Yes	Yes	No	Yes

-----\Federal, State & International Regulations - Part 1\-----

-SARA 302- -----SARA 313-----

Ingredient RQ TPQ List Chemical Catg.

Polyphosphoric Acids, Sodium Salts No No No No
(68915-31-1)

-----\Federal, State & International Regulations - Part 2\-----

-RCRA- -TSCA-

Ingredient	CERCLA	261.33	8(d)
Polyphosphoric Acids, Sodium Salts (68915-31-1)	No	No	No

Chemical Weapons Convention: No TSCA 12(b): No CDTA: No
 SARA 311/312: Acute: Yes Chronic: Yes Fire: No Pressure: No
 Reactivity: No (Mixture / Solid)

Australian Hazchem Code: None allocated.

Poison Schedule: None allocated.

WHMIS:

This MSDS has been prepared according to the hazard criteria of the Controlled Products Regulations (CPR) and the MSDS contains all of the information required by the CPR.

16. Other Information

NFPA Ratings: Health: 1 Flammability: 0 Reactivity: 0

Label Hazard Warning:

CAUTION! MAY CAUSE IRRITATION TO SKIN, EYES, AND RESPIRATORY TRACT. MAY BE HARMFUL IF SWALLOWED OR INHALED.

Label Precautions:

Keep container closed.
 Use with adequate ventilation.
 Avoid breathing dust.
 Wash thoroughly after handling.
 Avoid contact with eyes, skin and clothing.

Label First Aid:

If inhaled, remove to fresh air. Get medical attention for any breathing difficulty. In case of contact, immediately flush eyes or skin with plenty of water for at least 15 minutes. Get medical attention if irritation develops or persists. If swallowed, give large amounts of water to drink. Never give anything by mouth to an unconscious person. Get medical attention.

Product Use:

Laboratory Reagent.

Revision Information:

MSDS Section(s) changed since last revision of document include: 3.

Disclaimer:

Mallinckrodt Baker, Inc. provides the information contained herein in good faith but makes no representation as to its comprehensiveness or accuracy. This document is intended only as a guide to the appropriate precautionary handling of the material by a properly trained person using this product. Individuals receiving the information must exercise their independent judgment in determining its appropriateness for a particular purpose. MALLINCKRODT BAKER, INC. MAKES NO REPRESENTATIONS OR WARRANTIES, EITHER EXPRESS OR IMPLIED, INCLUDING WITHOUT LIMITATION ANY WARRANTIES OF MERCHANTABILITY, FITNESS FOR A PARTICULAR PURPOSE WITH RESPECT TO THE INFORMATION SET FORTH HEREIN OR THE PRODUCT TO WHICH THE INFORMATION REFERS. ACCORDINGLY, MALLINCKRODT BAKER, INC. WILL NOT BE RESPONSIBLE FOR DAMAGES RESULTING FROM USE OF OR RELIANCE UPON THIS INFORMATION.

Prepared by: Environmental Health & Safety

Phone Number: (314) 654-1600 (U.S.A.)



**ICL Performance
Products LP**

Material Safety Data Sheet

1. IDENTIFICATION OF THE SUBSTANCE/PREPARATION AND THE COMPANY UNDERTAKING

Identification

Product Name	Sodium Hexametaphosphate (SHMP)
Reference Number	AST10053
Date	May 1, 2006
Synonyms:	Glass H, Hexaphos, Sodaphos, SHMP; glassy Sodium Phosphate; Sodium Polyphosphate, glassy; Metaphosphoric Acid, Sodium Salt; Sodium Acid Metaphosphate; Graham's Salt.

Use of the substance or preparation

Food Ingredient

Company Information:

ICL PERFORMANCE PRODUCTS LP
622 Emerson Road - Suite 500
St. Louis, Missouri 63141

Emergency telephone: In USA call CHEMTREC: 1 800 424 9300
In Canada call CANUTEC: 1 613 996 6666

General Information: +1 800 244 6169 (Worldwide)

2. COMPOSITION/INFORMATION ON INGREDIENTS

Composition

<u>Substance</u>	<u>CAS No.</u>	<u>FINECS No.</u>	<u>%w/w</u>	<u>Risk Phrase</u>
Sodium Hexametaphosphate (Polyphosphoric acids, sodium salts)	68915-31-1	272-808-3	100	R36/37/38

3. HAZARDS IDENTIFICATION

Classification of the substance/preparation

EC Classification	None
Safety phrase	S26 S36

Human Health Effects

May cause skin, eye and respiratory tract irritation.

Environmental Effects

On the basis of available information, this material is not expected to produce any significant environmental effects when recommended use instructions are followed.

4. FIRST-AID MEASURES**General**

This product has low oral toxicity and is minimally irritating to the skin and eyes. Treatment is controlled removal of exposure and symptomatic and supportive care.

Eye contact

Rinse immediately with plenty of water. Get medical attention if irritation occurs and persists. The dry material may cause foreign body irritation in some individuals.

Skin contact

Wash with plenty of water. Prolonged contact with the dry material may cause drying or chapping of the skin.

Inhalation

Remove to fresh air immediately. If not breathing, give artificial respiration. If breathing is difficult, give oxygen. Inhalation of the dust may cause coughing and sneezing.

Ingestion

Drink plenty of water. Never give anything by mouth to an unconscious person. No significant adverse health effects are expected if only small amount (less than a mouthful) are swallowed.

5. FIRE FIGHTING MEASURES**Extinguishing media**

Non-combustible.
No special requirement.

Unsuitable extinguishing media

Non-combustible
No special requirement.

Exposure hazards

No special considerations.

Protective equipment

As a general precaution, firefighters, and others exposed, wear self-contained breathing apparatus.

6. ACCIDENTAL RELEASE MEASURES

Personal precautions

No special requirement.

Environmental precautions

Small quantities: Presents no environmental problems.

Large quantities: As general precaution, avoid discharge into the environment.

Methods for cleaning up

Sweep, scoop or vacuum and place into containers for disposal.

Flush area with water.

7. HANDLING AND STORAGE**Handling**

Good industrial practice in housekeeping and personal hygiene should be followed.

Avoid contact with eyes and skin.

Wash hands immediately after handling.

Remove material from clothing.

Engineering measures

Prevention of eye and skin contact may be required under normal use conditions. However, severe agitation or dispersion into the work environment may require enclosure of the process and local exhaust ventilation at the source to prevent release into the air. If the work environment controls are not implemented, then personal protection for inhalation, skin and eye may be required.

Storage

Store in cool, dry place to maintain product performance.

8. EXPOSURE CONTROLS/PERSONAL PROTECTION**Occupational exposure limit**

ACGIH TLV 10 mg/m³ (inhalable) 8-hr TWA, 3 mg/m³ (respirable) 8-hr TWA
OSHA PEL 15 mg/m³ (total dust) 8-hr TWA, 5 mg/m³ (respirable) 8-hr TWA

OSHA and ACGIH have not established specific exposure limits for this material. However, OSHA and ACGIH have established limits for particulates not otherwise regulated (PNOR) and particulates not otherwise classified (PNOC) which are the least stringent exposure limits applicable to dusts.

Respiratory protection

In case of insufficient ventilation, wear suitable respiratory equipment. Use approved respiratory protective equipment as described in the U.S. OSHA 29 CFR 1910.134 or European Standard EN149.

Hand/skin protection

Wearing protective clothes is recommended; wash hand and contaminated skin thoroughly after handling.

Eye protection

Wear appropriate protective eye glasses or chemical safety goggles as described in the U.S. OSHA 29 CFR 1910.133 or European Standard EN 166.

9. PHYSICAL AND CHEMICAL PROPERTIES**General Information**

Chemical Formula:	Na ₂ O P ₂ O ₅
Form	powder, free flowing
Color	White
Odor	Odorless

Important health, safety and environmental information

pH (1% solution) SHMP:	7.0
long chain SHMP:	5.6-6.8
Specific gravity:	1.79 (20 °C / 4 °C)
Water solubility:	< 150 g/l (partly soluble)
Melting point:	628 °C or 1162 °F
Boiling point:	1500 °C or 2732 °F
Bulk density:	700 kg/m ³ (loose) 850 kg/m ³ (packed)

Other Information

Miscibility with water	< 150g/l
Flash point:	not applicable
Lower/upper explosion limits:	not applicable
Minimum ignition temperature:	not applicable
Particulate size and distribution	> 45% -100 mesh USSS

10. STABILITY AND REACTIVITY

Solutions of this product will hydrolyze to form ortho-phosphate and other shorter chain phosphates. Dissolution is impacted by temperature and pH of the system.

Conditions to avoid

Excessive moisture.

Materials to avoid

No special material to avoid.

Hazardous decomposition products

Oxides of phosphorus

11. TOXICOLOGICAL INFORMATION**Laboratory data**

Oral LD ₅₀ (rat):	6600 mg/kg.
Dermal LD ₅₀ (rabbit):	> 7940 mg/kg.

Eye Irritation (rabbit): 1.3/110.0; slightly irritating
 Skin irritation (rabbit): 0.0/8.0, nonirritating

Rats fed this material in their diet for one month showed decreased growth, increased kidney, lung and spleen weight, and kidney damage. Rats fed this material for two years also showed decreased weight gain, increased kidney weight, and kidney changes. No increase in tumors was reported. No adverse effects in reproduction capacity were reported in a multigenerational study using rats fed this material.

This material has been defined as a hazardous chemical under the criteria of the OSHA Hazard Communication Standard (29 CFR 1910.1200).

12. ECOLOGICAL INFORMATION

Environmental Toxicity

The following data have been classified using the criteria adopted by the European Economic Community (EEC) for aquatic organism toxicity

48-hr EC50 Daphnia magna > 485 mg/l
 96-hr LC50 Rainbow trout > 1000 mg/l
 96-hr LC50 Medina & Mysid shrimp > 1000 mg/l

Environmental Fate

Inorganic compounds in contact with the soil, sub-surface or surface waters may be taken up by plants and utilized as essential nutrients. Phosphates may also form precipitates, usually with calcium or magnesium. The resultant compounds are insoluble in water and become a part of the soil or sediment. The term biodegradability, as such, is not applicable to inorganic compounds.

13. DISPOSAL CONSIDERATIONS

European waste catalog number

Unknown

Disposal Considerations

This material when discarded is not a hazardous waste as that term is defined by the U.S. Resource, Conservation and Recovery Act (RCRA), 40 CFR 261. Dry material may be land filled or recycled in accordance with local, state and federal regulations. Consult your attorney or appropriate regulatory officials for information on such disposal.

14. TRANSPORT INFORMATION

Road/Rail, Sea and Air

IMDG/UN	Not classified
ICAO/IATA	Not classified
RID/ADR	Unknown
Canadian TDG	Not classified
U.S. DOT	Not classified

15. REGULATORY INFORMATION

EC label

Hazard symbol: none
 Risk phrase R36/37/38 – irritating to eyes, respiratory system and skin.
 Safety phrase S26 – In case of contact with eyes, immediately flush with plenty of water and seek medical attention
 S36 – Wear suitable protective clothing

Chemical Inventory

USA TSCA: Listed
 Canada DSL: Listed
 EC: Listed
 Japan Listed
 Australia Listed
 Korea Listed
 Philippines Listed
 China Listed

Additional information

WHMIS Classification Not Controlled

SARA Hazard Notification

Hazard Categories Under Title III Rules (40 CFR 370): None
 Section 302 Extremely Hazardous Substances: None
 Section 313 Toxic Chemical(s): None

CERCLA Reportable Quantity: Not applicable

This product has been classified in accordance with the hazard criteria of the Canadian Controlled Products Regulation and the MSDS contains all the information required by the Canadian Controlled Products Regulation.

16. OTHER INFORMATION

	Health	Fire	Reactivity	Additional Information
Suggested NFPA Rating	1	0	0	
Suggested HMIS Rating	1	0	0	F F = Safety glasses, gloves, synthetic apron, dust respirator

Reason for revision: Revised section 1. Supersedes MSDS dated: November 1, 2006
 Drafted in accordance with ECC Dir 2001/58/EC

Although the information and recommendations set forth herein (hereinafter "Information") are presented in good faith and believed to be correct as of the date hereof, ICL Performance Products LP makes no representations as to the completeness or accuracy thereof. Information is supplied upon the condition that the persons receiving same will make their own determination as to its suitability for their purposes prior to use. In no event will ICL Performance Products LP be responsible for damages of any nature whatsoever resulting from the use of or reliance upon information. NO REPRESENTATIONS OR WARRANTIES, EITHER EXPRESS OR IMPLIED, OF MERCHANTABILITY, FITNESS FOR A PARTICULAR PURPOSE OR OF ANY OTHER NATURE ARE MADE HEREUNDER WITH RESPECT TO INFORMATION OR THE PRODUCT TO WHICH INFORMATION REFERS

Toxicity Studies for Sodium hexametaphosphate on Molluscs - Toxicology studies from the primary scientific literature on aquatic organisms






Use(s): pH Adjustment [Chem Class](#): Inorganic [U.S. EPA PC Code](#): 076402 [CAS Number](#): 10124-56-8

Sorted by Organism Group, Effect, Measurement, Endpoint and LatinName.

Note: Only partial study information is reported on these pages. Full study information can be found at the [U.S. EPA AQUIRE](#) web site.

Records 1 to 2 of 2

[First](#) [Previous](#) [Next](#) [Last](#)


Common Name Scientific Name	Effect	Measurement	Life Stage	Study Time	Toxicity Endpoint	Toxic Dose			Conc Units	Conc Type	Chem Desc	Exper. Type	Acute Tox Rating	Outlier	Year	Journal
						Mean	Min	Max								
Molluscs  Show list of all Molluscs Species																
 American or virginia oyster Crassostrea virginica	Development	Developmental changes, general	TROCHOPHORE LARVE, 18-24 H	NR h	NR	-	15,000	150,000	ug/L	T	PRA	Static			1987	 Int.J.Invertebr.Reprod.Dev. 12(2):161-172
 American or virginia oyster Crassostrea virginica	Mortality	Mortality	TROCHOPHORE LARVE, 18-24 H	NR h	NR	-	15,000	150,000	ug/L	T	PRA	Static			1987	 Int.J.Invertebr.Reprod.Dev. 12(2):161-172

Records 1 to 2 of 2

[First](#) [Previous](#) [Next](#) [Last](#)

Working with the Information on this Page

Click on underlined terms for definitions or go to the [Pesticide Tutorial](#) overview page.

Any underlined term with a book icon  has additional information.

To print this page, choose **Print**. To export this data, choose **Save As 'HTML Source'** and open it in Excel or equivalent program.

Product name:	Methyl isobutyl carbinol
MSDS number:	63
Material number:	80063
Published date:	07/28/2005(V1)

MATERIAL SAFETY DATA SHEET

1. Product and Company Identification

Product:	Methyl isobutyl carbinol
MSDS number:	63
Material number:	80063

Manufacturer name and address:

Celanese Ltd.
 1601 W. LBJ Freeway
 P.O. Box 819005
 Dallas, TX 75381-9005
 United States
 Phone: 972 443 4000
 Internet: www.celanesechemicals.us

Transportation emergency phone numbers: In USA, call 800 424 9300 Outside USA, call 703 527 3887, collect calls accepted

Product Use: Intermediate for lube oil additives, especially zinc dialkyl dithiophosphates; frothing agent for ore flotation, especially copper.

2. Composition / Information on Ingredients

Component	CAS Number	Percent %	OSHA hazard category:
METHYL ISOBUTYL CARBINOL	108-11-2	99	Hazardous

3. Hazards Identification

Emergency Overview:

- WARNING!
- Flammable liquid and vapor.
 - May cause respiratory tract and eye irritation.
 - May cause skin irritation.
 - Prolonged or repeated contact may dry skin and cause irritation.
 - Material creates a special hazard because it floats on water.

Transportation emergency:	800 424 9300	CHEMTREC, 24 hrs/day
	703 527 3887	Outside USA, collect calls accepted, 24 hrs/day
Product information:	800 835 5235	

Product name:	Methyl isobutyl carbinol
MSDS number:	63
Material number:	80063
Published date:	07/28/2005(V1)

Product Description

Appearance: Clear, colorless mobile liquid.
Odor: Slightly irritating, alcohol odor.

Potential health effects

Routes of exposure: Skin, eyes, inhalation, ingestion.

Immediate effects:

Skin: May cause skin irritation. Prolonged or repeated contact may dry skin and cause irritation. May be harmful if absorbed through skin. Symptoms of exposure may include: Central nervous system depression with headache, stupor, uncoordinated or strange behavior or unconsciousness. Drying, cracking or inflammation of skin.

Eyes: Exposure to vapors and liquid Causes eye irritation. Symptoms of exposure may include: Eye irritation, burning sensation, pain, watering, and/or change of vision.

Inhalation: Causes respiratory tract irritation. Harmful if inhaled. Symptoms of exposure may include: Central nervous system depression with nausea, dizziness, headache, stupor, uncoordinated or strange behavior or unconsciousness. Nasal discharge, hoarseness, coughing, chest pain and breathing difficulty.

Ingestion: May be harmful if swallowed. Symptoms of exposure may include: Nausea, vomiting, loss of appetite, gastrointestinal irritation and/or diarrhea. Central nervous system depression with nausea, headache and mental sluggishness.

Mutagenic: Does not show mutagenic potential in most in vitro tests.

Target organ effects:

- Overexposure (prolonged or repeated exposure) may cause:
 - Kidney damage
 - Central nervous system depression
 - Injury to the eyes
 - Irritation of the respiratory tract
 - Irritation of the digestive tract
 - Drying of the skin

Medical conditions which may be aggravated by exposure: Significant exposure to this chemical may adversely affect people with acute or chronic disease of the:

- Respiratory Tract
- Skin
- Eyes
- Kidneys
- Central nervous system
- Digestive tract

Transportation emergency: 800 424 9300 CHEMTREC, 24 hrs/day
 703 527 3887 Outside USA, collect calls accepted, 24 hrs/day

Product information: 800 835 5235

Product name:	Methyl isobutyl carbinol
MSDS number:	63
Material number:	80063
Published date:	07/28/2005(V1)

For further information, see:

- Section 4 - First Aid Measures
- Section 5 - Fire Fighting Measures
- Section 6 - Accidental Release Measures
- Section 8 - Exposure Controls/Personal Protection
- Section 9 - Physical and Chemical Properties
- Section 10 - Stability and Reactivity

4. First Aid Measures

Skin: Immediately flush skin with plenty of water. Remove contaminated clothing and shoes. Call a physician if irritation develops and persists. Wash clothing before reuse. Thoroughly clean shoes before reuse.

Eyes: Immediately flush eyes with plenty of water for at least 15 minutes. If easy to do, remove contact lenses, if worn. Get medical attention immediately.

Inhalation: Remove to fresh air. If not breathing, give artificial respiration. If breathing is difficult, give oxygen. Get medical attention.

Ingestion: DO NOT induce vomiting. Get medical attention immediately. If victim is fully conscious, give a cupful of water. Never give anything by mouth to an unconscious person.

5. Fire Fighting Measures

NFPA: Health: 2 Flammability: 2 Reactivity: 0

Flammable properties

Flash point (test method): 42.4 C (108 F)

Flammable limits in air, % by volume:

Upper: 5.5 %
Lower: 1 %

Autoignition temperature: 360.3 C (680 F)

Products of combustion: Carbon Monoxide.

Extinguishing Media: Use CO₂ or dry chemical for small fires. Use aqueous film forming foam for large fires.

Transportation emergency: 800 424 9300 CHEMTREC, 24 hrs/day
703 527 3887 Outside USA, collect calls accepted, 24 hrs/day

Product information: 800 835 5235

Product name:	Methyl isobutyl carbinol
MSDS number:	63
Material number:	80063
Published date:	07/28/2005(V1)

Fire Fighting Instructions: Water spray should be used to cool fire-exposed structures and vessels. Keep personnel removed from and upwind of fire. If potential for exposure to vapors or products of combustion exists, wear full fire fighting turnout gear and NIOSH approved self-contained breathing apparatus. Oxidizing chemicals may accelerate the burning rate in a fire situation.

Fire Fighting Environmental Concerns: Thoroughly decontaminate bunker gear and other fire-fighting equipment before re-use.

6. Accidental Release Measures

Spill or Leak Instructions Eliminate ignition sources. See Section 8 for appropriate personal protective equipment. Contain spill with dikes of soil or nonflammable absorbent to minimize contaminated area. If fire potential exists, blanket spill with alcohol type aqueous film-forming foam or use water fog stream to disperse vapors. Avoid run-off into storm sewers and ditches leading to waterways. If required, notify state and local authorities. Place leaking containers in well-ventilated area. Clean up small spills by using a nonflammable absorbent or flushing sparingly with water. Contain larger spills with nonflammable diking or absorbent. Clean up by vacuuming or sweeping.

Keep unnecessary people away; isolate hazard area and deny entry. Stay upwind; keep out of low areas. Isolate for 800 meters or 0.5 miles in all directions if tank, rail car, or tank truck is involved in fire. Material creates a special hazard because it floats on water. Assess the spill situation, as the spill may not evolve large amounts of hazardous airborne contaminants in many outdoor spill situations. It may be advisable in some cases to simply monitor the situation until spilled product is removed.

7. Handling and Storage

Handling: Use with adequate ventilation. Keep containers closed when not in use. Always open containers slowly to allow any excess pressure to vent. Avoid breathing vapor. Avoid contact with eyes, skin or clothing. Wash thoroughly with soap and water after handling. Decontaminate soiled clothing thoroughly before re-use. Destroy contaminated leather clothing.

This product may generate a static charge. Ground/bond equipment when transferring material to prevent static accumulation. Electrical equipment and circuits in all storage and handling must conform to requirements of National Electric Code (Article 500 and 501) for hazardous location.

Storage: Keep all containers tightly closed when not in use. Store out of direct sunlight and on an impermeable floor. Do not store with incompatible materials. See Section 10. Stability and Reactivity.

Transportation emergency: 800 424 9300 CHEMTREC, 24 hrs/day
703 527 3887 Outside USA, collect calls accepted, 24 hrs/day

Product information: 800 835 5235

Product name:	Methyl isobutyl carbinol
MSDS number:	63
Material number:	80063
Published date:	07/28/2005(V1)

8. Exposure Controls / Personal Protection

Engineering Controls: General or dilution ventilation is frequently insufficient as the sole means of controlling employee exposure. Local ventilation is usually preferred.

Protective Equipment A safety shower and eyebath should be readily available.

Skin protection: Wear impervious clothing and gloves to prevent contact. Butyl rubber is recommended. Other protective material may be used, depending on the situation, if adequate degradation and permeation data is available. If other chemicals are used in conjunction with this chemical, material selection should be based on protection for all chemicals present.

Eye/face protection: Wear chemical goggles when there is a reasonable chance of eye contact.

Respiratory protection: Based on workplace contaminant level and working limits of the respirator, use a respirator approved by NIOSH. The following is the minimum recommended equipment for an occupational exposure level. To estimate an occupational exposure level see Section 3, Section 8 and Section 11.

For concentrations > 1 and < 10 times the occupational exposure level: Use air-purifying respirator with full facepiece and organic vapor cartridge(s) or air-purifying full facepiece respirator with an organic vapor canister or a full facepiece powered air-purifying respirator fitted with organic vapor cartridge(s). The air purifying element must have an end of service life indicator, or a documented change out schedule must be established. Otherwise, use supplied air.

For concentrations more than 10 times the occupational exposure level and less than the lower of either 100 times the occupational exposure level or the IDLH: Use Type C full facepiece supplied-air respirator operated in positive-pressure or continuous-flow mode.

For concentrations > 100 times the occupational exposure level or greater than the IDLH level or unknown concentrations (such as in emergencies): Use self-contained breathing apparatus with full facepiece in positive-pressure mode or Type C positive-pressure full facepiece supplied-air respirator with an auxiliary positive-pressure self-contained breathing apparatus escape system.

For escape: Use self-contained breathing apparatus with full facepiece or any respirator specifically approved for escape.

Exposure guidelines

Transportation emergency:	800 424 9300	CHEMTREC, 24 hrs/day
	703 527 3887	Outside USA, collect calls accepted, 24 hrs/day
Product information:	800 835 5235	

Product name:	Methyl isobutyl carbinol
MSDS number:	63
Material number:	80063
Published date:	07/28/2005(V1)

Component	CAS Number	Percent %	ACGIH TWA	ACGIH STEL	ACGIH CEILING	OSHA TWA	OSHA STEL	OSHA CEILING	Celanese WEL *	Mexico TWA	Mexico STEL	Mexico CEILING
METHYL ISOBUTYL CARBINOL	108-11-2	99	25 ppm	40 ppm	-	25 ppm	-	-	-	25 ppm	40 ppm	-

Component	CAS Number	Percent %	1990 NIOSH IDLH (Recognized by OSHA)	1994 NIOSH IDLH
METHYL ISOBUTYL CARBINOL	108-11-2	99	2000 PPM	400 ppm

Comments: Celanese has adopted the ACGIH TLVs
* Workplace Exposure Limit

9. Physical and Chemical Properties

Appearance: Clear, colorless mobile liquid.

Odor: Slightly irritating, alcohol odor.

Vapor Pressure: 4.7 mm Hg at 20 deg C

Vapor Density (Air=1 @ 20°C): 3.53

Boiling Point (760 mmHgA): 132 C (269.6 F)

Freezing Point: < -50 C (< -58 F)

Solubility in Water @ 20°C: 1.82 grams per 100 grams H₂O

Specific Gravity: 0.808 at 20 deg C

Molecular Weight: 102.2

Evaporation Rate (n-Butyl acetate = 1): 0.26

10. Stability and Reactivity

Stability: Stable.

Conditions to Avoid: Avoid heat , flames, sparks, and other sources of ignition.

Incompatibility: Keep away from sulfuric and other strong inorganic acids, aluminum or lead (including equipment made of these metals), and oxidizing agents such as peroxides, nitric acid, perchloric acid or chromium trioxide.

Transportation emergency: 800 424 9300 CHEMTREC, 24 hrs/day
703 527 3887 Outside USA, collect calls accepted, 24 hrs/day

Product information: 800 835 5235

Product name:	Methyl isobutyl carbinol
MSDS number:	63
Material number:	80063
Published date:	07/28/2005(V1)

Hazardous Combustion or Decomposition Products: Thermal decomposition products may include oxides of carbon.

Hazardous Polymerization: Hazardous polymerization will not occur.

11. Toxicological Information

Component Toxicological Information

Component	METHYL ISOBUTYL CARBINOL
-----------	--------------------------

Acute Exposure: Excessive exposure leads to depression of the central nervous system which is generally reversible and is shown by headache, dizziness, drowsiness, loss of coordination and unconsciousness.

Oral LD50: 2.6g/kg (rats); Slightly toxic to animals. Nausea, vomiting, gastrointestinal irritation and diarrhea may occur.

Inhalation LC50: >3776 ppm (rats; vapor; 4hrs.); Slightly toxic to animals. Vapors are irritating to the respiratory tract.

Skin: Repeated or prolonged contact may cause drying of the skin dermatitis. Moderately irritating to rabbit skin. Slightly toxic (dermal LD50, rabbit:2.9g/kg).

Eyes: Liquid causes moderate to severe irritation of rabbit eyes. Vapors are irritating to the eyes.

Mutagenicity: Not mutagenic in bacterial, yeast and rat liver cell in vitro assays, including the Ames Test.

Carcinogenicity: No information.

Reproductive/Developmental Effects: No information.

Other: Methyl isobutyl carbinol has potentiated the liver toxicity of halogenated solvents (e.g., chloroform and carbon tetrachloride) in experimental animals at oral doses of 570 mg/kg or higher.

Transportation emergency:	800 424 9300	CHEMTREC, 24 hrs/day
	703 527 3887	Outside USA, collect calls accepted, 24 hrs/day
Product information:	800 835 5235	

Product name:	Methyl isobutyl carbinol
MSDS number:	63
Material number:	80063
Published date:	07/28/2005(V1)

Repeated Exposure: Male and female rats exposed for 6hr/day. 5 days/wk for 6 wks to 211. 825 or 3698 mg/m³ showed no overt signs of toxicity, effects on blood parameters or compound-related effects based on gross and microscopic examination of tissues. Increased kidney weight was observed in the males at the high dose. Effects on urine parameters were noted at all dose levels except for the low dose males. There are several other studies of limited quality and with limited details. In a 90-day inhalation study, kidney effects were reported in rats at 0.425 mg/1, but not in monkeys or dogs. The effect in rats was reversible on cessation of exposure. In mice exposed 12 times for 4 hours to vapor saturated air (approximately 20 mg/1), an anesthetic effect was reported, but no mortality. In rabbits exposed dermally 5 times over a period of 15-21 days at 2.5 g/kg, no systemic effects were observed.

12. Ecological Information

Component Ecological Information

Component	METHYL ISOBUTYL CARBINOL
	<p>Ecotoxicity: Methyl isobutyl carbinol exhibits low acute toxicity to aquatic species. The 96-hour LC50 for fish (<i>Pimephales promelas</i>) was greater than 92.4 ppm. There was no mortality at this level. The 24-hour LC50 value for fish (<i>Carassius auratus</i>) is 360 ppm. The 24-hour LC50 value for shrimp (<i>Artemia salina</i>) is 370 ppm. The 48-hour LC50 value for the clawed toad (<i>Xenopus laevis</i>) is 656 ppm. The 3-hour EC50 for inhibition of bacteria was greater than 100 ppm in the Activated Sludge Respiration Inhibition Test.</p>

Transportation emergency:	800 424 9300	CHEMTREC, 24 hrs/day
	703 527 3887	Outside USA, collect calls accepted, 24 hrs/day
Product information:	800 835 5235	

Product name:	Methyl isobutyl carbinol
MSDS number:	63
Material number:	80063
Published date:	07/28/2005(V1)

13. Disposal Considerations

Dispose of spilled material in accordance with state and local regulations for hazardous waste. Recommended methods are incineration or biological treatment at a federally or state-permitted disposal facility. Note that this information applies to the material as manufactured; processing, use, or contamination may make this information inappropriate, inaccurate, or incomplete.

Note that this handling and disposal information may also apply to empty containers, liners and rinsate. State or local regulations or restrictions are complex and may differ from federal regulations. This information is intended as an aid to proper handling and disposal; the final responsibility for handling and disposal is with the owner of the waste. See Section 9 - Physical and Chemical Properties.

EPA Hazardous Waste Code(s): D001

14. Transport Information

US Department of Transportation:

UN/NA Number:	UN 2053
Shipping name:	METHYL ISOBUTYL CARBINOL
Hazard class:	3
Packing Group:	PG III
Emergency Response Guide:	129

ICAO/IATA:

IATA UN Number:	UN 2053
Proper Shipping Name:	METHYL ISOBUTYL CARBINOL
Hazard Classification:	3
Packing group:	III
Label:	(Flammable Liquid)

IMDG:

International Marine UN Number:	UN 2053
Proper Shipping Name:	METHYL ISOBUTYL CARBINOL
Hazard Class:	3
Packing Group:	III
Flash point (test method):	42.4 C (108 F)

Transportation emergency:	800 424 9300	CHEMTREC, 24 hrs/day
	703 527 3887	Outside USA, collect calls accepted, 24 hrs/day
Product information:	800 835 5235	

Product name:	Methyl isobutyl carbinol
MSDS number:	63
Material number:	80063
Published date:	07/28/2005(V1)

Transport Canada

Trade Information

Schedule B Code (export): 2905.19.0020

15. Regulatory Information

U.S. STATE REGULATIONS

Chemicals associated with the product which are subject to the state right-to-know regulations are listed along with the applicable state(s):

METHYL ISOBUTYL CARBINOL 108-11-2

Pennsylvania	Listed
New Jersey	Listed
Illinois	Listed
Massachusetts	Listed

U.S. FEDERAL REGULATIONS

TSCA Inventory: We certify that all components are either on the TSCA inventory or qualify for an exemption.

Environmental Regulations:

SARA 311:

Acute health:	Yes
Chronic health:	No
Fire:	Yes
Sudden release of pressure:	No
Reactive:	No

INTERNATIONAL REGULATIONS

International Chemical Inventory

Listed on the chemical inventories of the following countries or qualifies for an exemption:

AUSTRALIA, CHINA, CANADA, EUROPE, KOREA, PHILIPPINES, JAPAN

Transportation emergency:	800 424 9300	CHEMTREC, 24 hrs/day
	703 527 3887	Outside USA, collect calls accepted, 24 hrs/day
Product information:	800 835 5235	

Product name:	Methyl isobutyl carbinol
MSDS number:	63
Material number:	80063
Published date:	07/28/2005(V1)

16. Other Information

Prepared by: Product Stewardship Department
Celanese Ltd.

Hazard ratings This information is intended solely for the use of individuals trained in the NFPA and/or HMIS systems.

NFPA: Health: 2 Flammability: 2 Reactivity: 0

HMIS: Health: 2 Flammability: 2 Reactivity: 0

Revisions: The following sections have been revised since the last issue of this MSDS.

Footer: Product Information number

For industrial use only. The information contained herein is accurate to the best of our knowledge. We do not suggest or guarantee that any hazards listed herein are the only ones which exist. Celanese makes no warranty of any kind, express or implied, concerning the safe use of this material in your process or in combination with other substances. Effects can be aggravated by other materials and/or this material may aggravate or add to the effects of other materials. This material may be released from gas, liquid, or solid materials made directly or indirectly from it. User has the sole responsibility to determine the suitability of the materials for any use and the manner of use contemplated. User must meet all applicable safety and health standards. Material safety data sheets are provided on the Internet by Celanese as a service to its customers. Possession of an Internet MSDS does not indicate that the possessor of the MSDS was a purchaser or user of the subject product.

Transportation emergency:	800 424 9300	CHEMTREC, 24 hrs/day
	703 527 3887	Outside USA, collect calls accepted, 24 hrs/day
Product information:	800 835 5235	

MATERIAL SAFETY DATA SHEET

POLYACRYLAMIDE HCP, ANIONIC

1. CHEMICAL PRODUCT AND COMPANY IDENTIFICATION

Brenntag Canada Inc.
43 Jutland Rd.
Toronto, ON
M8Z 2G6
(416) 259-8231

WHMIS#: 00065342
Index: HC14482/06D
Effective Date: 2006 October 06
Date of Revision: 2006 October 06

Website: <http://www.brenntag.ca>

EMERGENCY TELEPHONE NUMBERS (FOR EMERGENCIES INVOLVING CHEMICAL SPILLS OR RELEASE)

Toronto, ON (416) 226-6117
Edmonton, AB (780) 424-1754

Montreal, QC (514) 861-1211
Calgary, AB (403) 263-8660

Winnipeg, MB (204) 943-8827
Vancouver, BC (604) 685-5036

PRODUCT IDENTIFICATION

Product Name: Polyacrylamide HCP, Anionic.
Chemical Name: Ethanaminium, N,N,N-trimethyl-2-[(1-oxo-2-propenyl)oxy]-, chloride, polymer with 2-propenamamide.
Synonyms: Polyacrylamide HCP 511, 516, 526 W, 540.
Chemical Family: Anionic acrylamide copolymer salt. Anionic water-soluble polymer.
Molecular Formula: (C₈H₁₆NO₂ · C₃H₅NO · Cl)_n.
Product Use: Drying agent. Flocculant.

WHMIS Classification / Symbol:

Not regulated.

READ THE ENTIRE MSDS FOR THE COMPLETE HAZARD EVALUATION OF THIS PRODUCT.

2. COMPOSITION, INFORMATION ON INGREDIENTS (Not Intended As Specifications)

Ingredient	CAS#	ACGIH TLV	% Concentration
Ethanaminium, N,N,N-trimethyl-2-[(1-oxo-2-propenyl)oxy]-, chloride, polymer with 2-propenamamide	69418-26-4	---	90 - 95
Acrylamide	79-06-1	0.03 mg/m ³ (IV) (Skin)	*A3 < 1000 ppm

A3 = Animal Carcinogen (ACGIH-A3).

Skin Notation: Contact with skin, eyes and mucous membranes can contribute to the overall exposure and may invalidate the TLV. Consider measures to prevent absorption by these routes.

3. HAZARDS IDENTIFICATION

EMERGENCY OVERVIEW: Dust may cause mechanical irritation to skin, eyes and respiratory tract. Low hazard for usual industrial or commercial handling. High vapour concentrations may cause drowsiness. Can decompose at high temperatures forming toxic gases.

POTENTIAL HEALTH EFFECTS

Inhalation: Product may be mildly irritating to the nose, throat and respiratory tract and may cause coughing and sneezing. Excessive contact with powder may cause drying of mucous membranes of nose and throat due to absorption of moisture and oils. See "Other Health Effects" Section.

Skin Contact: This product may cause irritation due to abrasive action. Excessive contact with powder may cause drying of the skin due to absorption of moisture and oils.

Skin Absorption:	Not likely to be absorbed through the skin.
Eye Contact:	This product may cause irritation, redness and possible damage due to abrasiveness. Excessive contact with powder may cause drying of mucous membranes of the eyes due to absorption of moisture and oils.
Ingestion:	This product may cause mild gastrointestinal discomfort.
Other Health Effects:	Low hazard for usual industrial or commercial handling. In general, long-term exposure to high concentrations of dust may cause increased mucous flow in the nose and respiratory system airways. This condition usually disappears after exposure stops. Controversy exists as to the role exposure to dust has in the development of chronic bronchitis (inflammation of the air passages into the lungs). Other factors such as smoking and general air pollution are more important, but dust exposure may contribute. (4) May cause central nervous system (CNS) depression. CNS depression is characterized by headache, dizziness, drowsiness, nausea, vomiting and incoordination. Severe overexposures may lead to coma and possible death due to respiratory failure.

4. FIRST AID MEASURES

FIRST AID PROCEDURES

Inhalation:	If respiratory problems arise, move the victim to fresh air. Give artificial respiration ONLY if breathing has stopped. Give cardiopulmonary resuscitation (CPR) if there is no breathing AND no pulse. Obtain medical advice IMMEDIATELY.
Skin Contact:	Start flushing while removing contaminated clothing. Wash affected areas thoroughly with soap and water. If irritation, redness, or a burning sensation develops and persists, obtain medical advice.
Eye Contact:	Immediately flush eyes thoroughly for 15 minutes with running water. Hold eyelids open during flushing. If irritation persists, repeat flushing.
Ingestion:	Do not attempt to give anything by mouth to an unconscious person. If victim is alert and not convulsing, rinse mouth out and give 1/2 to 1 glass of water to dilute material. DO NOT induce vomiting. If spontaneous vomiting occurs, have victim lean forward with head down to avoid breathing in of vomitus, rinse mouth and administer more water. Obtain medical attention IMMEDIATELY.
Note to Physicians:	Treat symptomatically. Medical conditions that may be aggravated by exposure to this product include diseases of the skin, eyes or respiratory tract.

5. FIRE-FIGHTING MEASURES

Flashpoint (°C)	Autolgnition Temperature (°C)	Flammability Limits in Air (%):	
		LEL	UEL
> 100 (3)	Not available.	Not available.	Not available.
Flammability Class (WHMIS):	Not regulated.		
Hazardous Combustion Products:	Thermal decomposition products are toxic and may include hydrogen chloride, oxides of nitrogen and carbon and irritating gases.		
Unusual Fire or Explosion Hazards:	Not normally a fire hazard. Water content of product prevents ignition. Spilled material may cause floors and contact surfaces to become slippery. Enforce NO SMOKING rules in area of use.		
Sensitivity to Mechanical Impact:	Not expected to be sensitive to mechanical impact.		
Rate of Burning:	Not available.		
Explosive Power:	Not available.		
Sensitivity to Static Discharge:	Not expected to be sensitive to static discharge.		
EXTINGUISHING MEDIA			
Fire Extinguishing Media:	Foam. Carbon Dioxide. Dry Chemical. Use carbon dioxide or dry chemical media for small fires. If only water is available, use it in the form of a fog.		
FIRE FIGHTING INSTRUCTIONS			
Instructions to the Fire Fighters:	Isolate materials that are not involved in the fire and protect personnel. Spilled material may cause floors and contact surfaces to become slippery. Clean up immediately to eliminate slipping hazard. Do not allow to enter sewers or watercourses.		

Fire Fighting Protective Equipment: Use self-contained breathing apparatus and protective clothing.

6. ACCIDENTAL RELEASE MEASURES

Information in this section is for responding to spills, leaks or releases in order to prevent or minimize the adverse effects on persons, property and the environment. There may be specific reporting requirements associated with spills, leaks or releases, which change from region to region.

Containment and Clean-Up Procedures: In all cases of leak or spill contact vendor at Emergency Number shown on the front page of this MSDS. Eliminate all sources of ignition. Do not flush with water as aqueous solutions or powders that become wet render surfaces extremely slippery. Wear respirator, protective clothing and gloves. Avoid dry sweeping. Do not use compressed air to clean surfaces. Vacuuming is preferred. Return all material possible to container for proper disposal. Minimize air borne spreading of dust. Avoid accumulation and dispersion of dust to reduce explosion potential. Collect product for recovery or disposal. Ventilate enclosed spaces. Notify applicable government authority if release is reportable or could adversely affect the environment.

7. HANDLING AND STORAGE

HANDLING

Handling Practices: Use normal "good" industrial hygiene and housekeeping practices. Product becomes slippery when mixed with water. Clean up immediately to eliminate slipping hazard.

Ventilation Requirements: See Section 8, "Engineering Controls".

Other Precautions: Product becomes slippery when mixed with water. (3) Use only with adequate ventilation and avoid breathing vapours. Avoid contact with eyes, skin or clothing. Wash thoroughly with soap and water after handling. Wash contaminated clothing thoroughly before re-use.

STORAGE

Storage Temperature (°C): 0 to 35 °C. (3)

Ventilation Requirements: General exhaust is acceptable.

Storage Requirements: Store in a cool, well-ventilated area. Keep away from heat, sparks and flames. Keep containers closed. Avoid moisture contamination. Protect against physical damage.

Special Materials to be Used for Packaging or Containers: Confirm suitability of any material before using.

8. EXPOSURE CONTROLS / PERSONAL PROTECTION

Recommendations listed in this section indicate the type of equipment, which will provide protection against overexposure to this product. Conditions of use, adequacy of engineering or other control measures, and actual exposures will dictate the need for specific protective devices at your workplace.

ENGINEERING CONTROLS

Engineering Controls: General exhaust is acceptable. Local exhaust ventilation preferred. Make up air should be supplied to balance air that is removed by local or general exhaust ventilation. Ventilate low lying areas such as sumps or pits where dense dust may collect.

PERSONAL PROTECTIVE EQUIPMENT (PPE)

Eye Protection: Safety glasses with side shields are recommended to prevent eye contact. Use chemical safety goggles when there is potential for eye contact. Contact lenses should not be worn when working with this material.

Skin Protection: Gloves and protective clothing made from rubber or plastic should be impervious under conditions of use. Prior to use, user should confirm impermeability. Discard contaminated gloves.

Respiratory Protection: No specific guidelines available. A NIOSH/MSHA approved dust mask for concentrations of nuisance dust up to 100 mg/m³ particulate. An air-supplied respirator if concentrations are higher or unknown.

Other Personal Protective Equipment: Wear regular work clothing. The use of coveralls is recommended. Locate safety shower and eyewash station close to chemical handling area. Take all precautions to avoid personal contact.

EXPOSURE GUIDELINES

Particulate Not Otherwise Classified:	
ACGIH	OSHA
10 mg/m ³ - Inhalable particulate	50 mppcf* or 15 mg/m ³ - Total Dust
3 mg/m ³ - Respirable particulate	15 mppcf* or 5 mg/m ³ - Respirable Fraction

* mppcf = million particles per cubic foot

9. PHYSICAL AND CHEMICAL PROPERTIES (Not intended as Specifications)

Physical State:	Solid.
Appearance:	White granular solid.
Odour:	Odourless.
Odour Threshold (ppm):	Not applicable.
Boiling Range (°C):	Not available.
Melting/Freezing Point (°C):	Not available.
Vapour Pressure (mm Hg at 20° C):	Not available.
Vapour Density (Air = 1.0):	Not available.
Relative Density (g/cc):	1.0 - 1.25. (4)
Bulk Density:	Not available.
Viscosity:	50 cP @ 1 g/L; 250 cP @ 5.0 g/L. (3)
Evaporation Rate (Butyl Acetate = 1.0):	Not applicable.
Solubility:	Soluble in water.
% Volatile by Volume:	Not available.
pH:	4 - 9 @ 5 g/L. (3)
Coefficient of Water/Oil Distribution:	Not available.
Volatile Organic Compounds (VOC):	Not applicable.

10. STABILITY AND REACTIVITY**CHEMICAL STABILITY**

Under Normal Conditions:	Stable.
Under Fire Conditions:	Not readily flammable, but will support combustion.
Hazardous Polymerization:	Will not occur.
Conditions to Avoid:	High temperatures, sparks, open flames and all other sources of ignition. Above 100 °C (212 °F) can contribute to instability. Minimize air borne spreading of dust.
Materials to Avoid:	Strong oxidizers. Oxidizers may cause strong exothermic reaction. Lewis or mineral acids. Strong bases.
Decomposition or Combustion Products:	Thermal decomposition products are toxic and may include hydrogen chloride, oxides of nitrogen and carbon and irritating gases.

11. TOXICOLOGICAL INFORMATION**TOXICOLOGICAL DATA:**

SUBSTANCE	LD50 (Oral, Rat)	LD50 (Dermal, Rabbit)	LC50 (Inhalation, Rat, 4h)
Polyacrylamide	> 5000 mg/kg (3)	---	---
Carcinogenicity Data:	The ingredient(s) of this product (Acrylamide) is classified as a suspected carcinogen by IARC (IARC-2A). This product does not meet WHMIS criteria to be classed as D2A carcinogenic. This product may contain a trace amount (less than 0.1%, w/w) of a carcinogen (Acrylamide). It is expected that there will not be any health effects attributable to this product owing to it's exceptionally low concentration.		
Reproductive Data:	No adverse reproductive effects are anticipated.		
Mutagenicity Data:	No adverse mutagenic effects are anticipated.		
Teratogenicity Data:	No adverse teratogenic effects are anticipated.		
Respiratory / Skin Sensitization Data:	None known.		
Synergistic Materials:	None known.		

Other Studies Relevant to Material: None known.

12. ECOLOGICAL INFORMATION

Ecotoxicity: The following ecotoxicity information is based on results obtained from tests of analogous products:

LC50 (Danio rerio), 96 hr = > 100 mg/L; (3)
 IC50 (Scenedesmus subspicatus), 72 hr = > 100 mg/L; (3)
 EC50 (Daphnia magna), 48 hr = > 100 mg/L. (3)

Environmental Fate: This material is not expected to bioaccumulate. (3) Not readily biodegradable. Do not contaminate domestic or irrigation water supplies, lakes, streams, ponds, or rivers.

13. DISPOSAL CONSIDERATIONS

Deactivating Chemicals: None required.

Waste Disposal Methods: This information applies to the material as manufactured. Reevaluation of the product may be required by the user at the time of disposal since the product uses, transformations, mixtures and processes may influence waste classification. Dispose of waste material at an approved (hazardous) waste treatment/disposal facility in accordance with applicable local, provincial and federal regulations. Do not dispose of waste with normal garbage, or to sewer systems.

Safe Handling of Residues: See "Waste Disposal Methods".

Disposal of Packaging: Empty containers retain product residue. Recycling is encouraged. Treat package in the same manner as the product. Empty package may be disposed of with normal garbage.

14. TRANSPORTATION INFORMATION

CANADIAN TDG ACT SHIPPING DESCRIPTION:

This product is not regulated by TDG.

Label(s): Not applicable. Placard: Not applicable.

ERAP Index: ----. Exemptions: None known.

US DOT CLASSIFICATION (49CFR 172.101, 172.102):

This product is not regulated by DOT.

Label(s): Not applicable. Placard: Not applicable.

CERCLA-RQ: Not available. Exemptions: None known.

15. REGULATORY INFORMATION

CANADA

CEPA - NSNR: All constituents of this product are included on the DSL.

CEPA - NPRI: Not included.

Controlled Products Regulations Classification (WHMIS):
 Not regulated.

USA

Environmental Protection Act: All constituents of this product are included on the TSCA inventory.

OSHA HCS (29CFR 1910.1200): Not regulated.

~~NFPA 704~~: 1 Health, 1 Fire, 0 Reactivity (3)

~~HM 122~~: 1 Health, 1 Fire, 0 Reactivity (3)

INTERNATIONAL

This product or its components are on the European inventory of existing commercial chemicals (EINECS).

16. OTHER INFORMATION

REFERENCES

1. RTECS-Registry of Toxic Effects of Chemical Substances, Canadian Centre for Occupational Health and Safety RTECS database.
2. Clayton, G.D. and Clayton, F.E., Eds., Patty's Industrial Hygiene and Toxicology, 3rd ed., Vol. IIA,B,C, John Wiley and Sons, New York, 1981.
3. Supplier's Material Safety Data Sheet(s)
4. CHEMINFO, through "CCINFOdisc", Canadian Centre for Occupational Health and Safety, Hamilton, Ontario, Canada.
5. Guide to Occupational Exposure Values, 2005, American Conference of Governmental Industrial Hygienists, Cincinnati, 2005.
6. Regulatory Affairs Group, Brenntag Canada Inc.
7. The British Columbia Drug and Poison Information Centre, Poison Managements Manual, Canadian Pharmaceutical Association, Ottawa, 1981.
8. Lewis, Sr., Richard J., Carcinogenically Active Chemicals, Van Nostrand Reinhold, 1991, ISBN 0-442-31875-8.

The information contained herein is offered only as a guide to the handling of this specific material and has been prepared in good faith by technically knowledgeable personnel. It is not intended to be all-inclusive and the manner and conditions of use and handling may involve other and additional considerations. No warranty of any kind is given or implied and Brenntag Canada Inc. will not be liable for any damages, losses, injuries or consequential damages which may result from the use of or reliance on any information contained herein. This Material Safety Data Sheet is valid for three years.

To obtain revised copies of this or other Material Safety Data Sheets, contact your nearest Brenntag Canada Regional office.

British Columbia: 20333-102B Avenue, Langley, BC, V1M 3H1
Phone: (604) 513-9009 Facsimile: (604) 513-9010

Alberta: 6628 - 45 th. Street, Leduc, AB, T9E 7C9
Phone: (780) 986-4544 Facsimile: (780) 986-1070

Manitoba: 681 Plinquet Street, Winnipeg, MB, R2J 2X2
Phone: (204) 233-3416 Facsimile: (204) 233-7005

Ontario: 43 Jutland Road, Toronto, ON, M8Z 2G6
Phone: (416) 259-8231 Facsimile: (416) 259-6175

Quebec: 2900 Jean Baptiste Des., Lachine, PQ, H8T 1C8
Phone: (514) 636-9230 Facsimile: (514) 636-0877

Atlantic: A-105 Akerley Boulevard, Dartmouth, NS, B3B 1R7
Phone: (902) 468-9690 Facsimile: (902) 468-3085

Prepared By: Regulatory Affairs Group, Brenntag Canada Inc., (416) 259-8231.

MATERIAL SAFETY DATA SHEET

Hercules Canada Inc.
Paper Technologies and Ventures
942 Brant Street
Burlington, Ontario Canada L7R 3X8
(905) 632-7861 (BUSINESS)
(905) 848-8888 (24 HRS)

1 PRODUCT AND COMPANY IDENTIFICATION

PRODUCT NAME INFINITY® PS4137 PULP MILL ADDITIVE
CHEMICAL/Common Name anionic polyacrylamide
CAS NUMBER mixture

2 COMPOSITION / INFORMATION ON INGREDIENTS

Hazardous Ingredient	CASRN	Amount
petroleum distillates, hydrotreated light	64742-47-8	22.5 %

3 HAZARDS IDENTIFICATION

EMERGENCY OVERVIEW

WARNING!

May cause skin irritation.
May cause eye irritation.
Inhalation may cause respiratory tract irritation.
Surfaces subject to spills may become slippery.

POTENTIAL HEALTH EFFECTS

Ingestion may cause gastrointestinal irritation.
Aspiration may cause lung damage.
High concentrations may cause central nervous system depression (dizziness, drowsiness, incoordination).
Prolonged or repeated skin contact may cause allergic reaction (dermatitis).

Refer to Section 5 for Hazardous Combustion Products, and Section 10 for Hazardous Decomposition/Hazardous Polymerization Products.

4 FIRST AID MEASURES

SKIN

Wash thoroughly with soap and water. Remove contaminated clothing. Get immediate medical attention. Thoroughly wash clothing before reuse.

EYE

Remove contact lenses. Hold eyelids apart. Immediately flush eyes with plenty of low-pressure water for at least 15 minutes. Get immediate medical attention.

INHALATION

Remove to fresh air. Get medical attention if nasal, throat or lung irritation develops.

INGESTION

Do NOT induce vomiting. Get immediate medical attention. See Note to Physician.

NOTES TO PHYSICIAN

Aspiration into the lungs will result in chemical pneumonitis and may be fatal.

5 FIRE FIGHTING MEASURES

EXTINGUISHING MEDIA

Dry chemical, foam, carbon dioxide or clean extinguishing agents may be used on fires involving this product. Avoid using water if possible.

FIRE FIGHTING PROCEDURES

Wear self-contained breathing apparatus pressure-demand, MSHA/NIOSH approved (or equivalent) and full protective gear when fighting fires involving this product. Cool containers with water to prevent rupture.

CONDITIONS TO AVOID

None known.

HAZARDOUS COMBUSTION PRODUCTS

Thermal decomposition (destructive fires) yields elemental oxides.

FLASH POINT

> 93 °C Pinsky-Martens Closed Cup

6 ACCIDENTAL RELEASE MEASURES

Ventilate area. Clean up spills immediately. Wear protective equipment as required (see MSDS Section 8). For small spills: Add absorbent, sweep up, and dispose appropriately. Flush spill area with water spray. Wet area may be slippery; spread sand/grit and sweep up for disposal. For large spills: Dike to contain and pump into drums for use or disposal. In case of accidental spill or release, refer to Section 8, Personal Protective Equipment and General Hygiene Practices.

This product contains a petroleum hydrocarbon. Material will float on water and runoff may create an explosion hazard. Prevent runoff from spills or leaks entering navigable waters, streams or other bodies of water.

7 HANDLING AND STORAGE

GENERAL MEASURES

Store in a cool, dry, well-ventilated area at approximately 20° C (68° F). Keep container closed when not in use.

MATERIALS OR CONDITIONS TO AVOID

Keep away from heat, flame, sparks and other ignition sources. Avoid storing product near incompatible materials. See MSDS Section 10.

8 EXPOSURE CONTROLS / PERSONAL PROTECTION

WORK PRACTICES AND ENGINEERING CONTROLS

Eyewash fountains and safety showers should be easily accessible. Use process enclosures, local exhaust ventilation, or other engineering controls to control airborne levels below recommended exposure limits. Discharge from the ventilation system should comply with applicable air pollution control regulations. Keep floors clean and dry. Clean up spills immediately.

GENERAL HYGIENIC PRACTICES

Avoid contact with eyes, skin, and clothing. Avoid breathing vapour, fumes or mist. Handle in areas with adequate ventilation. Do not swallow. Avoid contamination of food, beverages, or smoking materials. Wash thoroughly after handling, and before eating, drinking or smoking. Remove contaminated clothing promptly and clean thoroughly before reuse.

RECOMMENDED EXPOSURE LIMITS

Supplier Recommended PELs

petroleum distillates, hydrotreated light 1200 mg/m³; 165 ppm

PERSONAL PROTECTIVE EQUIPMENT

Chemical goggles

Impervious gloves (polyethylene, nitrile, butyl)

Appropriate protective clothing

Appropriate respiratory protection is required when exposure to airborne contaminants may exceed acceptable limits. Respirators should be selected and used in accordance with OSHA, Subpart I (29 CFR 1910.134) and manufacturers recommendations.

PROTECTIVE MEASURES DURING REPAIR AND MAINTENANCE

Completely isolate and thoroughly clean all equipment, piping, or vessels before beginning maintenance or repairs.

Keep area clean.

9 PHYSICAL AND CHEMICAL PROPERTIES

PHYSICAL STATE:	liquid
COLOR:	white to off-white
ODOR:	slight hydrocarbon
Specific Gravity	1.002 at 21° C
Vapour Pressure	18 mmHg
Evaporation Rate	slower than butyl acetate
Vapour Density	heavier than air
Viscosity	383 cps at 21° C
pH Value	7.0
Freezing Point	< -5 °C

10 STABILITY AND REACTIVITY**HAZARDOUS DECOMPOSITION PRODUCTS**

Thermal decomposition (destructive fires) yields elemental oxides.

HAZARDOUS POLYMERIZATION

Not anticipated under normal or recommended handling and storage conditions.

GENERAL STABILITY CONSIDERATIONS

Stable under recommended handling and storage conditions.

INCOMPATIBLE MATERIALS

Incompatible with: oxidizing agents

11 TOXICOLOGICAL INFORMATION**CARCINOGENICITY INFORMATION**

Not listed as a carcinogen by NTP. Not regulated as a carcinogen by OSHA. Not evaluated by IARC.

REPORTED HUMAN EFFECTS

No human toxicity studies have been carried out with this product.

COMPONENT - petroleum distillates: Prolonged or repeated skin contact may cause irritation and dermatitis. Inhalation of vapour may cause irritation of the respiratory tract and symptoms of central nervous system depression, including dizziness and headache. Direct eye contact may cause irritation. Ingestion causes gastric irritation, pain, nausea, vomiting. Aspiration into the lungs will cause chemical pneumonia.

REPORTED ANIMAL EFFECTS

Oral LD50 (rat): > 5000 mg/kg. Dermal LD50 (rabbit): > 5000 mg/kg. Inhalation LC50 (rat): > 20 mg/l for 4 hour(s). Under occlusive conditions: Skin irritation (rabbit): corrosive. Under non-occlusive conditions: Slight rabbit skin irritant. Eye irritation (rabbit): mild.

12 ECOLOGICAL INFORMATION

ECOTOXICOLOGICAL INFORMATION

No ecological studies have been carried out on this product.

AQUATIC TOXICITY

Acute 48-hour LC50 (Ceriodaphnia dubia): .42 mg/l. Acute 96-hour LC50 (Rainbow trout): 120 mg/l.

13 DISPOSAL CONSIDERATIONS

WASTE DISPOSAL

Incineration in accordance with applicable regulations is the recommended disposal method. Landfilling in a permitted solid or hazardous waste facility is a suitable alternative after solidification to remove free liquids. When the drum is empty, rinse it with plenty of water before discarding. Waste water may be sent to a sanitary sewer treatment facility in accordance with any local agreement, a permitted waste treatment facility, or discharged under a permit. Disposal should be in accordance with applicable federal, provincial and local regulations.

14 TRANSPORT INFORMATION

TDG: Non-regulated

For information regarding transportation classification of this product, please contact Hercules Canada Inc. at (905) 279-3338.

15 REGULATORY INFORMATION

This product has been classified in accordance with the hazard criteria of the CPR and the MSDS contains all the information required by the CPR.

CEPA

All components of this product comply with substance notification requirements under CEPA.

CHEMICAL INVENTORIES

U.S. TSCA: The components of this product are included on the TSCA Inventory.

Canadian CEPA : Included on DSL Inventory.

WHMIS CLASSIFICATION

D2B - Other Toxic Effects/Toxic

PREPARED BY: Hercules Canada Inc., Regulatory Affairs, (905) 279-3338

16 OTHER INFORMATION

HMIS RATINGS:

Health	2	Moderate Hazard
Flammability	1	Slight Hazard
Reactivity	0	Minimal Hazard

LIST OF ACRONYMS

ACGIH: American Conferences of Governmental Industrial Hygienists
AIHA WEEL: American Industrial Hygienists Association - Workplace Environmental Exposure Level
CASRN: Chemical Abstracts Service Registry Number
CERCLA: Comprehensive Emergency Response, Compensation and Liability Act
HMIS: Hazardous Materials Identification System
IARC: International Agency for Research on Cancer
NTP: National Toxicology Program
OSHA: Occupational Safety and Health Administration
PEL: OSHA Permissible Exposure Limit
RCRA: Resource Conservation and Recovery Act
RQ: Reportable Quantity
SARA: Superfund Amendment Reauthorization Act
STEL: Short-Term Exposure Limit
TLV: Threshold Limit Values (registered trademark of ACGIH)
TPQ: Threshold Planning Quantity
TSCA: Toxic Substance Control Act
TWA: Time Weighted Average

DISCLAIMER

The information and recommendations contained in this Material Safety Data Sheet have been compiled from sources believed to be reliable and to represent the most reasonable current opinion on the subject when the MSDS was prepared. No warranty, guaranty or representation is made as to the correctness or sufficiency of the information. The user of this product must decide what safety measures are necessary to safely use this product, either alone or in combination with other products, and determine its environmental regulatory compliance obligations under any applicable federal or provincial laws.



Material Safety Data Sheet

SECTION I – PRODUCT IDENTIFICATION AND USES

Product name	ANIONIC POLYACRYLAMIDE, PAM for short of Polyacrylamide
Applications	Works as a flocculant and/or coagulant for mineral processing Other varied applications – water treatment, paper mill, textile etc...
Sales representative	LMS Canada

SECTION II – CHEMICAL INGREDIENTS

Main ingredient	(CH ₂ CHCONH ₂) _n polymer
------------------------	---

SECTION III – PHYSICAL & CHEMICAL DATA

Physical state	Solid
Appearance	Colorless or white granular powder
Odour	None
Vapor pressure	N/A
Melting point	Approx 200 °C
Solubility	20 – 30%
pH value	Approx 6.0
Bulk density	Varies with granular size and moisture content. For rough calculation purpose: approx 0.7g /cm ³

SECTION IV – FIRE AND EXPLOSION

Flammability & explosion	Flammable. Dust explosions may occur if material is efficiently fine and dispersed in air.
Means of extinction	Foam, CO ₂ or dry chemical powder. Use water with precautions as this material becomes extremely slippery and swells when it has absorbed water. It may lead a mechanical bursting hazard under certain conditions. Full protective equipment and self contained breathing apparatus must be worn when combating fire.
Flashpoint	N/A

SECTION V – STABILITY AND REACTIVITY

Chemical stability	Stable at room temperature
Incompatibility with other substances	Flammability may be enhanced by presence of strong oxidizers. Swells enormously and becomes much heavier when material absorbs water, mechanical bursting hazard may occur in the process.

Reactivity, and under what conditions

May emit acid fumes once heated to decomposition.

SECTION VI – TOXICOLOGICAL PROPERTIES

Skin contact	Non-irritating to slightly irritating to skin
Eye contact	May result in moderate mechanical irritation by palpable powder or granular forms. Dust may cause stinging eyes.
Inhalation of dust	Large quantity of dust inhalation may cause irritation to lung.
Ingestion	Consult a physician if possible. Do not induce vomiting except directed by a physician.

SECTION VII – PREVENTIVE MEASURES**Personal protective gear**

Where creation of dust is unavoidable, prolonged and/or repeated skin exposure are unavoidable, use conventional approved or equivalent respiratory protection equipment based on consideration of airborne and duration of exposure.

Hand and skin

Gloves are recommended. No special type of protection clothing is required. Regular long sleeved garments and long pants should be sufficed.

Eye

Use appropriate eye protection equipment to minimize contact with dust from dry product. Avoid wearing contact lenses in the presence of dust.

Other

To avoid accidentally ingesting this product, wash hands at breaks and before eating.

Use adequate ventilation to prevent dust from accumulating in workplace.

SECTION VIII – FIRST AID MEASURES

Skin	Remove contaminated clothing; wash exposed skin thoroughly with soap and water. Treat any irritation symptomatically. Laundry clothing before reusing.
Eye	Hold eyelids apart and rinse with running water. If irritation persists, seek for medical attention.
Inhalation of dust	Remove victim to a well-ventilated area. If irritation develops, obtain medical attention. If breathing becomes difficult, administer oxygen if available. Obtain medical attention immediately.
Ingestion	Consult a physician. Do not induce vomiting unless directed by a physician.
Other	Eye wash facilities should be available at workplace.

SECTION IX – STORAGE, SHIPPING & DISPOSAL**Spillage and waste disposal**

Do not rinse spilled area with water until the following steps have been conducted:

Take measures to eliminate foot or vehicular traffic to avoid spraying material out of the spilled area. Scoop up spilled dry material and place in an appropriate container for disposal or re-use. Sweep up dust and remaining material. Use an appropriate vacuum (with filter to avoid dispersing respirable dust into air) to remove powder residue.

Once wet, remaining powder will cause surface to become extremely slippery

and pose a hazard similar to ice. Clean up personnel should take precautions when rinsing the surface with water.

Discharge into drains, sewers or waterways is not recommended due to its persistence and swolleness in aquatic media. It may cause clogging drains, filters and plumbing systems. Dispose this material in accordance with all applicable regulations.

Handling procedures and equipment

Avoid contact with moisture as the material forms a gel which is extremely slippery when absorbing water. Eliminate conditions that may pose slipperiness. Wear a dust mask or respirator when handling this material, or where possibility of inhalation exists. Wear suitable clothing to avoid prolonged or repeated skin contact. Observe good personal hygiene. Prohibit eating, drinking and smoking in contaminated areas. Wash hands; remove contaminated clothing and protective equipment before eating.

Packing and shipping information

Use water-resistant methods.

Storage requirement

Store in a dry, cool, and ventilated area away from oxidizers. Ensure containers are properly closed and bags are properly sealed. All the stock should be properly labeled. Check regularly for spills.

Keep locked up and out of reach of children.

Keep away from sources of ignitions.

SECTION X – PREPARATION OF MSDS

Prepared and translated by LMS, Canada

Last update April, 2006

Note: The information in this Material Safety Data Sheet associates only to the specific material designated herein and does not apply to uses in combination with any other materials or for any other processes. The information given is based on technical data provided by the manufacturer and those publications available when compiling/updating document and we believed to be reliable. It is subject to change or update without notice. Because conditions of applications vary and are beyond our control, it is users' responsibility to obtain safety data for combinations with other materials, or for applications in other processes. Always follow local safety regulations applicable on erection sites.

1. CHEMICAL PRODUCT AND COMPANY IDENTIFICATION

Product: HYPERFLOC® AF 200, AF 300, AF 400, AF 300-H, AF 300-HH, AF 300 PWG, AF 300 G,
and AF 1100 Series

Supplier: HYCHEM, INC.
10014 N. Dale Mabry Highway, Suite 213
Tampa, FL 33618

Current Revision Date: 8/7/03 **Last Revision Date:** 5/18/00

Emergency Telephone Number: (800) 327-2998

2. COMPOSITION/INFORMATION ON INGREDIENTS

Chemical Family: Anionic acrylamide copolymer powder.

3. HAZARDOUS IDENTIFICATION

Aqueous solutions or powders that become wet render surfaces extremely slippery.

4. FIRST AID MEASURES

Inhalation: Move to fresh air.

Skin Contact: Wash with water and soap as a precaution. In case of skin irritation, consult a physician.

Eye Contact: Rinse thoroughly with plenty of water. In case of persistent eye irritation, consult a physician.

Ingestion: The product is not considered toxic based on studies on laboratory animals.

The information provided in this Safety Data Sheet is correct to the best of our knowledge, information and belief at the date of its publication. The information given is designed only as guidance for safe handling, use, processing, storage, transportation, disposal and release, and is not to be considered a warranty or quality specification. The information relates only to the specific material designated and may not be valid for such material used in combination with any other materials or in any process unless specified in the text.

5. FIRE-FIGHTING MEASURES

- Suitable Extinguishing Media:** Water, water spray, foam, dry powder, carbon dioxide (CO₂).
- Special Fire-Fighting Precautions:** Aqueous solutions or powders that become wet render surfaces extremely slippery.
- Special Protective Equipment for Firefighters:** No special protective equipment required.

6. ACCIDENTAL RELEASE MEASURES

- Personal Precautions:** No special precautions required.
- Environmental Precautions:** Do not contaminate water.
- Methods for Cleaning Up:** Do not flush with water. Clean up promptly by scoop or vacuum. Keep in suitable and closed containers for disposal. After cleaning, flush away traces with water.

7. HANDLING AND STORAGE

- Handling:** Avoid contact with skin and eyes. Avoid dust formation. Do not breathe dust. Wash hands before breaks and at the end of workday.
- Storage:** Keep in a dry, cool place (0 - 35°C).

8. EXPOSURE CONTROLS / PERSONAL PROTECTION

Engineering Measures to Reduce Exposure: Use local exhaust if dusting occurs. Natural ventilation is adequate in absence of dusts.

Personal Protection Equipment

- **Respiratory Protection:** Dust safety masks are recommended where concentration of total dust is more than 10 mg/m³.
- **Hand Protection:** Rubber gloves
- **Eye Protection:** Safety glasses with side shields. Do not wear contact lenses.
- **Skin and Body Protection:** No special protective clothing required.

Hygiene Measures: Wash hands before breaks and immediately after handling the product. Handle in accordance with good industrial hygiene and safety practice.

9. PHYSICAL AND CHEMICAL PROPERTIES

Form:	Granular solid
Color:	White
Odor:	None
pH:	4 - 9 @ 5 g/l for product series. See Technical Bulletin for specific value.
Melting Point (°C):	Not applicable
Flash Point (°C):	Not applicable
Autoignition Point (°C):	Not applicable
Vapor Pressure (mm Hg):	Not applicable
Bulk Density:	See Technical Bulletin
Water Solubility:	See Technical Bulletin
Viscosity (mPa s):	See Technical Bulletin

10. STABILITY AND REACTIVITY

Stability:	Product is stable. No hazardous polymerization will occur.
Materials to Avoid:	Oxidizing agents may cause exothermic reactions.
Hazardous Decomposition Products:	Thermal decomposition may produce: carbon oxides and nitrogen oxides (NOx).

11. TOXICOLOGICAL INFORMATION

Acute toxicity:

- Oral: LD50/oral/rat > 5000 mg/kg
- Dermal: The results of testing on rabbits showed this material to be non-toxic even at high dose levels.
- Inhalation: The product is not expected to be toxic by inhalation.

Irritation

- Skin: The results of testing on rabbits showed this material to be non-irritating to the skin.
- Eyes: Testing conducted according to the Draize technique showed the material produces no corneal or iridial effects and only slight transitory conjunctival effects similar to those which all granular materials have on conjunctivae.

Sensitization: The results of testing on guinea pigs showed this material to be non-sensitizing.

Chronic Toxicity: A two-year feeding study on rats did not reveal adverse health effects. A one-year feeding study on dogs did not reveal adverse health effects.

12. ECOLOGICAL INFORMATION

- Fish: LC50/Fathead minnows/96 hours > 1000 mg/l
- Algae: EC50/ 72h / Selenastrum capricornutum/96 hours > 500 mg/l
- Bioaccumulation: The product is not expected to bioaccumulate.
- Persistence / Degradability: Not readily biodegradable.

13. DISPOSAL CONSIDERATIONS

- Waste from residues / unused products: In accordance with federal, state, and local regulations.
- Contaminated Packaging: Rinse empty containers with water and use the rinse water to prepare the working solution. Can be landfilled or incinerated, when in compliance with local regulations.

14. TRANSPORT INFORMATION

Not regulated by the Department of Transportation

15. REGULATORY INFORMATION

All components of this product are on TSCA and DSL inventories.

- RCRA status: Not a hazardous waste.
- Hazardous Waste Number: Not applicable.
- Reportable Quantity (40 CFR 302): Not applicable.
- Threshold Planning Quantity (40 CFR 355): Not applicable.

California Proposition 65 Information: The following statement is made in order to comply with the California Safe Drinking Water and Toxic Enforcement Act of 1986: This product contains a chemical(s) known to the State of California to cause cancer: acrylamide.

HMIS & NFPA Ratings:	HMIS	NFPA
Health:	1	1
Flammability:	1	1
Reactivity:	0	0

16. OTHER INFORMATION

Person to Contact: A. Sands

APPENDIX 2.10-B

Process Flow Diagrams for the Frac Sand Plan

Flow Details of Process Flow Diagrams given below:

WP-PFD-001 revP2 Area 01/Wet Plant: Screening and Scrubbing

		STREAM	100	101	102	103	104	105	106	107	108	108A	109	110	111	112	113	114	115
AVERAGE	SOLIDS, TPH	264.6	107.2	157.4	22.5	134.9	134.9	129.7	2.7	132.2	132.2	132.2	132.2	2.7	129.5	129.5	129.5	5.4	
	WATER, m ³ /h	5.4	2.2	3.2	1.2	229.2	404.8	2.6	398.3	46.5	7.0	51.4	396.7	351.2	45.5	50.4	240.6	708.5	
	SLURRY, m ³ /h	105.2	42.6	62.6	9.7	280.1	455.7	51.6	359.3	96.4	56.9	101.3	446.6	352.2	94.4	99.3	299.5	711.5	
	% SOLIDS	96.0	96.0	96.0	96.0	37.1	25.0	96.0	0.7	74.0	96.0	72.0	25.0	0.8	74.0	72.0	36.0	.75	
	SLURRY S.G.	2.565	2.565	2.565	2.448	1.300	1.184	2.265	1.004	1.854	2.448	1.813	1.184	1.005	1.854	1.813	1.279	1.005	
	SOLIDS S.G.																		
DESIGN	SOLIDS, TPH	264.6	126.6	188.9	27.0	161.9	161.9	155.6	3.2	158.7	158.7	158.7	158.7	3.2	155.4	155.4	155.4	6.4	
	WATER, m ³ /h	5.4	2.6	3.9	1.4	229.6	405.2	3.2	349.4	55.8	8.4	61.8	476.0	421.4	54.5	60.4	288.6	770.8	
	SLURRY, m ³ /h	105.2	51.1	75.1	11.6	280.6	466.2	61.9	360.6	115.6	68.3	121.6	535.9	422.6	113.3	119.1	347.3	773.2	
	% SOLIDS	96.0	96.0	96.0	96.0	41.4	28.6	96.0	0.9	74.0	96.0	72.0	25.0	0.8	74.0	72.0	36.0	.85	
	SLURRY S.G.	2.57	2.57	2.57	2.46	1.35	1.22	2.57	1.01	1.85	2.46	1.61	1.18	1.01	1.85	1.81	1.28	1.01	
	SOLIDS S.G.																		

Source: Outotec, 2008

WP-PFD-002 revP2 Area 02/Wet Plant: Density Separator Circuit – Friable

		STREAM	114	200	201	202	203	204	205	206	207	208	209	210	211	212	213	214
AVERAGE	SOLIDS, TPH	129.5	80.9	48.6	63.6	17.3	112.2	112.2	48.6	48.6	-	48.6	63.6	63.6	63.6	-	-	
	WATER, m ³ /h	240.6	293.4	17.2	22.3	332.4	39.5	145.8	17.2	128.6	2.6	190.8	22.3	3.3	168.5	297.1		
	SLURRY, m ³ /h	289.5	323.9	35.6	46.3	338.9	81.9	48.2	164.1	35.6	128.6	20.6	214.8	46.3	27.3	168.5	297.1	
	% SOLIDS	35.0	21.6	74.0	74.0	5.0	74.0	95.0	25.0	74.0	-	95.0	25	74.0	95.0	-	-	
	SLURRY S.G.	1.279	1.155	1.854	1.854	1.032	1.854	2.448	1.184	1.854	-	2.45	1.184	1.854	2.448	-	-	
	SOLIDS S.G.																	
DESIGN	SOLIDS, TPH	155.4	97.1	58.3	76.3	20.8	134.7	134.7	58.3	58.3	-	58.3	76.3	76.3	76.3	-	-	
	WATER, m ³ /h	288.6	338.1	20.5	26.8	372.6	47.3	7.1	174.9	20.5	154.4	3.1	228.9	26.8	4.0	202.1	356.5	
	SLURRY, m ³ /h	347.3	374.8	42.5	55.6	380.5	98.1	57.9	196.9	42.5	154.4	25.1	257.7	55.6	32.8	202.1	356.5	
	% SOLIDS	35.0	22.3	74.0	74.0	5.3	74.0	95.0	25.0	74.0	-	95.0	25.0	74.0	95.0	-	-	
	SLURRY S.G.	1.28	1.16	1.85	1.85	1.03	1.85	2.45	1.18	1.85	-	2.45	1.85	1.85	2.448	-	-	
	SOLIDS S.G.																	

Source: Outotec, 2008

WP-PFD-003 revP2 Area 03/Wet Plant: Crushing – Non Friable

		STREAM	106	300	301	302	303
AVERAGE	SOLIDS, TPH	129.7	162.1	32.4	129.7	129.6	
	WATER, m ³ /h	2.6	4.4	1.8	219.4	240.8	
	SLURRY, m ³ /h	51.6	65.6	14	268.3	289.7	
	% SOLIDS	98.0	97.4	95.0	37.1	35.0	
	SLURRY S.G.	2.565	2.541	2.448	1.301	1.279	
	SOLIDS S.G.						
DESIGN	SOLIDS, TPH	155.6	194.5	38.9	155.6	155.6	
	WATER, m ³ /h	3.2	4.9	1.7	263.3	288.9	
	SLURRY, m ³ /h	61.9	78.3	16.4	322	347.6	
	% SOLIDS	98.0	97.5	95.0	37.1	35.0	
	SLURRY S.G.	2.57	2.55	2.45	1.30	1.28	
	SOLIDS S.G.						

Source: Outotec, 2008

WP-PFD-004 revP2 Area 04/Wet Plant: Density Separator Circuit – Non Friable

	STREAM	303	400	401	402	403	404	405	406	407	408	409	410
AVERAGE	SOLIDS, TPH	129.6	80.0	49.6	49.6	53.0	49.6	49.6	27.1	-	102.6	110.3	25.5
	WATER, m ³ /h	240.8	312.8	19.3	148.9	20.6	19.3	2.6	351.9	129.6	5.4	42.9	33.5
	SLURRY, m ³ /h	289.7	343.0	38.0	167.6	40.6	38.0	21.3	362.1	129.6	44.1	84.5	43.1
	% SOLIDS	35.0	20.4	72.0	25.0	72.0	72.0	95.0	7.1	-	95.0	72.0	43.2
	SLURRY S.G.	1.279	1.145	1.813	1.184	1.813	1.813	2.448	1.046	-	2.448	1.813	1.368
	SOLIDS S.G.												
DESIGN	SOLIDS, TPH	155.6	96.0	59.5	59.5	63.6	59.5	59.5	32.5	-	123.1	132.4	33.2
	WATER, m ³ /h	288.9	357.1	23.2	178.6	24.71	23.2	3.1	392.1	155.5	6.5	51.5	43.6
	SLURRY, m ³ /h	347.6	393.3	45.6	201.1	48.7	45.6	25.6	404.4	155.5	52.9	101.4	56.0
	% SOLIDS	35.0	21.2	72.0	25.0	72.0	72.0	95.0	7.7	-	95.0	72.0	43.0
	SLURRY S.G.	1.28	1.15	1.81	1.18	1.81	1.81	2.45	1.05	-	2.45	1.81	1.37
	SOLIDS S.G.												

Source: Outotec, 2008

WP-PFD-005 revP2 Area 05/Wet Plant: Plant Thickener

	STREAM	115	203	214	406	407	409	410	500	501	610	808
AVERAGE	SOLIDS, TPH	5.4	17.3	-	27.1	-	110.3	25.5	49.8	-	-	-
	WATER, m ³ /h	1393.3	332.4	297.1	351.9	129.6	42.9	33.5	26.81	1374.2	-	-
	SLURRY, m ³ /h	1412.1	338.9	297.1	362.1	129.6	84.5	43.1	45.60	-	-	-
	% SOLIDS	.75	5.0	-	7.1	-	72.0	43.2	65.0	-	-	-
	SLURRY S.G.	1.005	1.032	-	1.046	-	1.813	1.368	1.679	-	-	-
	SOLIDS S.G.											
DESIGN	SOLIDS, TPH	6.4	20.8	-	32.5	-	132.4	33.2	49.7	-	-	-
	WATER, m ³ /h	770.8	372.6	356.5	392.1	155.5	51.5	43.6	32.2	1508.7	-	-
	SLURRY, m ³ /h	773.2	380.5	356.5	404.4	155.5	101.4	56.0	45.7	-	-	-
	% SOLIDS	.85	5.3	-	7.7	-	72.0	43.0	65.0	-	-	-
	SLURRY S.G.	1.01	1.03	-	1.05	-	1.81	1.37	1.68	-	-	-
	SOLIDS S.G.											

Source: Outotec, 2008

DP-PFD-001 revP3 Area 06/Dry Plant: Drying and Screening – Friable

	STREAM	205	207	600	601	602	603	604	605	606	607	608	609
AVERAGE	SOLIDS, TPH	112.2	112.2	112.2		112.2	X	X	X	75.5	16.9	16.8	2.9
	WATER, m ³ /h	5.9	5.9	5.9	5.9								
	SLURRY, m ³ /h	48.2	48.2	-	5.9								
	% SOLIDS	95.0	95.0	95.0		100.0				100.0	100.0	100.0	100.0
	SLURRY S.G.	2.448	2.448	2.448									
	SOLIDS S.G.					2.65				2.65	2.65	2.65	2.65
DESIGN	SOLIDS, TPH	134.7	134.7	134.7	-	134.7	X	X	X	90.6	20.3	20.2	3.5
	WATER, m ³ /h	7.1	7.1	7.1	7.1								
	SLURRY, m ³ /h	57.9	57.9	-	7.1								
	% SOLIDS	95.0	95.0	95.0	-	100.0				100.0	100.0	100.0	100.0
	SLURRY S.G.	2.45	2.45	2.45	-								
	SOLIDS S.G.												

Source: Outotec, 2008

DP-PFD-002 revP3 Area 07/Dry Plant: Screening and Magnetic Separation – Friable

	STREAM	606	607	608	609	700	701	702	703	704	705	706	707	708	709	710
AVERAGE	SOLIDS, TPH	75.5	16.9	16.8	2.9	27.5	48.0	1.4	28.1	2.4	45.6	0.8	16.1	1.4	16.0	6.0
	WATER, m ³ /h															
	SLURRY, m ³ /h															
	% SOLIDS	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0
	SLURRY S.G.															
DESIGN	SOLIDS, TPH	90.6	20.3	20.2	3.5	33.0	57.6	1.6	31.3	2.9	54.7	1.0	19.3	1.6	19.2	7.1
	WATER, m ³ /h															
	SLURRY, m ³ /h															
	% SOLIDS	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0
	SLURRY S.G.															

Source: Outotec, 2008

DP-PFD-003 revP2 Area 08/Dry Plant: Drying and Screening – Non Friable

	STREAM	408	800	801	802	803	804	805	806	807	808	809
AVERAGE	SOLIDS, TPH	102.6	102.6	102.6	-	TR	TR	TR	59.2	10.4	18.4	14.4
	WATER, m ³ /h	5.4	5.4		5.4							
	SLURRY, m ³ /h	44.1	-		5.4							
	% SOLIDS	95.0	95.0	100.0	-				100.0	100.0	100.0	100.0
	SLURRY S.G.	2.448	2.448		-							
DESIGN	SOLIDS, TPH	123.1	123.1	123.1	-	0.3	0.1	0.1	71.0	15.0	22.5	18.0
	WATER, m ³ /h	6.5	6.5		6.5							
	SLURRY, m ³ /h	52.9	-		6.5							
	% SOLIDS	95.0	95.0	100.0	-				100.0	100.0	100.0	100.0
	SLURRY S.G.	2.45	2.45									

Source: Outotec, 2008

DP-PFD-004 revP3 Area 09/Dry Plant : Storage Silos – Friable and Non Friable

	STREAM	703	705	707	709	806	807	808	900	901
AVERAGE	SOLIDS, TPH	26.1	45.6	16.1	16.0	59.2	10.4	18.4	250	250
	WATER, m ³ /h									
	SLURRY, m ³ /h									
	% SOLIDS	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0
	SLURRY S.G.									
DESIGN	SOLIDS, TPH	31.3	54.7	19.3	19.2	71.0	15.0	22.5	250	250
	WATER, m ³ /h									
	SLURRY, m ³ /h									
	% SOLIDS	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0
	SLURRY S.G.									

Source: Outotec, 2008



DP-PFD-005 revP2 Area 09/ Dry Plant: Plant Product Load Out

	STREAM	900	901
AVERAGE	SOLIDS, TPH	250	250
	WATER, m ³ /h		
	SLURRY, m ³ /h		
	% SOLIDS	100.0	100.0
	SLURRY S.G.		
	SOLIDS S.G.	2.65	2.65
DESIGN	SOLIDS, TPH	250	250
	WATER, m ³ /h		
	SLURRY, m ³ /h		
	% SOLIDS	100.0	100.0
	SLURRY S.G.		

Source: Outotec, 2008

DRAWING:
WP-PFD-003 revP2 Area 03/Wet Plant: Crushing – Non Friable



	STREAM	106	300	301	302	303
AVERAGE	SOLIDS, TPH	129.7	162.1	32.4	129.7	129.6
	WATER, m ³ /h	2.6	4.4	1.8	219.4	240.8
	SLURRY, m ³ /h	51.6	65.6	14	268.3	289.7
	% SOLIDS	98.0	97.4	95.0	37.1	35.0
	SLURRY S.G.	2.565	2.541	2.448	1.301	1.279
	SOLIDS S.G.					
DESIGN	SOLIDS, TPH	155.6	194.5	38.9	155.6	155.6
	WATER, m ³ /h	3.2	4.9	1.7	263.3	288.9
	SLURRY, m ³ /h	61.9	78.3	16.4	322	347.6
	% SOLIDS	98.0	97.5	95.0	37.1	35.0
	SLURRY S.G.	2.57	2.55	2.45	1.30	1.28

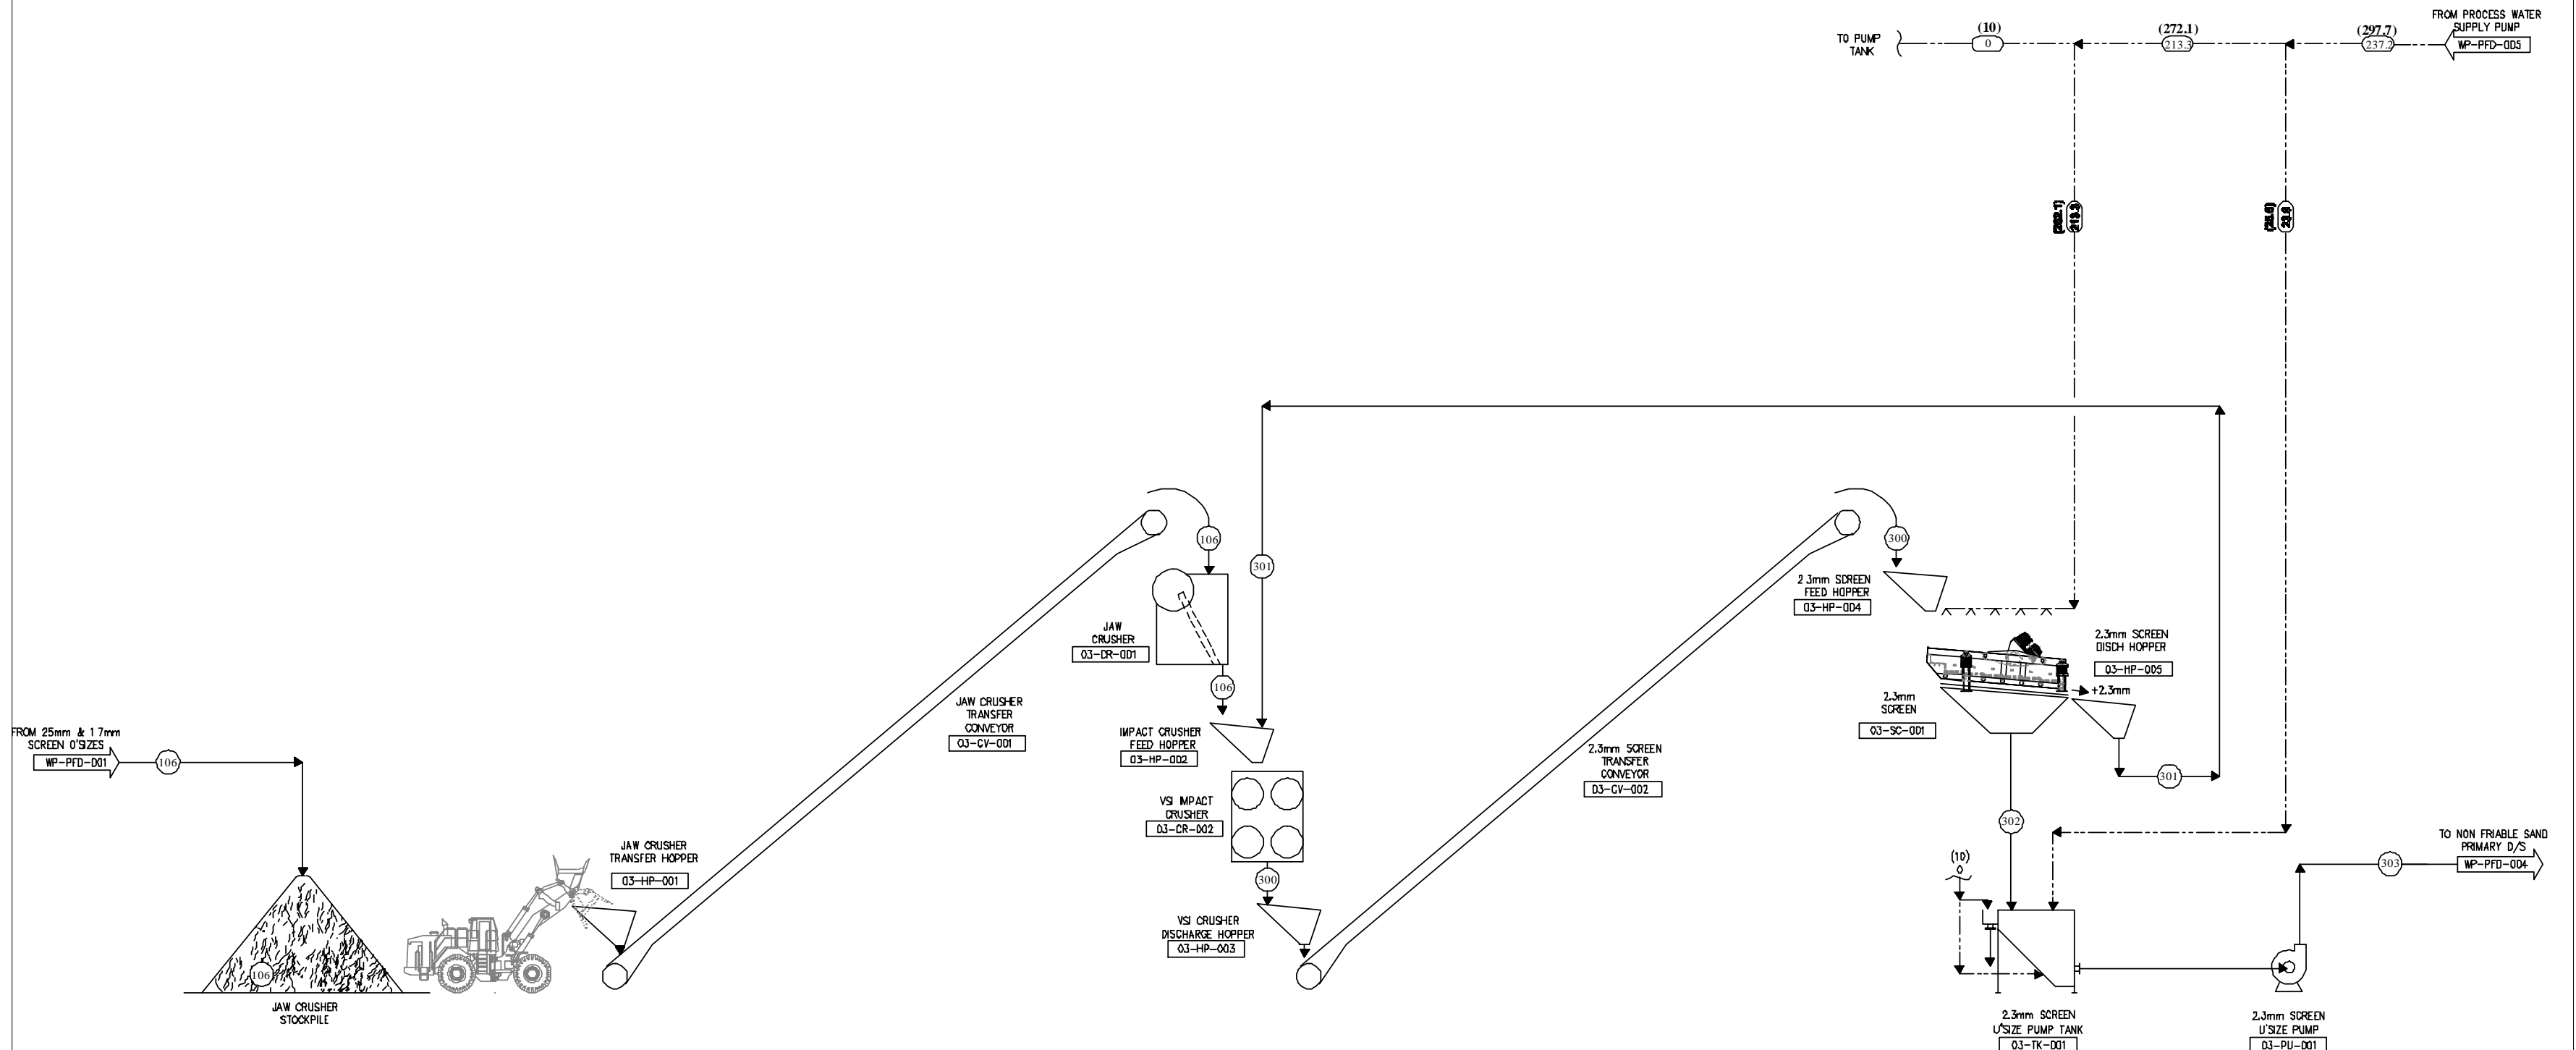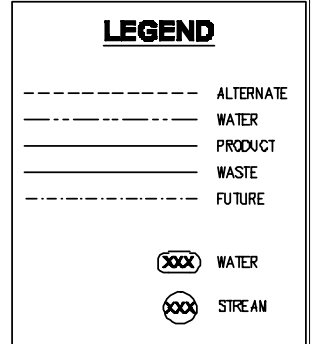

Source: adapted from Outotec, 2008

DRAWING:
WP-PFD-004 revP2 Area 04/Wet Plant: Density Separator Circuit – Non Friable



	STREAM	303	400	401	402	403	404	405	406	407	408	409	410
AVERAGE	SOLIDS, TPH	129.6	80.0	49.6	49.6	53.0	49.6	49.6	27.1	-	102.6	110.3	25.5
	WATER, m ³ /h	240.8	312.8	19.3	148.9	20.6	19.3	2.6	351.9	129.6	5.4	42.9	33.5
	SLURRY, m ³ /h	289.7	343.0	38.0	167.6	40.6	38.0	21.3	362.1	129.6	44.1	84.5	43.1
	% SOLIDS	35.0	20.4	72.0	25.0	72.0	72.0	95.0	7.1	-	95.0	72.0	43.2
	SLURRY S.G.	1.279	1.145	1.813	1.184	1.813	1.813	2.448	1.046	-	2.448	1.813	1.368
DESIGN	SOLIDS, TPH	155.6	96.0	59.5	59.5	63.6	59.5	59.5	32.5	-	123.1	132.4	33.2
	WATER, m ³ /h	288.9	357.1	23.2	178.6	24.71	23.2	3.1	392.1	155.5	6.5	51.5	43.6
	SLURRY, m ³ /h	347.6	393.3	45.6	201.1	48.7	45.6	25.6	404.4	155.5	52.9	101.4	56.0
	% SOLIDS	35.0	21.2	72.0	25.0	72.0	72.0	95.0	7.7	-	95.0	72.0	43.0
	SLURRY S.G.	1.28	1.15	1.81	1.18	1.81	1.81	2.45	1.05	-	2.45	1.81	1.37

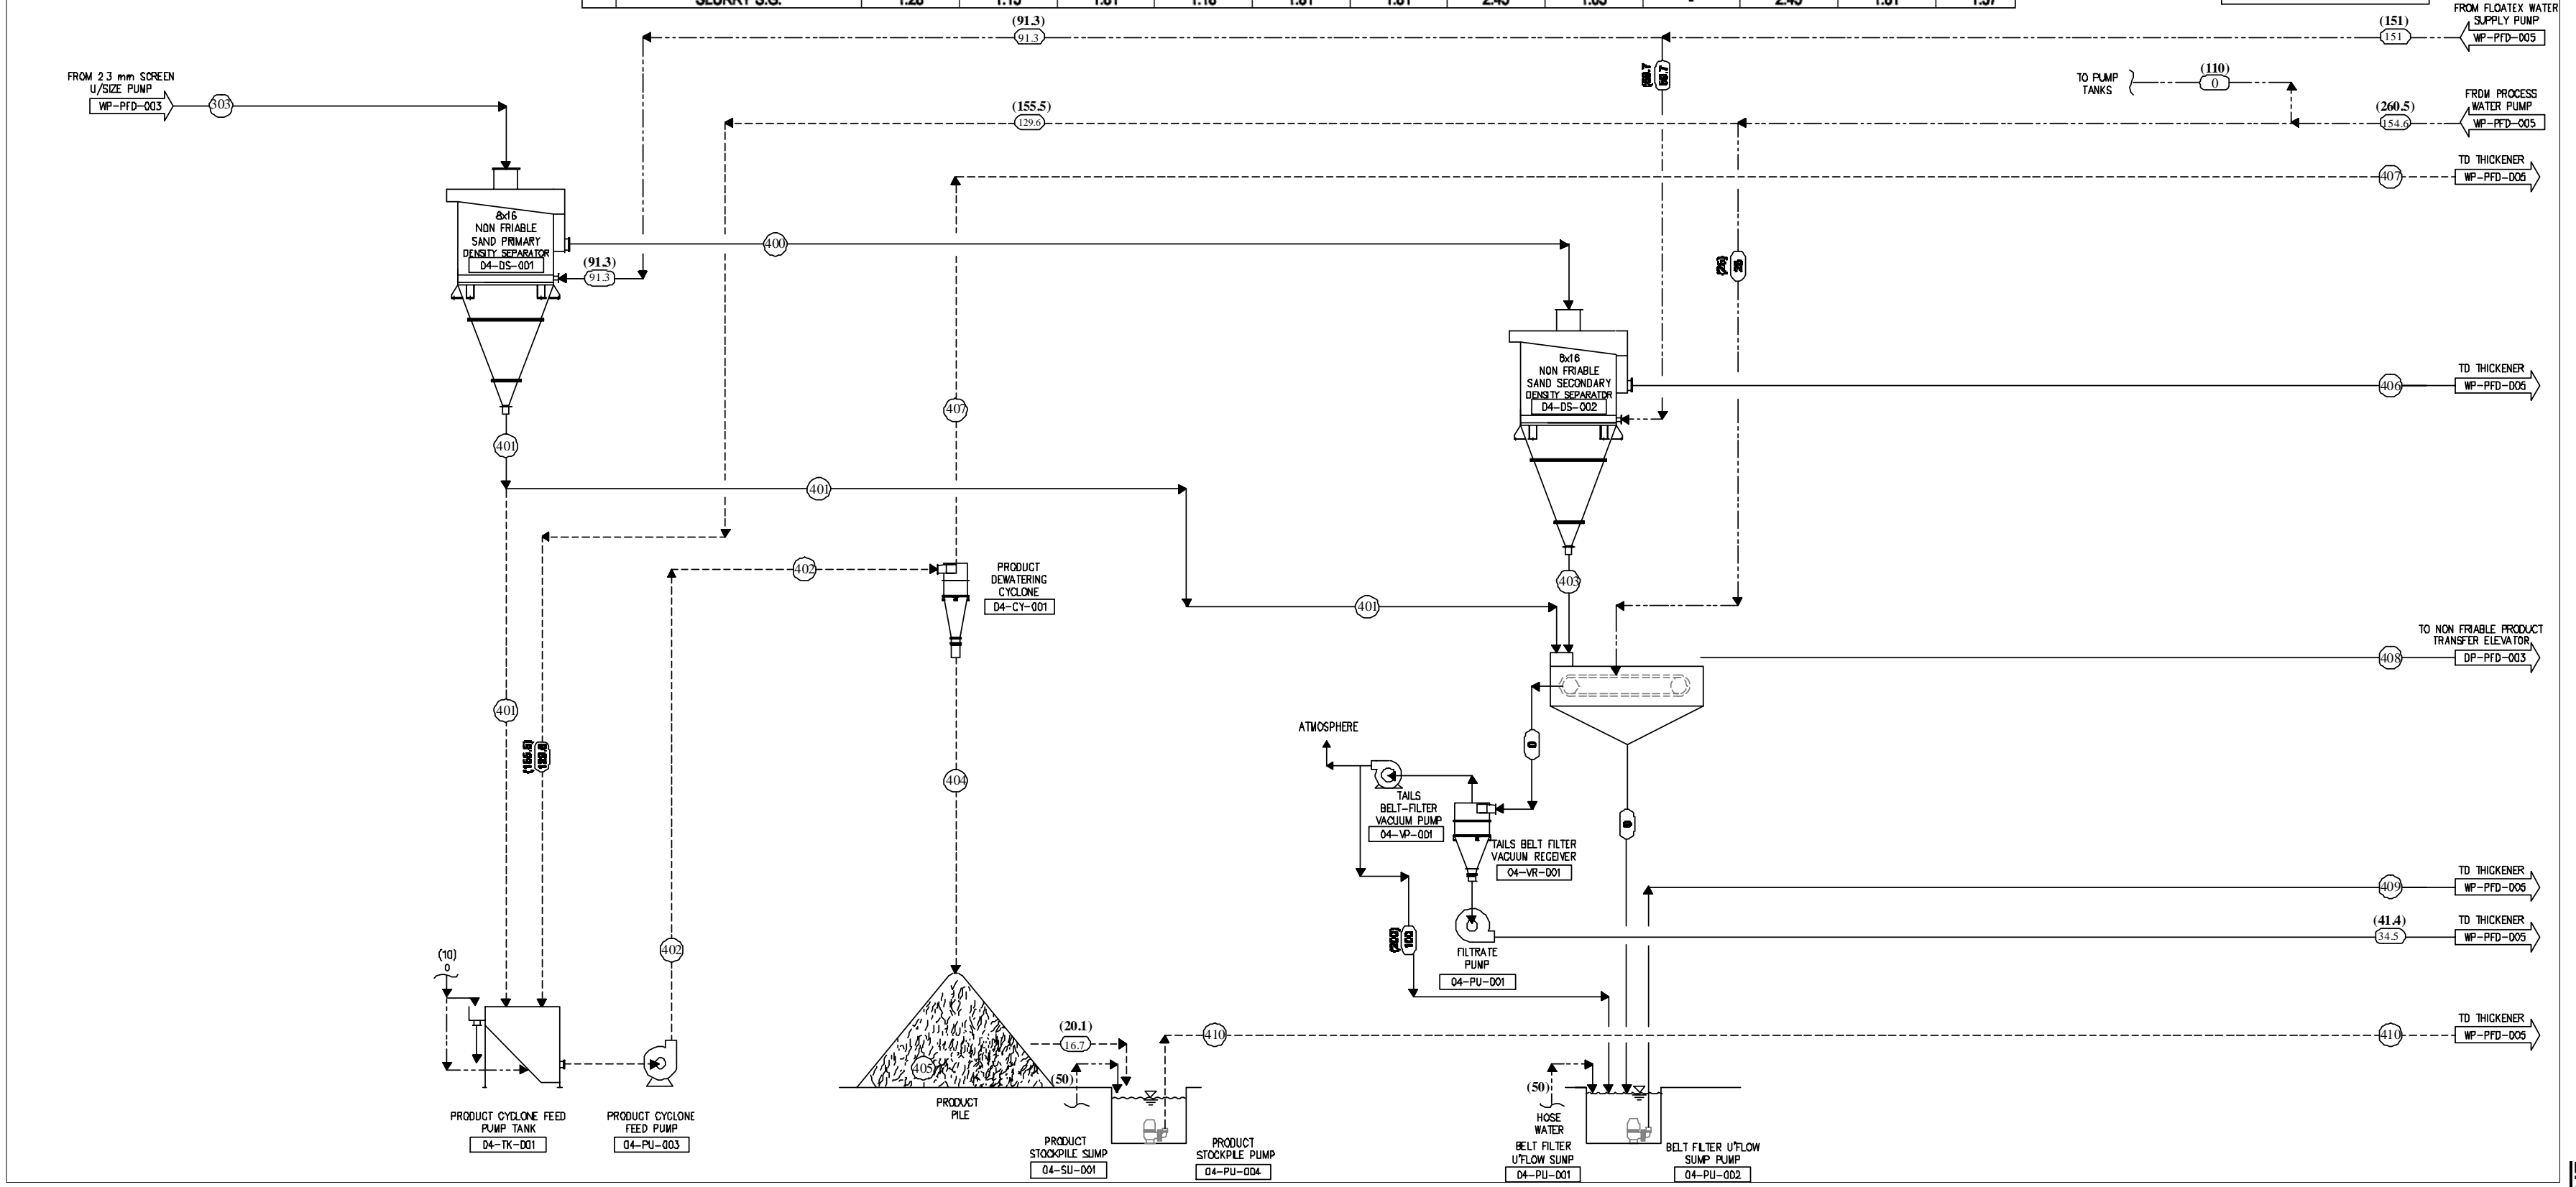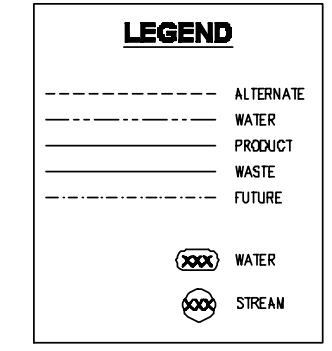

Source: adapted from Outotec, 2008

DRAWING:
WP-PFD-005 revP2 Area 05/Wet Plant: Plant Thickener



	STREAM	115	203	214	406	407	409	410	500	501	610	808
AVERAGE	SOLIDS, TPH	5.4	17.3	-	27.1	-	110.3	25.5	49.8	-	-	-
	WATER, m³/h	1393.3	332.4	297.1	351.9	129.6	42.9	33.5	26.81	1374.2	-	-
	SLURRY, m³/h	1412.1	338.9	297.1	362.1	129.6	84.5	43.1	45.60	-	-	-
	% SOLIDS	.75	5.0	-	7.1	-	72.0	43.2	65.0	-	-	-
	SLURRY S.G.	1.005	1.032	-	1.046	-	1.813	1.368	1.679	-	-	-
DESIGN	SOLIDS, TPH	6.4	20.8	-	32.5	-	132.4	33.2	49.7	-	-	-
	WATER, m³/h	770.8	372.6	356.5	392.1	155.5	51.5	43.6	32.2	1508.7	-	-
	SLURRY, m³/h	773.2	380.5	356.5	404.4	155.5	101.4	56.0	45.7	-	-	-
	% SOLIDS	.85	5.3	-	7.7	-	72.0	43.0	65.0	-	-	-
	SLURRY S.G.	1.01	1.03	-	1.05	-	1.81	1.37	1.68	-	-	-

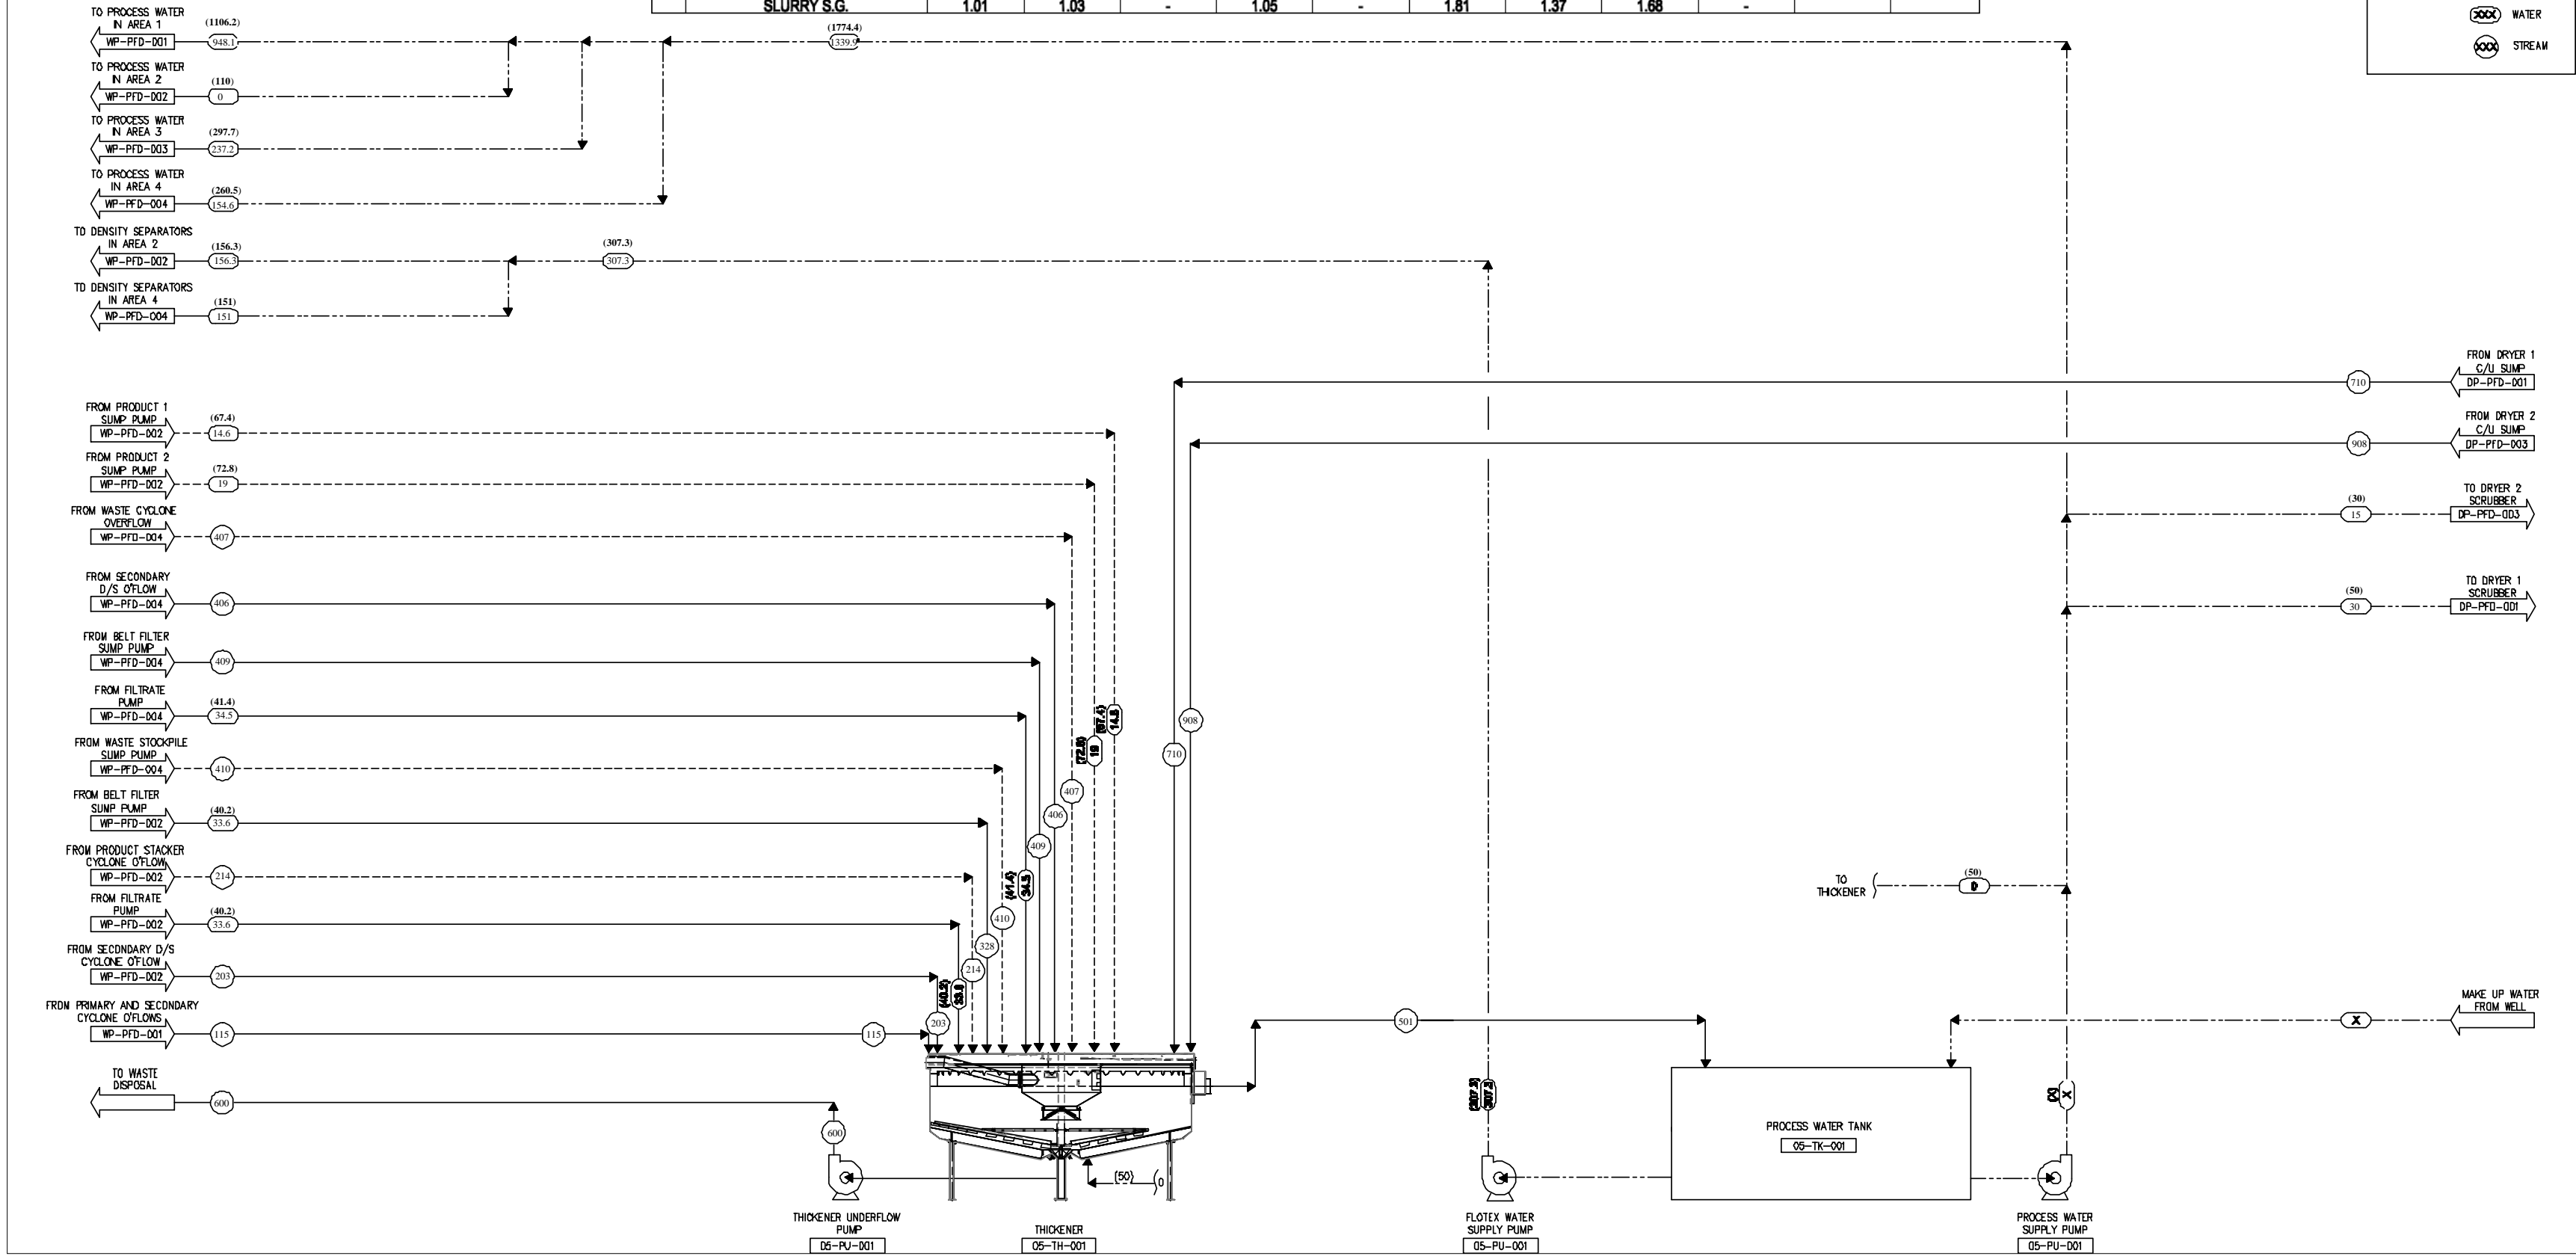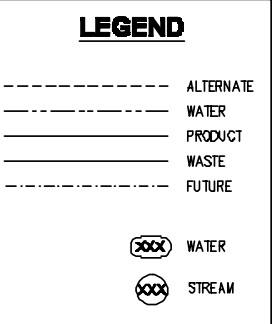

Source: adapted from Outotec, 2008

DRAWING:
DP-PFD-001 revP3 Area 06/Dry Plant: Drying and Screening – Friable

	STREAM	205	207	600	601	602	603	604	605	606	607	608	609
AVERAGE	SOLIDS, TPH	112.2	112.2	112.2		112.2	X	X	X	75.5	16.9	16.8	2.9
	WATER, m ³ /h	5.9	5.9	5.9	5.9								
	SLURRY, m ³ /h	48.2	48.2	-	5.9								
	% SOLIDS	95.0	95.0	95.0		100.0				100.0	100.0	100.0	100.0
	SLURRY S.G.	2.448	2.448	2.448									
DESIGN	SOLIDS, TPH	134.7	134.7	134.7	-	134.7	X	X	X	90.8	20.3	20.2	3.5
	WATER, m ³ /h	7.1	7.1	7.1	7.1								
	SLURRY, m ³ /h	57.9	57.9	-	7.1								
	% SOLIDS	95.0	95.0	95.0	-	100.0				100.0	100.0	100.0	100.0
	SLURRY S.G.	2.45	2.45	2.45	-								

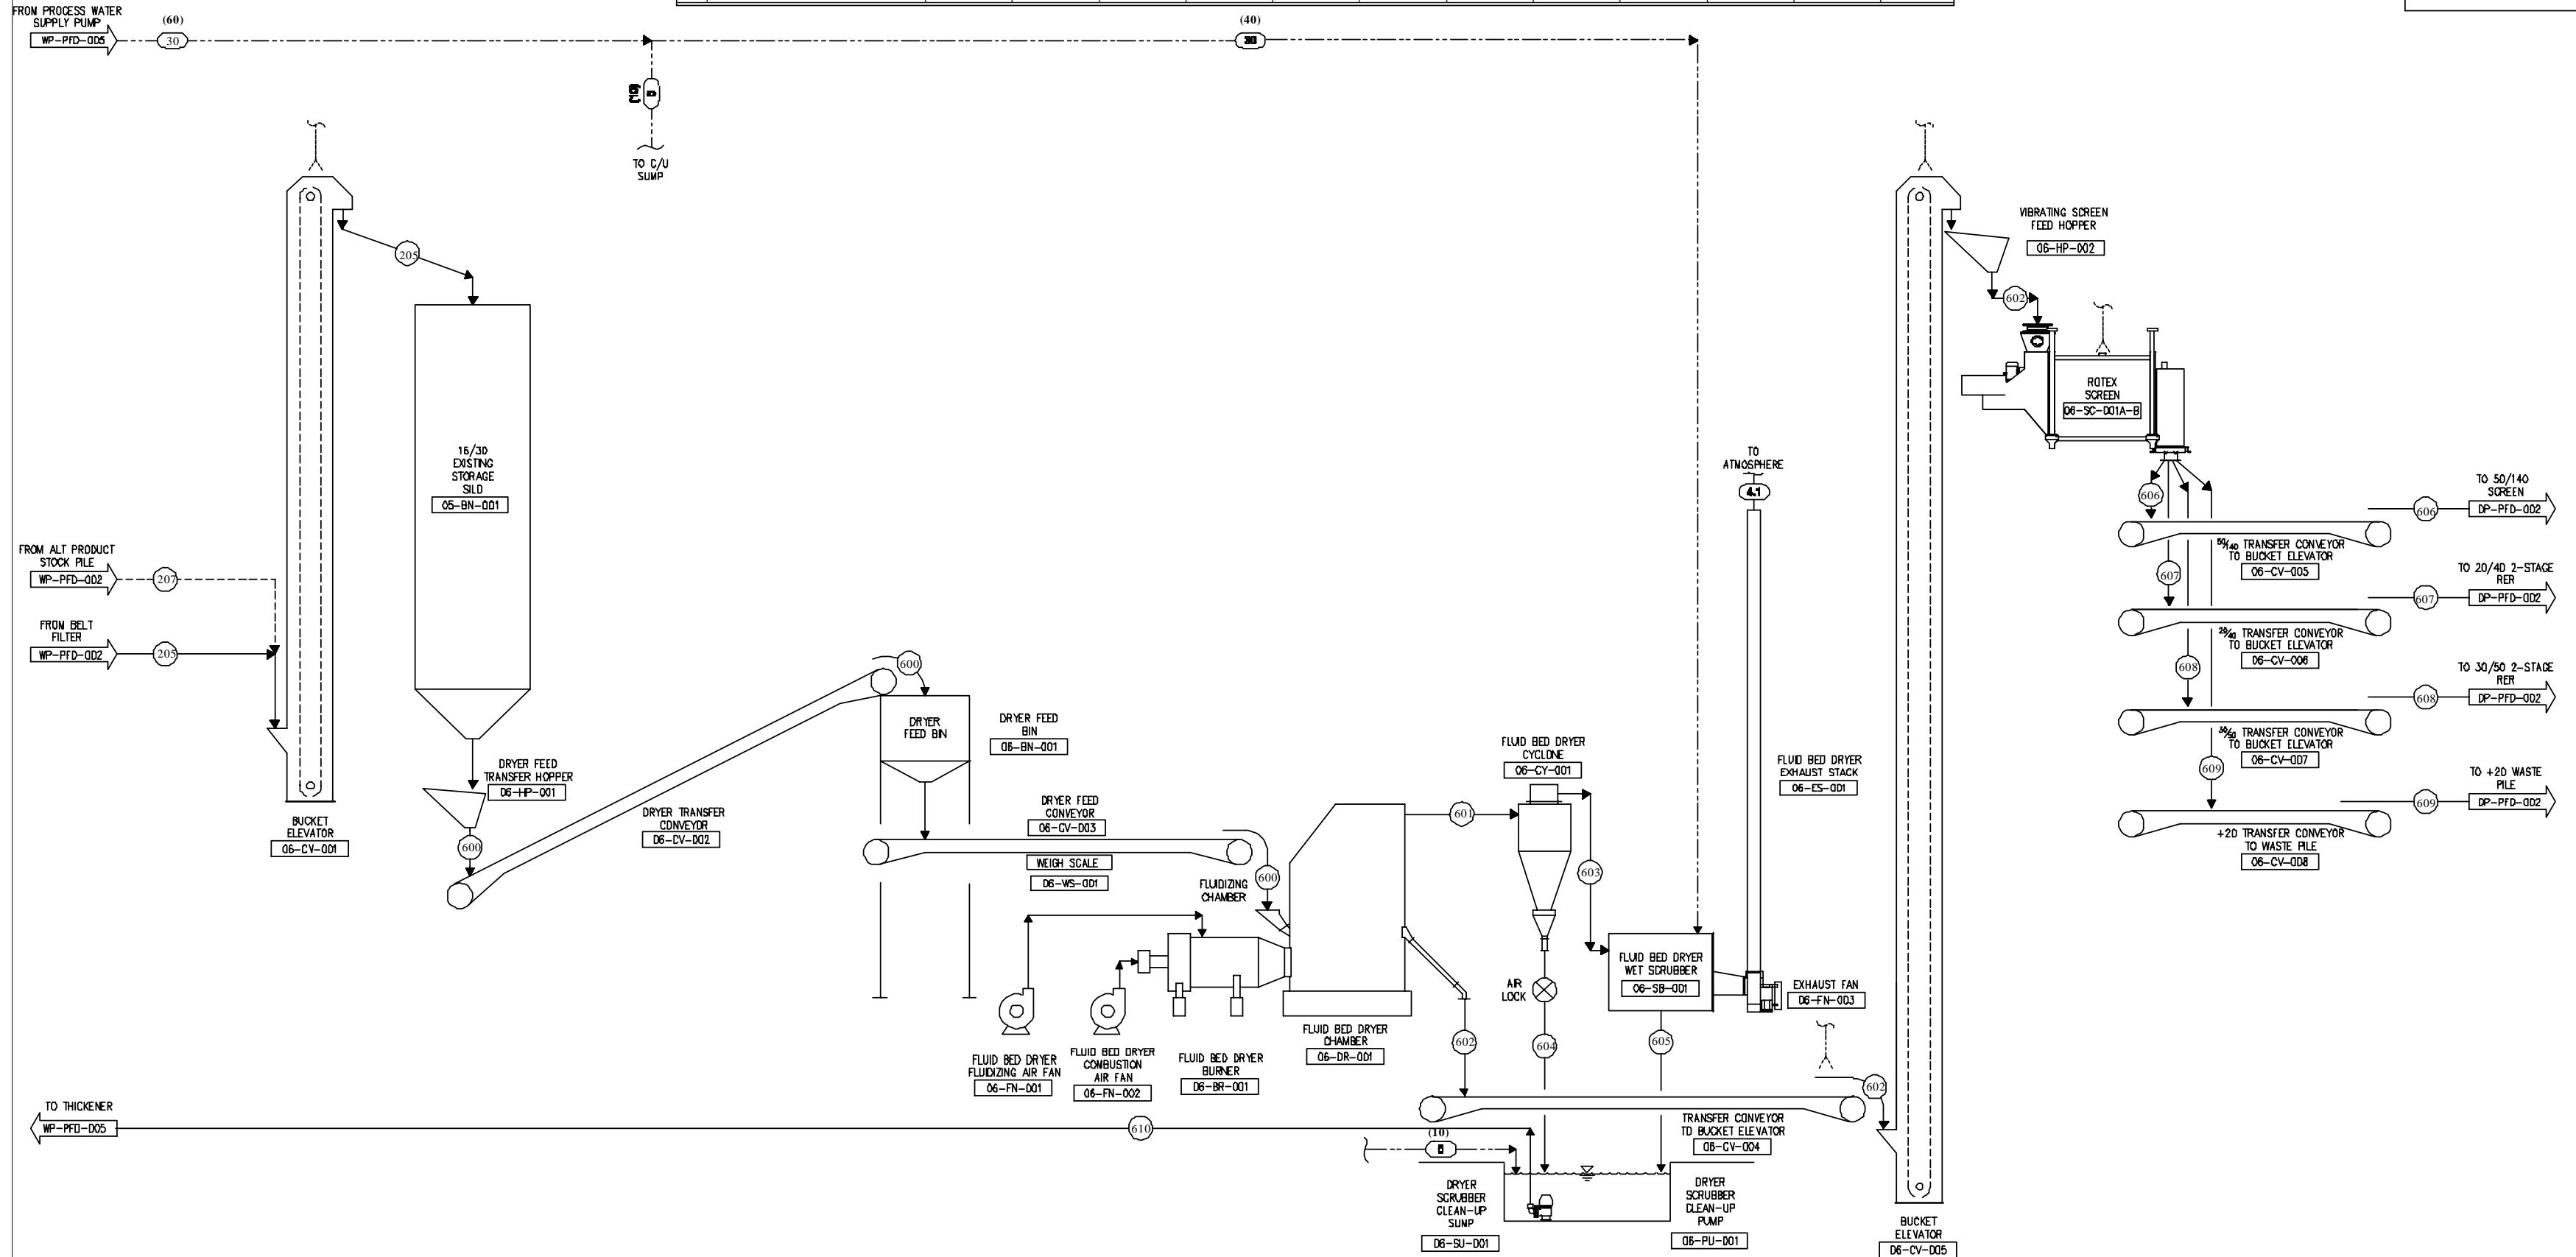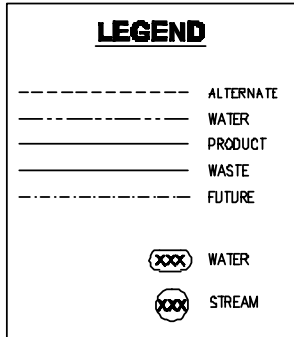



Source: adapted from Outotec, 2008


DRAWING:
DP-PFD-002 revP3 Area 07/Dry Plant: Screening and Magnetic Separation – Friable

	STREAM	606	607	608	609	700	701	702	703	704	705	706	707	708	709	710
AVERAGE	SOLIDS, TPH	75.5	16.9	16.8	2.9	27.5	48.0	1.4	26.1	2.4	45.6	0.8	16.1	1.4	16.0	6.0
	WATER, m ³ /h															
	SLURRY, m ³ /h															
	% SOLIDS	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0
	SLURRY S.G.															
DESIGN	SOLIDS, TPH	90.6	20.3	20.2	3.5	33.0	57.6	1.6	31.3	2.9	54.7	1.0	19.3	1.6	19.2	7.1
	WATER, m ³ /h															
	SLURRY, m ³ /h															
	% SOLIDS	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0	100.0
	SLURRY S.G.															

LEGEND


- ALTERNATE
- - - WATER
- PRODUCT
- WASTE
- - - FUTURE

 WATER
 STREAM

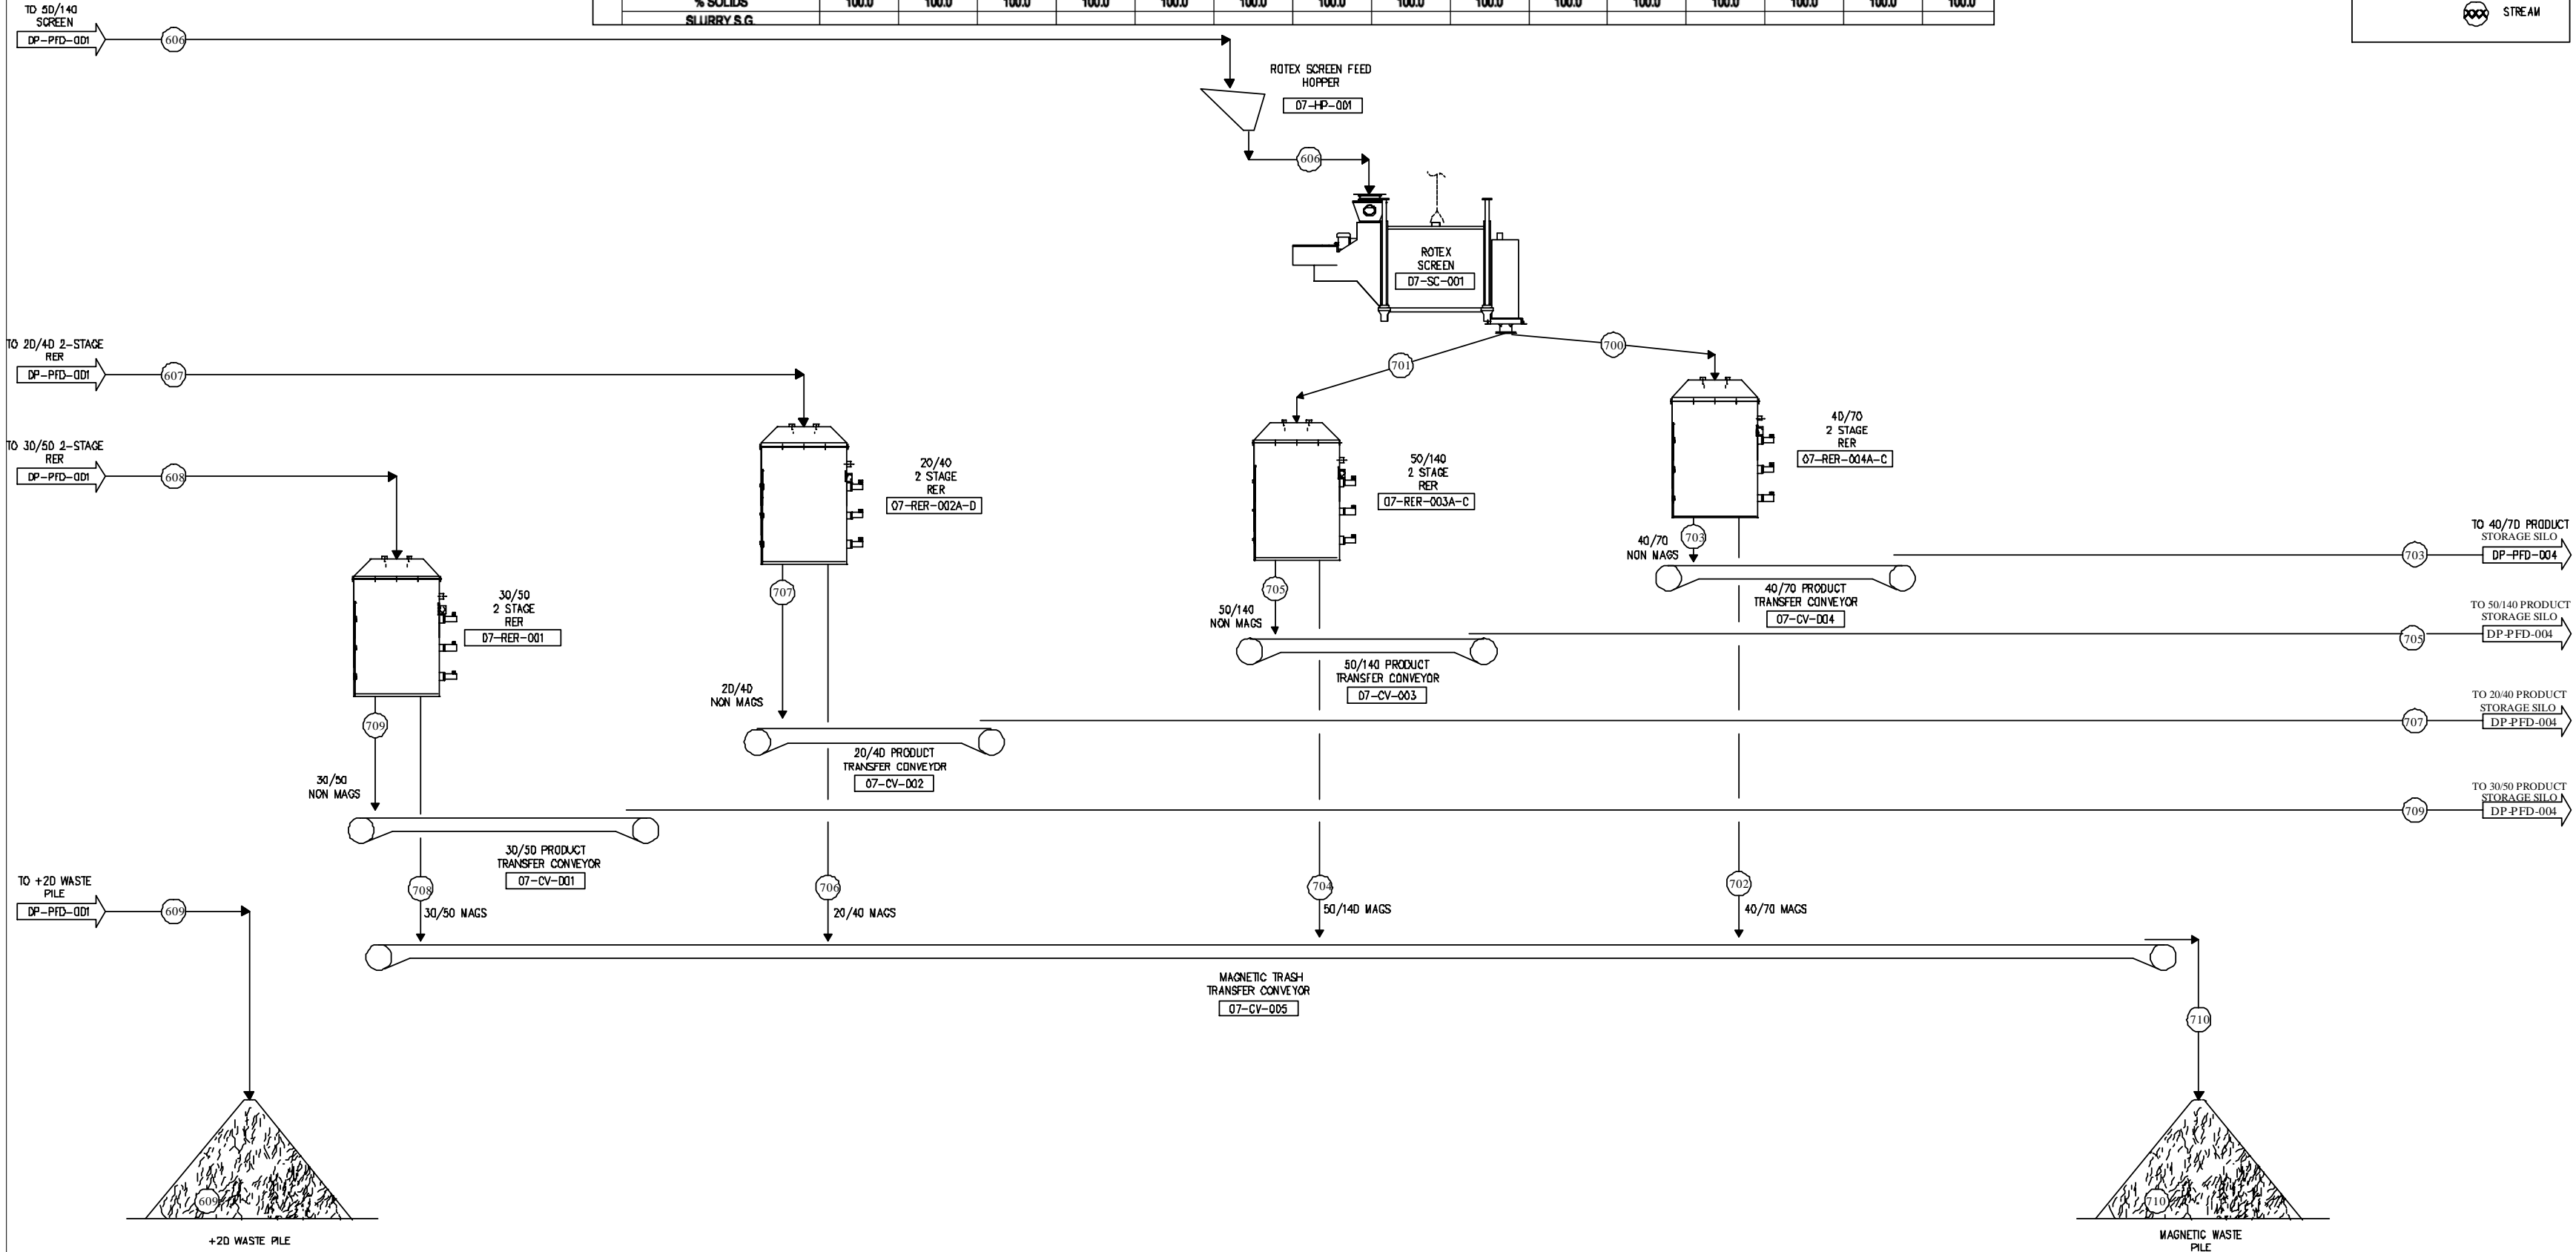


Source: adapted from Outotec, 2008

DRAWING:
DP-PFD-003 revP2 Area 08/Dry Plant: Drying and Screening – Non Friable

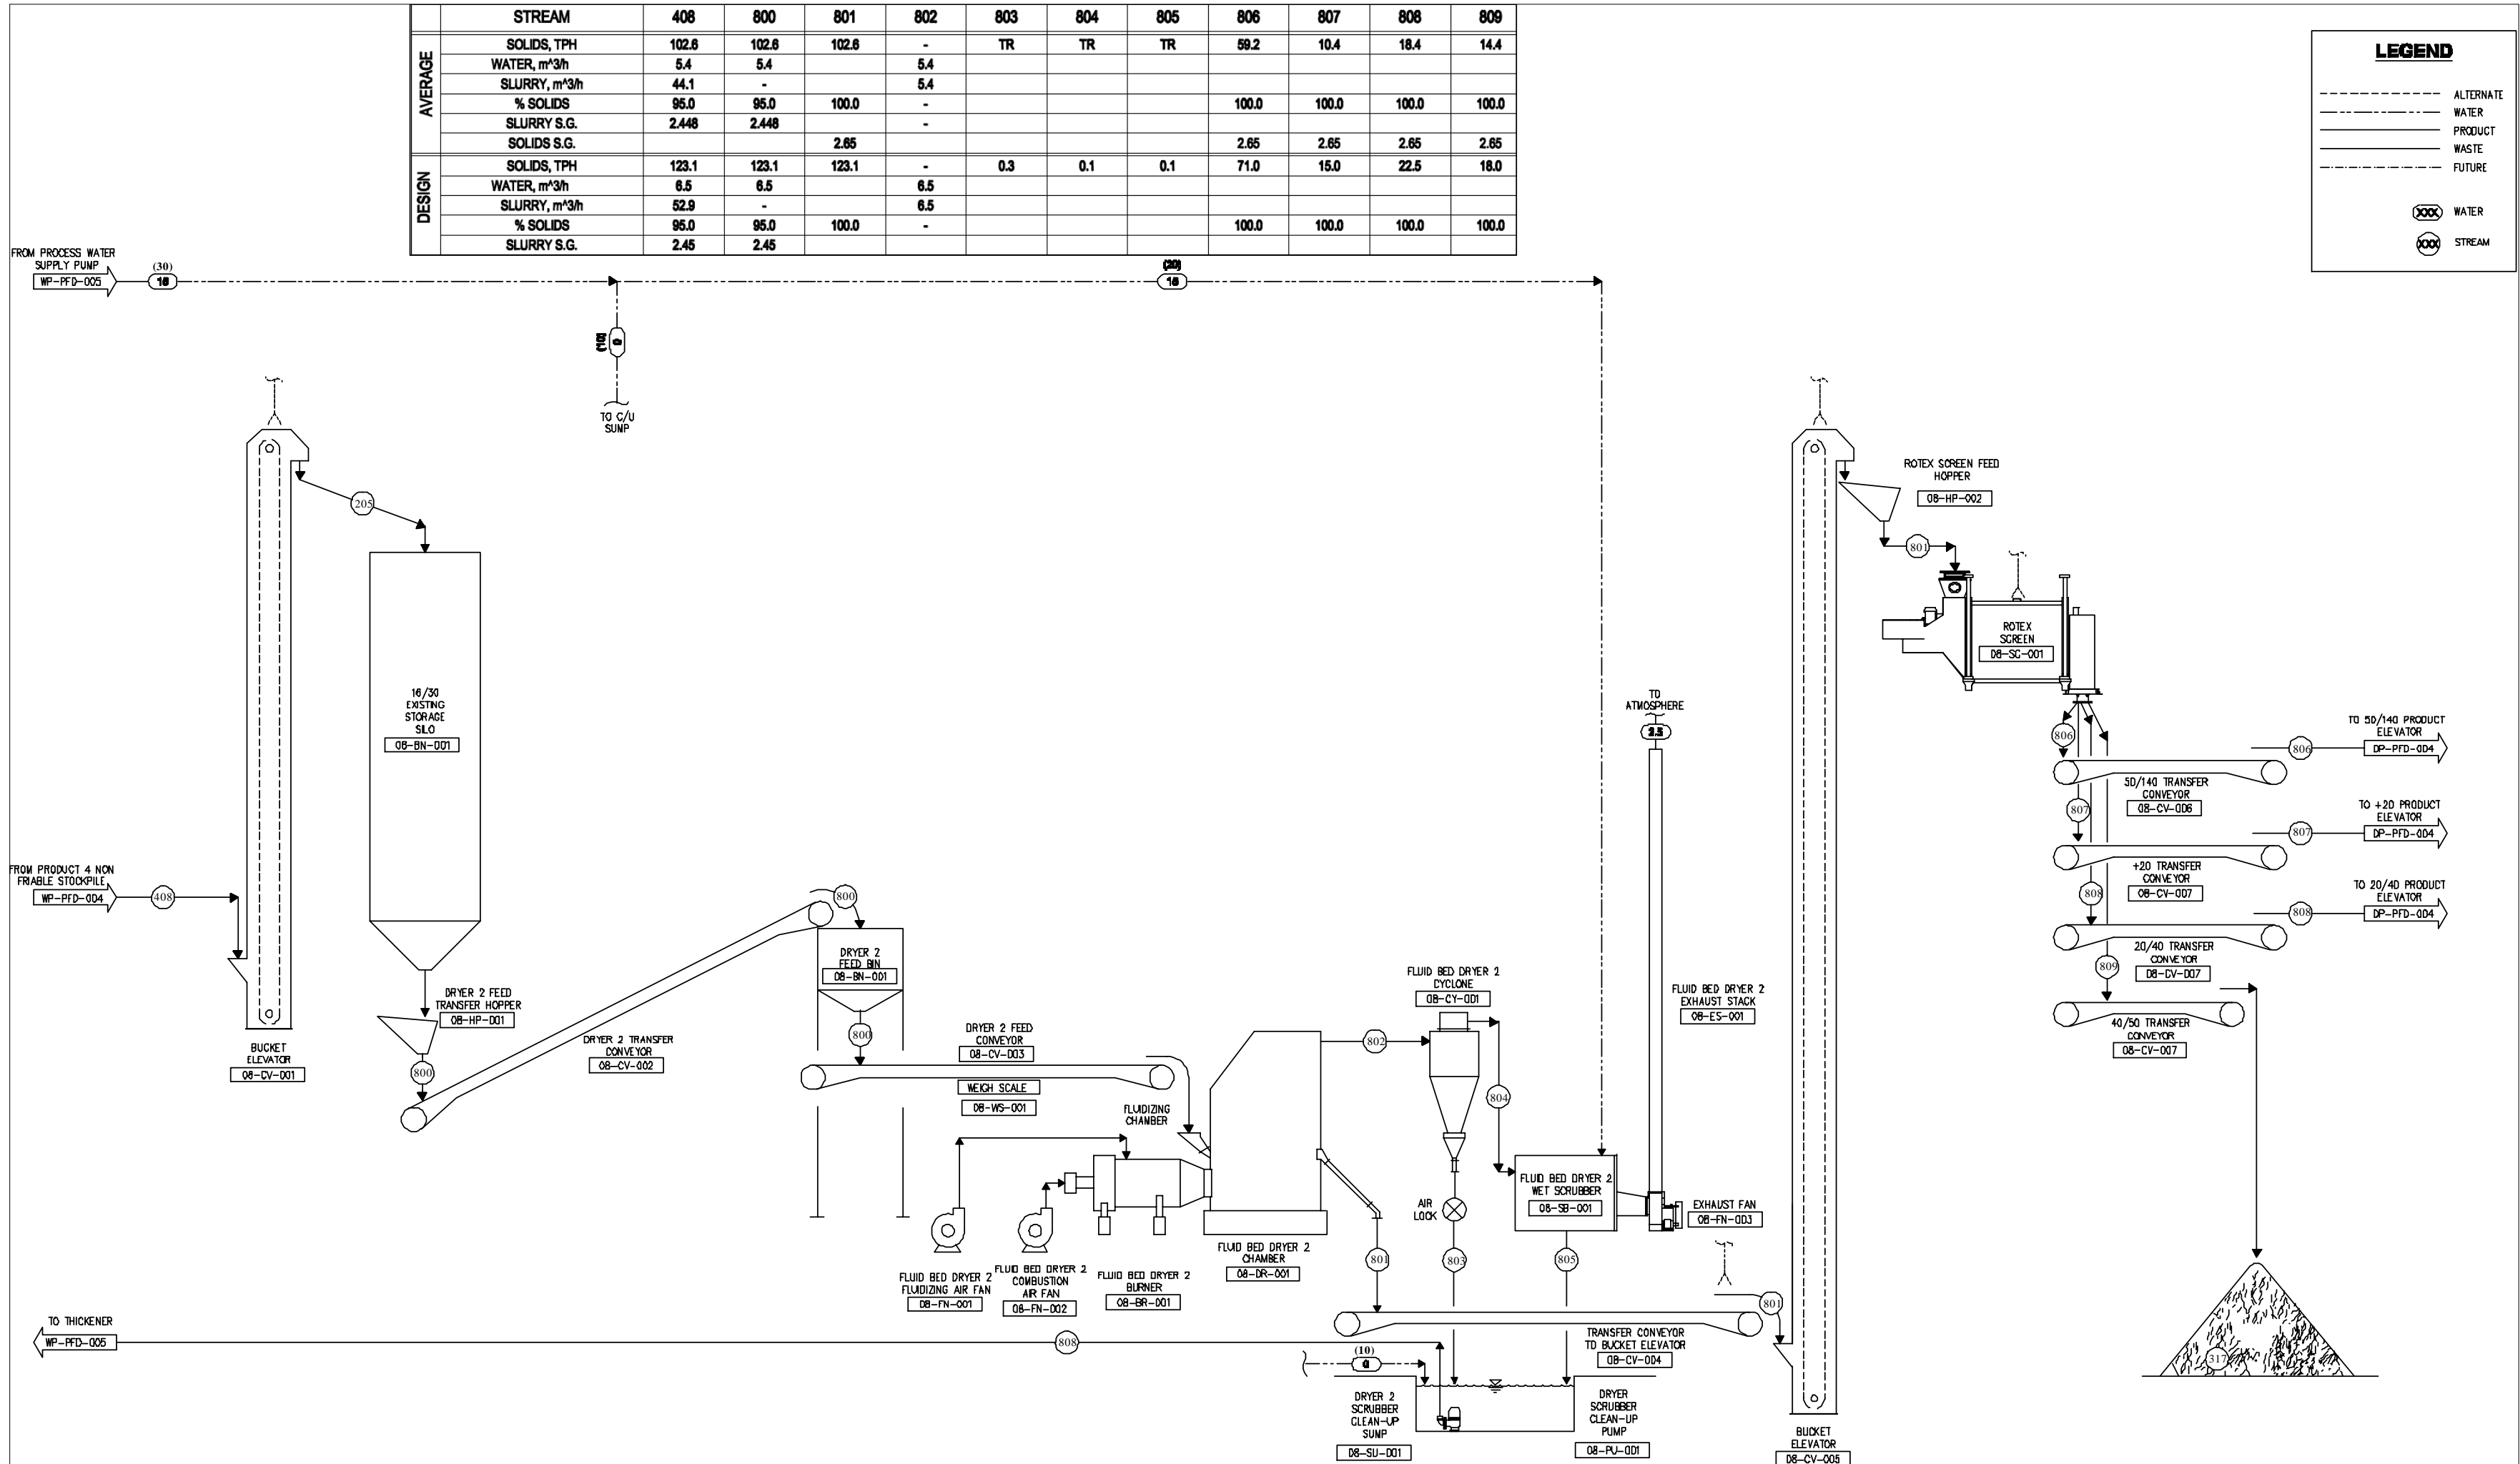

Source: adapted from Outotec, 2008

DRAWING:
DP-PFD-004 revP3 Area 09/Dry Plant : Storage Silos – Friable and Non Friable

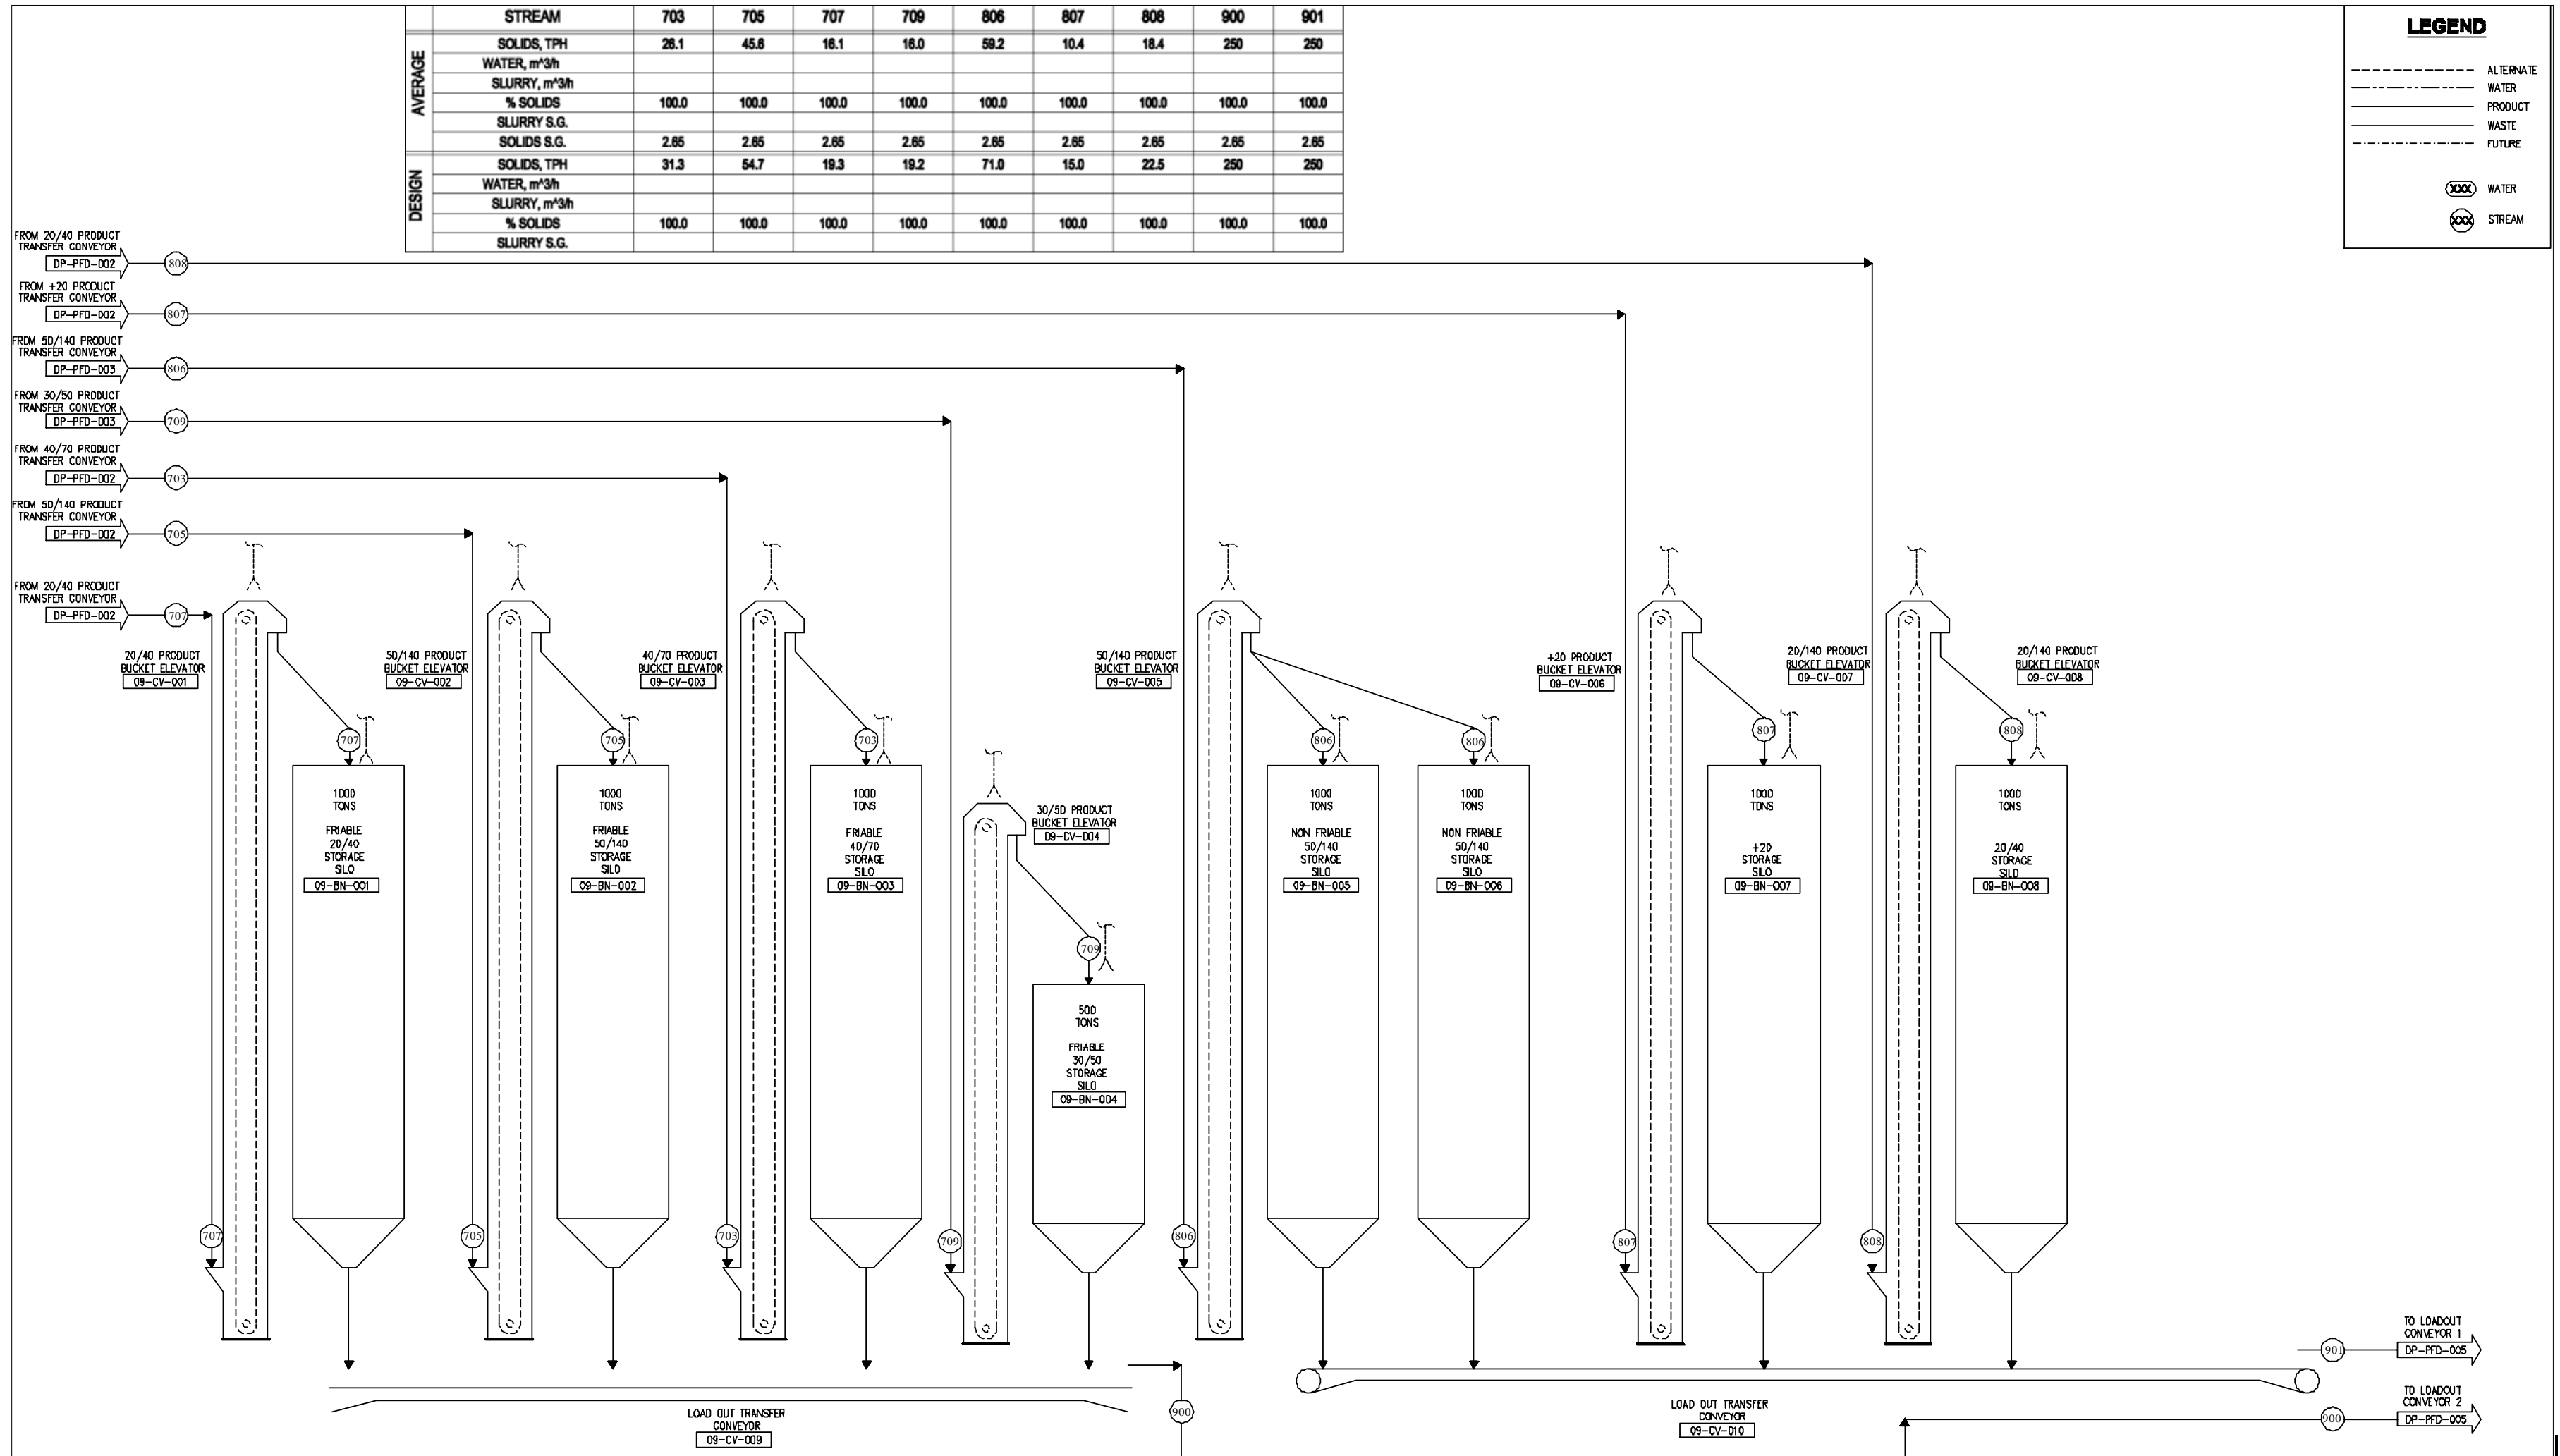

LEGEND

- - - - - ALTERNATE
- — — — WATER
- — — — PRODUCT
- — — — WASTE
- — — — FUTURE
- (with 'X') WATER
- (with 'S') STREAM


Source: adapted from Outotec, 2008

DRAWING:
DP-PFD-005 revP2 Area 09/ Dry Plant: Plant Product Load Out

	STREAM	900	901
AVERAGE	SOLIDS, TPH	250	250
	WATER, m ³ /h		
	SLURRY, m ³ /h		
	% SOLIDS	100.0	100.0
	SLURRY S.G.		
DESIGN	SOLIDS, TPH	250	250
	WATER, m ³ /h		
	SLURRY, m ³ /h		
	% SOLIDS	100.0	100.0
	SLURRY S.G.		

LEGEND

- ALTERNATE
- WATER
- PRODUCT
- WASTE
- FUTURE
- (X) WATER
- (O) STREAM

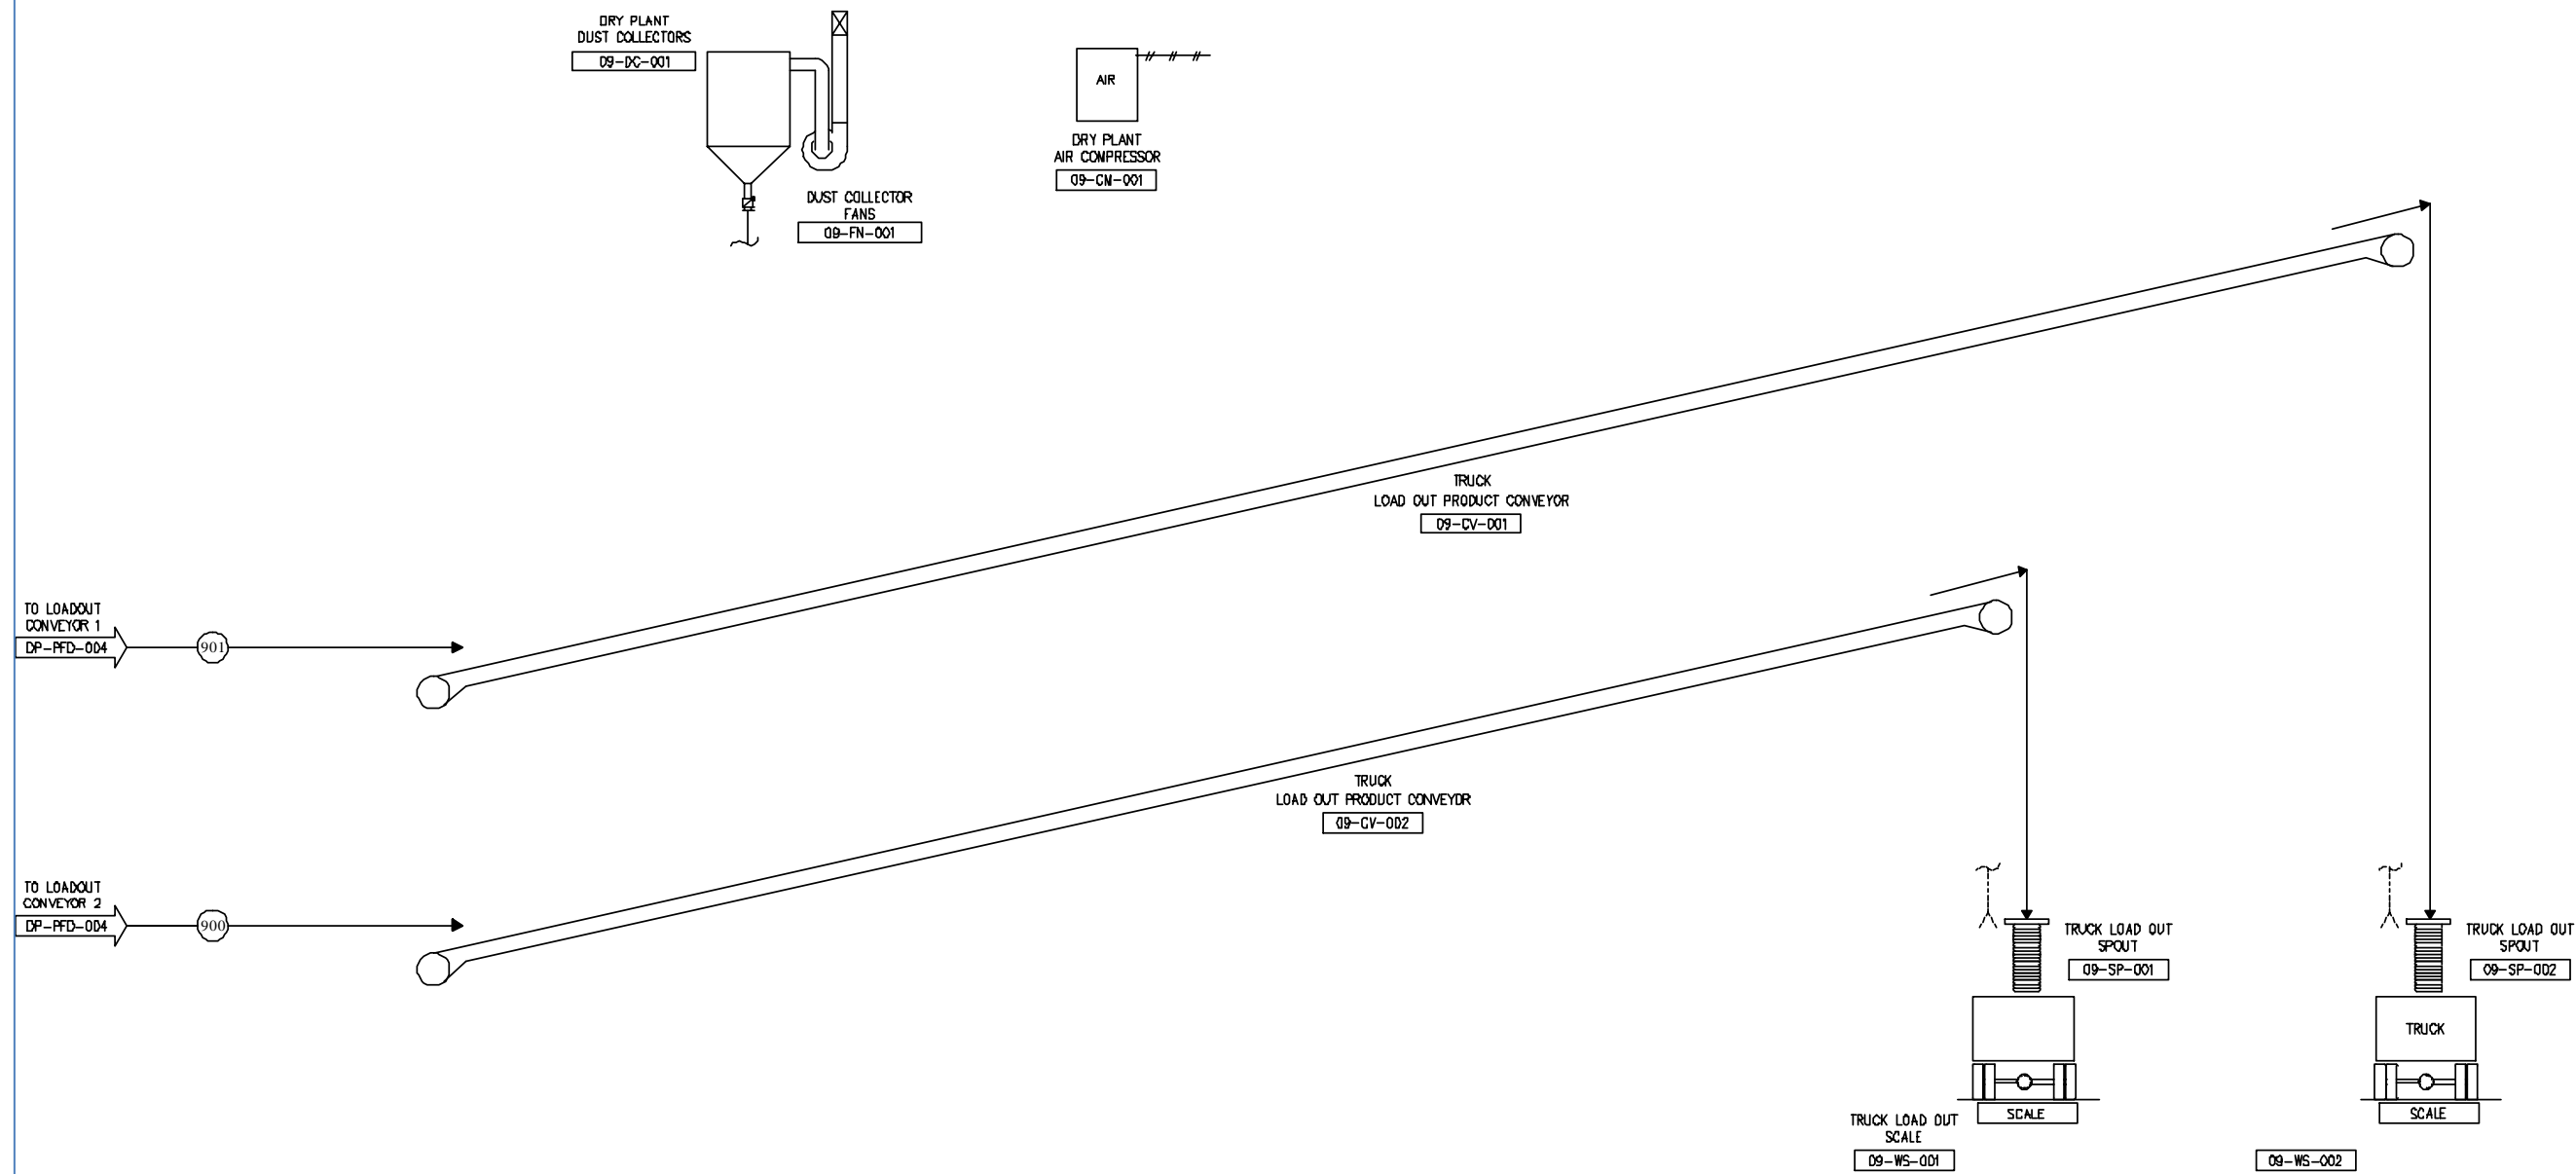

Source: adapted from Outotec, 2008

APPENDIX 2.14

Supplemental Material for Site Water Management

	Page
Appendix 2.14-A: Detailed Key Parameters and Considerations used for the Water Balance Model	2.14-1
Appendix 2.14-B: Water Balance Model Results for Year 1 through Year 4 Operations	2.14-7
Appendix 2.14-C: Water Balance Model Results for Year 5 through Year 8 Operations	2.14-11
Appendix 2.14-D: Water Balance Model Results for Year 9 and Year 10 Operations	2.14-15
Appendix 2.14-E: Water Balance Model Results for the Closure and Post Closure Periods	2.14-18
Appendix 2.14-F: Water Balance Model Results for Temporary Suspension after Year 5 & the State of Inactivity after one year of Temporary Suspension	2.14-23

APPENDIX 2.14-A

**Detailed Key Parameters and Considerations used for
the Water Balance Model**

Table 2.14-A1. Input Data - Average Concentrations for Frac Sand Plant Overflow and Underflow

RESULTS OF ANALYSIS	FRAC SAND PLANT OVERFLOW				FRAC SAND PLANT UNDERFLOW			
	FSTOF-1	FSTOF-2	AVERAGE ¹	MAXIMUM	FSTUF-1	FSTUF-2	AVERAGE ¹	MAXIMUM
Sample ID	L714607-1	L714607-2			L714613-1	L714613-2		
ALS Sample ID								
Matrix	Water	Water			Water	Water		
	mg/L	mg/L			mg/L	mg/L		
Physical Tests								
Hardness (as CaCO3)	149	194	171.5	194	192	142	167	192
Total Suspended Solids	<3.0	11.9	6.7	11.9	41.9	5.9	23.9	41.9
Dissolved Metals								
Aluminum (Al)-Dissolved	0.0069	0.0044	0.00565	0.0069	0.0057	0.0066	0.00615	0.0066
Antimony (Sb)-Dissolved	0.00148	0.00132	0.0014	0.00148	0.00137	0.00145	0.00141	0.00145
Arsenic (As)-Dissolved	0.000743	0.000813	0.000778	0.000813	0.000829	0.000653	0.000741	0.000829
Barium (Ba)-Dissolved	0.0503	0.0688	0.05955	0.0688	0.0696	0.0489	0.05925	0.0696
Beryllium (Be)-Dissolved	<0.00020	<0.00020	0.0001	0.0001	<0.00020	<0.00020	0.0001	0.0001
Bismuth (Bi)-Dissolved	<0.00050	<0.00050	0.00025	0.00025	<0.00050	<0.00050	0.00025	0.00025
Boron (B)-Dissolved	0.0444	0.07	0.0572	0.07	0.069	0.0408	0.0549	0.069
Cadmium (Cd)-Dissolved	0.00007	0.000068	0.000069	0.00007	0.000082	0.000066	0.000074	0.000082
Calcium (Ca)-Dissolved	38.2	48.7	43.45	48.7	48.1	36.8	42.45	48.1
Chromium (Cr)-Dissolved	0.00021	0.0003	0.000255	0.0003	0.00027	0.0002	0.000235	0.00027
Cobalt (Co)-Dissolved	0.00093	0.00096	0.000945	0.00096	0.00283	0.00087	0.00185	0.00283
Copper (Cu)-Dissolved	0.00385	0.00212	0.002985	0.00385	0.00292	0.00282	0.00287	0.00292
Iron (Fe)-Dissolved	<0.010	<0.010	0.005	0.005	<0.010	<0.010	0.005	0.005
Lead (Pb)-Dissolved	<0.000050	<0.000050	0.000025	0.000025	<0.000050	<0.000050	0.000025	0.000025
Lithium (Li)-Dissolved	0.0074	0.0131	0.01025	0.0131	0.0128	0.0068	0.0098	0.0128
Magnesium (Mg)-Dissolved	12.9	17.7	15.3	17.7	17.4	12	14.7	17.4
Manganese (Mn)-Dissolved	0.0182	0.0389	0.02855	0.0389	0.0864	0.0155	0.05095	0.0864
Mercury (Hg)-Dissolved	<0.000010	<0.000010	0.000005	0.000005	<0.000010	<0.000010	0.000005	0.000005
Molybdenum (Mo)-Dissolved	0.0123	0.0189	0.0156	0.0189	0.0189	0.0117	0.0153	0.0189
Nickel (Ni)-Dissolved	0.02	0.0276	0.0238	0.0276	0.0292	0.0188	0.024	0.0292
Phosphorus (P)-Dissolved	<0.30	<0.30	0.15	0.15	<0.30	<0.30	0.15	0.15
Potassium (K)-Dissolved	3.16	4.04	3.6	4.04	3.99	3	3.495	3.99
Selenium (Se)-Dissolved	0.0005	0.00035	0.000425	0.0005	0.00034	0.00047	0.000405	0.00047
Silicon (Si)-Dissolved	0.75	1.52	1.135	1.52	1.47	0.708	1.089	1.47
Silver (Ag)-Dissolved	0.000018	0.000021	0.0000195	0.000021	<0.000010	0.000027	0.000016	0.000027
Sodium (Na)-Dissolved	16.2	17.4	16.8	17.4	17.1	15.8	16.45	17.1
Strontium (Sr)-Dissolved	0.776	1.15	0.963	1.15	1.15	0.719	0.9345	1.15
Thallium (Tl)-Dissolved	0.000083	0.000052	0.0000675	0.000083	0.000051	0.000073	0.000062	0.000073
Tin (Sn)-Dissolved	<0.00010	<0.00010	0.00005	0.00005	<0.00010	<0.00010	0.00005	0.00005
Titanium (Ti)-Dissolved	<0.010	<0.010	0.005	0.005	<0.010	<0.010	0.005	0.005
Uranium (U)-Dissolved	0.00436	0.00656	0.00546	0.00656	0.00655	0.00402	0.005285	0.00655
Vanadium (V)-Dissolved	0.000141	0.000188	0.0001645	0.000188	0.000175	0.000138	0.0001565	0.000175
Zinc (Zn)-Dissolved	0.0084	0.0107	0.00955	0.0107	0.0132	0.0084	0.0108	0.0132

NOTE: 1 If the concentration was below the detection limit, half the detection limit was used to calculate the average.

Table 2.14-A2. Groundwater Quality Data (Golder, 2008b)

ASSUMED RATIO FOR GROUNDWATER FROM LIMESTONE TO GROUNDWATER FROM SANDSTONE FORMATION: 2.34

	SAMPLE ID	HG-3 LS	HG-7 LS	HG-7 LS	LIMESTONE AVERAGE ¹	LIMESTONE MAXIMUM ¹	LIMESTONE MINIMUM ¹	HG-3 SS	HG-3 SS	HG-7 SS	SANDSTONE AVERAGE ¹	SANDSTONE MAXIMUM ¹	SANDSTONE MINIMUM ¹	AVERAGE AUG-08
	Date Sampled	15-AUG-08	15-AUG-08	15-AUG-08	Aug-08	Aug-08	Aug-08	15-AUG-08	15-AUG-08	15-AUG-08	Aug-08	Aug-08	Aug-08	GROUNDWATER QUALITY USED FOR MODELING
	Time Sampled													
PARAMETER	Lab Sample ID	L672682-1	L672682-3	L672682-6				L672682-2	L672682-5	L672682-4				
	Units	Water	Water	Water				Water	Water	Water				
Total Suspended Solids	mg/L	4.6	1.5	7.9	4.7	7.9	1.5	1.5	1.5	1.5	1.5	1.5	1.5	3.7
Dissolved Elements														
Aluminum (Al)-Dissolved	mg/L	0.0005	0.0005	0.0215	0.00750	0.0215	0.0005	0.0005	0.0344	0.0005	0.0118	0.0344	0.0005	
Antimony (Sb)-Dissolved	mg/L	0.000025	0.000025	0.000025	0.00003	0.000025	0.000025	0.000025	0.000025	0.000025	0.000025	0.000025	0.000025	
Arsenic (As)-Dissolved	mg/L	0.0011	0.000988	0.00122	0.00110	0.00122	0.000988	0.000218	0.000227	0.000162	0.000202333			0.000833
Cadmium (Cd)-Dissolved	mg/L	0.0000057	0.0000057	0.0000057	0.00001	0.0000057	0.0000057	0.0000057	0.0000057	0.0000057	0.00001	0.0000057	0.0000057	0.0000057
Chromium (Cr)-Dissolved	mg/L	0.001	0.001	<0.00070	0.001	0.001	0.001	0.00107	0.00092	0.001	0.00100	0.00107	0.00092	0.00100
Cobalt (Co)-Dissolved	mg/L	0.00016	0.00005	0.00005	0.00009	0.00016	0.00005	0.00005	0.00005	0.00014	0.00008	0.00014	0.00005	0.00008
Copper (Cu)-Dissolved	mg/L	0.00092	0.00049	0.00033	0.00058	0.00092	0.00033	0.00021	0.00034	0.00055	0.00037	0.00055	0.00021	0.00052
Iron (Fe)-Dissolved	mg/L	0.005	0.005	0.005	0.005	0.005	0.005	0.005	0.005	0.005	0.005	0.005	0.005	0.005
Lead (Pb)-Dissolved	mg/L	0.000025	0.000025	0.000025	0.00003	0.00003	0.00003	0.000025	0.000074	0.000025	0.000041	0.000074	0.000025	0.000030
Molybdenum (Mo)-Dissolved	mg/L	0.000418	0.00051	0.000525	0.000484	0.000525	0.000418	0.00112	0.0011	0.00108	0.00110	0.00112	0.00108	0.00067
Nickel (Ni)-Dissolved	mg/L	0.00112	0.00114	0.00075	0.00100	0.00114	0.00075	0.00033	0.00005	0.0012	0.00053	0.00120	0.00005	0.00086
Selenium (Se)-Dissolved	mg/L	0.0001	0.00013	0.0005		0.0005	0.0001	0.00005	0.00012	0.00011	0.00009	0.00012	0.00005	0.00020
Zinc (Zn)-Dissolved	mg/L		0.001	0.0026		0.0026		0.0127	0.0201	0.0038	0.01	0.02	0.004	

Table 2.14-A3. Upstream Minago River Water Quality Data

Sample ID		MRW2	MRW2	MRW2	MRW2	MRW2	MRW2X	MRW2X	MINIMUM	AVERAGE ¹	MAXIMUM
Date Sampled		16-May-07	13-Jun-07	17-Jul-07	15-Aug-07	14-Sep-07	16-Oct-07	07-May-08			
UTM (NAD 83) Easting		472484	472484	472484	472484	472476	472571	472571			
UTM (NAD 83) Northing		6001209	6001209	6001209	6001209	6001212	6001166	6001166			
Lab Sample ID		L507178-2	L518885-6	L532666-5	L544316-5	L555597-1	L569390-20	L632454-4			
	Units	Water	Water	Water	Water	Water	Water	Water			
Total Suspended Solids	mg/L	6.7	1.5	4.9	3.3	3.3	4	12.5	1.5	5.2	12.5
Dissolved Elements											
Aluminum (Al)-Dissolved	mg/L	0.0119	0.0135	0.0053	0.026	0.0037	0.0046	0.0194	0.00370	0.01206	0.02600
Antimony (Sb)-Dissolved	mg/L	0.00005	0.00005	0.00012	0.00005	0.000025	0.000025	0.000025	0.00003	0.00005	0.00012
Arsenic (As)-Dissolved	mg/L	0.00048	0.00063	0.00086	0.00072	0.000582	0.000497	0.000461	0.00046	0.00060	0.00086
Cadmium (Cd)-Dissolved	mg/L	0.000025	0.000025	0.000025	0.000025	0.0000085	0.0000085	0.0000085	0.00001	0.00002	0.00003
Chromium (Cr)-Dissolved	mg/L	0.00025	0.00025	0.00025	0.00025	0.00005	0.00035	0.0002	0.00005	0.00023	0.00035
Cobalt (Co)-Dissolved	mg/L	0.00005	0.00005	0.00005	0.00005	0.00005	0.00005	0.00005	0.00005	0.00005	0.00005
Copper (Cu)-Dissolved	mg/L	0.00043	0.00049	0.00084	0.00033	0.00118	0.00028	0.00045	0.00028	0.00057	0.00118
Iron (Fe)-Dissolved	mg/L	0.055	0.071	0.102	0.117	0.052	0.047	0.041	0.04100	0.06929	0.11700
Lead (Pb)-Dissolved	mg/L	0.000025	0.000025	0.000224	0.000052	0.000025	0.000025	0.000025	0.00003	0.00006	0.00022
Molybdenum (Mo)-Dissolved	mg/L	0.000145	0.000156	0.000111	0.000126	0.000119	0.00010	0.000132	0.00010	0.00013	0.00016
Nickel (Ni)-Dissolved	mg/L	0.00025	0.00025	0.00585	0.00025	0.00032	0.00019	0.00029	0.00019	0.00106	0.00585
Selenium (Se)-Dissolved	mg/L	0.00025	0.00025	0.00025	0.00081	0.00005	0.00005	0.00005	0.00005	0.00024	0.00081
Zinc (Zn)-Dissolved	mg/L	0.0005	0.0005	0.0026	0.0005	0.0005	0.0005	0.0019	0.00050	0.00100	0.00260

Note:

1

If the sample concentration was less than the detection limit, half the detection limit was used to compute the average.

Table 2.14-A4. Upstream Oakley Creek Water Quality Data (2006 – 2008)

Sample ID		OCW-2A	OCW-2A	OCW-2A	OCW-2A	OCW-2A	OCW-2A	OCW2	Duplicate OCW2	OCW2	OCW2	OCW2	OCW2	OCW2	OCW2	MINIMUM	AVERAGE ¹	MAXIMUM
Date Sampled		May 16, 2006	Jun. 20, 2006	Jul. 18-20, 2006	Aug 22-24, 2006	Sep. 19-21, 2006	Oct. 12, 2006	16-May-07	16-May-07	12-Jun-07	15-Jul-07	15-Aug-07	14-Sep-07	16-Oct-07	07-May-08			
UTM (NAD 83) Easting		487559	487559	487559	487559	487559	487559	487344	487344	487344	487344	487344	487463	487463	487463			
UTM (NAD 83) Northing		5990974	5990974	5990974	5990974	5990974	5990974	5990878	5990878	5990878	5990878	5990878	5990961	5990961	5990961			
Lab Sample ID								L507178-6		L518885-2	L532666-1	L544316-1	L555597-6	L569390-19	L632454-2			
	Units	Water	Water	Water	Water	Water	Water	Water		Water	Water	Water	Water	Water	Water			
Total Suspended Solids	mg/L	1.0	<1	11.0	<1	1.0	<1	<3.0		<3.0	<3.0	<3.0	<1.0	3.5	4.5		4.20	
Dissolved Elements																		
Aluminum (Al)-Dissolved	mg/L	0.001800	0.002100	0.003600	0.003500	0.001800	0.001100	0.002400	0.00220	0.002800	0.002500	0.008700	0.001700	0.001200	0.0019	0.00110	0.00266	0.00870
Antimony (Sb)-Dissolved	mg/L	0.000025	0.000025	0.000025	0.000025	0.000025	0.000025	0.000050	0.00005	0.000050	0.000050	0.000050	0.000025	0.000025	0.000025	0.00003	0.00003	0.00005
Arsenic (As)-Dissolved	mg/L	0.000300	0.000300	0.000500	0.000600	0.000500	0.000400	0.000280	0.00029	0.000340	0.000580	0.000420	0.000303	0.000191	0.000259	0.00019	0.00038	0.00060
Cadmium (Cd)-Dissolved	mg/L	0.000010	0.000005	0.000005	0.000005	0.000005	0.000005	0.000025	0.00003	0.000025	0.000025	0.000025	0.000006	0.000006	0.0000057	0.00001	0.00001	0.00003
Chromium (Cr)-Dissolved	mg/L	0.000800	0.000050	0.000100	0.000050	0.000050	0.000500	0.000250	0.00025	0.000250	0.001000	0.000250	0.000050	0.000350	0.00015	0.00005	0.00029	0.00100
Cobalt (Co)-Dissolved	mg/L	0.000010	0.000010	0.000010	0.000010	0.000010	0.000010	0.000050	0.00005	0.000050	0.000050	0.000050	0.000050	0.000050	0.00005	0.00001	0.00003	0.00005
Copper (Cu)-Dissolved	mg/L	0.000050	0.000100	0.000200	0.000050	0.000400	0.000050	0.000220	0.00018	0.000180	0.000130	0.000170	0.000250	0.000050	0.00014	0.00005	0.00016	0.00040
Iron (Fe)-Dissolved	mg/L	0.021	0.032	0.091	0.122	0.042	0.026	0.015	0.015	0.032	0.055	0.152	0.031	0.038	0.035	0.015	0.051	0.152
Lead (Pb)-Dissolved	mg/L	0.000030	0.000010	0.000020	0.000010	0.000010	0.000010	0.000025	0.00003	0.000025	0.000025	0.000025	0.000025	0.000025	0.000025	0.00001	0.00002	0.00003
Molybdenum (Mo)-Dissolved	mg/L	0.000090	0.000090	0.000110	0.000090	0.000090	0.000080	0.000102	0.00010	0.000102	0.000110	0.000096	0.000095	0.000092	0.000195	0.00008	0.00010	0.00020
Nickel (Ni)-Dissolved	mg/L	0.000250	0.000250	0.000250	0.000250	0.000250	0.000250	0.000250	0.00025	0.000250	0.000250	0.000250	0.000240	0.000100	0.00005	0.00005	0.00022	0.00025
Selenium (Se)-Dissolved	mg/L	0.000250	0.000250	0.000250	0.000250	0.000250	0.000250	0.000250	0.00025	0.000250	0.000250	0.000600	0.000050	0.000050	0.00005	0.00005	0.00023	0.00060
Zinc (Zn)-Dissolved	mg/L	0.000250	0.000250	0.000250	0.000250	0.000250	0.000250	0.001200	0.00110	0.000500	0.000500	0.001500	0.001200	0.000500	0.0005	0.00025	0.00061	0.00150

Note: 1 If the sample concentration was less than the detection limit, half the detection limit was used to compute the average.

Table 2.14-A5. Laboratory CCME Detection Limits

ELEMENT	mg/L
Aluminum (Al)-Dissolved	0.0050
Antimony (Sb)-Dissolved	0.0005
Arsenic (As)-Dissolved	0.0005
Cadmium (Cd)-Dissolved	0.000017
Chromium (Cr)-Dissolved	0.0010
Cobalt (Co)-Dissolved	0.0003
Copper (Cu)-Dissolved	0.0010
Iron (Fe)-Dissolved	0.0300
Lead (Pb)-Dissolved	0.0005
Molybdenum (Mo)-Dissolved	0.0010
Nickel (Ni)-Dissolved	0.0010
Selenium (Se)-Dissolved	0.0010
Zinc (Zn)-Dissolved	0.0050
Total Suspended Solids (TSS)	3.00

APPENDIX 2.14-B

Water Balance Model Results for Year 1 through Year 4 Operations

Projected Flows during Year 1 to Year 4 Operations

FLOW	Year 1			Year 2			Year 3			Year 4		
	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate
	NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER
	m ³ /day	m ³ /day	m ³ /day	m ³ /day	m ³ /day	m ³ /day	m ³ /day	m ³ /day	m ³ /day	m ³ /day	m ³ /day	m ³ /day
UNIT EVAPORATION	0	18	14	0	18	14	0	18	14	0	18	14
UNIT PPT (U-PPT)	0	41	21	0	41	21	0	41	21	0	41	21
Q1	31,999	31,999	31,999	31,999	31,999	31,999	31,999	31,999	31,999	31,999	31,999	31,999
Q2	5,724	5,724	5,724	5,724	5,724	5,724	5,724	5,724	5,724	5,724	5,724	5,724
Q3	26,276	26,276	26,276	26,276	26,276	26,276	26,276	26,276	26,276	26,276	26,276	26,276
Q4	1,440	1,440	1,440	1,440	1,440	1,440	1,440	1,440	1,440	1,440	1,440	1,440
Q5	96	96	96	96	96	96	96	96	96	96	96	96
Q6	4,188	4,188	4,188	4,188	4,188	4,188	4,188	4,188	4,188	4,188	4,188	4,188
Q7	0	0	0	0	0	0	0	0	0	0	0	0
Q8	96	96	96	96	96	96	96	96	96	96	96	96
Q9	0	0	0	0	0	0	0	0	0	0	0	0
Q10	10,632	10,632	10,632	10,632	10,632	10,632	10,632	10,632	10,632	10,632	10,632	10,632
Q11	6	6	6	6	6	6	6	6	6	6	6	6
Q12	5	5	5	5	5	5	5	5	5	5	5	5
Q13	72	72	72	72	72	72	72	72	72	72	72	72
Q14	12	12	12	12	12	12	12	12	12	12	12	12
Q15	1,440	1,440	1,440	1,440	1,440	1,440	1,440	1,440	1,440	1,440	1,440	1,440
Q16	72	72	72	72	72	72	72	72	72	72	72	72
Q17	24	24	24	24	24	24	24	24	24	24	24	24
Q19	1,080	1,080	1,080	1,080	1,080	1,080	1,080	1,080	1,080	1,080	1,080	1,080
Q20	32,928	32,928	32,928	32,928	32,928	32,928	32,928	32,928	32,928	32,928	32,928	32,928
Q21	20,856	20,856	20,856	20,856	20,856	20,856	20,856	20,856	20,856	20,856	20,856	20,856
Q21x	0	0	0	0	0	0	0	0	0	0	0	0
Q22	12,072	12,072	12,072	12,072	12,072	12,072	12,072	12,072	12,072	12,072	12,072	12,072
Q23	0	676	103	0	676	103	0	676	103	0	676	103
Q24	2,892	2,892	2,892	2,892	2,892	2,892	2,892	2,892	2,892	2,892	2,892	2,892
Q25	772	772	772	772	772	772	772	772	772	772	772	772
Q26	15,736	16,412	15,839	15,736	16,412	15,839	15,736	16,412	15,839	15,736	16,412	15,839
Q - Liquid PPT on TWRMF	0	24,186	12,711	0	24,186	12,711	0	24,186	12,711	0	24,186	12,711
Q - Retained Water in Tailings Voids	724	1,467	847	1,467	1,467	1,467	1,467	1,467	1,467	1,467	1,467	1,467
Q - TWRMF Supernatant	14,422	111,531	37,996	30,237	123,790	37,406	30,328	123,881	37,496	30,408	123,961	37,576
Q27	0	15,563	18,678	13,710	27,823	18,088	13,800	27,913	18,178	13,880	27,993	18,258
Q - Pit Dewatering	8,000	8,000	8,000	8,000	8,000	8,000	8,000	8,000	8,000	8,000	8,000	8,000
Q - Precipitation on Pit	0	7,723	4,059	0	7,723	4,059	0	7,723	4,059	0	7,723	4,059
Q28	8,000	15,723	12,059	8,000	15,723	12,059	8,000	15,723	12,059	8,000	15,723	12,059
Q29	34,276	105,612	57,012	47,985	145,733	56,423	48,075	146,007	56,513	48,156	146,250	56,593
Q - Precipitation on Polishing Pond	0	4,878	2,564	0	4,878	2,564	0	4,878	2,564	0	4,878	2,564
Q - Evaporation from Polishing Pond	0	2,168	1,701	0	2,168	1,701	0	2,168	1,701	0	2,168	1,701
Q30	34,276	108,322	57,874	47,985	148,443	57,285	48,075	148,717	57,375	48,156	148,960	57,455
Q31	10,632	10,632	10,632	10,632	10,632	10,632	10,632	10,632	10,632	10,632	10,632	10,632
Q32	15,368	97,690	47,242	24,280	137,811	46,653	24,338	138,085	46,743	24,390	138,328	46,823
Q32	15,368	97,690	47,242	24,280	137,811	46,653	24,338	138,085	46,743	24,390	138,328	46,823
Q33	69,120	864,000	164,160	69,120	864,000	164,160	69,120	864,000	164,160	69,120	864,000	164,160
Q34	84,488	961,690	211,402	93,400	1,001,811	210,813	93,458	1,002,085	210,903	93,510	1,002,328	210,983

FLOW RATIOS:

Q32 / Q33	RATIO OF DISCHARGE TO MINAGO TO FLOW IN MINAGO	22%	11%	29%	35%	16%	28%	35%	16%	28%	35%	16%	29%
-----------	--	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----

Projected Concentrations in Flows during Year 1 to Year 4 Operations

SCENARIO: FLOW	WATER QUALITY PARAM.	ESTIMATED AVERAGE CONCENTRATION												REGULATIONS							
		Year 1			Year 2			Year 3			Year 4			Metal Mining Liquid Effluent Regulations (2002, last amended in 2012)		Manitoba Water Quality Standards, Objectives, and Guidelines (Manitoba Water Stewardship, 2011)		Canadian Water Quality Guidelines for the Protection of Aquatic Life (CCME, 2011)			
		Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate								
		NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	Monthly Mean	Grab Sample	TIER II Water Quality Objectives assuming hardness = 150 mg/L CaCO ₃	Freshwater	assuming hardness = 65 mg/L CaCO ₃	assuming hardness = 150 mg/L CaCO ₃		
(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)									
Q26	TWRMF INFLOW	Al	0.515	0.494	0.512	0.515	0.494	0.512	0.515	0.494	0.512	0.515	0.494	0.512							
Q26	TWRMF INFLOW	Sb	0.0042	0.0040	0.0041	0.0042	0.0040	0.0041	0.0042	0.0040	0.0041	0.0042	0.0040	0.0041							
Q26	TWRMF INFLOW	As	0.0032	0.0031	0.0032	0.0032	0.0031	0.0032	0.0032	0.0031	0.0032	0.0032	0.0031	0.0032	0.5	1	0.15 mg/L (4-Day, 3-Year) ^A	Tier II	0.005	0.005	
Q26	TWRMF INFLOW	Cd	0.00078	0.00075	0.00078	0.00078	0.00075	0.00078	0.00078	0.00075	0.00078	0.00078	0.00075	0.00078			0.00033 ^B	Tier II	0.000023 ^a	0.000047 ^a	
Q26	TWRMF INFLOW	Cr	0.0139	0.0133	0.0138	0.0139	0.0133	0.0138	0.0139	0.0133	0.0138	0.0139	0.0133	0.0138			0.10331 ^C	Tier II	0.0089	0.0089	
Q26	TWRMF INFLOW	Co	0.0110	0.0106	0.0109	0.0110	0.0106	0.0109	0.0110	0.0106	0.0109	0.0110	0.0106	0.0109							
Q26	TWRMF INFLOW	Cu	0.0367	0.0353	0.0365	0.0367	0.0353	0.0365	0.0367	0.0353	0.0365	0.0367	0.0353	0.0365	0.3	0.6	0.01266 ^D	Tier II	0.002 ^b	0.00334 ^b	
Q26	TWRMF INFLOW	Fe	2.42	2.32	2.40	2.42	2.32	2.40	2.42	2.32	2.40	2.42	2.32	2.40					0.3	0.3	0.3
Q26	TWRMF INFLOW	Pb	0.00614	0.00591	0.00611	0.00614	0.00591	0.00611	0.00614	0.00591	0.00611	0.00614	0.00591	0.00611	0.2	0.4	0.0039 ^E	Tier II	0.00184 ^c	0.00533 ^c	
Q26	TWRMF INFLOW	Mo	0.0121	0.0116	0.0120	0.0121	0.0116	0.0120	0.0121	0.0116	0.0120	0.0121	0.0116	0.0120					0.073		
Q26	TWRMF INFLOW	Ni	0.550	0.528	0.547	0.550	0.528	0.547	0.550	0.528	0.547	0.550	0.528	0.547	0.5	1	0.07329 ^F	Tier II	0.06889 ^d	0.13007 ^d	
Q26	TWRMF INFLOW	Se	0.0078	0.0075	0.0077	0.0078	0.0075	0.0077	0.0078	0.0075	0.0077	0.0078	0.0075	0.0077					0.001	0.001	0.001
Q26	TWRMF INFLOW	Zn	0.0330	0.0318	0.0328	0.0330	0.0318	0.0328	0.0330	0.0318	0.0328	0.0330	0.0318	0.0328	0.5	1	0.16657 ^G	Tier II	0.03	0.03	0.03
Q27	TWRMF Decant	Al	0.564	0.497	0.468	0.527	0.476	0.467	0.527	0.476	0.468	0.529	0.478	0.469					0.005 - 0.1	0.005 - 0.1	0.005 - 0.1
Q27	TWRMF Decant	Sb	0.005	0.004	0.004	0.004	0.004	0.004	0.004	0.004	0.004	0.004	0.004	0.004							
Q27	TWRMF Decant	As	0.004	0.003	0.003	0.004	0.003	0.003	0.004	0.003	0.004	0.004	0.004	0.004	0.5	1	0.15 mg/L (4-Day, 3-Year) ^A	Tier II	0.005	0.005	
Q27	TWRMF Decant	Cd	0.00086	0.00076	0.00072	0.00082	0.00074	0.00073	0.00083	0.00076	0.00075	0.00085	0.00077	0.00077			0.00033 ^B	Tier II	0.000023 ^a	0.000047 ^a	
Q27	TWRMF Decant	Cr	0.015	0.014	0.013	0.014	0.013	0.013	0.014	0.013	0.013	0.014	0.013	0.013			0.10331 ^C	Tier II	0.0089	0.0089	
Q27	TWRMF Decant	Co	0.012	0.011	0.010	0.011	0.010	0.010	0.011	0.010	0.010	0.011	0.010	0.010							
Q27	TWRMF Decant	Cu	0.040	0.036	0.034	0.038	0.034	0.034	0.038	0.034	0.034	0.039	0.035	0.035	0.3	0.6	0.01266 ^D	Tier II	0.002 ^b	0.00334 ^b	
Q27	TWRMF Decant	Fe	2.64	2.33	2.20	2.46	2.22	2.18	2.44	2.21	2.16	2.43	2.20	2.15					0.3	0.3	0.3
Q27	TWRMF Decant	Pb	0.007	0.006	0.006	0.007	0.006	0.006	0.0072	0.0066	0.0067	0.008	0.007	0.007	0.2	0.4	0.0039 ^E	Tier II	0.00184 ^c	0.00533 ^c	
Q27	TWRMF Decant	Mo	0.013	0.012	0.011	0.013	0.012	0.012	0.013	0.012	0.012	0.014	0.013	0.013					0.073		
Q27	TWRMF Decant	Ni	0.601	0.529	0.498	0.560	0.505	0.494	0.558	0.503	0.493	0.557	0.503	0.493	0.5	1	0.07329 ^F	Tier II	0.06889 ^d	0.13007 ^d	
Q27	TWRMF Decant	Se	0.008	0.008	0.007	0.008	0.008	0.008	0.008	0.008	0.008	0.008	0.008	0.008					0.001	0.001	0.001
Q27	TWRMF Decant	Zn	0.037	0.033	0.033	0.037	0.034	0.034	0.039	0.036	0.036	0.041	0.038	0.038	0.5	1	0.16657 ^G	Tier II	0.03	0.03	0.03

Projected Concentrations in Flows during Year 1 to Year 4 Operations

2.14-10

SCENARIO:	FLOW	WATER QUALITY PARAM.	ESTIMATED AVERAGE CONCENTRATION												REGULATIONS						
			Year 1			Year 2			Year 3			Year 4			Metal Mining Liquid Effluent Regulations (2002, last amended in 2012)		Manitoba Water Quality Standards, Objectives, and Guidelines (Manitoba Water Stewardship, 2011)		Canadian Water Quality Guidelines for the Protection of Aquatic Life (CCME, 2011)		
			Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate							
			NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	Monthly Mean	Grab Sample	TIER II Water Quality Objectives assuming hardness = 150 mg/L CaCO ₃	Freshwater	assuming hardness = 65 mg/L CaCO ₃	assuming hardness = 150 mg/L CaCO ₃	
(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)									
Q29	POLISHING POND INFLOW	Al	0.009	0.080	0.159	0.157	0.175	0.155	0.158	0.175	0.156	0.159	0.176	0.157				0.005 - 0.1	0.005 - 0.1	0.005 - 0.1	
Q29	POLISHING POND INFLOW	Sb	0.00003	0.00066	0.00136	0.00127	0.00146	0.00134	0.00128	0.00147	0.00135	0.00129	0.00148	0.00136							
Q29	POLISHING POND INFLOW	As	0.001	0.001	0.002	0.002	0.002	0.002	0.002	0.002	0.002	0.002	0.002	0.002	0.5	1	0.15 mg/L (4-Day, 3-Year) ^A	Tier II	0.005	0.005	
Q29	POLISHING POND INFLOW	Cd	0.000006	0.000118	0.000241	0.000238	0.000267	0.000239	0.000243	0.000274	0.000245	0.000250	0.000281	0.000252			0.00033 ^B	Tier II	0.000023 ^a	0.000047 ^a	
Q29	POLISHING POND INFLOW	Cr	0.001	0.003	0.005	0.005	0.005	0.005	0.005	0.005	0.005	0.005	0.005	0.005			0.10331 ^C	Tier II	0.0089	0.0089	
Q29	POLISHING POND INFLOW	Co	0.00008	0.00166	0.00337	0.00328	0.00369	0.00328	0.00328	0.00369	0.00329	0.00329	0.00329	0.00329							
Q29	POLISHING POND INFLOW	Cu	0.00052	0.00573	0.01145	0.01124	0.01261	0.01128	0.0114	0.0128	0.0115	0.01159	0.01297	0.01163	0.3	0.6	0.01266 ^D	Tier II	0.002 ^b	0.00334 ^b	
Q29	POLISHING POND INFLOW	Fe	0.005	0.349	0.724	0.706	0.795	0.703	0.705	0.792	0.701	0.704	0.790	0.700				0.3	0.3	0.3	
Q29	POLISHING POND INFLOW	Pb	0.00003	0.00096	0.00198	0.00195	0.00223	0.00205	0.00209	0.00239	0.00219	0.00223	0.00255	0.00234	0.2	0.4	0.0039 ^E	Tier II	0.00184 ^c	0.00533 ^c	
Q29	POLISHING POND INFLOW	Mo	0.001	0.002	0.004	0.004	0.005	0.004	0.004	0.005	0.004	0.005	0.005	0.005				0.073			
Q29	POLISHING POND INFLOW	Ni	0.001	0.079	0.164	0.161	0.180	0.159	0.161	0.180	0.159	0.161	0.181	0.160	0.5	1	0.07329 ^F	Tier II	0.06889 ^d	0.13007 ^d	
Q29	POLISHING POND INFLOW	Se	0.0002	0.0014	0.0026	0.0025	0.0028	0.0026	0.0025	0.0029	0.0026	0.0025	0.0029	0.0026				0.001	0.001	0.001	
Q29	POLISHING POND INFLOW	Zn	0.005	0.009	0.014	0.014	0.015	0.014	0.014	0.016	0.015	0.015	0.016	0.016	0.5	1	0.16657 ^G	Tier II	0.03	0.03	

Notes:

August 2008 groundwater chemistry was assumed in the modeling.

- A Arsenic limits: 0.15 mg/L for averaging duration 4 days (4-Day, 3-Year or 7Q10 Design Flow); 0.34 mg/L for averaging duration 1 hr (1-Day, 3-Year or 1Q10 Design Flow)
- B Cadmium limits: $[e^{(0.7409[\ln(\text{Hardness})]-4.719)} \times [1.101672 - (\ln(\text{Hardness})(0.041838))]]$ for 4 days averaging duration.
 $[e^{(1.0166[\ln(\text{Hardness})]-3.924)} \times [1.136672 - (\ln(\text{Hardness})(0.041838))]]$ for 1 hour averaging duration.
- C Chromium limits: Chromium III: $[e^{(0.8190[\ln(\text{Hardness})]+0.6848)} \times [0.860]]$ for 4 days averaging duration.
Chromium III: $[e^{(0.8190[\ln(\text{Hardness})]+3.7256)} \times [0.316]]$ for 1 hour averaging duration.
Chromium VI: 0.011 mg/L for averaging duration 4 days (4-Day, 3-Year or 7Q10 Design Flow); 0.016 mg/L for averaging duration 1 hr (1-Day, 3-Year or 1Q10 Design Flow)
- D Copper limits: $[e^{(0.8545[\ln(\text{Hardness})]-1.702)} \times [0.960]]$ for 4 Days hour averaging duration.
 $[e^{(0.9422[\ln(\text{Hardness})]-1.700)} \times [0.960]]$ for 1 hour averaging duration.
- E Lead limits: $[e^{(1.273[\ln(\text{Hardness})]-4.705)} \times [1.46203 - (\ln(\text{Hardness})(0.145712))]]$ for 4 Days averaging duration.
 $[e^{(1.273[\ln(\text{Hardness})]-1.460)} \times [1.46203 - (\ln(\text{Hardness})(0.145712))]]$ for 1 hour averaging duration.
- F Nickel limits: $[e^{(0.8460[\ln(\text{Hardness})]+0.0584)} \times [0.997]]$ for 4 Days averaging duration.
 $[e^{(0.8460[\ln(\text{Hardness})]+2.255)} \times [0.998]]$ for 1 hour averaging duration.
- G Zinc limits: $[e^{(0.8473[\ln(\text{Hardness})]+0.884)} \times [0.986]]$ for 4 Days averaging duration.
 $[e^{(0.8473[\ln(\text{Hardness})]+0.884)} \times [0.978]]$ for 1 hour averaging duration.

Canadian water quality guidelines for the protection of aquatic life (CCME, 2011)

- a Cadmium limit: Cadmium concentration = $10^{0.86[\log_{10}(\text{hardness})]-3.2}$ µg/L
- b Copper limit: Copper concentration = $e^{0.8545[\ln(\text{hardness})]-1.465} \times 0.2$ µg/L
- c Lead limit: Lead concentration = $e^{1.273[\ln(\text{hardness})]-4.705}$ µg/L
- d Nickel limit: Nickel concentration = $e^{0.76[\ln(\text{hardness})]+1.06}$ µg/L

APPENDIX 2.14-C

Water Balance Model Results for Year 5 through Year 8 Operations

Projected Flows during Year 5 to Year 8 Operations

2.14-12

Q32 / Q33	RATIO OF DISCHARGE TO MINAGU TO FLOW IN MINAGU	35%	16%	29%	35%	16%	28%	35%	16%	29%	36%	16%	29%
-----------	--	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----

Projected Concentrations in Flows during Year 5 to Year 8 Operations

SCENARIO:	WATER QUALITY	ESTIMATED AVERAGE CONCENTRATION												REGULATIONS					
		Year 5			Year 6			Year 7			Year 8			Metal Mining Liquid Effluent Regulations (2002, last amended in 2012)		Manitoba Water Quality Standards, Objectives, and Guidelines (Manitoba Water Stewardship, 2011)		Canadian Water Quality Guidelines for the Protection of Aquatic Life (CCME, 2011)	
		Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate						
		NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	Monthly Mean	Grab Sample	TIER II Water Quality Objectives assuming hardness = 150 mg/L CaCO ₃	Freshwater	assuming hardness = 65 mg/L CaCO ₃	assuming hardness = 150 mg/L CaCO ₃
PARAM.	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)					
Q26 TWRMF INFLOW	Al	0.515	0.494	0.512	0.515	0.494	0.512	0.515	0.494	0.512	0.515	0.494	0.512						
Q26 TWRMF INFLOW	Sb	0.0042	0.0040	0.0041	0.0042	0.0040	0.0041	0.0042	0.0040	0.0041	0.0042	0.0040	0.0041						
Q26 TWRMF INFLOW	As	0.0032	0.0031	0.0032	0.0032	0.0031	0.0032	0.0032	0.0031	0.0032	0.0032	0.0031	0.0032	0.5	1	0.15 mg/L (4-Day, 3-Year) ^A	Tier II	0.005	0.005
Q26 TWRMF INFLOW	Cd	0.00078	0.00075	0.00078	0.00078	0.00075	0.00078	0.00078	0.00075	0.00078	0.00078	0.00075	0.00078			0.00033 ^B	Tier II	0.000023 ^a	0.000047 ^a
Q26 TWRMF INFLOW	Cr	0.0139	0.0133	0.0138	0.0139	0.0133	0.0138	0.0139	0.0133	0.0138	0.0139	0.0133	0.0138			0.10331 ^C	Tier II	0.0089	0.0089
Q26 TWRMF INFLOW	Co	0.0110	0.0106	0.0109	0.0110	0.0106	0.0109	0.0110	0.0106	0.0109	0.0110	0.0106	0.0109						
Q26 TWRMF INFLOW	Cu	0.0367	0.0353	0.0365	0.0367	0.0353	0.0365	0.0367	0.0353	0.0365	0.0367	0.0353	0.0365	0.3	0.6	0.01266 ^D	Tier II	0.002 ^b	0.00334 ^b
Q26 TWRMF INFLOW	Fe	2.42	2.32	2.40	2.42	2.32	2.40	2.42	2.32	2.40	2.42	2.32	2.40					0.3	0.3
Q26 TWRMF INFLOW	Pb	0.00614	0.00591	0.00611	0.00614	0.00591	0.00611	0.00614	0.00591	0.00611	0.00614	0.00591	0.00611	0.2	0.4	0.0039 ^E	Tier II	0.00184 ^c	0.00533 ^c
Q26 TWRMF INFLOW	Mo	0.0121	0.0116	0.0120	0.0121	0.0116	0.0120	0.0121	0.0116	0.0120	0.0121	0.0116	0.0120					0.073	
Q26 TWRMF INFLOW	Ni	0.550	0.528	0.547	0.550	0.528	0.547	0.550	0.528	0.547	0.550	0.528	0.547	0.5	1	0.07329 ^F	Tier II	0.06889 ^d	0.13007 ^d
Q26 TWRMF INFLOW	Se	0.0078	0.0075	0.0077	0.0078	0.0075	0.0077	0.0078	0.0075	0.0077	0.0078	0.0075	0.0077					0.001	0.001
Q26 TWRMF INFLOW	Zn	0.0330	0.0318	0.0328	0.0330	0.0318	0.0328	0.0330	0.0318	0.0328	0.0330	0.0318	0.0328	0.5	1	0.16657 ^G	Tier II	0.03	0.03
Q27 TWRMF Decant	Al	0.532	0.481	0.473	0.538	0.487	0.479	0.543	0.490	0.482	0.540	0.488	0.478					0.005 - 0.1	0.005 - 0.1
Q27 TWRMF Decant	Sb	0.004	0.004	0.004	0.004	0.004	0.004	0.005	0.004	0.004	0.005	0.004	0.004						
Q27 TWRMF Decant	As	0.004	0.004	0.004	0.004	0.004	0.004	0.005	0.004	0.004	0.005	0.004	0.004	0.5	1	0.15 mg/L (4-Day, 3-Year) ^A	Tier II	0.005	0.005
Q27 TWRMF Decant	Cd	0.00088	0.00079	0.00079	0.00090	0.00082	0.00081	0.00093	0.00084	0.00083	0.00094	0.00085	0.00084			0.00033 ^B	Tier II	0.000023 ^a	0.000047 ^a
Q27 TWRMF Decant	Cr	0.014	0.013	0.013	0.014	0.013	0.013	0.015	0.013	0.013	0.014	0.013	0.013			0.10331 ^C	Tier II	0.0089	0.0089
Q27 TWRMF Decant	Co	0.011	0.010	0.010	0.011	0.010	0.010	0.011	0.010	0.010	0.011	0.010	0.010						
Q27 TWRMF Decant	Cu	0.040	0.036	0.035	0.040	0.037	0.036	0.041	0.037	0.037	0.041	0.037	0.037	0.3	0.6	0.01266 ^D	Tier II	0.002 ^b	0.00334 ^b
Q27 TWRMF Decant	Fe	2.43	2.19	2.15	2.44	2.20	2.17	2.44	2.20	2.16	2.41	2.17	2.13					0.3	0.3
Q27 TWRMF Decant	Pb	0.008	0.008	0.008	0.009	0.008	0.008	0.0093	0.0085	0.0085	0.010	0.009	0.009	0.2	0.4	0.0039 ^E	Tier II	0.00184 ^c	0.00533 ^c
Q27 TWRMF Decant	Mo	0.015	0.013	0.013	0.015	0.014	0.014	0.016	0.015	0.015	0.016	0.015	0.015					0.073	
Q27 TWRMF Decant	Ni	0.559	0.504	0.495	0.563	0.508	0.499	0.566	0.510	0.501	0.561	0.505	0.495	0.5	1	0.07329 ^F	Tier II	0.06889 ^d	0.13007 ^d
Q27 TWRMF Decant	Se	0.008	0.008	0.008	0.008	0.008	0.008	0.008	0.008	0.008	0.008	0.008	0.008					0.001	0.001
Q27 TWRMF Decant	Zn	0.043	0.040	0.041	0.046	0.042	0.043	0.048	0.045	0.045	0.050	0.046	0.046	0.5	1	0.16657 ^G	Tier II	0.03	0.03

Projected Concentrations in Flows during Year 5 to Year 8 Operations

2.14-14

0 Nickel limit. Nickel concentration = 0.0001 mg/L

APPENDIX 2.14-D

Water Balance Model Results for Year 9 and Year 10 Operations

Projected Concentrations in Flows during Year 9 and Year 10 Operations

SCENARIO:	WATER QUALITY	ESTIMATED AVERAGE CONCENTRATION				REGULATIONS							
		Year 9			Year 10	Metal Mining Liquid Effluent Regulations (2002, last amended in 2012)		Manitoba Water Quality Standards, Objectives, and Guidelines (Manitoba Water Stewardship, 2011)		Canadian Water Quality Guidelines for the Protection of Aquatic Life (CCME, 2011)			
		Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate								
		NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	NOVEMBER TO APRIL	Monthly Mean	Grab Sample	TIER II Water Quality Objectives assuming hardness = 150 mg/L CaCO ₃	Freshwater	assuming hardness = 65 mg/L CaCO ₃	assuming hardness = 150 mg/L CaCO ₃		
PARAM.	(mg/L)	(mg/L)	(mg/L)	(mg/L)									
Q26	TWRMF INFLOW	Al	0.515	0.494	0.512	0.515					0.005 - 0.1	0.005 - 0.1	0.005 - 0.1
Q26	TWRMF INFLOW	Sb	0.0042	0.0040	0.0041	0.0042							
Q26	TWRMF INFLOW	As	0.0032	0.0031	0.0032	0.0032	0.5	1	0.15 mg/L (4-Day, 3-Year) ^A	Tier II	0.005		0.005
Q26	TWRMF INFLOW	Cd	0.00078	0.00075	0.00078	0.00078			0.00033 ^B	Tier II	0.000023 ^a		0.000047 ^a
Q26	TWRMF INFLOW	Cr	0.0139	0.0133	0.0138	0.0139			0.10331 ^C	Tier II	0.0089		0.0089
Q26	TWRMF INFLOW	Co	0.0110	0.0106	0.0109	0.0110							
Q26	TWRMF INFLOW	Cu	0.0367	0.0353	0.0365	0.0367	0.3	0.6	0.01266 ^D	Tier II	0.002 ^b		0.00334 ^b
Q26	TWRMF INFLOW	Fe	2.42	2.32	2.40	2.42					0.3		0.3
Q26	TWRMF INFLOW	Pb	0.00614	0.00591	0.00611	0.00614	0.2	0.4	0.0039 ^E	Tier II	0.00184 ^c		0.00533 ^c
Q26	TWRMF INFLOW	Mo	0.0121	0.0116	0.0120	0.0121					0.073		
Q26	TWRMF INFLOW	Ni	0.550	0.528	0.547	0.550	0.5	1	0.07329 ^F	Tier II	0.06889 ^d		0.13007 ^d
Q26	TWRMF INFLOW	Se	0.0078	0.0075	0.0077	0.0078					0.001		0.001
Q26	TWRMF INFLOW	Zn	0.0330	0.0318	0.0328	0.0330	0.5	1	0.16657 ^G	Tier II	0.03		0.03
Q27	TWRMF Decant	Al	0.540	0.487	0.479	0.533					0.005 - 0.1	0.005 - 0.1	0.005 - 0.1
Q27	TWRMF Decant	Sb	0.005	0.004	0.004	0.004							
Q27	TWRMF Decant	As	0.005	0.004	0.005	0.005	0.5	1	0.15 mg/L (4-Day, 3-Year) ^A	Tier II	0.005		0.005
Q27	TWRMF Decant	Cd	0.00096	0.00087	0.00086	0.00095			0.00033 ^B	Tier II	0.000023 ^a		0.000047 ^a
Q27	TWRMF Decant	Cr	0.014	0.013	0.013	0.014			0.10331 ^C	Tier II	0.0089		0.0089
Q27	TWRMF Decant	Co	0.011	0.010	0.010	0.01097							
Q27	TWRMF Decant	Cu	0.042	0.038	0.037	0.04131	0.3	0.6	0.01266 ^D	Tier II	0.002 ^b		0.00334 ^b
Q27	TWRMF Decant	Fe	2.39	2.15	2.12	2.34					0.3		0.3
Q27	TWRMF Decant	Pb	0.010	0.009	0.009	0.010	0.2	0.4	0.0039 ^E	Tier II	0.00184 ^c		0.00533 ^c
Q27	TWRMF Decant	Mo	0.017	0.015	0.015	0.017					0.073		
Q27	TWRMF Decant	Ni	0.558	0.503	0.494	0.550	0.5	1	0.07329 ^F	Tier II	0.06889 ^d		0.13007 ^d
Q27	TWRMF Decant	Se	0.008	0.008	0.008	0.008					0.001		0.001
Q27	TWRMF Decant	Zn	0.052	0.048	0.048	0.053	0.5	1	0.16657 ^G	Tier II	0.03		0.03

Projected Concentrations in Flows during Year 9 and Year 10 Operations

SCENARIO:	FLOW	WATER QUALITY PARAM.	ESTIMATED AVERAGE CONCENTRATION				REGULATIONS					
			Year 9		Year 10		Metal Mining Liquid Effluent Regulations (2002, last amended in 2012)		Manitoba Water Quality Standards, Objectives, and Guidelines (Manitoba Water Stewardship, 2011)		Canadian Water Quality Guidelines for the Protection of Aquatic Life (CCME, 2011)	
			Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate						
			NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	NOVEMBER TO APRIL	Monthly Mean	Grab Sample	TIER II Water Quality Objectives assuming hardness = 150 mg/L CaCO ₃	Freshwater	assuming hardness = 65 mg/L CaCO ₃	assuming hardness = 150 mg/L CaCO ₃
Q29	LISHING POND INFL	Al	0.165	0.182	0.162	0.166				0.005 - 0.1	0.005 - 0.1	0.005 - 0.1
Q29	LISHING POND INFL	Sb	0.00134	0.00153	0.00140	0.00135						
Q29	LISHING POND INFL	As	0.002	0.002	0.002	0.002	0.5	1	0.15 mg/L (4-Day, 3-Year) ^A	Tier II	0.005	0.005
Q29	LISHING POND INFL	Cd	0.000285	0.000318	0.000285	0.000291			0.00033 ^B	Tier II	0.000023 ^a	0.000047 ^a
Q29	LISHING POND INFL	Cr	0.005	0.005	0.005	0.005			0.10331 ^C	Tier II	0.0089	0.0089
Q29	LISHING POND INFL	Co	0.00333	0.00372	0.00332	0.00336						
Q29	LISHING POND INFL	Cu	0.01259	0.01401	0.01256	0.01278	0.3	0.6	0.01266 ^D	Tier II	0.002 ^b	0.00334 ^b
Q29	LISHING POND INFL	Fe	0.705	0.786	0.697	0.708				0.3	0.3	0.3
Q29	LISHING POND INFL	Pb	0.00298	0.00336	0.00306	0.00310	0.2	0.4	0.0039 ^E	Tier II	0.00184 ^c	0.00533 ^c
Q29	LISHING POND INFL	Mo	0.005	0.006	0.005	0.006				0.073		
Q29	LISHING POND INFL	Ni	0.165	0.183	0.162	0.166	0.5	1	0.07329 ^F	Tier II	0.06889 ^d	0.13007 ^d
Q29	LISHING POND INFL	Se	0.0026	0.0030	0.0027	0.0026				0.001	0.001	0.001
Q29	LISHING POND INFL	Zn	0.019	0.020	0.019	0.019	0.5	1	0.16657 ^G	Tier II	0.03	0.03

Notes:

August 2008 groundwater chemistry was assumed in the modeling.

- A Arsenic limits: 0.15 mg/L for averaging duration 4 days (4-Day, 3-Year or 7Q10 Design Flow); 0.34 mg/L for averaging duration 1 hr (1-Day, 3-Year or 1Q10 Design Flow)
- B Cadmium limits: $[e^{(0.7409 \ln(\text{Hardness}) - 4.719)} \times [1.101672 - (\ln(\text{Hardness})(0.041838))]]$ for 4 days averaging duration.
 $[e^{(1.0166 \ln(\text{Hardness}) - 3.924)} \times [1.136672 - (\ln(\text{Hardness})(0.041838))]]$ for 1 hour averaging duration.
- C Chromium limits: Chromium III: $[e^{(0.8190 \ln(\text{Hardness}) + 0.6848)} \times [0.860]]$ for 4 days averaging duration.
Chromium III: $[e^{(0.8190 \ln(\text{Hardness}) + 3.7256)} \times [0.316]]$ for 1 hour averaging duration.
Chromium VI: 0.011 mg/L for averaging duration 4 days (4-Day, 3-Year or 7Q10 Design Flow); 0.016 mg/L for averaging duration 1 hr (1-Day, 3-Year or 1Q10 Design Flow)
- D Copper limits: $[e^{(0.8545 \ln(\text{Hardness}) - 1.702)} \times [0.960]]$ for 4 Days hour averaging duration.
 $[e^{(0.9422 \ln(\text{Hardness}) - 1.700)} \times [0.960]]$ for 1 hour averaging duration.
- E Lead limits: $[e^{(1.273 \ln(\text{Hardness}) - 4.705)} \times [1.46203 - (\ln(\text{Hardness})(0.145712))]]$ for 4 Days averaging duration.
 $[e^{(1.273 \ln(\text{Hardness}) - 1.460)} \times [1.46203 - (\ln(\text{Hardness})(0.145712))]]$ for 1 hour averaging duration.
- F Nickel limits: $[e^{(0.8460 \ln(\text{Hardness}) + 0.0584)} \times [0.997]]$ for 4 Days averaging duration.
 $[e^{(0.8460 \ln(\text{Hardness}) + 2.255)} \times [0.998]]$ for 1 hour averaging duration.
- G Zinc limits: $[e^{(0.8473 \ln(\text{Hardness}) + 0.884)} \times [0.986]]$ for 4 Days averaging duration.
 $[e^{(0.8473 \ln(\text{Hardness}) + 0.884)} \times [0.978]]$ for 1 hour averaging duration.

Canadian water quality guidelines for the protection of aquatic life (CCME, 2011)

- a Cadmium limit: Cadmium concentration = $10^{(0.86 \log_{10}(\text{hardness}) - 3.2)}$ µg/L
- b Copper limit: Copper concentration = $e^{(0.8545 \ln(\text{hardness}) - 1.465)}$ * 0.2 µg/L
- c Lead limit: Lead concentration = $e^{(1.273 \ln(\text{hardness}) - 4.705)}$ µg/L
- d Nickel limit: Nickel concentration = $e^{(0.76 \ln(\text{hardness}) + 1.06)}$ µg/L

APPENDIX 2.14-E

Water Balance Model Results for the Closure and Post Closure Periods

Projected Concentrations in Flows during the Closure Periods

SCENARIO: FLOW	WATER QUALITY PARAM.	ESTIMATED AVERAGE CONCENTRATION					REGULATIONS						
		Closure (Stage 1)		Closure (Stage 2)			Metal Mining Liquid Effluent Regulations (2002, last amended in 2012)		Manitoba Water Quality Standards, Objectives, and Guidelines (Manitoba Water Stewardship, 2011)		Canadian Water Quality Guidelines for the Protection of Aquatic Life (CCME, 2011)		
		Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate							
		MAY (mg/L)	JUNE TO OCTOBER (mg/L)	NOVEMBER TO APRIL (mg/L)	MAY (mg/L)	JUNE TO OCTOBER (mg/L)	Monthly Mean	Grab Sample	TIER II Water Quality Objectives assuming hardness = 150 mg/L CaCO ₃	Freshwater	assuming hardness = 65 mg/L CaCO ₃	assuming hardness = 150 mg/L CaCO ₃	
Q26	TWRMF INFLOW	Al	0.009	0.009	0.000	0.006	0.008				0.005 - 0.1	0.005 - 0.1	0.005 - 0.1
Q26	TWRMF INFLOW	Sb	0.0000	0.0000	0.0000	0.0006	0.0008						
Q26	TWRMF INFLOW	As	0.0008	0.0008	0.0000	0.0006	0.0008	0.5	1	0.15 mg/L (4-Day, 3-Year) ^A	Tier II	0.005	0.005
Q26	TWRMF INFLOW	Cd	0.00001	0.00001	0.00000	0.00002	0.00003			0.00033 ^B	Tier II	0.000023 ^a	0.000047 ^a
Q26	TWRMF INFLOW	Cr	0.0010	0.0010	0.0000	0.0011	0.0016			0.10331 ^C	Tier II	0.0089	0.0089
Q26	TWRMF INFLOW	Co	0.0001	0.0001	0.0000	0.0003	0.0005						
Q26	TWRMF INFLOW	Cu	0.0005	0.0005	0.0000	0.0011	0.0016	0.3	0.6	0.01266 ^D	Tier II	0.002 ^b	0.00334 ^b
Q26	TWRMF INFLOW	Fe	0.01	0.01	0.00	0.03	0.05				0.3	0.3	0.3
Q26	TWRMF INFLOW	Pb	0.00004	0.00003	0.00000	0.00057	0.00082	0.2	0.4	0.0039 ^E	Tier II	0.00184 ^c	0.00533 ^c
Q26	TWRMF INFLOW	Mo	0.0007	0.0007	0.0000	0.0011	0.0016				0.073		
Q26	TWRMF INFLOW	Ni	0.001	0.001	0.000	0.001	0.002	0.5	1	0.07329 ^F	Tier II	0.06889 ^d	0.13007 ^d
Q26	TWRMF INFLOW	Se	0.0002	0.0002	0.0000	0.0011	0.0016				0.001	0.001	0.001
Q26	TWRMF INFLOW	Zn	0.0046	0.0046	0.0000	0.0057	0.0082	0.5	1	0.16657 ^G	Tier II	0.03	0.03
Q27	TWRMF Decant	Al	0.368	0.197	0.210	0.203	0.200				0.005 - 0.1	0.005 - 0.1	0.005 - 0.1
Q27	TWRMF Decant	Sb	0.003	0.002	0.002	0.002	0.002						
Q27	TWRMF Decant	As	0.004	0.003	0.003	0.003	0.004	0.5	1	0.15 mg/L (4-Day, 3-Year) ^A	Tier II	0.005	0.005
Q27	TWRMF Decant	Cd	0.00067	0.00040	0.00046	0.00046	0.00048			0.00033 ^B	Tier II	0.000023 ^a	0.000047 ^a
Q27	TWRMF Decant	Cr	0.010	0.006	0.006	0.006	0.006			0.10331 ^C	Tier II	0.0089	0.0089
Q27	TWRMF Decant	Co	0.008	0.004	0.00401	0.00388	0.00376						
Q27	TWRMF Decant	Cu	0.029	0.016	0.01835	0.01793	0.01847	0.3	0.6	0.01266 ^D	Tier II	0.002 ^b	0.00334 ^b
Q27	TWRMF Decant	Fe	1.59	0.80	0.80	0.77	0.73				0.3	0.3	0.3
Q27	TWRMF Decant	Pb	0.008	0.005	0.006	0.006	0.007	0.2	0.4	0.0039 ^E	Tier II	0.00184 ^c	0.00533 ^c
Q27	TWRMF Decant	Mo	0.012	0.008	0.010	0.010	0.011				0.073		
Q27	TWRMF Decant	Ni	0.375	0.192	0.199	0.191	0.184	0.5	1	0.07329 ^F	Tier II	0.06889 ^d	0.13007 ^d
Q27	TWRMF Decant	Se	0.006	0.003	0.004	0.004	0.004				0.001	0.001	0.001
Q27	TWRMF Decant	Zn	0.040	0.029	0.035	0.035	0.039	0.5	1	0.16657 ^G	Tier II	0.03	0.03

Projected Concentrations in Flows during the Closure Periods

SCENARIO:	FLOW	WATER QUALITY PARAM.	ESTIMATED AVERAGE CONCENTRATION					REGULATIONS						
			Closure (Stage 1)		Closure (Stage 2)			Metal Mining Liquid Effluent Regulations (2002, last amended in 2012)		Manitoba Water Quality Standards, Objectives, and Guidelines (Manitoba Water Stewardship, 2011)		Canadian Water Quality Guidelines for the Protection of Aquatic Life (CCME, 2011)		
			Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate							
			MAY (mg/L)	JUNE TO OCTOBER (mg/L)	NOVEMBER TO APRIL (mg/L)	MAY (mg/L)	JUNE TO OCTOBER (mg/L)	Monthly Mean	Grab Sample	TIER II Water Quality Objectives assuming hardness = 150 mg/L CaCO ₃	Freshwater	assuming hardness = 65 mg/L CaCO ₃	assuming hardness = 150 mg/L CaCO ₃	
Q29	POLISHING POND INFLOW	Al	0.166	0.197	0.000	0.203	0.200					0.005 - 0.1	0.005 - 0.1	0.005 - 0.1
Q29	POLISHING POND INFLOW	Sb	0.00135	0.00175	0.00000	0.00183	0.00189							
Q29	POLISHING POND INFLOW	As	0.002	0.003	0.000	0.003	0.004	0.5	1	0.15 mg/L (4-Day, 3-Year) ^A	Tier II	0.005	0.005	
Q29	POLISHING POND INFLOW	Cd	0.000291	0.000396	0.000000	0.000455	0.000481			0.00033 ^B	Tier II	0.000023 ^a	0.000047 ^b	
Q29	POLISHING POND INFLOW	Cr	0.005	0.006	0.000	0.006	0.006			0.10331 ^C	Tier II	0.0089	0.0089	
Q29	POLISHING POND INFLOW	Co	0.00336	0.00390	0.00000	0.00388	0.00376							
Q29	POLISHING POND INFLOW	Cu	0.01278	0.01638	0.00000	0.01793	0.01847	0.3	0.6	0.01266 ^D	Tier II	0.002 ^b	0.00334 ^b	
Q29	POLISHING POND INFLOW	Fe	0.708	0.799	0.000	0.771	0.729				0.3	0.3	0.3	
Q29	POLISHING POND INFLOW	Pb	0.00310	0.00505	0.00000	0.00647	0.00727	0.2	0.4	0.0039 ^E	Tier II	0.00184 ^c	0.00533 ^c	
Q29	POLISHING POND INFLOW	Mo	0.006	0.008	0.000	0.010	0.011				0.073			
Q29	POLISHING POND INFLOW	Ni	0.166	0.192	0.000	0.191	0.184	0.5	1	0.07329 ^F	Tier II	0.06889 ^d	0.13007 ^d	
Q29	POLISHING POND INFLOW	Se	0.0026	0.0034	0.0000	0.0035	0.0036				0.001	0.001	0.001	
Q29	POLISHING POND INFLOW	Zn	0.019	0.029	0.000	0.035	0.039	0.5	1	0.16657 ^G	Tier II	0.03	0.03	

Notes:

August 2008 groundwater chemistry was assumed in the modeling.

A Arsenic limits: 0.15 mg/L for averaging duration 4 days (4-Day, 3-Year or 7Q10 Design Flow); 0.34 mg/L for averaging duration 1 hr (1-Day, 3-Year or 1Q10 Design Flow)

B Cadmium limits: $[e^{(0.7409[\ln(\text{Hardness})]-4.719)} \times [1.101672 - \{\ln(\text{Hardness})(0.041838)\}]]$ for 4 days averaging duration.
 $[e^{(1.0166[\ln(\text{Hardness})]-3.924)} \times [1.136672 - \{\ln(\text{Hardness})(0.041838)\}]]$ for 1 hour averaging duration.

C Chromium limits: Chromium III: $[e^{(0.8190[\ln(\text{Hardness})]+0.6848)} \times [0.860]]$ for 4 days averaging duration.
 Chromium III: $[e^{(0.8190[\ln(\text{Hardness})]+3.7256)} \times [0.316]]$ for 1 hour averaging duration.
 Chromium VI: 0.011 mg/L for averaging duration 4 days (4-Day, 3-Year or 7Q10 Design Flow); 0.016 mg/L for averaging duration 1 hr (1-Day, 3-Year or 1Q10 Design Flow)

D Copper limits: $[e^{(0.8545[\ln(\text{Hardness})]-1.702)} \times [0.960]]$ for 4 Days hour averaging duration.
 $[e^{(0.9422[\ln(\text{Hardness})]-1.700)} \times [0.960]]$ for 1 hour averaging duration.

E Lead limits: $[e^{(1.273[\ln(\text{Hardness})]-4.705)} \times [1.46203 - \{\ln(\text{Hardness})(0.145712)\}]]$ for 4 Days averaging duration.
 $[e^{(1.273[\ln(\text{Hardness})]-1.460)} \times [1.46203 - \{\ln(\text{Hardness})(0.145712)\}]]$ for 1 hour averaging duration.

F Nickel limits: $[e^{(0.8460[\ln(\text{Hardness})]+0.0584)} \times [0.997]]$ for 4 Days averaging duration.
 $[e^{(0.8460[\ln(\text{Hardness})]+2.255)} \times [0.998]]$ for 1 hour averaging duration.

G Zinc limits: $[e^{(0.8473[\ln(\text{Hardness})]+0.884)} \times [0.986]]$ for 4 Days averaging duration.
 $[e^{(0.8473[\ln(\text{Hardness})]+0.884)} \times [0.978]]$ for 1 hour averaging duration.

Canadian water quality guidelines for the protection of aquatic life (CCME, 2011)

a Cadmium limit: Cadmium concentration = $10^{0.86[\log_{10}(\text{hardness})]-3.2}$ µg/L

b Copper limit: Copper concentration = $e^{0.8545[\ln(\text{hardness})]-1.465} \times 0.2$ µg/L

c Lead limit: Lead concentration = $e^{1.273[\ln(\text{hardness})]-4.705}$ µg/L

d Nickel limit: Nickel concentration = $e^{0.76[\ln(\text{hardness})]+1.06}$ µg/L

Projected Concentrations in Flows during the Post Closure Period

SCENARIO:	FLOW	WATER QUALITY PARAM.	ESTIMATED AVERAGE CONCENTRATION									REGULATIONS					
			Year 12 (Post Closure)			Year 13 (Post Closure)			Year 14 (Post Closure)			Metal Mining Liquid Effluent Regulations (2002, last amended in 2012)		Manitoba Water Quality Standards, Objectives, and Guidelines (Manitoba Water Stewardship, 2011)		Canadian Water Quality Guidelines for the Protection of Aquatic Life (CCME, 2011)	
			Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate						
			NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	Monthly Mean	Grab Sample	TIER II Water Quality Objectives assuming hardness = 150 mg/L CaCO ₃	Freshwater	assuming hardness = 65 mg/L CaCO ₃	assuming hardness = 150 mg/L CaCO ₃
(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)									
Q26	TWRMF INFLOW	Al	0.000	0.009	0.015	0.000	0.009	0.015	0.000	0.009	0.015				0.005 - 0.1	0.005 - 0.1	0.005 - 0.1
Q26	TWRMF INFLOW	Sb	0.0000	0.0009	0.0015	0.0000	0.0009	0.0015	0.0000	0.0009	0.0015						
Q26	TWRMF INFLOW	As	0.0000	0.0009	0.0015	0.0000	0.0009	0.0015	0.0000	0.0009	0.0015	0.5	1	0.15 mg/L (4-Day, 3-Year) ^A	Tier II	0.005	0.005
Q26	TWRMF INFLOW	Cd	0.00000	0.00003	0.00005	0.00000	0.00003	0.00005	0.00000	0.00003	0.00005			0.00033 ^B	Tier II	0.000023 ^a	0.000047 ^a
Q26	TWRMF INFLOW	Cr	0.0000	0.0018	0.0030	0.0000	0.0018	0.0030	0.0000	0.0018	0.0030			0.10331 ^C	Tier II	0.0089	0.0089
Q26	TWRMF INFLOW	Co	0.0000	0.0005	0.0009	0.0000	0.0005	0.0009	0.0000	0.0005	0.0009						
Q26	TWRMF INFLOW	Cu	0.0000	0.0018	0.0030	0.0000	0.0018	0.0030	0.0000	0.0018	0.0030	0.3	0.6	0.01266 ^D	Tier II	0.002 ^b	0.00334 ^b
Q26	TWRMF INFLOW	Fe	0.00	0.05	0.09	0.00	0.05	0.09	0.00	0.05	0.09				0.3	0.3	0.3
Q26	TWRMF INFLOW	Pb	0.00000	0.00090	0.00149	0.00000	0.00090	0.00149	0.00000	0.00090	0.00149	0.2	0.4	0.0039 ^E	Tier II	0.00184 ^c	0.00533 ^c
Q26	TWRMF INFLOW	Mo	0.0000	0.0018	0.0030	0.0000	0.0018	0.0030	0.0000	0.0018	0.0030				0.073		
Q26	TWRMF INFLOW	Ni	0.000	0.002	0.003	0.000	0.002	0.003	0.000	0.002	0.003	0.5	1	0.07329 ^F	Tier II	0.06889 ^d	0.13007 ^d
Q26	TWRMF INFLOW	Se	0.0000	0.0018	0.0030	0.0000	0.0018	0.0030	0.0000	0.0018	0.0030				0.001	0.001	0.001
Q26	TWRMF INFLOW	Zn	0.0000	0.0090	0.0149	0.0000	0.0090	0.0149	0.0000	0.0090	0.0149	0.5	1	0.16657 ^G	Tier II	0.03	0.03
Q27	TWRMF Decant	Al	0.213	0.206	0.203	0.215	0.208	0.205	0.218	0.210	0.207				0.005 - 0.1	0.005 - 0.1	0.005 - 0.1
Q27	TWRMF Decant	Sb	0.002	0.002	0.002	0.002	0.002	0.002	0.002	0.002	0.002						
Q27	TWRMF Decant	As	0.004	0.004	0.004	0.005	0.005	0.005	0.006	0.006	0.006	0.5	1	0.15 mg/L (4-Day, 3-Year) ^A	Tier II	0.005	0.005
Q27	TWRMF Decant	Cd	0.00055	0.00054	0.00056	0.00062	0.00061	0.00062	0.00069	0.00067	0.00068			0.00033 ^B	Tier II	0.000023 ^a	0.000047 ^a
Q27	TWRMF Decant	Cr	0.006	0.006	0.006	0.006	0.006	0.006	0.006	0.006	0.006			0.10331 ^C	Tier II	0.0089	0.0089
Q27	TWRMF Decant	Co	0.004	0.004	0.004	0.00374	0.00361	0.00351	0.00362	0.00350	0.00341						
Q27	TWRMF Decant	Cu	0.020	0.020	0.020	0.02231	0.02172	0.02200	0.02398	0.02331	0.02348	0.3	0.6	0.01266 ^D	Tier II	0.002 ^b	0.00334 ^b
Q27	TWRMF Decant	Fe	0.73	0.70	0.67	0.67	0.65	0.61	0.62	0.59	0.56				0.3	0.3	0.3
Q27	TWRMF Decant	Pb	0.009	0.009	0.009	0.011	0.010	0.011	0.012	0.012	0.013	0.2	0.4	0.0039 ^E	Tier II	0.00184 ^c	0.00533 ^c
Q27	TWRMF Decant	Mo	0.012	0.012	0.013	0.015	0.014	0.015	0.017	0.016	0.017				0.073		
Q27	TWRMF Decant	Ni	0.192	0.184	0.178	0.185	0.178	0.172	0.180	0.173	0.167	0.5	1	0.07329 ^F	Tier II	0.06889 ^d	0.13007 ^d
Q27	TWRMF Decant	Se	0.004	0.004	0.004	0.004	0.004	0.004	0.004	0.004	0.004				0.001	0.001	0.001
Q27	TWRMF Decant	Zn	0.046	0.045	0.049	0.056	0.055	0.057	0.064	0.063	0.065	0.5	1	0.16657 ^G	Tier II	0.03	0.03

Projected Concentrations in Flows during the Post Closure Period

SCENARIO:	WATER QUALITY	PARAM.	ESTIMATED AVERAGE CONCENTRATION									REGULATIONS					
			Year 12 (Post Closure)			Year 13 (Post Closure)			Year 14 (Post Closure)			Metal Mining Liquid Effluent Regulations (2002, last amended in 2012)		Manitoba Water Quality Standards, Objectives, and Guidelines (Manitoba Water Stewardship, 2011)		Canadian Water Quality Guidelines for the Protection of Aquatic Life (CCME, 2011)	
			Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate						
			NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	Monthly Mean	Grab Sample	TIER II Water Quality Objectives	Freshwater	assuming hardness = 65 mg/L CaCO ₃	assuming hardness = 150 mg/L CaCO ₃
(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)			assuming hardness = 150 mg/L CaCO ₃						
Q29	POLISHING POND INFLOW	Al	0.000	0.206	0.203	0.000	0.208	0.205	0.000	0.210	0.207						
Q29	POLISHING POND INFLOW	Sb	0.00000	0.00196	0.00201	0.00000	0.00208	0.00212	0.00000	0.00218	0.00222						
Q29	POLISHING POND INFLOW	As	0.000	0.004	0.004	0.000	0.005	0.005	0.000	0.006	0.006	0.5	1	0.15 mg/L (4-Day, 3-Year) ^A	Tier II	0.005	0.005
Q29	POLISHING POND INFLOW	Cd	0.000000	0.000537	0.000557	0.000000	0.000609	0.000625	0.000000	0.000674	0.000685			0.00033 ^B	Tier II	0.000023 ^a	0.000047 ^a
Q29	POLISHING POND INFLOW	Cr	0.000	0.006	0.006	0.000	0.006	0.006	0.000	0.006	0.006			0.10331 ^C	Tier II	0.0089	0.0089
Q29	POLISHING POND INFLOW	Co	0.00000	0.00374	0.00363	0.00000	0.00361	0.00351	0.00000	0.00350	0.00341						
Q29	POLISHING POND INFLOW	Cu	0.00000	0.01994	0.02034	0.00000	0.02172	0.02200	0.00000	0.02331	0.02348	0.3	0.6	0.01266 ^D	Tier II	0.002 ^b	0.00334 ^b
Q29	POLISHING POND INFLOW	Fe	0.000	0.705	0.667	0.000	0.645	0.612	0.000	0.593	0.562				0.3	0.3	0.3
Q29	POLISHING POND INFLOW	Pb	0.00000	0.00860	0.00925	0.00000	0.01049	0.01101	0.00000	0.01217	0.01257	0.2	0.4	0.0039 ^E	Tier II	0.00184 ^c	0.00533 ^c
Q29	POLISHING POND INFLOW	Mo	0.000	0.012	0.013	0.000	0.014	0.015	0.000	0.016	0.017				0.073		
Q29	POLISHING POND INFLOW	Ni	0.000	0.184	0.178	0.000	0.178	0.172	0.000	0.173	0.167	0.5	1	0.07329 ^F	Tier II	0.06889 ^d	0.13007 ^d
Q29	POLISHING POND INFLOW	Se	0.0000	0.0038	0.0039	0.0000	0.0040	0.0041	0.0000	0.0042	0.0043				0.001	0.001	0.001
Q29	POLISHING POND INFLOW	Zn	0.000	0.045	0.049	0.000	0.055	0.057	0.000	0.063	0.065	0.5	1	0.16657 ^G	Tier II	0.03	0.03

Notes:

August 2008 groundwater chemistry was assumed in the modeling.

- A Arsenic limits: 0.15 mg/L for averaging duration 4 days (4-Day, 3-Year or 7Q10 Design Flow); 0.34 mg/L for averaging duration 1 hr (1-Day, 3-Year or 1Q10 Design Flow)
- B Cadmium limits: $[e^{0.7409[\ln(\text{Hardness})]-4.719}] \times [1.101672 - \{\ln(\text{Hardness})(0.041838)\}]$ for 4 days averaging duration.
 $[e^{1.0166[\ln(\text{Hardness})]-3.924}] \times [1.136672 - \{\ln(\text{Hardness})(0.041838)\}]$ for 1 hour averaging duration.
- C Chromium limits: Chromium III: $[e^{0.8190[\ln(\text{Hardness})+0.6848]}] \times [0.860]$ for 4 days averaging duration.
 Chromium III: $[e^{0.8190[\ln(\text{Hardness})+3.7256]}] \times [0.316]$ for 1 hour averaging duration.
 Chromium VI: 0.011 mg/L for averaging duration 4 days (4-Day, 3-Year or 7Q10 Design Flow); 0.016 mg/L for averaging duration 1 hr (1-Day, 3-Year or 1Q10 Design Flow)
- D Copper limits: $[e^{0.8545[\ln(\text{Hardness})]-1.702}] \times [0.960]$ for 4 Days hour averaging duration.
 $[e^{0.9422[\ln(\text{Hardness})]-1.700}] \times [0.960]$ for 1 hour averaging duration.
- E Lead limits: $[e^{1.273[\ln(\text{Hardness})]-4.705}] \times [1.46203 - \{\ln(\text{Hardness})(0.145712)\}]$ for 4 Days averaging duration.
 $[e^{1.273[\ln(\text{Hardness})]-1.460}] \times [1.46203 - \{\ln(\text{Hardness})(0.145712)\}]$ for 1 hour averaging duration.
- F Nickel limits: $[e^{0.8460[\ln(\text{Hardness})+0.0584]}] \times [0.997]$ for 4 Days averaging duration.
 $[e^{0.8460[\ln(\text{Hardness})+2.255]}] \times [0.998]$ for 1 hour averaging duration.
- G Zinc limits: $[e^{0.8473[\ln(\text{Hardness})+0.884]}] \times [0.986]$ for 4 Days averaging duration.
 $[e^{0.8473[\ln(\text{Hardness})+0.884]}] \times [0.978]$ for 1 hour averaging duration.

Canadian water quality guidelines for the protection of aquatic life (CCME, 2011)

- a Cadmium limit: Cadmium concentration = $10^{0.86[\log_{10}(\text{hardness})]-3.2}$ µg/L
- b Copper limit: Copper concentration = $e^{0.8545[\ln(\text{hardness})]-1.465} \times 0.2$ µg/L
- c Lead limit: Lead concentration = $e^{1.273[\ln(\text{hardness})]-4.705}$ µg/L
- d Nickel limit: Nickel concentration = $e^{0.76[\ln(\text{hardness})+1.06]}$ µg/L

APPENDIX 2.14-F

Water Balance Model Results
for Temporary Suspension after Year 5
& the State of Inactivity after one year of Temporary
Suspension

Projected Concentrations in Flows during Temporary Suspension and the State of Inactivity

SCENARIO:		WATER QUALITY PARAM.	ESTIMATED AVERAGE CONCENTRATION						REGULATIONS					
			TS after Year 5			SI after one year TS			Metal Mining Liquid Effluent Regulations (2002, last amended in 2012)		Manitoba Water Quality Standards, Objectives, and Guidelines (Manitoba Water Stewardship, 2011)		Canadian Water Quality Guidelines for the Protection of Aquatic Life (CCME, 2011)	
			Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate						
			NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	Monthly Mean	Grab Sample	TIER II Water Quality Objectives assuming hardness = 150 mg/L CaCO ₃	Freshwater	assuming hardness = 65 mg/L CaCO ₃	assuming hardness = 150 mg/L CaCO ₃
FLOW	PARAM.	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)							
Q26	TWRMF INFLOW	Al	0.000	0.006	0.010	0.000	0.007	0.012				0.005 - 0.1	0.005 - 0.1	0.005 - 0.1
Q26	TWRMF INFLOW	Sb	0.0000	0.0006	0.0010	0.0000	0.0007	0.0012						
Q26	TWRMF INFLOW	As	0.0000	0.0006	0.0010	0.0000	0.0007	0.0012	0.5	1	0.15 mg/L (4-Day, 3-Year) ^A	Tier II	0.005	0.005
Q26	TWRMF INFLOW	Cd	0.00000	0.00002	0.00004	0.00000	0.00002	0.00004			0.00033 ^B	Tier II	0.000023 ^a	0.000047 ^a
Q26	TWRMF INFLOW	Cr	0.0000	0.0013	0.0021	0.0000	0.0014	0.0024			0.10331 ^C	Tier II	0.0089	0.0089
Q26	TWRMF INFLOW	Co	0.0000	0.0004	0.0006	0.0000	0.0004	0.0007						
Q26	TWRMF INFLOW	Cu	0.0000	0.0013	0.0021	0.0000	0.0014	0.0024	0.3	0.6	0.01266 ^D	Tier II	0.002 ^b	0.00334 ^b
Q26	TWRMF INFLOW	Fe	0.00	0.04	0.06	0.00	0.04	0.07				0.3	0.3	0.3
Q26	TWRMF INFLOW	Pb	0.00000	0.00064	0.00104	0.00000	0.00071	0.00120	0.2	0.4	0.0039 ^E	Tier II	0.00184 ^c	0.00533 ^c
Q26	TWRMF INFLOW	Mo	0.0000	0.0013	0.0021	0.0000	0.0014	0.0024				0.073		
Q26	TWRMF INFLOW	Ni	0.000	0.001	0.002	0.000	0.001	0.002	0.5	1	0.07329 ^F	Tier II	0.06889 ^d	0.13007 ^d
Q26	TWRMF INFLOW	Se	0.0000	0.0013	0.0021	0.0000	0.0014	0.0024				0.001	0.001	0.001
Q26	TWRMF INFLOW	Zn	0.0000	0.0064	0.0104	0.0000	0.0071	0.0120	0.5	1	0.16657 ^G	Tier II	0.03	0.03
Q27	TWRMF Decant	Al	0.498	0.440	0.376	0.395	0.350	0.303				0.005 - 0.1	0.005 - 0.1	0.005 - 0.1
Q27	TWRMF Decant	Sb	0.004	0.004	0.004	0.004	0.003	0.003						
Q27	TWRMF Decant	As	0.005	0.004	0.004	0.005	0.005	0.005	0.5	1	0.15 mg/L (4-Day, 3-Year) ^A	Tier II	0.005	0.005
Q27	TWRMF Decant	Cd	0.00090	0.00081	0.00074	0.00084	0.00076	0.00070			0.00033 ^B	Tier II	0.000023 ^a	0.000047 ^a
Q27	TWRMF Decant	Cr	0.013	0.012	0.011	0.011	0.010	0.009			0.10331 ^C	Tier II	0.0089	0.0089
Q27	TWRMF Decant	Co	0.010	0.009	0.008	0.00789	0.00701	0.00601						
Q27	TWRMF Decant	Cu	0.039	0.035	0.031	0.03398	0.03047	0.02755	0.3	0.6	0.01266 ^D	Tier II	0.002 ^b	0.00334 ^b
Q27	TWRMF Decant	Fe	2.19	1.92	1.60	1.60	1.41	1.18				0.3	0.3	0.3
Q27	TWRMF Decant	Pb	0.010	0.009	0.009	0.011	0.010	0.010	0.2	0.4	0.0039 ^E	Tier II	0.00184 ^c	0.00533 ^c
Q27	TWRMF Decant	Mo	0.016	0.015	0.014	0.017	0.016	0.015				0.073		
Q27	TWRMF Decant	Ni	0.512	0.450	0.377	0.388	0.342	0.288	0.5	1	0.07329 ^F	Tier II	0.06889 ^d	0.13007 ^d
Q27	TWRMF Decant	Se	0.008	0.007	0.007	0.007	0.006	0.006				0.001	0.001	0.001
Q27	TWRMF Decant	Zn	0.051	0.048	0.049	0.059	0.054	0.054	0.5	1	0.16657 ^G	Tier II	0.03	0.03

Projected Concentrations in Flows during Temporary Suspension and the State of Inactivity

SCENARIO:		WATER QUALITY PARAM.	ESTIMATED AVERAGE CONCENTRATION						REGULATIONS					
			TS after Year 5			SI after one year TS			Metal Mining Liquid Effluent Regulations (2002, last amended in 2012)		Manitoba Water Quality Standards, Objectives, and Guidelines (Manitoba Water Stewardship, 2011)		Canadian Water Quality Guidelines for the Protection of Aquatic Life (CCME, 2011)	
			Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate	Tailings only; max.tailings leaching rate						
			NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	NOVEMBER TO APRIL	MAY	JUNE TO OCTOBER	Monthly Mean	Grab Sample	TIER II Water Quality Objectives assuming hardness = 150 mg/L CaCO ₃	Freshwater	assuming hardness = 65 mg/L CaCO ₃	assuming hardness = 150 mg/L CaCO ₃
FLOW		(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)	(mg/L)							
Q29	POLISHING POND INFLOW	Al	0.009	0.046	0.041	0.000	0.350	0.303				0.005 - 0.1	0.005 - 0.1	0.005 - 0.1
Q29	POLISHING POND INFLOW	Sb	0.00003	0.00039	0.00038	0.00000	0.00340	0.00316						
Q29	POLISHING POND INFLOW	As	0.001	0.001	0.001	0.000	0.005	0.005	0.5	1	0.15 mg/L (4-Day, 3-Year) ^A	Tier II	0.005	0.005
Q29	POLISHING POND INFLOW	Cd	0.000006	0.000077	0.000072	0.000000	0.000757	0.000700			0.00033 ^B	Tier II	0.000023 ^a	0.000047 ^a
Q29	POLISHING POND INFLOW	Cr	0.001	0.002	0.002	0.000	0.010	0.009			0.10331 ^C	Tier II	0.0089	0.0089
Q29	POLISHING POND INFLOW	Co	0.00008	0.00089	0.00078	0.00000	0.00701	0.00601						
Q29	POLISHING POND INFLOW	Cu	0.00052	0.00355	0.00326	0.00000	0.03047	0.02755	0.3	0.6	0.01266 ^D	Tier II	0.002 ^b	0.00334 ^b
Q29	POLISHING POND INFLOW	Fe	0.005	0.175	0.148	0.000	1.414	1.179				0.3	0.3	0.3
Q29	POLISHING POND INFLOW	Pb	0.00003	0.00085	0.00088	0.00000	0.01036	0.01026	0.2	0.4	0.0039 ^E	Tier II	0.00184 ^c	0.00533 ^c
Q29	POLISHING POND INFLOW	Mo	0.001	0.002	0.002	0.000	0.016	0.015				0.073		
Q29	POLISHING POND INFLOW	Ni	0.001	0.040	0.034	0.000	0.342	0.288	0.5	1	0.07329 ^F	Tier II	0.06889 ^d	0.13007 ^d
Q29	POLISHING POND INFLOW	Se	0.0002	0.0009	0.0008	0.0000	0.0064	0.0060				0.001	0.001	0.001
Q29	POLISHING POND INFLOW	Zn	0.005	0.008	0.009	0.000	0.054	0.054	0.5	1	0.16657 ^G	Tier II	0.03	0.03

Notes:

August 2008 groundwater chemistry was assumed in the modeling.

- A Arsenic limits: 0.15 mg/L for averaging duration 4 days (4-Day, 3-Year or 7Q10 Design Flow); 0.34 mg/L for averaging duration 1 hr (1-Day, 3-Year or 1Q10 Design Flow)
- B Cadmium limits: $[e^{(0.7409[\ln(\text{Hardness})]-4.719)} \times [1.101672 - \{\ln(\text{Hardness})(0.041838)\}]]$ for 4 days averaging duration. $[e^{(1.0166[\ln(\text{Hardness})]-3.924)} \times [1.136672 - \{\ln(\text{Hardness})(0.041838)\}]]$ for 1 hour averaging duration.
- C Chromium limits: Chromium III: $[e^{(0.8190[\ln(\text{Hardness})]+0.6848)} \times [0.860]]$ for 4 days averaging duration. Chromium III: $[e^{(0.8190[\ln(\text{Hardness})]+3.7256)} \times [0.316]]$ for 1 hour averaging duration. Chromium VI: 0.011 mg/L for averaging duration 4 days (4-Day, 3-Year or 7Q10 Design Flow); 0.016 mg/L for averaging duration 1 hr (1-Day, 3-Year or 1Q10 Design Flow)
- D Copper limits: $[e^{(0.8545[\ln(\text{Hardness})]-1.702)} \times [0.960]]$ for 4 Days hour averaging duration. $[e^{(0.9422[\ln(\text{Hardness})]-1.700)} \times [0.960]]$ for 1 hour averaging duration.
- E Lead limits: $[e^{(1.273[\ln(\text{Hardness})]-4.705)} \times [1.46203 - \{\ln(\text{Hardness})(0.145712)\}]]$ for 4 Days averaging duration. $[e^{(1.273[\ln(\text{Hardness})]-1.460)} \times [1.46203 - \{\ln(\text{Hardness})(0.145712)\}]]$ for 1 hour averaging duration.
- F Nickel limits: $[e^{(0.8460[\ln(\text{Hardness})]+0.0584)} \times [0.997]]$ for 4 Days averaging duration. $[e^{(0.8460[\ln(\text{Hardness})]+2.255)} \times [0.998]]$ for 1 hour averaging duration.
- G Zinc limits: $[e^{(0.8473[\ln(\text{Hardness})]+0.884)} \times [0.986]]$ for 4 Days averaging duration. $[e^{(0.8473[\ln(\text{Hardness})]+0.884)} \times [0.978]]$ for 1 hour averaging duration.

Canadian water quality guidelines for the protection of aquatic life (CCME, 2011)

- a Cadmium limit: Cadmium concentration = $10^{(0.86[\log_{10}(\text{hardness})]-3.2)}$ µg/L
- b Copper limit: Copper concentration = $e^{(0.8545[\ln(\text{hardness})]-1.465)}$ * 0.2 µg/L
- c Lead limit: Lead concentration = $e^{(1.273[\ln(\text{hardness})]-4.705)}$ µg/L
- d Nickel limit: Nickel concentration = $e^{(0.79[\ln(\text{hardness})]+1.06)}$ µg/L